



Fine Recycled Concrete Aggregates Particle Morphological Parameters and Packing Properties

L. G. Pedersen^(✉) and L. M. Ottosen

Department of Civil Engineering, Technical University of Denmark,
Kgs. Lyngby, Denmark

Keywords: Fine recycled concrete aggregates · Packing properties · Workability · Rheology

1 Introduction

In the European Union, concrete accounts for 25% of the construction and demolition waste generated each year. At the same time, in many places around Europe the availability of natural rounded aggregates for the production of concrete is becoming a crucial question. These two trends suggest that crushed particles, such as crushed stone aggregates and recycled concrete aggregates (RCA), can be a necessity for concrete production to accommodate resource scarcity. When recycling concrete as aggregates, an important part to investigate is to use the fraction of fine recycled concrete aggregates (FRCA) as it constitutes 40–60% of the crushed concrete.

The proportioning of aggregates for the use in concrete is influenced by morphology characteristics of particles, such as shape, angularity and surface texture, which has a significant effect on the workability, rheology and mechanical properties of cementitious suspensions, among others [1] reviews the effect of packing characteristics of aggregates on the rheo-physical properties. This study investigates the morphology of crushed particles, FRCA, with nonspherical shapes.

2 Materials and Methods

Four sands were studied (Fig. 1), the first sand is a naturally rounded sea dredge 0–4mm sand (S1), whereas the other three sands S2, S3 and S4 are produced by crushed concrete (0–4mm). The FRCAs were obtained from three different construction sites in the area around Copenhagen and the concrete was crushed with gyratory crusher (cone crusher).

The investigation of the FRCA includes:

- Evaluation of particle shape
- Grain size distribution
- Packing

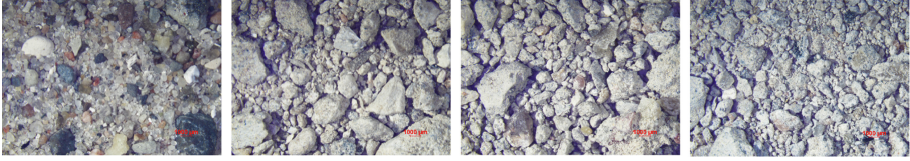


Fig. 1. The four sands studied in this paper, from left S1–S4.

3 Results

The sands particle shape, shown in Fig. 2, is quantified by the roundness, R (the average radius of curvature of the surface features) [2], the sphericity, S (reflecting the similarity between the length and height of a particle) [3], and regularity, ρ , described

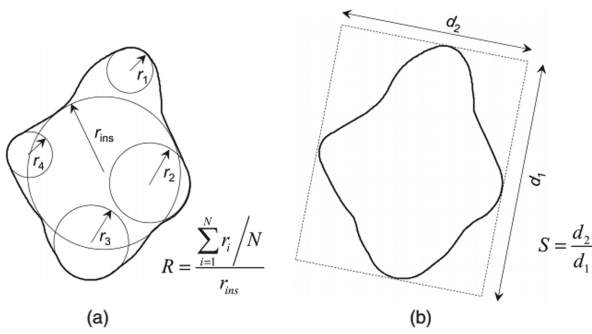


Fig. 2. Definitions of (a) roundness, R , (b) sphericity, S , (adapted from [4]).

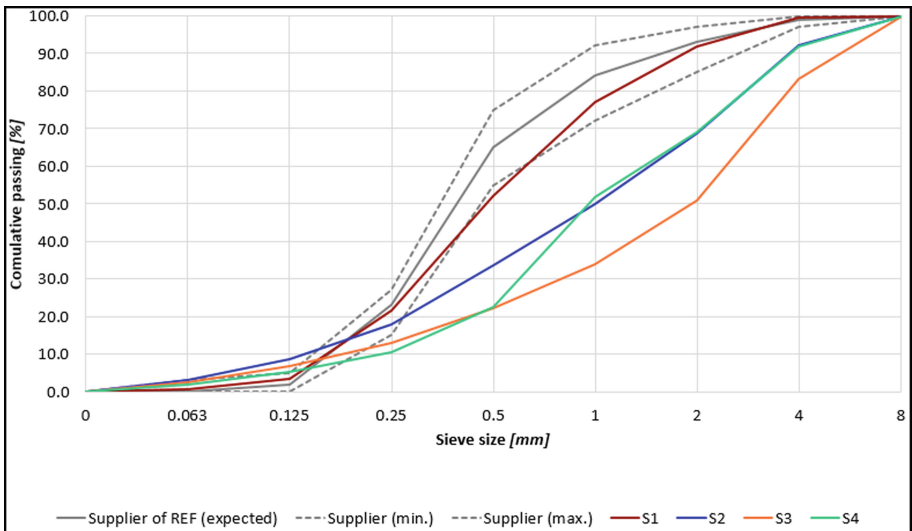


Fig. 3. Particle size distribution of the sands.

as $\rho = \frac{R+S}{2}$. The particle shape was determined as the average values of a visual assessment from microscope images.

The particle size distributions were determined according to DS/EN 933-1 and are shown in Fig. 3 for the four sands. Two specific packing fractions were measured for the four sands to characterize their properties further. The packing fractions were determined according to [5], the random loose packing fraction (RLP fraction), which

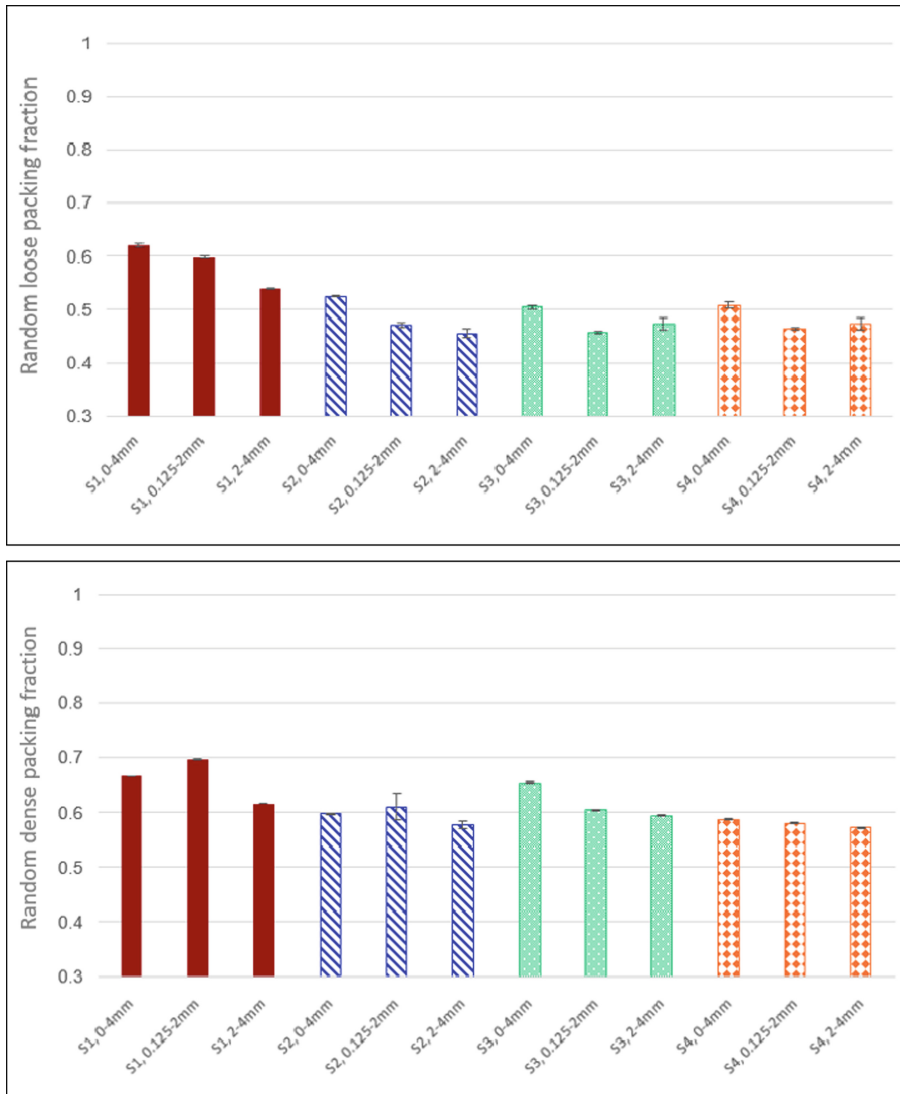


Fig. 4. Random loose packing fraction (top) and random dense packing fraction (bottom) for the sands and various fractions.

theoretical is defined as the loosest packing fraction by pouring grains, and the random dense packing fraction, this value is empirically defined and depends on the specific amount of energy brought to the system. All FRCA tested here have lower packing fractions than the reference sea dredged sand.

4 Conclusions

In this study, the particle morphology and packing properties were investigated for various FRCAs, and the FRCAs are more angular than the sea dredge sand where weathering has beside rounding the particles removed most of the weak minerals. The packing properties showed the sphericity of the particles as the dominant morphological parameter regarding packing. The study also showed that the packing properties similar to the morphology parameters depends on the type of sand and not on the sand fraction.

Acknowledgements. Norrecco and Dansk Beton are greatly acknowledged for collaboration and financial support.

References

1. Mehdipour, I., Khayat, K.H.: Understanding the role of particle packing characteristics in rheophysical properties of cementitious suspensions: a literature review. *Constr. Build. Mater.* **161**, 340–353 (2018)
2. Wadell, H.: Volume, shape, and roundness of rock particles. *J. Geol.* **40**(5), 443–451 (1932)
3. Powers, M.C.: A new roundness scale for sedimentary particles. *J. Sediment. Petrol.* **23**(2), 1117–1119 (1953)
4. Hryciw, R.D., Zheng, J., Shetler, K.: Particle roundness and sphericity from image assemblies by chart estimates and computer methods. *J. Geotech. Geoenviron. Eng.* **142**(9), 04016038 (2016)
5. DGF: Laboratoriehåndbogen – DGF Bulletin 15. Dansk Geoteknisk Forening, Lyngby, Denmark (2001)