

Mössbauer Spectroscopy: an elegant tool for the active sites identification and quantification in Pt-Sn-In based naphtha reforming catalysts

Ali Jahel · Sylvie Lacombe · Priscilla Avenier ·
Josette Olivier-Fourcade · Jean-Claude Jumas

Published online: 29 November 2011
© Springer Science+Business Media B.V. 2011

Abstract Trimetallic PtSnIn/Al₂O₃-Cl catalysts have been synthesized by successive impregnations (SI) of metals and characterized by ¹¹⁹Sn Mössbauer Spectroscopy (MS). Various Sn-species have been identified thanks to the use of a Δ (Quadrupole Splitting) – δ (Isomer shift) diagram. ¹¹⁹Sn MS results show that addition of different amounts of In (0.11 to 0.55 wt.%) lead to the formation of Pt_xSn(O) oxo-metallic phases. As the In loading increases these Pt_xSn(O) oxo-metallic phases are richer in Pt. The preferential formation of a given Sn phase in these catalysts is directly related to the preparation method.

Keywords Naphtha-reforming catalysts · Pt-Sn-In Mössbauer Spectroscopy · Pt_xSn(O) oxo-metallic phases

1 Introduction


Alumina supported Pt-Sn heterogeneous catalysts are widely employed in the catalytic naphtha reforming industry [1]. Trimetallic catalysts are considered to be superior to their bimetallic counterparts in terms of stability and resistance to deactivation by coke. However, little information about these materials can be found in the literature. Few examples exist on the promotion of Pt-Sn systems by another metal such as indium [2].

¹¹⁹Sn Mössbauer Spectroscopy (MS) is a powerful tool to fully classify Sn species as a function of their hyperfine parameters in these systems [3, 4] as shown on Fig. 1.

A. Jahel · S. Lacombe · P. Avenier
IFP Energies nouvelles, Rond-point de l'échangeur de Solaize, BP 3, 69360 Solaize, France

J. Olivier-Fourcade · J.-C. Jumas (✉)
Institut Charles Gerhardt Montpellier (UMR 5253), Université Montpellier II, CC1502,
Place E. Bataillon, 34095 Montpellier cedex 5, France
e-mail: jumas@univ-montp2.fr

Fig. 1 Classification of the Sn species [3] observed on Sn-based catalysts and of model compounds as a function of their Mössbauer parameters

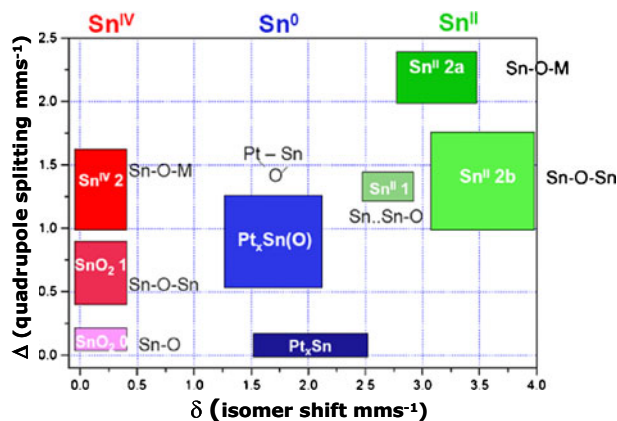

Using this diagram we have previously shown that the presence of In in Pt/Al₂O₃SnIn-Cl catalysts obtained by co-precipitation of Sn and In with the alumina precursor following a sol-gel method (CP samples) favours the formation of Pt_xSn alloys [5, 6]. In the absence of indium, a Sn⁰ unalloyed phase was rather identified. The consequent activity and selectivity differences have been interpreted on the basis of these results [5]. In this paper we present an ¹¹⁹Sn Mössbauer characterization for PtSnIn based catalysts obtained by successive impregnations (SI) of metals.

2 Preparation of catalysts by SI and characterization by ¹¹⁹Sn MS

The calcined γ -alumina support was first impregnated with In using the proper amount of In(NO₃)₃ · 5H₂O to yield 0.10, 0.30, 0.40 and 0.55 wt.% of In relative to support's mass. After this, each of the obtained supports was impregnated with SnCl₂ · 2H₂O (0.30 wt.% of support's mass). Finally the obtained bimetallic supports were impregnated with H₂PtCl₆ (0.30 wt.% of support's mass). The chlorine content of the catalysts was adjusted to approximately 1 wt.% by injecting distilled water to the catalyst at 520° in dry air flow.

¹¹⁹Sn Mössbauer spectra were recorded at room temperature in the transmission mode on a standard spectrometer using a Ca^{119m}SnO₃ source of 370 MBq nominal activity. All isomer shifts are given with respect to the room temperature spectrum of BaSnO₃. All catalysts were characterized in the reduced form (500°C, 2 h in 1 l/h/g H₂ stream). The reduction was performed in special-U shaped reduction cells adapted for MS measurements. Once reduction was completed, the cell was neutralized and sealed under vacuum.

3 Results and discussion

The different Sn species (Table 1) have been identified using the diagram reported on Fig. 1. Ratios with which Sn species are formed have been estimated from the contributions of their sub-spectra corrected using their different *f* factors (Lamb

Table 1 ^{119}Sn hyperfine parameters δ (mms^{-1}), Δ (mms^{-1}) of species and their corrected contribution CC (%) to spectra of reduced SI samples recorded at room temperature

Sample	δ	Δ	FWHM ^[a]	CC ^[b]	Attribution	Absorption (%)
PtSnIn _{0.11} Al ₂ O ₃ -Cl	0.36(0)	1.48(6)	0.88(2)	4	Sn ^{IV} 2	0.88
	3.10(3)	2.17(3)	0.88(6)	26	Sn ^{II} 2a	
	3.86(2)	1.32(2)	0.88(3)	50	Sn ^{II} 2b	
	1.95(6)	1.48(6)	0.88(2)	20	Pt _x Sn(O)	
PtSnIn _{0.31} Al ₂ O ₃ -Cl	0.02(0)	0.68(1)	1.07(2)	8	SnO ₂ 1	0.63
	3.15(3)	2.49(4)	1.07(3)	36	Sn ^{II} 2a	
	3.55(3)	1.18(4)	1.07(7)	40	Sn ^{II} 2b	
	1.46(0)	1.35(3)	1.07(2)	16	Pt _x Sn(O)	
PtSnIn _{0.41} Al ₂ O ₃ -Cl	-0.20(0)	0.30(1)	1.01(2)	4	SnO ₂ 1	0.59
	3.26(5)	2.34(5)	1.01(1)	36	Sn ^{II} 2a	
	3.61(5)	1.14(6)	1.01(5)	43	Sn ^{II} 2b	
	1.25(9)	1.08(9)	1.01(2)	17	Pt _x Sn(O)	
PtSnIn _{0.55} Al ₂ O ₃ -Cl	3.16(5)	2.08(6)	1.07(6)	44	Sn ^{II} 2a	0.74
	3.73(7)	1.34(9)	1.07(2)	34	Sn ^{II} 2b	
	1.05(6)	1.28(7)	1.07(2)	22	Pt _x Sn(O)	

[a] Full Width at Half Maximum, [b] Corrected Contribution (quantitative)

Mössbauer factors). Experimentally these f factors have been determined as 0.55 (SnO₂ 1 and Sn^{IV} 2), 0.18 (Sn⁰/alloys), 0.34 (Pt_xSn(O)), 0.35 (Sn^{II} 2a) and 0.31 (Sn^{II} 2b) [7].

At 0.11 wt% In, the obtained spectrum is composed of 4-subspectra: an unreduced “Sn^{IV} 2” oxide, the two “Sn^{II} 2a” and “Sn^{II} 2b” oxides and a metallic Sn phase ($\delta = 1.95 \text{ mms}^{-1}$ and $\Delta = 1.48 \text{ mms}^{-1}$). The hyperfine parameters of this phase thus lie at the lower limit of isomer shifts of Sn-rich Pt_xSn alloys (Fig. 1), but its relatively high quadrupole splitting indicates that this phase is rather an oxo-metallic Pt_xSn(O) phase. Higher In loadings (0.31, 0.41 and 0.55 wt%) also lead to a comparable formation of these oxo-metallic phases (16, 17 and 22% respectively). More importantly, the isomer shift of the formed Pt_xSn(O) phase in trimetallic catalysts decreases when the In content increases. The Pt and Sn relative atomic concentrations in these formed Pt_xSn(O) phases can be estimated starting from the isomer shift at which the phase is observed in the spectrum and following the same rule applied for Pt_xSn alloys, i.e. phases with lower isomer shifts are richer in Pt and those with higher isomer shifts are richer in Sn [3]. This implies that in trimetallic catalysts, as the In loading increases, less Sn is engaged in the observed Pt_xSn(O) phase. Such a decrease in the Sn atomic concentration is in accordance with the substitution of Sn by the added In, which is also an evidence of the close Pt-In proximity in these catalysts. The effect of indium in the ternary PtSnIn based system is therefore qualitatively understood as a function of its introduction method, its loading, and the introduction method of the other elements, i.e. Pt and Sn. The CP catalysts have surprisingly higher Sn⁰/Pt ratios compared to SI catalysts, where the elements were initially thought to be closer to Pt due to the preparation method. This is attributed to the presence of Pt_xSn alloys in CP catalysts only and to the replacement of Sn in Pt_xSn(O) by surface indium in SI catalysts. The interpretation

of activity and selectivity differences for the two differently prepared PtSnIn systems is mostly based on these Sn⁰/Pt ratios [7].

4 Conclusions

This study represents a solid basis for the profound understanding of complex metallic interactions that exist in PtSnIn based systems. MS is an elegant analytical tool which provides valuable complementary information to other techniques such as EXAFS and XPS. Thanks to MS it has been shown that the preferential formation of a given Sn phase in these catalysts is directly related to the preparation method, as well as the presence (or not) of other promoters.

Acknowledgements Authors are thankful to the Languedoc Roussillon Region for the financial support to X-rays and gamma-rays platform (Contracts n° 2006 Q-086 and 2008 – 094192).

References

1. Antos, G.J., Aitani, A.M.: Catalytic Naphtha Reforming, 2nd edn. Marcel Dekker, New York (2004)
2. Bocanegra, S.A., Castro, A.A., Scelza, O.A., de Miguel S.R.: Characterization and catalytic behavior in the n-butane dehydrogenation of trimetallic InPtSn/MgAl₂O₄ catalysts. *Appl. Catal. Gen.* **333**(1), 49–56 (2007)
3. Olivier-Fourcade, J., Womes, M., Jumas, J.-C., Le Peltier, F., Morin, S., Didillon, B.: Investigation of redox properties of different PtSn/Al₂O₃ catalysts. *Chem. Phys. Chem.* **5**, 1734–1744 (2004)
4. Womes, M., Le Peltier, F., Morin, S., Didillon, B., Olivier-Fourcade, J., Jumas, J.-C.: Study of the reaction mechanisms between Sn-(n-C₄H₉)₄ and alumina surface sites—application to the controlled preparation of PtSn/Al₂O₃ catalysts. *J. Mol. Catal. A: Chem.* **266**, 55–64 (2007)
5. Jahel, A., Avenier, P., Lacombe, S., Olivier-Fourcade, J., Jumas, J.-C.: Effect of indium in trimetallic Pt/Al₂O₃SnIn-Cl naphtha-reforming catalysts. *J. Catal.* **272**, 275–286 (2010)
6. Jahel, A., Avenier, P., Lacombe, S., Olivier-Fourcade, J., Jumas, J.-C.: Investigation by Mössbauer spectroscopy of Sn redox transformations during H₂/O₂ titration on Pt/Al₂O₃Sn-Cl and Pt/Al₂O₃SnIn-Cl naphtha reforming catalysts. *J. Phys.: Conf. Ser.* **217**, 011245 (2010)
7. Jahel, A.: Study of the indium addition to the Pt-Sn/Al₂O₃-Cl system used in catalytic naphtha reforming. PhD thesis, Montpellier (2010)