

RESIDUAL STRESS CALCULATIONS AND MEASUREMENTS – REVIEW AND ASSESSMENT OF THE IIW ROUND ROBIN RESULTS

H. Wohlfahrt, Th. Nitschke-Pagel, K. Dilger,
D. Siegele, M. Brand, J. Sakkietibutra and T. Loose

ABSTRACT

A Round Robin Programme was established by a working group of Commission X in 1997 in order to evaluate the possibilities of residual stress and distortion prediction (RSDP) in welded structures and to validate and benchmark prediction codes based on finite element simulation of the welding process. Calculations on residual stresses have been carried out on an austenitic steel plate with well-defined material and geometrical data, welding conditions and with the proposal to use the kinematic hardening model. In addition, a second programme for measurements of residual stresses in this plate has been started in 2003. Measurements have been taken on three austenitic steel plates using the X-ray measuring method as well as neutron diffraction methods and different kinds and variations of the hole drilling method. Although a rough agreement between the measured results and the calculated ones was found in principle, distinct differences have been observed in detail – especially for the longitudinal residual stresses. The calculations indicated nearly constant tensile stresses of the order of the initial yield strength in the weld seam and in the adjacent heat affected zone (HAZ). The measurements however revealed stress maxima in the HAZ with values clearly higher than the initial yield strength. Therefore additional calculations have been carried out with different hardening models in order to investigate their influence on the residual stress results. In fact, calculations performed with the isotropic hardening model could approve these stress maxima quite exactly. In further detailed investigations, it could be shown that the reason for the stress maxima is the strain hardening in the HAZ due to thermal stresses during the welding process. Finally basic considerations could explain that the kinematic hardening model, including the Bauschinger effect, cannot account for this hardening effect. Literature indicates that the Bauschinger effect is at least not fully effective at high working temperatures of austenitic steels. Altogether, the calculation programme has shown that a rough estimation of the residual stress state after welding is possible without any special distinction of the hardening model to be used. For a more precise and detailed information, the chosen hardening model is of significant relevance.

IIW-Thesaurus keywords: Simulating; Residual stresses; Distortion; Work hardening; Diffraction; Measurement; Austenitic steels.

120

1 Intention of the Round Robin Programme

A Round Robin Programme was established by a working group of Commission X in 1997 in order to evaluate the possibilities of Residual Stress and Distortion Prediction (RSDP) in welded structures and to validate and benchmark prediction codes based on finite element simulation of the welding process. In addition to the calculation programme (RSDP phase I and phase II) on residual stresses in an austenitic steel plate a second programme for measurements of residual stresses in this plate has been started in 2003. The purpose was to compare the results

of both programmes and thus to validate both methods alternately.

However, significant differences have been found between the calculations of longitudinal residual stresses according to the RSDP programme, phase II, and the measured longitudinal residual stresses. Therefore, additional calculations seemed to be necessary in order to investigate the influence of the material model used in the simulation of the welding process on the calculated residual stresses. Whereas in the RSDP programme, a kinematic material law was recommended and additional calculations have been carried out with the material laws of isotropic hardening, kinematic hardening, mixed hardening and ideal elastic-plastic material behaviour.

2 Basic Items of the Round Robin

Programme

2.1 Welded austenitic steel plate

As a reference for calculations and as a test object for measurements, three plates of the low-carbon austenitic stainless steel 316LNSPH (dimensions in Figure 1) have been used. Each plate was supported at three points. In a prefabricated U-shaped groove (depth ~7 mm) along the 270 mm-long middle line, two passes of filler material (316L, 1.2 mm diameter) have been deposited with tungsten inert gas welding (GTAW). The thermal cycles during welding of both deposits have been controlled by four thermocouples on the upper surface of the plate at different positions along the seam and in different

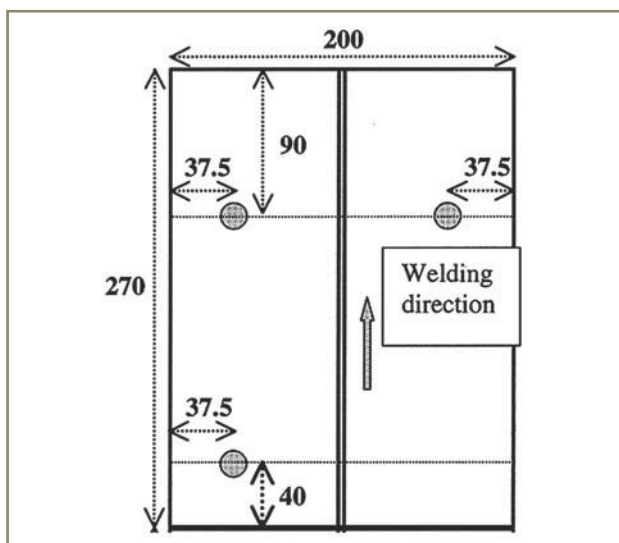


Figure 1 – Geometry of the plate, dimensions in mm, plate thickness: 30 mm [1]

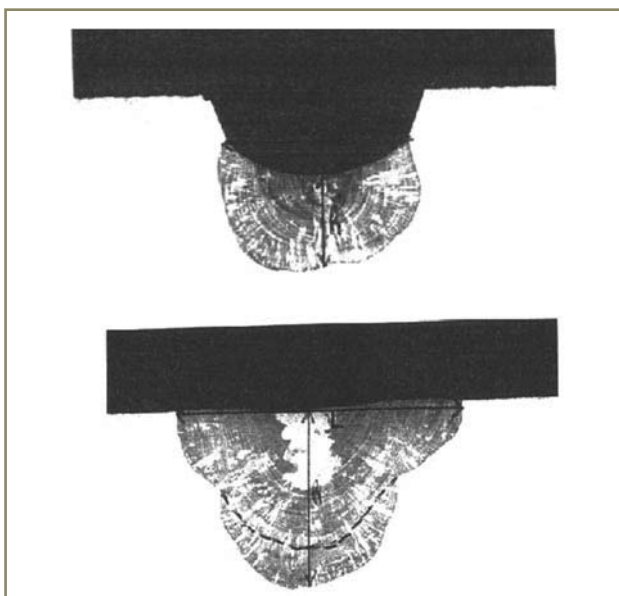


Figure 2 – Macrographs of the 1st pass ($h = 2.7$ mm, 17.5 mm²) and the 2nd pass ($h = 5.9$ mm, total welded zone = 38.5 mm²) [1]

distances from the fusion line. The measured thermal cycles during welding in a laboratory of the Electricité de France Company are registered in [1], where also more details about the welding conditions and a database of the thermal and mechanical material properties are given. Figure 2 illustrates the macrographs of the first and second pass of the weld seam.

2.2 Conditions and requirements of calculations

2.2.1 Conditions and requirements of RSDP (Phase I and Phase II)

For the modelling of the heat input from the welding process, the finite element programme SYSWELD was mainly used, and for modelling the materials deformation behaviour, the kinematic hardening model was recommended. For comparison of the results from the different participants, it was proposed to calculate the longitudinal, transverse and radial residual stresses versus the thickness of the plate (Line 1 and Line 2 in Figure 3) and along lines transverse to the seam at the top side and the bottom side of the plate (Line 3 and Line 4).

The RSDP benchmark has been started in Phase I with 2D analyses but the numerical results required a significant improvement of the quality. As main influence factors on the results the modelling of the heat input, the mesh size near the notch, the assumption of the stress state in the third direction (plane stress, plane strain) and the strain history were identified [2]. Therefore, a second part of the Round Robin has been started with 3D modelling of the geometry and the moving of the heat source. As a first important validation of the modelling of the temperature distribution, the thermal cycles have been compared with the temperature cycles measured during the welding process. Here, the peak temperature and the slope of the temperature profile were identified as the main critical factors influencing the results [3].

2.2.2 Conditions and requirements of additional calculations

The additional 3D thermo-mechanical simulations have been performed in 2008 with the finite element programme SYSWELD (version 2008.1). The plate has been discretised by 55.000 linear volume elements of the type "3008". The elements representing the weld pool have an edge-length of 1 mm. Figure 4 shows the surface and a cross-section of the finite element mesh. To simulate the material input of the filler material during welding, the elements representing the filler material were modelled to have an

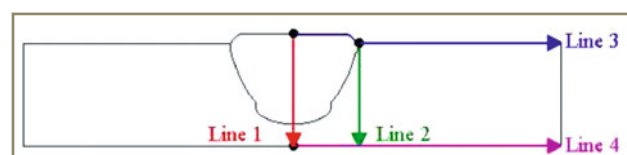


Figure 3 – Lines along which stress calculations have been requested

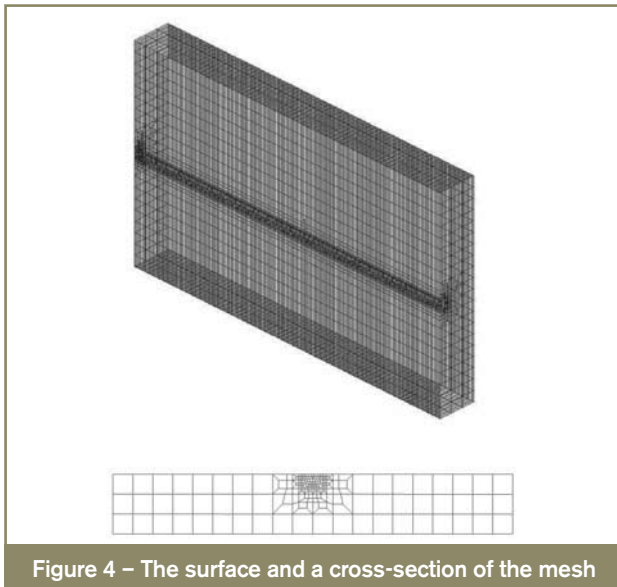


Figure 4 – The surface and a cross-section of the mesh

artificial reduced Young's modulus of 1.000 MPa before welding, and if the elements are heated over 1 450 °C (melting temperature) during welding, the material state was changed to real material properties. Considering the melting of the material, the accumulated plastic strains and the hardening were reset (command "TF") when the melting temperature was achieved. Isotropic, kinematic and mixed hardening models were selected.

The thermo-mechanical calculation was performed in two sequential calculated steps. At first, the temperature distributions, known as the heat effect of welding [4], were calculated. A comparison of measured thermocycles and calculated temperature-time curves, in different distances from the weld pool, is given in Figure 5. Afterwards, the resulting mechanical behaviour is calculated with the calculated temperature distribution as a main input. In different analyses, the heat input was modelled using the Goldak heat source [6] or other heat sources like a conical heat source as used for temperature-field calculation as shown in Figure 5. Geometrical parameters of the heat sources have been fitted to the measured thermocycles. More details about the conditions of these calculations

can be found in [7]. For the given thermophysical properties of austenitic material an excellent agreement between measurement and simulation of the temperature distribution can be achieved.

2.3 Conditions and requirements of measurements

The intention of the measurement programme was the determination of residual stresses at the surface and also in deeper layers by means of different non-destructive and semi-destructive methods using the possibilities of various laboratories. The longitudinal and transverse residual stress components should be measured at different distances from the weld centre line along Line 3 in Figure 3 with non-destructive techniques and along lines parallel to Line 3 in appropriate distances from each other with semi-destructive hole drilling techniques according to Figure 6, respectively. With neutron diffraction, it was also possible to measure the residual stresses along a line parallel to Line 3 in deeper layers. Depth profiles of the longitudinal and the transverse residual stresses have been taken along Line 1 (Figure 3) with neutron diffraction and with the deep hole drilling method and also parallel to Line 1 in a distance of

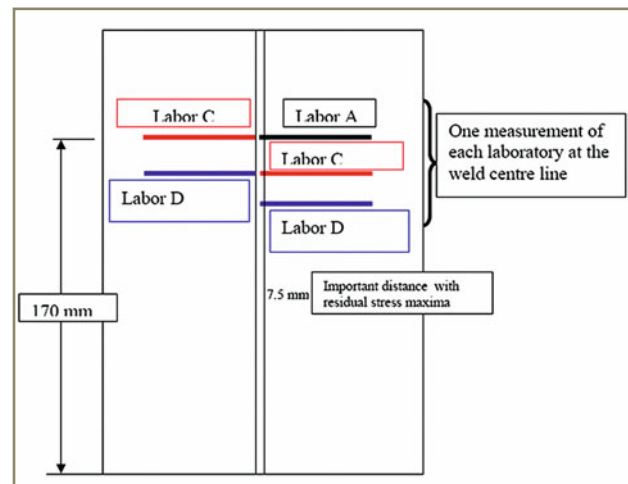


Figure 6 – Plan for measurements of different laboratories with the X-ray and with the hole drilling method [8]

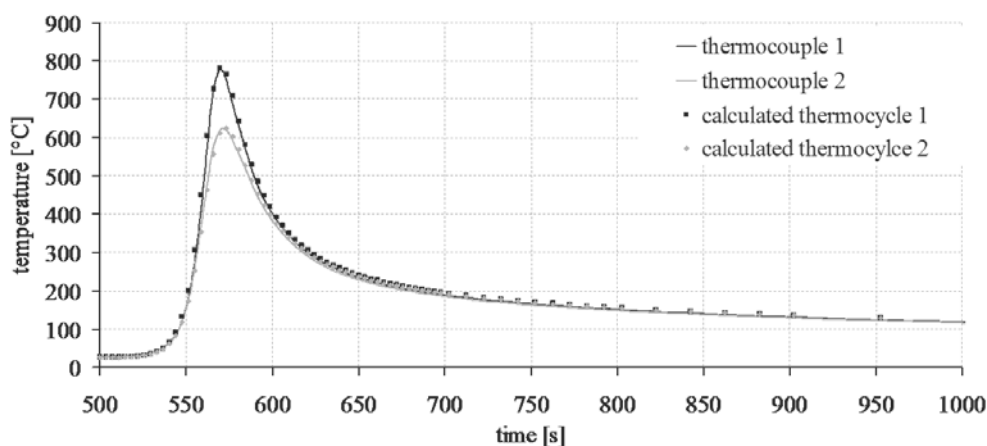


Figure 5 – Comparison of measured and calculated thermocycles across the weld for the 1st pass using a conical heat source [6]

Table 1 – Institutions using non-destructive measuring techniques X-ray diffractometry or neutron diffraction.

Measurements with X-ray diffractometry				
Institution	Measuring positions	Measuring method, radiation	Detector, spot size, irradiated area	Ψ -tilt angles
Institut für Füge- und Schweißtechnik, University of Braunschweig, Dr. Nitschke-Pagel	on a line transverse to the seam, ca. 200 mm from the beginning of the seam, only transverse stresses	X-ray diffractometer, $\sin^2\Psi$ -method, Cr-radiation		
Fraunhofer-Institut Werkstoffmechanik, Freiburg, Germany, Dr. Pfeiffer	on a line transverse to the seam, 170 mm from the beginning of the seam	X-ray STRESSTECH X3000, $\sin^2\Psi$ -method, Mn $K\alpha$ -radiation	2 mm diameter 2 x 22 mm ² , oscillation	11 between +/- 45°
CETIM, Senlis, France, Dr. Lieurade	on a line transverse to the seam, 110 mm from the beginning of the seam	X-ray portable unit, multiple linear regression, Mn $K\alpha$ -radiation	position sensitive spot size 2.5 mm diameter	7 between 0 < $\sin^2\Psi$ < 0.5
Czech Techn. University Prague, Czech Republic, Dr. Ganev	on a line transverse to the seam, 50 mm from the beginning of the seam	portable diffractometer, system. for analysis LUCIA, Cr $K\beta$ -radiation	position sensitive spot size 2 mm, 2 x 22 mm ² , oscillation	
Hitachi Res. Laboratory, Japan, Dr. Shinobu Okido	on five lines transverse to the seam, ~ 20 mm to 66 mm from beginning of the seam	X-ray diffractometer, $\sin^2\Psi$ method, fit with elliptical function, Mn $K\alpha$ -radiation	position sensitive spot size 2 and 3 mm, oscillation	11 between +/- 41.6°
Measurements with neutron diffraction				
Institution	Measuring positions, depth, distance from the beginning of the seam	Measuring method, wavelength, diffraction angle	Gauge volume	
GKSS Res. Laboratory, Geesthacht, Germany Dr. Staron	on lines transverse to the seam, depth 3 mm and 15 mm; 170 mm from the beginning of the seam; in-depth scan: along line 1, Figure 3	Neutron diffractometer ARES, 0.1647 nm, 98.4°	longitud. 3 x 3 x 3 mm ³ , transverse 3 x 3 x 30 mm ³ normal 3x3x30 mm ³	
Institute Laue Langevin, Grenoble, France, Dr. Bruno	on a line transverse to the seam, depth 2 mm; in-depth scan: 2 mm from the weld edge	Neutron diffraction, strain scanner SALSA, 0.1768 nm, ~ 95°	longitud. 3 x 3 x 3 mm ³ , transverse 2 x 2 x 20 mm ³ normal 1x1x20 mm ³	
Monash Univ., ANSTO Melbourne, Australia, Dr. Paradowska	on a line transverse to the seam, depth 3 mm,	Neutron diffraction, strain scanner TASS on HIFAR	longitud. 3 x 3 x 3 mm ³ , transverse 3 x 3 x 20 mm ³ normal 3 x 3 x 20 mm ³	
Rutherford Appleton Lab., Didcot, UK, Dr. Paradowska	on a line transverse to the seam, depth 3 mm and 15 mm; in-depth scan: along line1, Figure 3	Neutron diffraction, ENGIN-X, ISIS Facility	longitud. 3 x 3 x 3 mm ³ , transverse 3 x 3 x 20 mm ³ normal 3 x 3 x 20 mm ³	
<i>Reflecting lattice planes γ-Fe {311}, E = 196 GPa, $\nu = 0.28$ (X-ray) or $\nu = 0.3$ (neutron diffraction). Order of institutions according to the date of measurements.</i>				

about 7 mm from the weld centre line with neutron diffraction. Additionally, it seemed interesting to measure both residual stress components along a line perpendicular to the seam on the backside of the plate (Line 4).

The participants of the measuring programme, their various measuring methods and important parameters of the different techniques are summarized in Table 1 and Table 2.

Table 2 – Institutions using the semi-destructive or destructive measuring techniques: hole drilling method and deep hole drilling method

Measurements with destructive measuring techniques			
Institution	Measuring positions, distances from seam beginning	Measuring method, drilling device, drill diameter, hole depth	Hole diameter, strain gage rosettes (SGR), gage length, stress evaluation
TWI Great Abington, UK, Dr. Wei	on a line transverse to the seam: 110 or 125 mm from the end of plate	abrasion jets for hole drilling, constant depth of holes ca. 1.9 mm	2.1 mm Ø, SGR, 1.59 mm length of individual gage
Paton Electric Welding Institute, Kiev, Ukraine, Prof. Lobanov	on lines transverse to the seam: 106, 116.5, 128 mm	constant depth of holes 1.0 mm	Electron speckle interferometry for measurement of strains,
Fraunhofer-Institut Werkstoffmechanik, Freiburg, Germany, Dr. Pfeiffer	on a line transverse to the seam: 170 mm, mechanical polishing	IHD, high speed drilling device	0.9 mm, SGR, MPA II differential method
CETIM, Senlis, France, Dr. Lieurade	measuring point 6 mm from the weld centre line, 75 mm from the weld beginning	IHD, milling machine, monobloc TC drill, 2 mm Ø	strain gauges, E = 193 GPa, $\nu = 0.3$
Materialprüfungsanstalt Universität Stuttgart, Germany, Dr. Kockelmann	on a line transverse to the seam: ca. 170 mm from the weld beginning	IHD, high speed drilling turbine, 0.8 mm, 1.6 mm Ø	1,10; 1.82 mm Ø, SGR, 5.13 mm Ø, HBM/Kockelmann
Institut Füge/Schweißtechnik, Universität Braunschweig, Germany, Dr. Nitschke-Pagel		IHD, micro measurements milling guide, hard metal drill, 1.6 mm Ø	SGR, 5.13 mm Ø, Schajer method
Institute of Applied Mechanics Brno, Czech Republic, Dr. Slovacek,	on a line transverse to the seam: 170 mm, polish.: emery paper	IHD, SINT high speed drilling device, TC drill, 1.4 mm Ø	SGR, EVAL RSM integral method and power series method
Institute for Materials Science, Welding and Forming, Graz University of Technology, Austria, Dr. Enzinger	on lines transverse to the seam: 100, 110, 120 mm	IHD, hard metal drill. 1.6 mm Ø	1.66-1.87 mm Ø, SGR; 5.14 mm Ø, HBM/Kockelmann E = 206 MPa, $\nu = 0.3$
Department of Mechanical Engineering, University of Bristol, UK, Prof. Smith	on lines transverse to the seam: 65 mm 90 mm	IHD, DHD	

*Different distances from the end of the plate for various measurements.
IHD = incremental hole drilling, DHD = deep hole drilling, E = 196 GPa, $\nu = 0.28$*

3 Results of residual stress calculations

3.1 Calculations according to the IIW programme “RSDP Phase I and Phase II”

As reported in Section 2.2, the RSDP Round Robin has been started with 2D analyses. But due to the simplifications, especially in the heat source modelling and in the 2D stress state, the results of distortion and residual stresses have shown significant discrepancies and were not able to describe the real behaviour of the plate. The calculations have been followed by 3D calculations considering the moving heat source, the fitting of the heat

input to measured thermocycles and temperature dependent material parameters given as input parameters to all participants. The kinematic material law was proposed and used in all calculations. As main results, it can be concluded that the temperature profiles calculated from different partners show relatively small differences with a deviation in the peak temperature of ~ 20 %, but in the residual stresses larger differences were found especially in the region close to the weld pool [9, 10].

Figure 7 shows the longitudinal residual stresses along Line 3 from the centreline of the weld via the heat affected zone to the plate surface. The longitudinal stresses show tension in the weld with peak stresses between 250 and 300 MPa followed by a transition zone whereas the width of this zone deviates in the results from the different

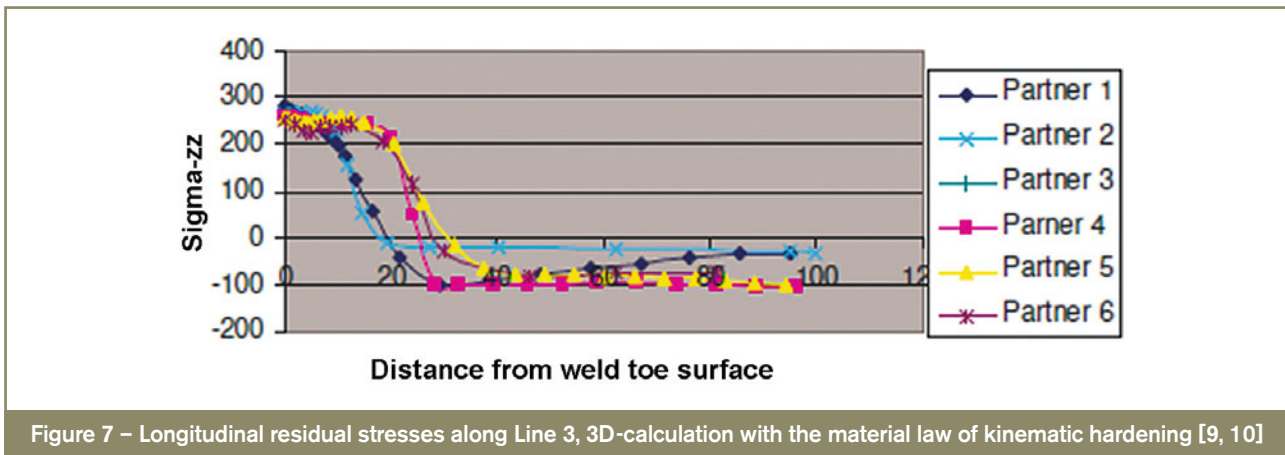


Figure 7 – Longitudinal residual stresses along Line 3, 3D-calculation with the material law of kinematic hardening [9, 10]

partners. The transverse residual stresses on the other hand Figure 8 shows larger discrepancies in the region of interest in the weld material and the neighbouring heat affected zone. In the centreline of the weld, the stress results vary from compression to tension, and therefore also in a region up to 30 mm from the weld centreline, significant differences in the results from different participants are obtained.

3.2 Additional calculations with different strain hardening approaches

As already mentioned, the additional new calculations have been performed in order to clarify whether the use of other hardening rules than proposed in the RSDP programme (Phase II) could provide a better agreement with the results of measurements, especially indicating also the maxima of the longitudinal residual stresses in the HAZ.

Figure 9 and Figure 10 represent calculated distributions of longitudinal and transverse residual stresses in the surface layer of the austenitic steel plate. A purely isotropic hardening model was used for the calculations referring to the state after welding of the second pass. The distribution of longitudinal residual stresses at nodes in Figure 9 reveals clearly a lower magnitude (about 270 MPa) of tensile residual stresses along the weld centre line in comparison with maximum magnitudes of 380 MPa on both sides of the weld seam [11].

Figure 10 indicates that the distribution of transverse residual stresses is not symmetrical with regard to a centreline transverse to the weld seam. The maxima of tensile residual stresses are closer to one end of the seam. This result may be a consequence of the continuous welding process beginning at one end of the plate. Along the middle of the seam a rather broad band of compressive residual stresses with a magnitude of about -50 MPa is noticeable, which is surrounded on both sides by tensile residual stresses with magnitudes up to more than 150 MPa.

The distribution of longitudinal residual stresses over various cross sections in Figure 11 indicates high tensile residual stresses in the range of 400 MPa also in deeper layers, whereas tensile residual stresses (Figure 12) in the transverse direction reach only a smaller depth below surface.

For comparisons (and further discussions), plots of residual stress values versus distance from the weld centre line are used in the following. The next figures represent such distributions of calculated longitudinal and transverse residual stresses along a line transverse to the weld seam in a distance of 180 mm from the weld start. The characteristic features of all distributions of longitudinal residual stresses, calculated with a pure or partly isotropic strain hardening model, show minima at the weld centre line with magnitudes of ca. 270 MPa and maxima in a

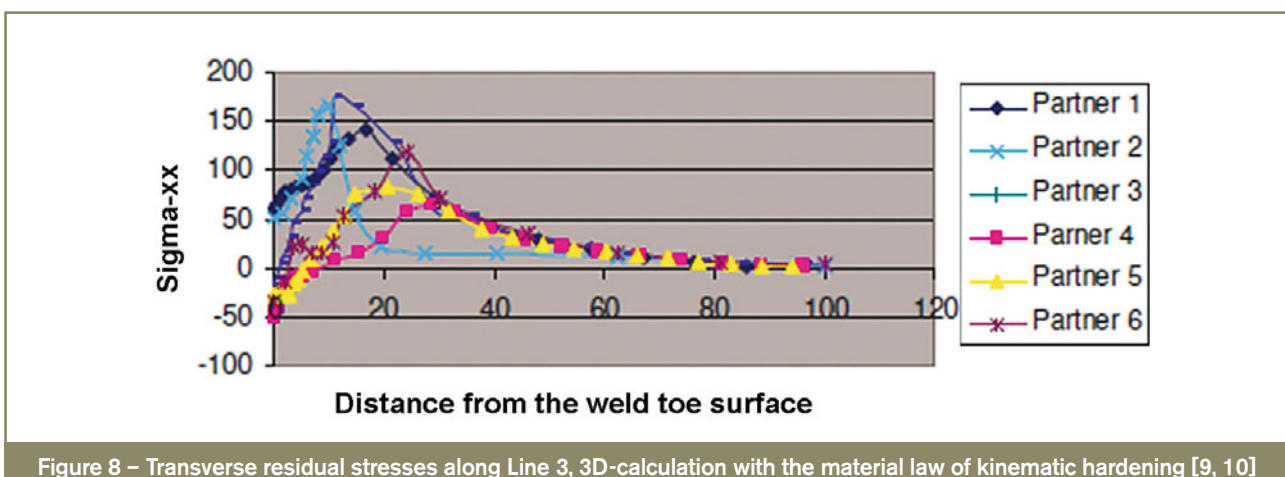


Figure 8 – Transverse residual stresses along Line 3, 3D-calculation with the material law of kinematic hardening [9, 10]

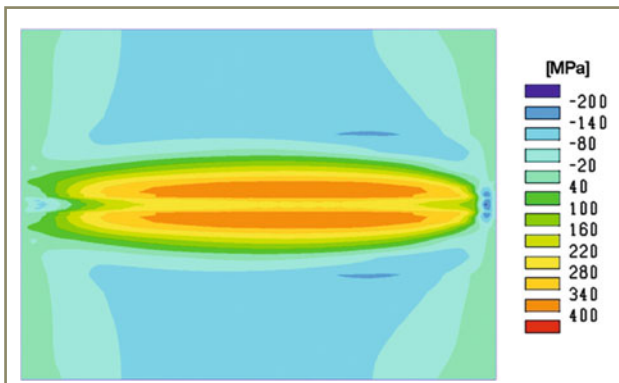


Figure 9 – Longitudinal residual stresses (nodal solution) at the top side of the welded austenitic steel plate, 3D-calculation with the material law of isotropic hardening, [11]

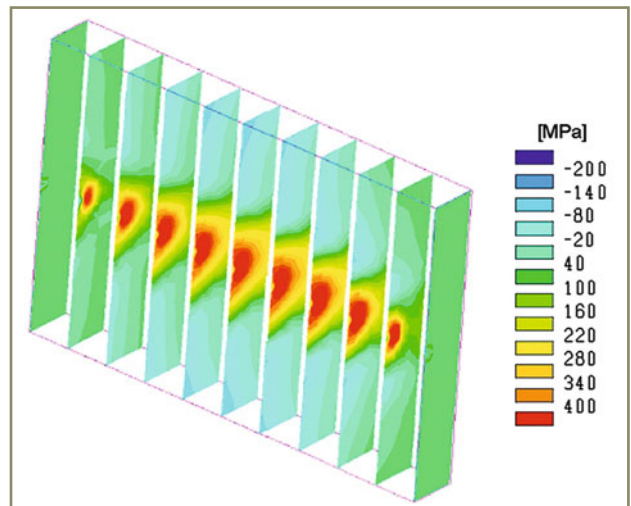


Figure 11 – Longitudinal residual stress distributions over various cross-sections calculated with the material law of isotropic hardening [11]

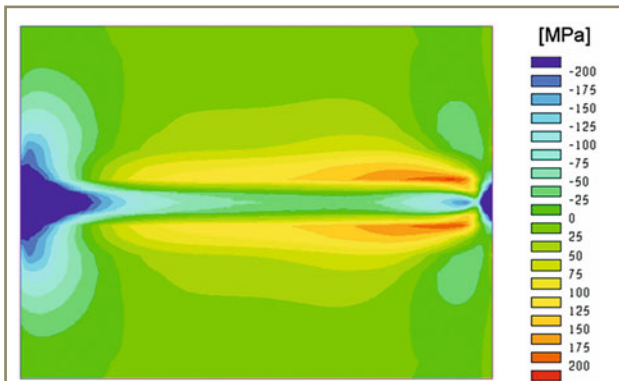


Figure 10 – Transverse residual stresses (nodal solution) at the top side of the welded austenitic steel plate, 3D-calculation with the material law of isotropic hardening [11]

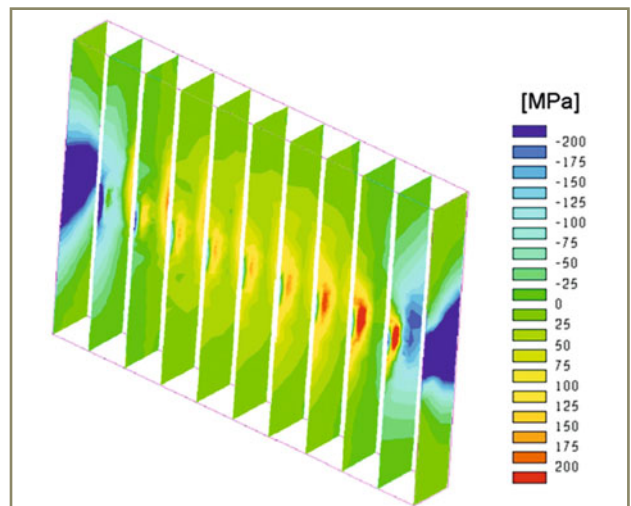


Figure 12 – Transverse residual stress distributions over various cross-sections calculated with the material law of isotropic hardening [11]

126

distance of approximately 8 mm from the weld centre line with various magnitudes, Figure 13.

It is clearly visible that the magnitudes of the maxima decrease with an increasing percentage of kinematic hardening in the model assumptions, from ca. 380 MPa in calculations with a pure isotropic hardening model down

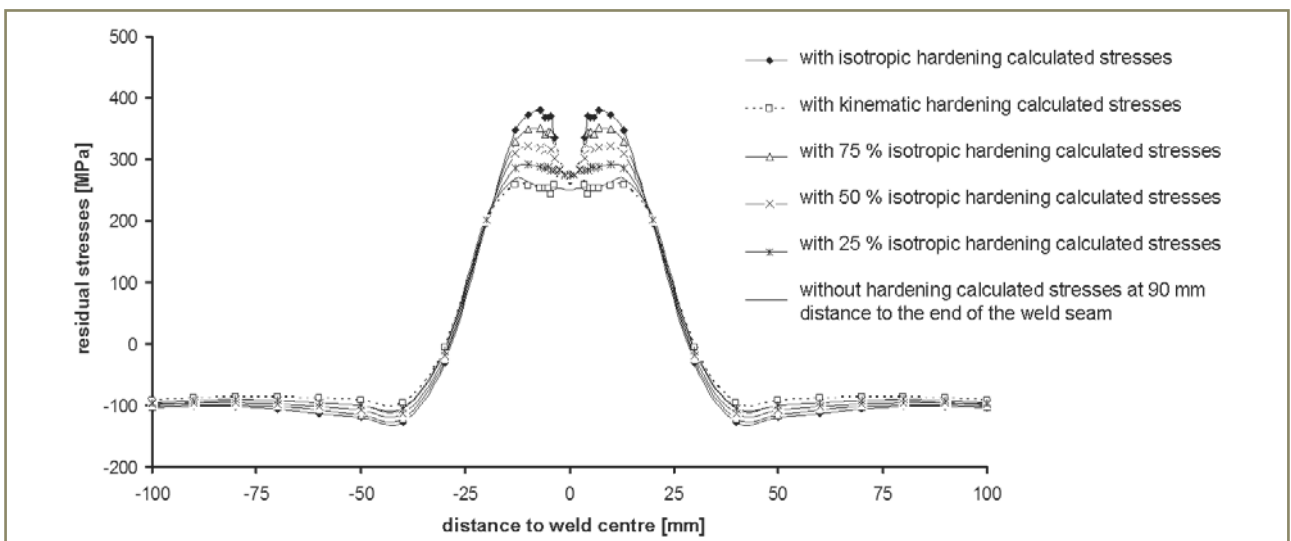


Figure 13 – Longitudinal residual stresses at nodes versus distance from the weld centre line calculated with various material laws [7]

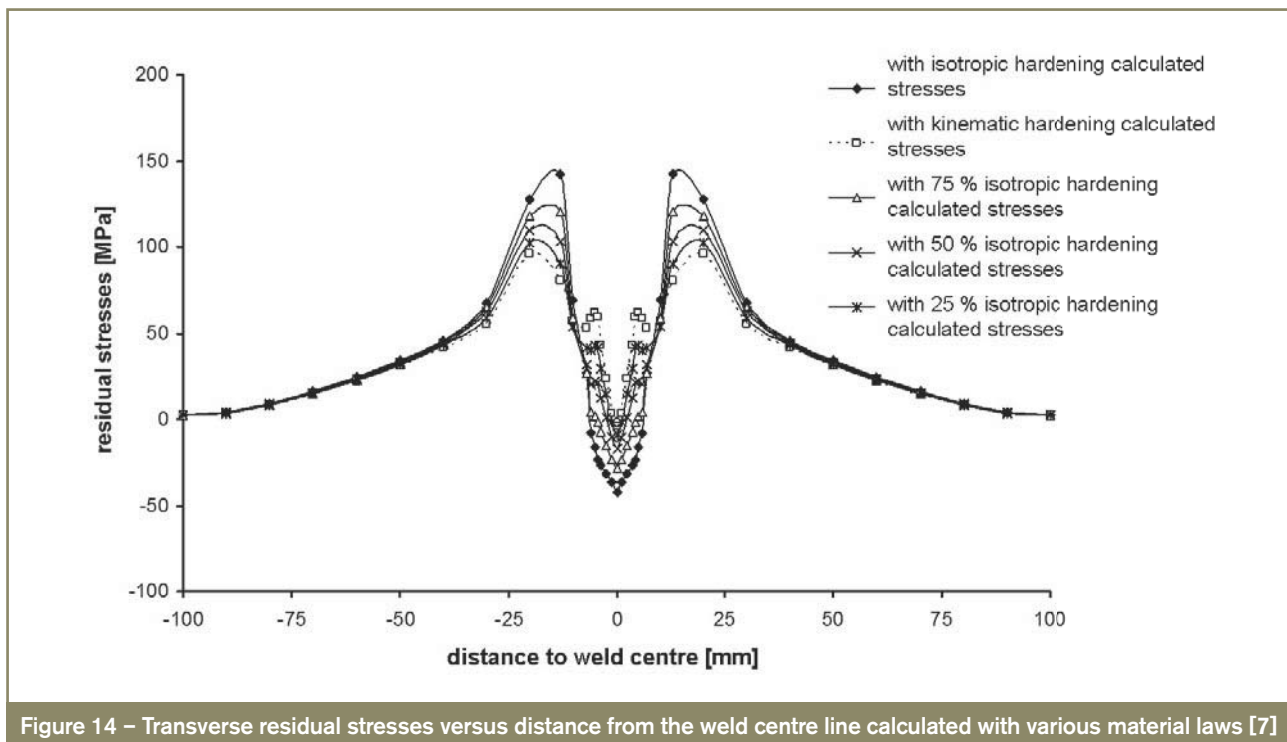


Figure 14 – Transverse residual stresses versus distance from the weld centre line calculated with various material laws [7]

to ca. 300 MPa of a rather weak maximum in calculations with the assumption of 75 % of kinematic hardening. Calculations with a pure kinematic hardening model result in a nearly horizontal distribution of maximum longitudinal stresses of ca. 250 MPa over the weld seam and adjacent areas, practically the same result as with calculations using an ideal elastic-plastic material behaviour.

Distributions of transverse residual stresses calculated with various material laws are illustrated in Figure 14. The assumption of pure isotropic hardening results, in the highest tensile stress maxima of about 150 MPa in a distance of ca. 10 mm from the centre line in comparison with lower stress maxima if the calculation models, contain percentages up to 75 % of kinematic hardening. The minimum stress at the weld centre line, with -50 MPa, is most pronounced under the assumption of pure isotropic hardening. Calculation models containing different percentages of kinematic hardening result in stress minima with lower magnitudes in the compressive range at the centre line.

4 Results of residual stress measurements

As can be seen in Table 1 and Table 2 an important number of institutions has carried out measurements of residual stresses of one of the test plates with various techniques and different methodologies. Typical results of each measuring technique will be illustrated in the following figures. The figures are supplemented by Table 3 in order to present as much as possible the entity of all results, which cannot be shown in detail. Results, which

do not agree with the illustrated main tendencies, will be specifically mentioned [8, 12 and 13].

4.1 Distributions of residual stresses versus distance from the weld centre line, measurements integrating over a distinct depth

4.1.1 Non-destructive measurements

Non-destructive measurements have been carried out in laboratories A, B, I and L by means of X-rays and in laboratories G, H, N and P with the neutron diffraction method. Individual measuring conditions are summarized in Table 1. An important feature of each method is the “integration volume” over which an averaged value of the locally varying residual stresses is taken and if stress gradients versus depth are to be anticipated especially the “integration depth” as the thickness of the layer over which the varying stresses are integrated. It must be emphasized that the integration depth of the X-ray method is only 10 μm , that is extraordinary low in comparison with all other methods. The incremental hole drilling technique, for instance, uses a first step with a depth of 0.02 mm or of 0.05 mm, whereas in neutron diffraction the integration depth is, for instance, 3 mm.

Typical residual stress distributions taken by X-ray diffractometry are shown in Figure 15. They are characterised by the stress minima at the weld centre line, ca. -150 MPa for the transverse stress component and ca. +300 MPa for the longitudinal component, and by pronounced tensile stress maxima in the HAZ, +300 MPa in the transverse stress distribution and +500 MPa in the distribution of longitudinal stresses in distances of ca. 10 mm and 6 mm to 8 mm from the centre line, respectively. In larger

Table 3 – Magnitudes of longitudinal and transverse residual stresses measured with different techniques at the weld centre line and in distances of 6 to 8 mm or 10 mm as well as in 20 mm from the weld centre line

Labor, method, integration depth, plate number	At (or close to) the centre line		6 to 8 mm (long.) or 10 mm (transv.) from the centre line		20 mm from the centre line	
	longitud. stress	transverse stress	longitud. stress	transverse stress	longitud. stress	transverse stress
A, X-ray, 10 μm, I, II	290, 302	-144, (-71)	512, 495	287, 361	-178, 86	-279, -6
B, X-ray, 10 mm, III			428, 430	356		
I, X-Ray, 10 μm, II			255, 240	396, 404	-77, 80	191, 213
L, X-Ray, 10 μm, I	(-116)	(-183)	(258, 269)	167, -22	-133, 96	29, 33
A, incr. hole dr., II	200	0	540	110	-10	-50
B, incr. hole dr., III	150		580	170		
C, incr. hole dr., II	150	-115	492, 563	14, 49	289	34
D, hole drill, 0.02, II	262	-27	480	56	78	-44
E, incr. hole dr., II	480	20	380 - 480	80 - 90	0 - 100	-270 - 0
F, incr. hole dr., II	-50, 350	-60, 70	0, 350	-20, 150	-80, -120	-120, -230
M, hole.dr., 1.0 mm, III	191 - 293	-40 - 157	346 - 410	(43 - 165)	218	81
K, hole dr., 1.9 mm, III	255	167	321, 356	(135, 160)	213	152
G, neutr. diff., 2 mm, III			280	260	220	140
H, neutr. diff., 3 mm, I	180	0	270, 290	100	120	0
N, neutr. diff., 3 mm, I	180	0	330, 370	100	160	70
P, neutr. diff., 3 mm, I	160	20	300, 320	80 - 100	80 - 140	30 - 40

*Stress magnitudes in MPa.
Results in brackets are obtained under different conditions.*

128

distances from the weld, the residual stresses decrease to lower values, which are rather inconsistent in different measurements. It can be concluded that this inconsistency, in areas more remote from the weld, is rather a consequence of foregoing machining operations, which induce stresses in a very thin surface layer of the plate, than of the heat input due to welding (Figure 15).

The results of other measurements by means of X-rays offer a qualitative confirmation of the mentioned results with the same pattern of minima at the weld centre and maxima in the HAZ. The results of laboratory I show also sharp stress maxima in the HAZ, but the maximum

magnitudes of longitudinal and transverse stresses look like exchanged, Figure 16. Laboratory L on the other side has provided a laminar illustration by measuring stresses along five lines transverse to the seam in distances between 20 mm and 66 mm from the beginning of the seam, Figure 17. Minimum magnitudes and partly compressive stresses along the weld centre and areas with maximum magnitudes more outside are clearly to be seen. Possibly the quantitative differences between the results of laboratories I, L and laboratories A, B can be a consequence of the fact that measurements have been carried out in different distances to the beginning of the weld seam (see Table 3).

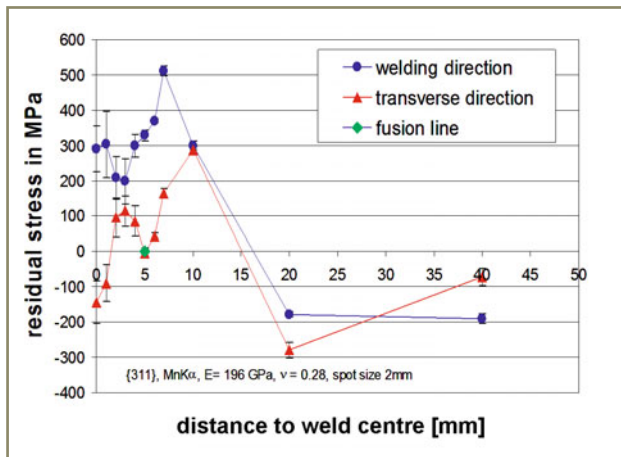


Figure 15 – X-ray results, laboratory A, plate I. Distribution of longitudinal and transverse residual stresses measured over a depth of ca. 10 μm [8]

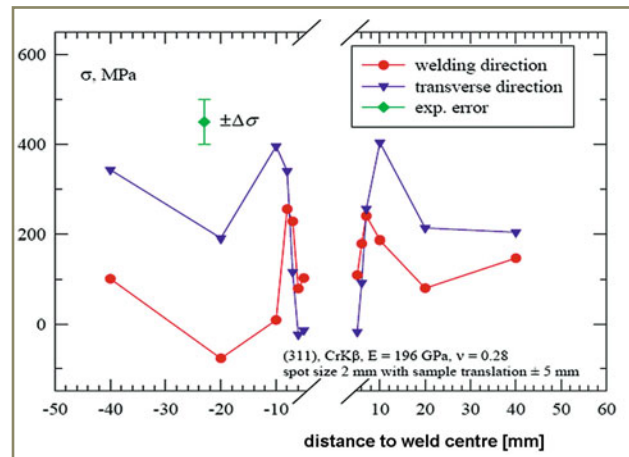


Figure 16 – X-ray results, laboratory I, plate II. Distribution of longitudinal and transverse residual stresses measured over a depth of ca. 10 μm [12]

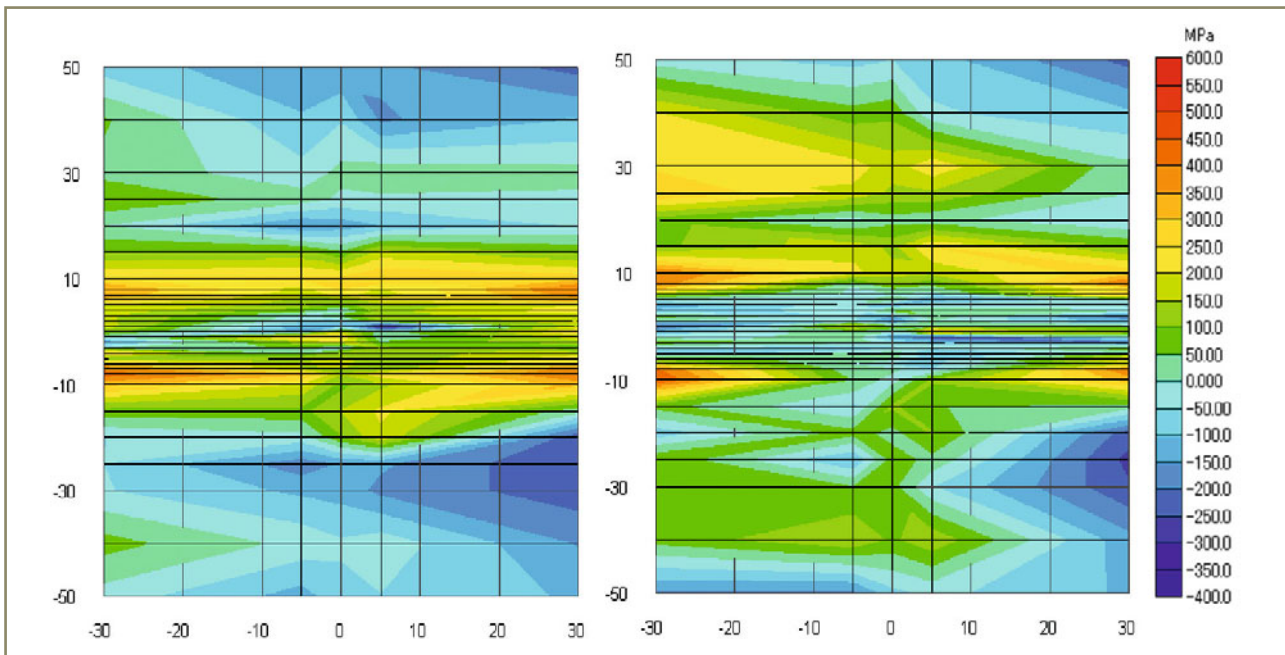


Figure 17 – Planar illustration of residual stresses measured by means of X-rays, laboratory L, plate I, longitudinal stresses (left), transverse stresses (right) in MPa over the distance from the centre of electrochemical polished area in mm [13]

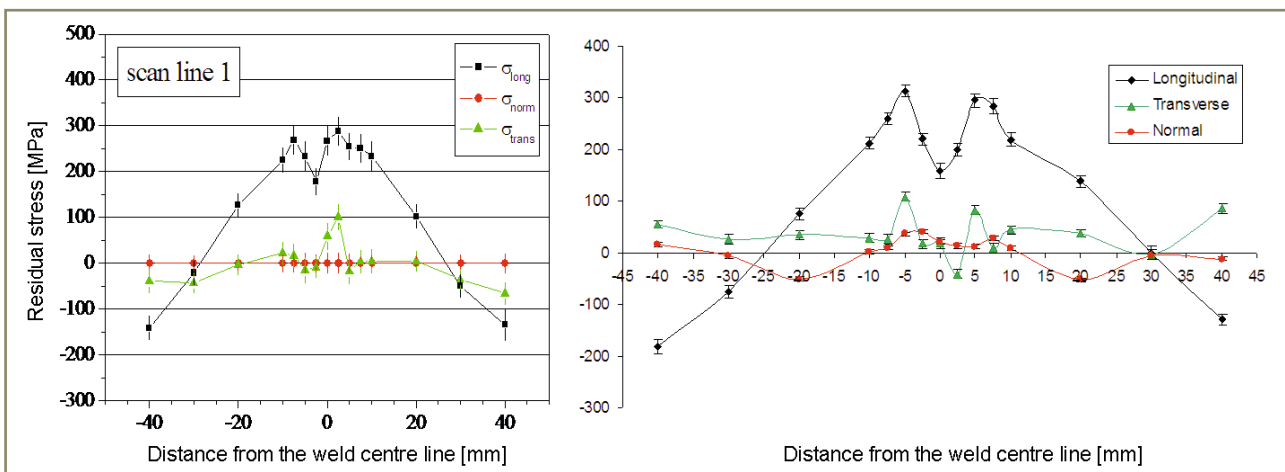


Figure 18 – Results of neutron diffraction, laboratory H (left) and P (right), plate I, measuring depth = 3 mm [12, 13]

The residual stress distributions taken by neutron diffraction reveal also the same characteristics: relative stress minima at the weld centre line and tensile stress maxima in certain distances from the centre line. However the maxima are less pronounced than in the X-ray measurements, for instance +100 MPa for the transverse stress component and +300 MPa for the longitudinal component, as can be seen in typical stress distributions in Figure 18. In connection with these results, one has to keep in mind that the neutron diffraction measurements evaluate stress values averaged over a depth of 3 mm. In the longitudinal stress distributions, balancing compressive stresses can clearly be seen in distances bigger than 25 mm respectively 30 mm from the weld centre line. The magnitudes of the transverse stresses beyond the weld seam, as well as the normal stresses, remain in a very low range over the whole width.

4.1.2 Semi-destructive measurements

Two institutions used the hole drilling method in order to find residual stress distributions versus distance from the weld centre line. At each measuring point, the measured stresses are integrated over a distinct depth below surface.

Laboratory K used measuring lines transverse to the seam in distances of 110 mm respectively 125 mm from the end of the seam. The results reported in Figure 19 indicate maxima of the longitudinal stress component of 356 MPa respectively 327 MPa in distances of 7.5 mm from the centre line on both sides of the seam. At the weld centre line, longitudinal stresses attain a minimum value of 255 MPa on the top side of the plate (side A). The transverse component shows nearly constant values between 135 MPa and 167 MPa. Longitudinal stresses measured

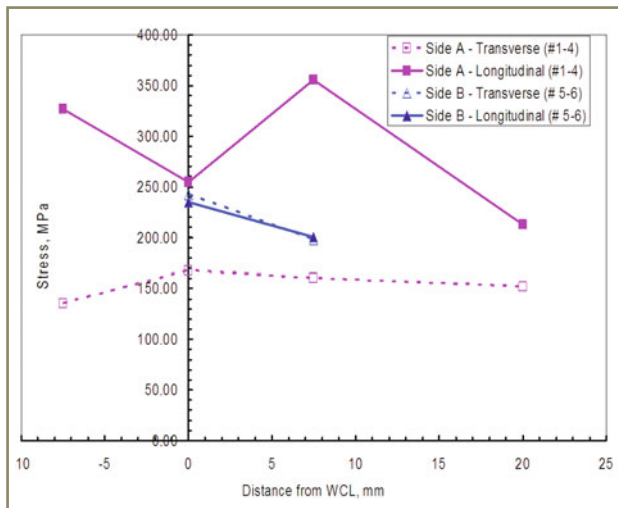


Figure 19 – Hole drilling results, laboratory K, plate III, residual stresses averaged over a depth of 1.9 mm [12]

on the back side (side B) indicate a maximum magnitude at the weld centre line (235 MPa) and a lower stress value in a distance of 7.5 mm from the centre line; transverse stresses are nearly identical on this side of the plate.

The technique of laboratory M is a sophisticated variant of the hole drilling method using electron speckle interferometry for the measurement of deformations during hole drilling. Measurements are taken along lines transverse to the seam in distances of 106 mm, 116.5 mm and 128 mm from the end of the seam and the integration depth of each measured stress value was 1.0 mm in this case. Results in Figure 20 reveal again tensile maxima of longitudinal stresses between 346 MPa and 410 MPa in distances of 7.5 mm from the centre line and minima at the centre line between 191 MPa and 293 MPa. Two courses of transverse stresses show distinct minima in the compressive range at the centre line, the third course does not exhibit such a minimum, but nearly the highest tensile stress at the centre line.

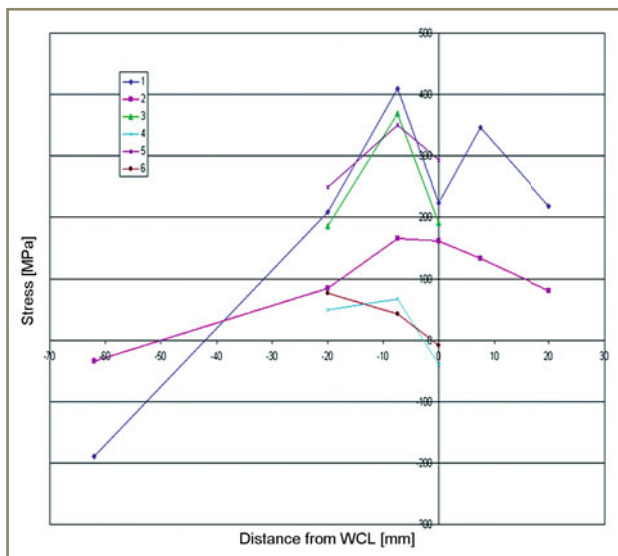


Figure 20 – Electron speckle-interferometry after hole drilling, laboratory M, plate III, residual stresses averaged over a depth of 1.0 mm [13-15]

In order to indicate the main results of the measurements and even some contradiction, in Table 3 magnitudes of longitudinal and transverse residual stresses which have been measured at the weld centre line, are summarized in the important positions between 6 mm and 8 mm from the centre line and in a distance of 20 mm from the centre line. Additional to magnitudes measured by means of X-rays and with neutron diffractometry, results found with the first step of the incremental hole drilling method close to the surface can give a useful completion and also some confirmation of the residual stress values measured for instance by means of X-rays at the weld centre line, although the hole drilling technique may produce errors due to the necessary polishing of the surface of the weld seam. But X-ray measurements at the top of the weld seam are also difficult and connected with rather big measuring errors.

As one can see in Table 3, most of the stress values measured by means of incremental hole drilling underline the existence of a relative minimum at the weld centre line and are also a good confirmation of stress maxima in a distance between ca. 6 mm and 8 mm from the centre line, even if individual values are not in accordance with this tendency. Differences of results of X-ray measurements of laboratories I and L have been discussed already in the foregoing chapter and it has been mentioned, that they also underline the tendency of maxima in the HAZ and a minimum close to the weld centre line (Figure 16 and Figure 17).

Finally all measurements of the longitudinal stress component reveal rather clear patterns, very close to the surface (X-ray, incremental hole drilling) and also in deeper layers (hole drilling, neutron diffraction): a relative minimum of tensile stresses at the weld centre line and tensile stress maxima in the HAZ in a distance of 6–8 mm from the centre line. Considering the magnitudes of the maxima, a clear tendency can be observed: these magnitudes are obviously higher in layers very close to the surface and decrease with the measuring depth. Magnitudes in layers very close to the surface (X-ray, incremental hole drilling) are mainly in the range between 400 MPa and 500 MPa (mean value 477 MPa, with exception of laboratory I and L) whereas in a measuring depth of 1.0 mm or 1.9 mm (hole drilling method with constant hole depth, laboratories K and M) these magnitudes are in the range between 320 MPa and 410 MPa (mean value 358 MPa) and in measuring depths of 2.0 mm and 3.0 mm (neutron diffraction) the lowest magnitudes between 270 MPa and 370 MPa (mean value 309 MPa) have been found. For the minima at the weld centre line, such a tendency cannot be observed. With some exceptions, these minima remain at medium magnitudes. With the exception of X-ray measurements, all results demonstrate balancing compressive longitudinal stresses in distances bigger than 25 mm to 30 mm from the centre line.

Transverse stresses show (with two exceptions) minimum magnitudes at the weld centre line, often in the

compressive range or close to zero. Transverse stress distributions measured by means of X-rays or with the hole drilling method indicate in principle similar patterns as longitudinal stresses, but with smaller minima at the centre line or minima in the compressive range (see Table 3) and smaller maxima in the HAZ. Values measured in the HAZ (10 mm from the weld centre line) with the incremental hole drilling method are rather inconsistent and cannot confirm the maxima.




According to measurements versus distance from the centre line in a depth of 15 mm with neutron diffraction techniques, longitudinal residual stresses show a maximum magnitude between 180 MPa (laboratory H) and 230 MPa (laboratory P, Figure 21) in the position below the centre line and decrease down to zero in a distance of ca. 25 mm and in bigger distances from the centre line to compressive stresses. Magnitudes of transverse stresses below the centre line are 100 MPa in the compressive range and decrease to zero respectively change into the tensile range with increasing distance from the centre line.

4.2 Distributions of residual stresses versus depth below surface

Typically for the incremental hole drilling method, evaluations of the residual stresses are at distinct positions down to a depth in the range of 1 mm. Consequently, such measurements offer information about residual stress gradients in surface layers of an appropriate thickness. Information about the residual stress field, in deeper layers respectively about the course of residual stresses down to deeper layers, has been taken with other techniques like neutron diffraction or the deep hole drilling method.

4.2.1 Measurements with the hole drilling method, depth values < 1.2 mm [12]

Examples of residual stress distributions versus the depth below the surface at selected positions are illustrated in Figure 22 to Figure 26. At the same distances to the centre line, magnitudes of measurements close to the surface are obviously within a reasonable scatter band,

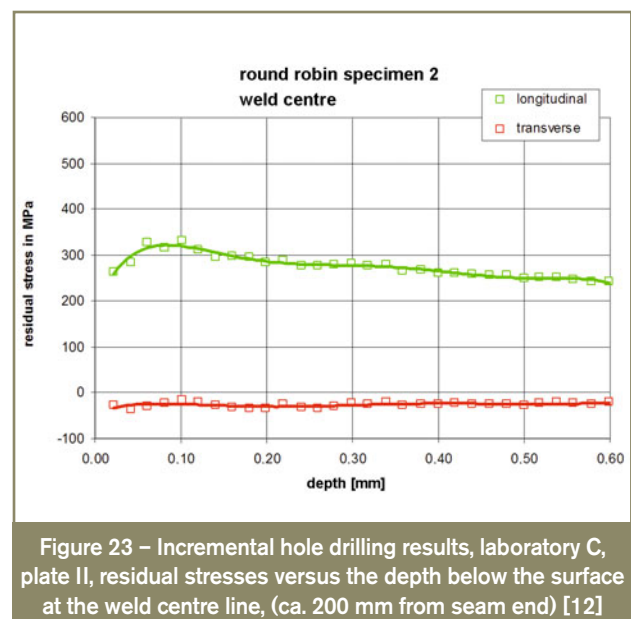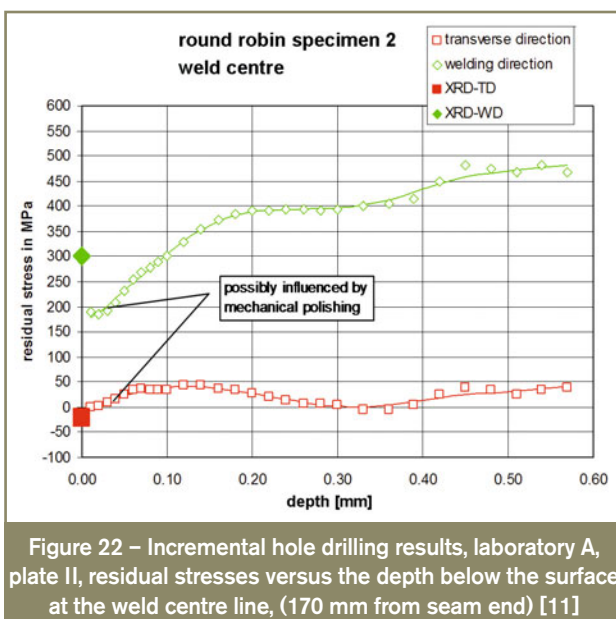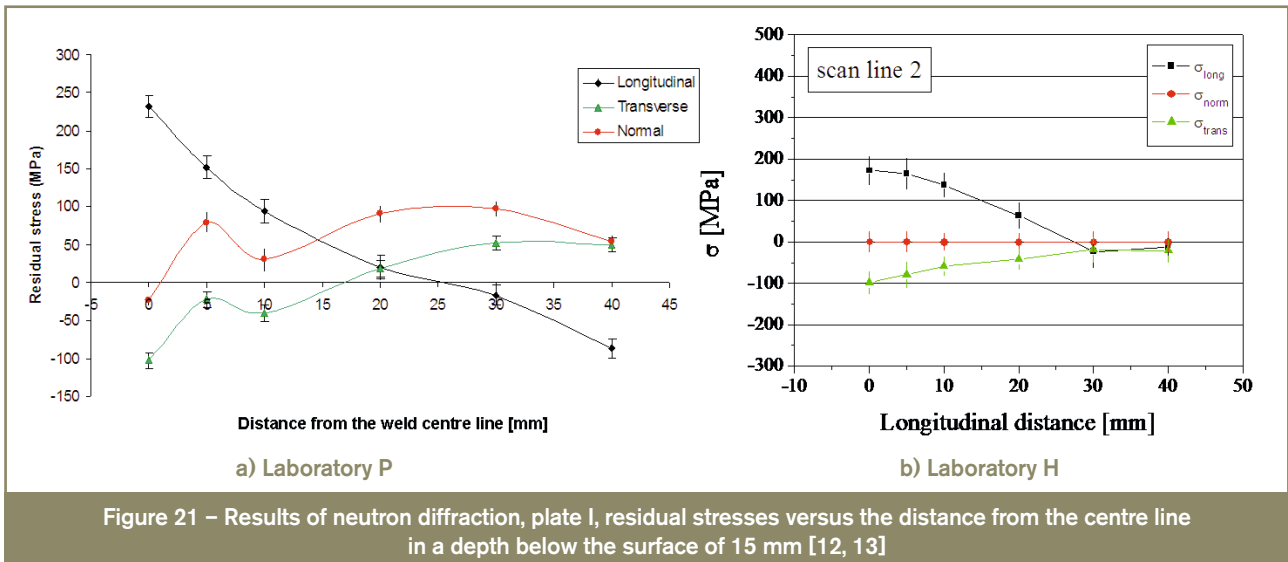

as already shown in Table 3. But courses of longitudinal residual stresses versus the depth below the surface under the weld centre line show some inconsistencies: longitudinal stresses with strongly increasing magnitudes versus the depth below the surface have been evaluated (Figure 22) as well as nearly constant or slowly decreasing (Figure 23) longitudinal stresses.

But as inscribed in Figure 22, very low magnitudes of longitudinal and transverse stresses, measured by laboratory A very close to the surface, may be a consequence of mechanical polishing, which was especially necessary on the uneven surface of the seam. Due to general experience, the mechanical polishing could have changed the original stress values in the direction of compressive stresses and the rather steep increase of longitudinal stresses in layers very close to the surface would become understandable in this case – and also in other cases.

At the position of the maxima of longitudinal residual stresses in distances between 6 mm and 8 mm from the weld centre line, results of different laboratories are really consistent. A decrease from high maximum tensile stresses close to the surface was observed towards deeper layers in all measurements. This decrease is followed by a new, small increase of magnitudes towards the final depth (Figure 24). A comparison of results of laboratory E indicates that the increment of the drilling depth may have a substantial influence on the stress distribution.

In a distance of 20 mm from the centre line, low longitudinal residual stresses show in most measurements, with the exception of the first values close to the surface, nearly constant magnitudes of 150 MPa or ca. 200 MPa over a wide depth range (Figure 25). The steep increase of stresses close to the surface in two cases could again be a consequence of mechanical polishing.

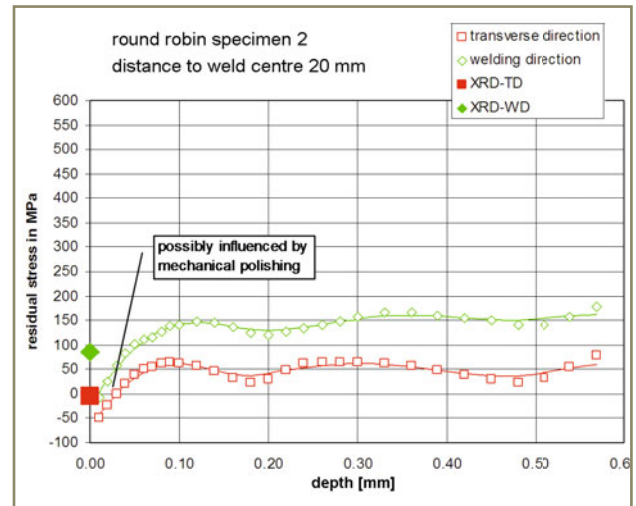


Figure 25 – Incremental hole drilling results, laboratory A plate II, residual stresses versus the depth below the surface at a distance of ca. 20 mm from the weld centre line [12]

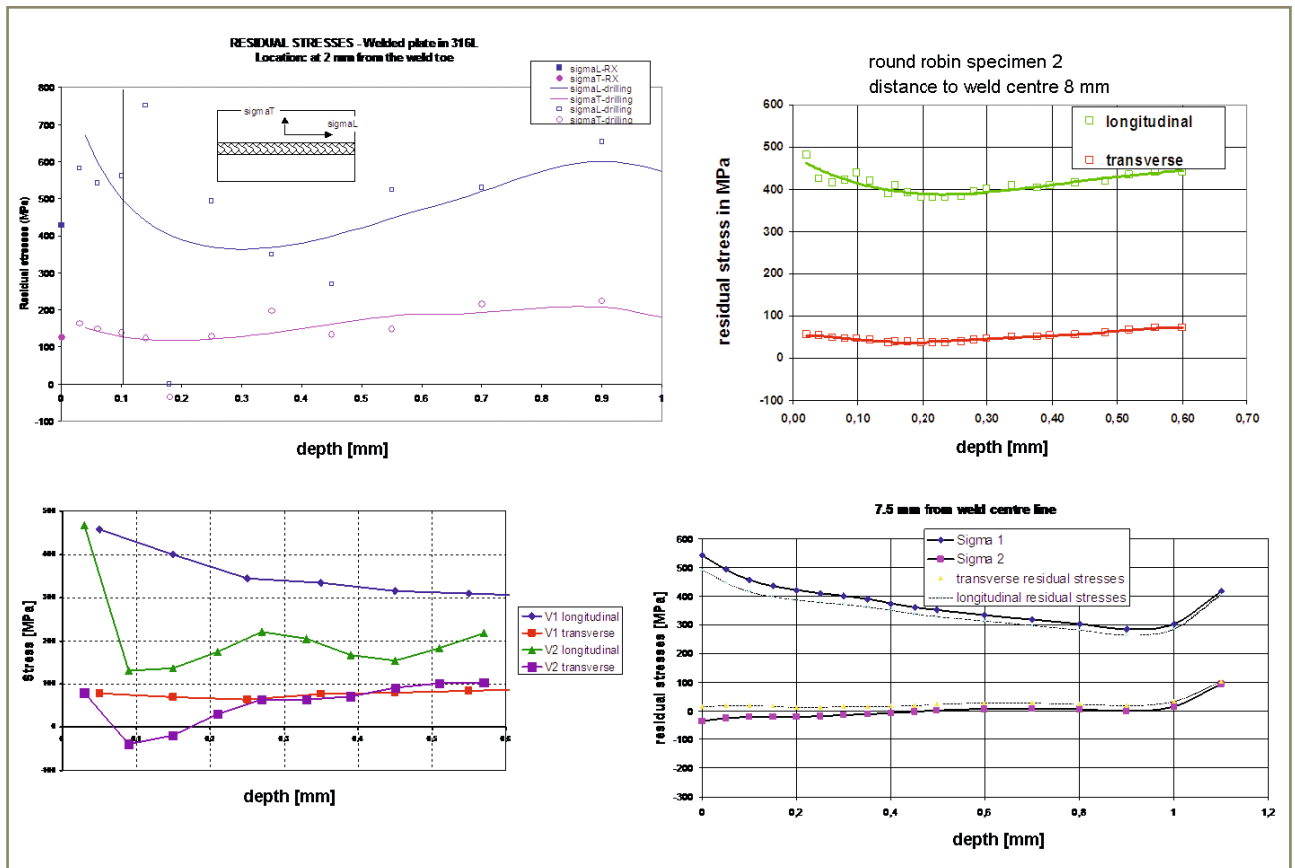


Figure 24 – Incremental hole drilling results, laboratories B (upper left, plate III), C (upper right), D (lower left), E (lower right), plate II, residual stresses versus the depth below the surface at a distance of ca. 6 mm from the weld centre line [11, 12]

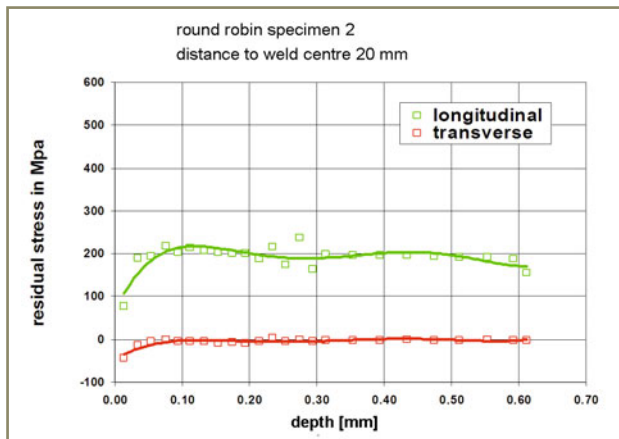


Figure 26 – Incremental hole drilling results, laboratory C plate II, residual stresses versus the depth below the surface at a distance of ca. 20 mm from the weld centre line, (ca. 200 mm from seam end) [12]

Small magnitudes of transverse residual stresses remain nearly constant versus the depth below the surface – under the weld centre line mainly in the compressive range and at positions between 6 mm and 8 mm from the centre line mostly in the tensile range between 50 MPa and 200 MPa (Figure 22 to Figure 24). In a distance of 20 mm from the centre line, courses of transverse stresses versus the depth below the surface are nearly constant with small magnitudes either in the tensile or in the compressive range, Figure 25 and Figure 26.

4.2.2 Measurements with neutron diffraction and with the deep hole drilling technique, depth values > 1.2 mm

With the neutron diffraction technique, longitudinal and transverse stress components have been measured versus the distance from the surface to a depth of maximal 27 mm and also along line scans transverse to the seam in a depth of 15 mm. Measurements of the longitudinal stress component versus the depth under the weld centre line indicate an increase of tensile stresses up to magnitudes of ca. 230 MPa or 370 MPa in layers of 6 mm

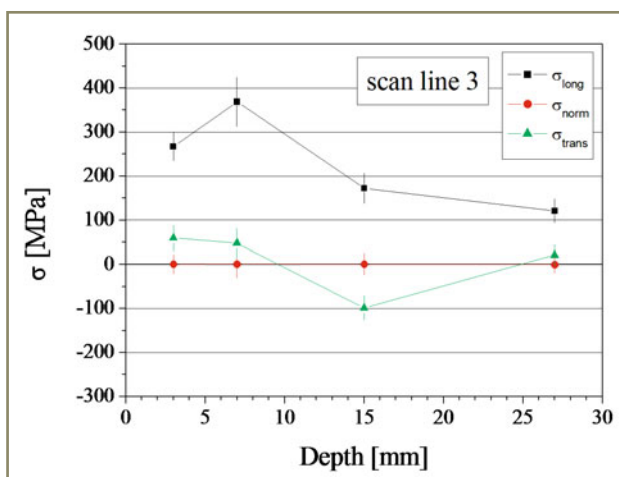


Figure 27 – Neutron diffraction results, laboratory H, plate I, residual stresses versus the depth below the surface at the weld centre line, (170 mm from seam end) [12]

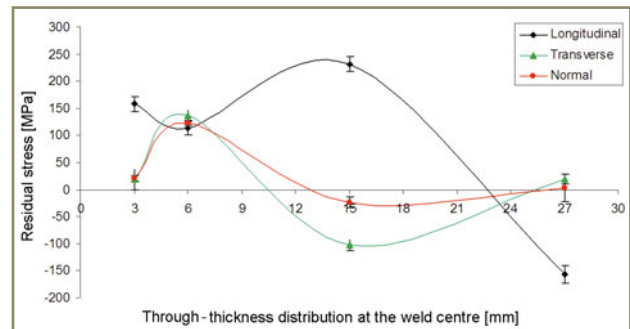


Figure 28 – Neutron diffraction results, laboratory P, plate I, residual stresses versus the depth below the surface at the weld centre line [13]

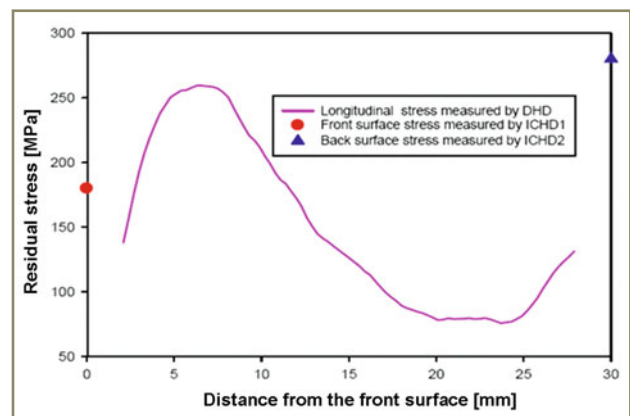


Figure 29 – Results of the deep hole drilling method, Laboratory Q, plate III, longitudinal residual stresses versus the depth below the surface at the weld centre line [13]

respectively 15 mm below the surface (Figure 27 and Figure 28).

According to these measurements, tensile residual stresses are still present in layers of more than 20 mm below surface. With the deep hole drilling method, a similar distribution of the longitudinal stress component versus the depth below the surface, with a maximum magnitude of more than 250 MPa in a depth of ca. 6 mm, has been evaluated (laboratory Q, Figure 29). In-depth measurements at the position 6 mm from the weld centre line (laboratory G, Figure 30) revealed also tensile longitudinal stresses between 200 MPa and 300 MPa in a depth between 2 mm and 6 mm which are slowly decreasing from 6 mm to 10 mm depth.

4.3 Results of additional investigations

4.3.1 Calculated deformations of the plate due to welding

In addition to residual stress evaluations, the bending around the weld axis (angular distortion) as well as the bending around an axis transverse to the weld seam, have been measured and calculated at the Fraunhofer-Institut für Werkstoffmechanik, Freiburg. Figure 31 and Figure 32 illustrate measured distortions in comparison with different calculations. As seen in the figures, the bending around an axis transverse to the weld (Figure 31) is much less

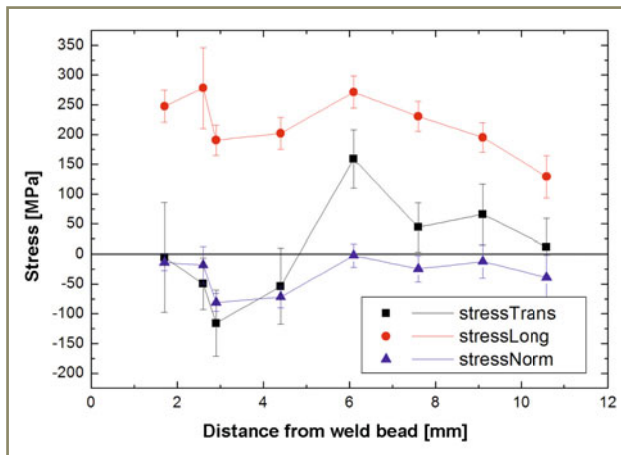


Figure 30 – Neutron diffraction results, laboratory G, plate III, residual stresses versus the depth below the surface in a distance of 6 mm from the weld centre line [12]

pronounced – nearly negligible – in comparison with the angular distortion (Figure 32). The differences between the measured and the calculated values are rather small. The influence of the dead and birth technique of the filler material with respect to displacements due to welding is negligible (Figure 31).

4.3.2 Metallographic investigations

Hardness measurements with different loads (HV 0.2, HV 1, HV 5) along lines transverse to the weld seam showed constant values in the seam and in the HAZ [17]. Neither significantly lower hardness values in the weld seam nor really significant hardness maxima in a distance of the weld seam could be observed.

According to [18], a certain content of δ -ferrite to avoid hot cracking phenomena has to be anticipated in the weld seam. This fact was supported by additional metallographic inspections that have revealed a dendritic structure in the weld seam with some amount δ -ferrite [17].

5 Discussion

5.1 Comparison of calculated and measured residual stress distributions

The main discrepancy between older calculations with the assumption of kinematic hardening and newer ones with the assumption of isotropic hardening concerns the

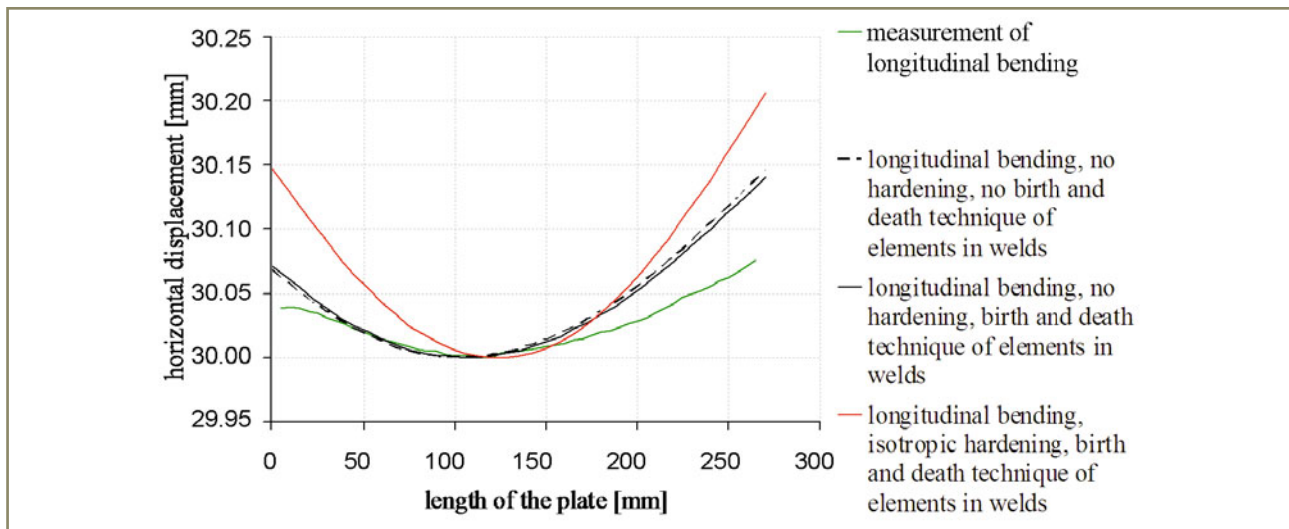


Figure 31 – Measured and calculated longitudinal bending around an axis transverse to the weld [16]

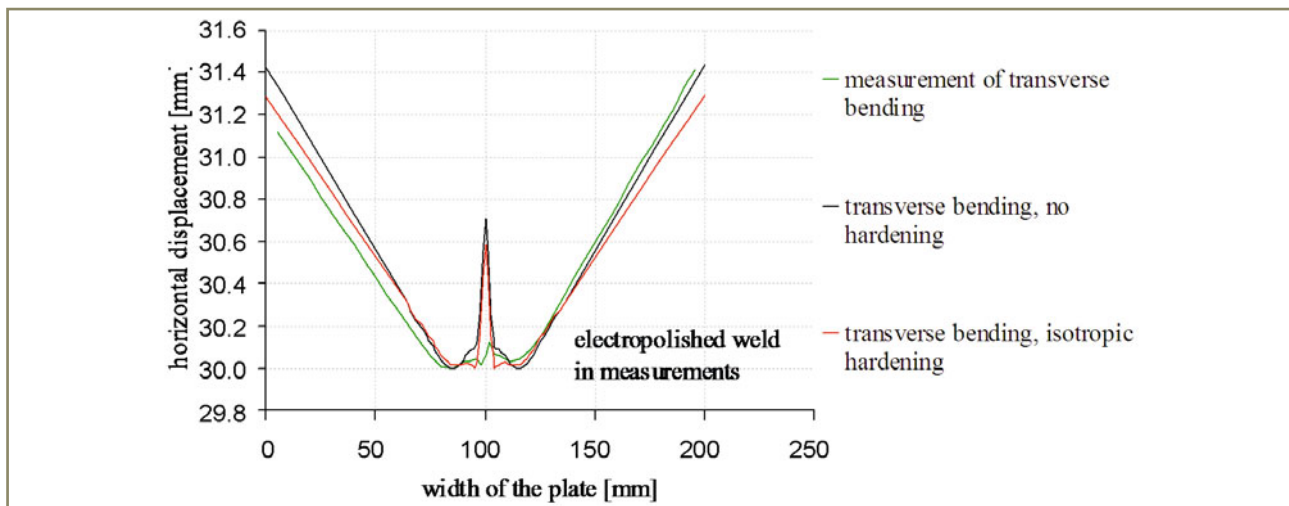


Figure 32 – Measured and calculated angular distortion (transverse bending around the weld axis) [16]

distribution of longitudinal residual stresses. Older calculations demonstrate a rather flat, horizontal course of longitudinal tensile stresses in areas close to the weld seam, partially with a weak maximum at the centre line with magnitudes in the range of the yield strength of the base material (approximately 250 MPa). In a distance of 15 to 25 mm from the centre line, longitudinal stresses decrease and change to compressive stresses, see Figures 7 and 13. Contrasting with this result, new calculations with the model of isotropic hardening indicate longitudinal residual stresses with a minimum of tensile stresses in the range of the yield strength at the weld centre line (approximately 270 MPa) and distinct maxima with magnitudes of ca. 380 MPa in a distance of approximately 8 mm from the centre line. It is obvious that results of older calculations do not agree with the reported measured pattern of longitudinal stresses. On the other

side, the agreement of longitudinal stress distributions calculated under the assumption of isotropic hardening with measured ones becomes nearly perfect if measurements and calculations with the same integration depth of stresses are compared, with regard to magnitudes of the maxima, and also with regard to their position. Figure 33 confirms this statement, calculations and measurements by means of the hole drilling method in connection with electron Speckle-interferometry are compared.

The comparison of new calculations and measurements of transverse residual stresses in Figure 34 indicate a situation which is not as clear as for longitudinal stresses. Only two of measured residual stress distributions show stress minima in the compressive range at the weld centre line and are therefore in agreement with calculated stresses. But the measurement in a distance of 128 mm

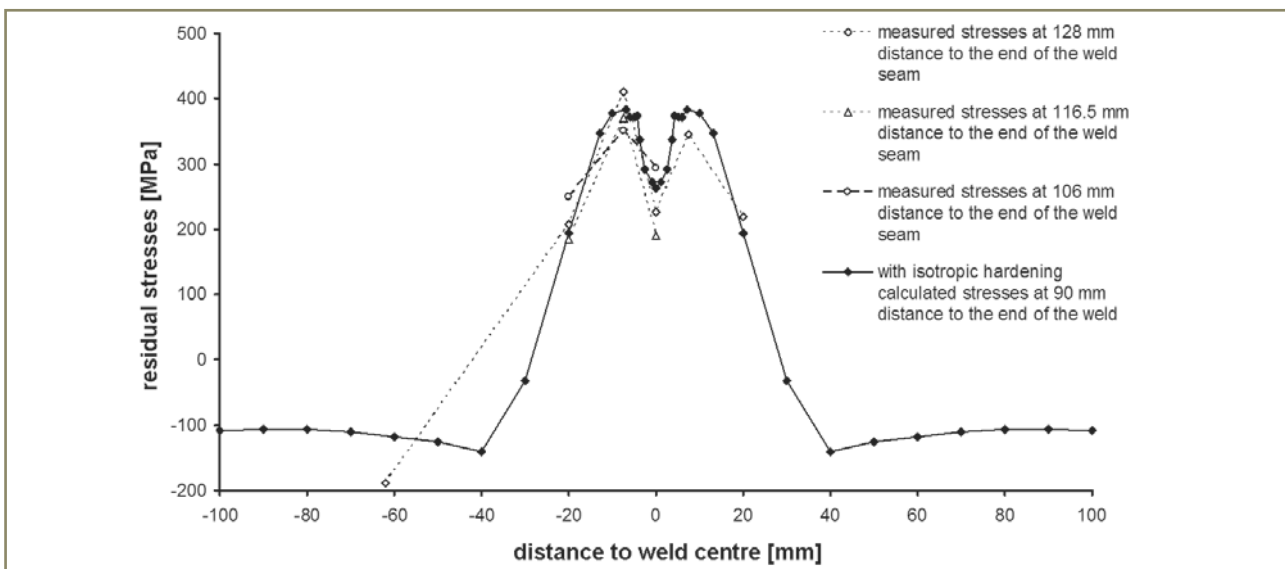


Figure 33 – Longitudinal residual stresses measured by means of hole drilling and electron Speckle-interferometry (stresses averaged over a depth of 1 mm, laboratory M in the IIW Round Robin Programme) in comparison with calculated longitudinal residual stresses (isotropic hardening, element size 1 mm³), [7]

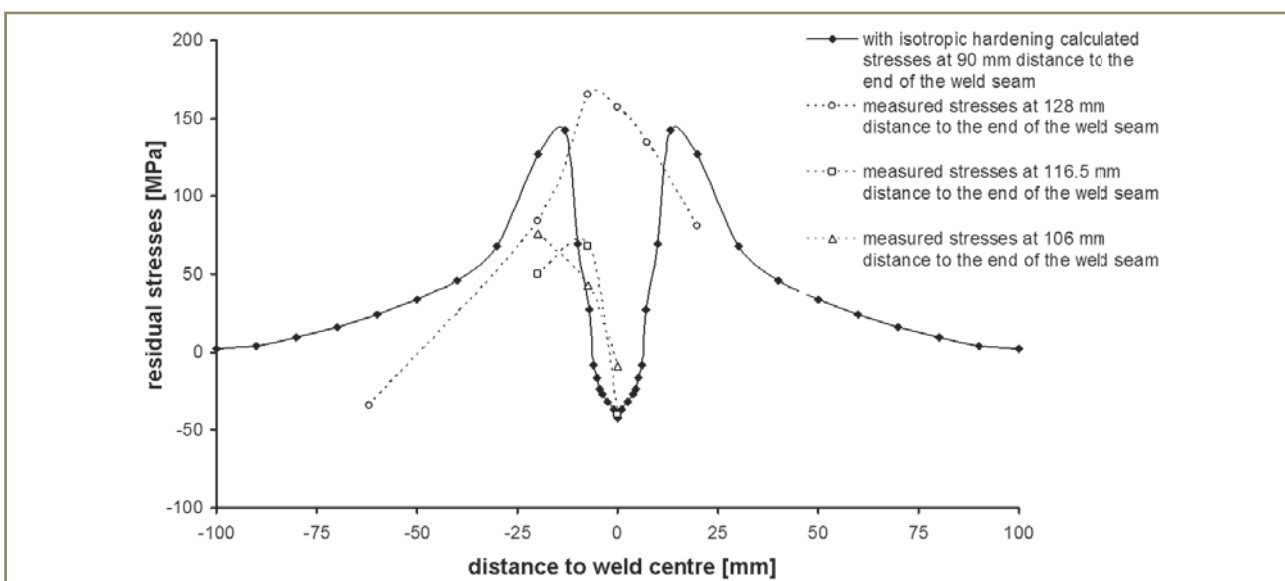


Figure 34 – Transverse residual stresses measured by means of hole drilling and electron Speckle-interferometry (stresses averaged over a depth of 1 mm, laboratory M in the IIW Round Robin Programme) in comparison with calculated longitudinal residual stresses (isotropic hardening, element size 1 mm³), [7]

from the end of the weld seam indicates a tensile stress maximum of more than 150 MPa at the weld centre line. This discrepancy to other measured results could possibly be a consequence of different distances of measurements to the end of the seam because the distribution of transverse residual stresses is asymmetric as already shown in Figure 10. In addition, it should be mentioned that other measurements by means of X-ray diffraction or neutron diffraction exhibited also tensile stress maxima of 300 MPa or at least 100 MPa in distances of ca. 10 mm from the weld centre line and a stress minimum in the compressive range at the weld centre line [8, 12, 13] and support therefore the calculated result in principle.

It should also be mentioned here, that distributions of transverse residual stresses computed by using the kinematic hardening model or the isotropic hardening model do not show fundamental qualitative discrepancies, however noticeable quantitative discrepancies.

5.2 Discussion about calculated stress maxima and differences between calculations with different strain hardening models

Consequently important points of the discussion have to be whether explanations for maxima and minima of longitudinal residual stresses can be given and why maxima cannot be found by calculations with a kinematic hardening model. Considerations which are able to explain both effects of calculations – the existence of calculated maxima and minima as well as the difference between these two calculation models – are discussed in [11].

Explanations considering maxima of residual stresses in the HAZ are based on the assumption that work hardening is produced due to developing thermal stresses. Examples of detailed calculations concerning the development of thermal respectively residual stresses (Figure 35) and the development of the temperature and work

hardening dependent flow stress (Figure 36) as well as of the finally accumulated plastic strain confirm (Figure 37) this assumption and are shown in related figures.

Figure 35 illustrates, as an example, the development of longitudinal stresses during welding of the second layer at selected times intervals and gives a first advice in which areas thermal stresses can become high enough to reach the local flow stress and produce plastic deformation and work hardening. The figure starts at 3 000 s after complete cooling down from the first pass with the residual stress distribution due to the first pass. These stresses are reduced at first during the heating of the second pass, but then, as a consequence of the hindered thermal expansion, compressive stresses develop on both sides of the weld seam. As these stresses, magnitude for instance more than 300 MPa at 3 245 s just before the temperature maximum, reach the decreasing flow stress of the heated material plastic deformation and work hardening will be the consequence in areas close to the seam.

Very early in the cooling process (3 301 s) tensile stresses grow up in the seam and in adjacent zones as a consequence of the hindered thermal shrinkage and of the again increasing yield stress. During the following intervals, tensile stresses grow obviously faster in areas close to the weld seam than in the seam itself. It has to be assumed that, in the HAZ close to the seam, the work hardening produced during heating is already effective and enables higher magnitudes of stresses than in the weld seam.

During the cooling process, the work hardening can also occur in the weld seam, as well as in the HAZ. Therefore, after the completion of the cooling, residual stresses in the HAZ near the fusion line can reach such appreciably high magnitudes as 380 MPa due to work hardening influences. Shrinkage tensile stresses in the weld seam, however, remain with 275 MPa only a little bit higher than the original yield stress. As a consequence of the increasing yield stress, the shrinkage of the cooling weld

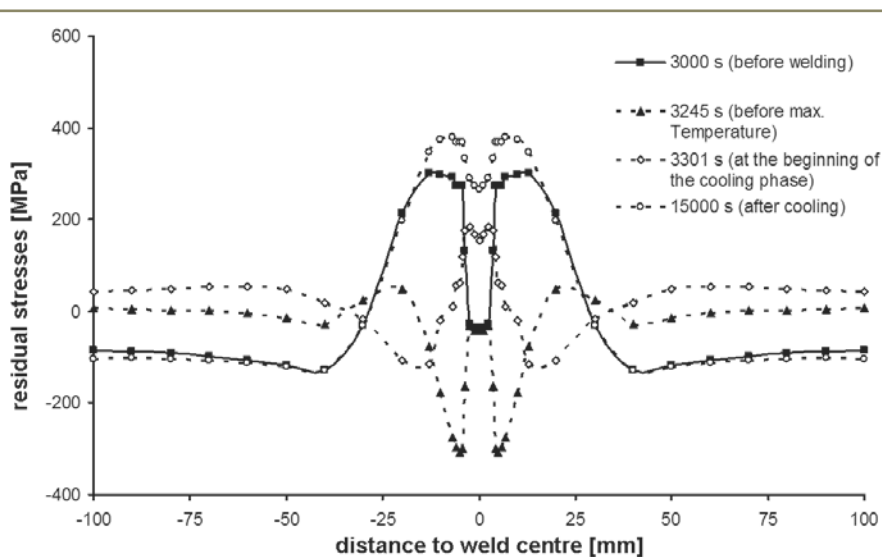


Figure 35 – Longitudinal stresses after selected time intervals during welding of the 2nd pass, 3 000 s = time until complete cooling after the 1st pass [7]

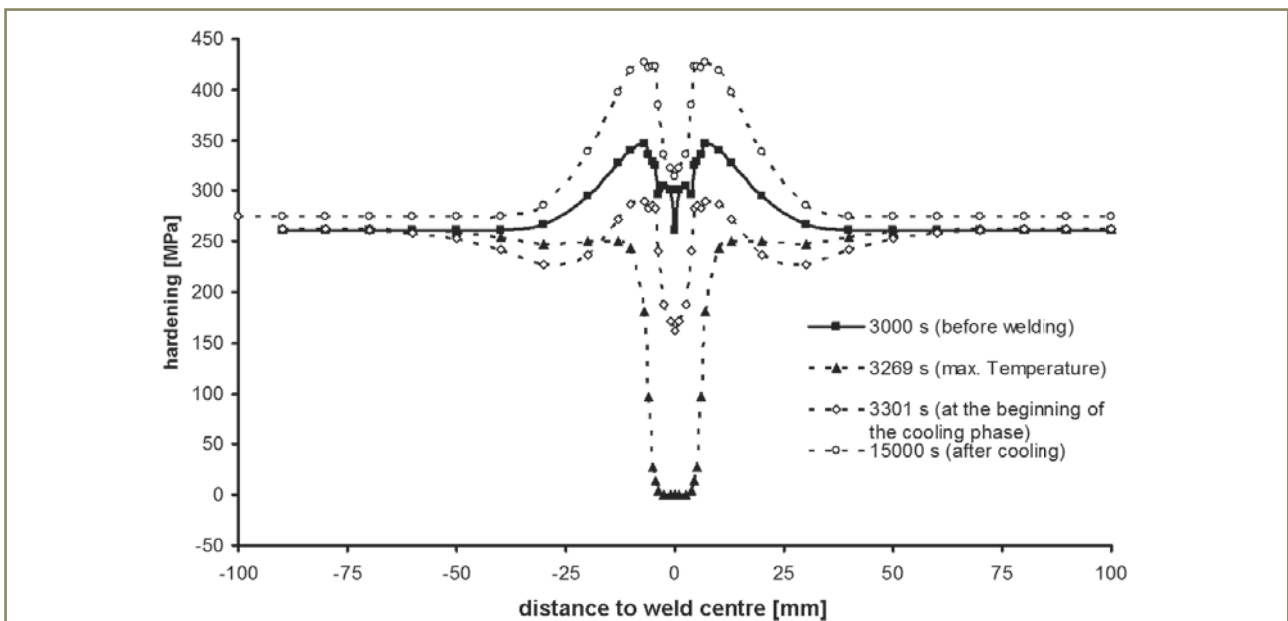


Figure 36 – Isotropic hardening variable after selected time intervals of the 2nd pass, 3 000 s = time until the completion of the cooling after the 1st pass [7]

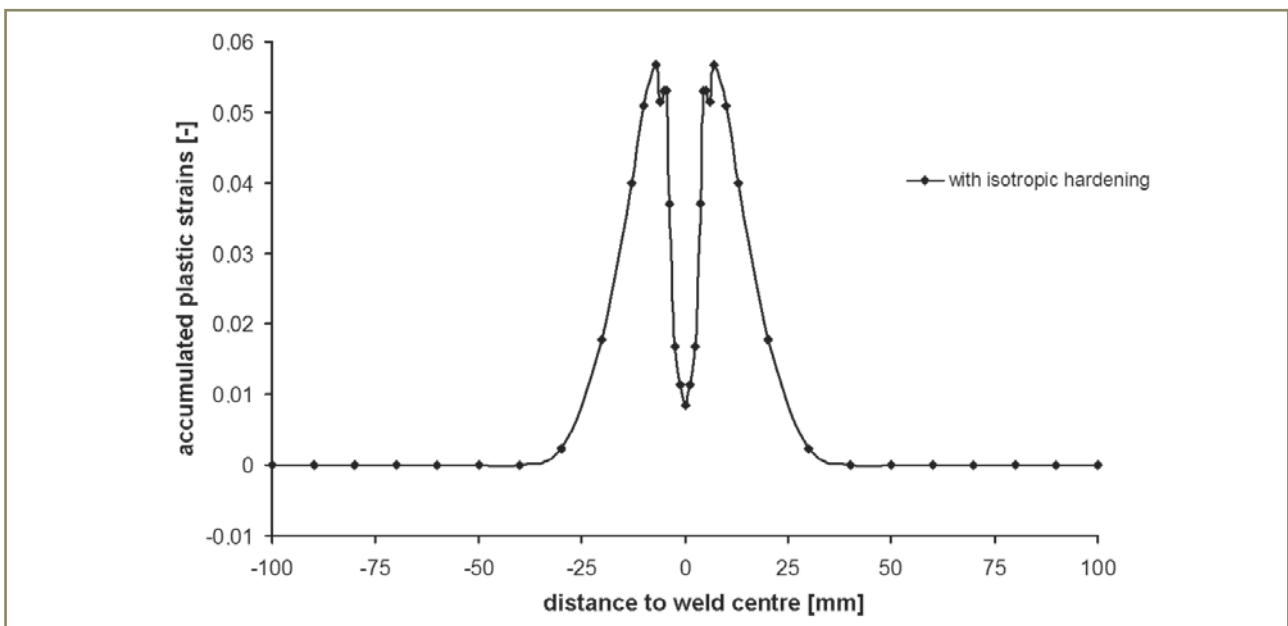


Figure 37 – Calculated accumulated plastic strains using the isotropic hardening model [7]

seam can also result in elastic strains and consequently the amount of plastic strains and therefore of work hardening is kept low. Very low accumulated plastic strains in the weld seam, Figure 37, underline this assumption. Balancing compressive stresses, in areas more remote from the seam, increase at first during the cooling period and then cover a wider range with smaller magnitudes.

Adequate conclusions concerning the work hardening can be drawn for transverse stresses. They are presented for instance in [7].

The proposed strain hardening in the seam and in areas close to the seam is also confirmed in figures illustrating the development of the temperature dependent and hardening

dependent flow stress of the material (isotropic hardening). It can directly be seen at selected time intervals of the 2nd pass in Figure 36. During welding of the first layer, a small increase of the flow stress has already occurred due to strain hardening in areas on both sides of the seam. The beginning of the 2nd pass (3 000 s) is denoted by this increased flow stress which is reduced again during the heating of the 2nd pass. At the maximum temperature, the flow stress in the weld seam becomes zero (3 269 s). At the beginning of the cooling period (3 301 s), the flow stress has risen again and, in the HAZ, a small work hardening effect can already be achieved. Until the end of the cooling period (15 000 s), the high flow stress value of 430 MPa is reached in the HAZ, whereas in the seam the flow stress attains a value of only 330 MPa.

A third indication for the work hardening effect is offered by the distribution of the calculated accumulated plastic strain in comparison with given material data. According to Figure 37, maxima of the accumulated plastic strain are in the HAZ and represent approx. 5.7 %, whereas in the weld seam only small plastic strains are revealed. A list of work hardening data for the austenitic steel given for the IIW Round Robin indicates a yield strength of 419 MPa at room temperature after a plastic deformation with a strain of 5 % [1]. Magnitudes of nearly 400 MPa of maximum tensile stresses are obviously consistent with this yield strength value.

For an explanation of different results of calculations with kinematic hardening respectively with isotropic hardening, the possibility of an influence of the Bauschinger effect on final resulting residual stresses has to be discussed. The kinematic hardening model takes into account the Bauschinger effect, whereas the isotropic model does not. Both hardening models consider the increase of compressive stresses during the heating period as a first load cycle and the opposite increase of tensile stresses during cooling as a second load cycle. But taking into consideration the Bauschinger effect with the kinematic model means that the beginning of plastic flow in the second load cycle (load reversal during cooling down) is lowered compared with the onset of plastic flow during the first load cycle (heating up). Consequently, the kinematic hardening model excludes the increase of the flow stress due to the work hardening in the first cycle and calculates a rather low flow stress or yield stress after completed cooling. Final tensile stresses will be limited by this relatively low yield strength. Results of calculations using the kinematic hardening law seem to indicate such a case: namely nearly constant tensile residual stresses with amounts in the range of the original yield strength at room temperature.

To take into consideration the influence of the Bauschinger effect is really necessary for cyclic plastic deformations at room or low temperatures, especially for materials with a high strain hardening exponent as for instance austenitic steels. On the other hand, indications can be found in literature [19, 20] that the Bauschinger effect is not effective – or at least not fully effective - at high working temperatures of austenitic steels. As, of course, during welding rather high temperatures exist also in the HAZ, calculations of residual stresses due to welding give more accurate results with the isotropic hardening model. It is able to account even for strong work hardening effects during the heating process and increased yield strength values can be anticipated during cooling down and finally at room temperature in the hardened HAZ close to the weld seam. Consequently, developing tensile stresses are limited only by these enhanced yield strength values and can become higher than with the kinematic hardening model. Measured and calculated maxima of tensile residual stresses in the longitudinal direction can be understood in this way. The possible errors by using the kinematic hardening model, on the other side, will be particularly substantial for materials with a high hardening coefficient [7].

5.3 Discussion about hardness measurements

Considerations about the interaction of work hardening and thermal stresses respectively residual stresses discussed above seem to be consistent. However, HV 0.2 hardness measurements along lines transverse to the seam have shown constant hardness values in the seam and in the HAZ close to the seam. Higher hardness values in the HAZ close to the seam could not be observed.

This result raises the question whether or why a difference of approximately 100 MPa in the flow stress at the weld centre line and in the HAZ cannot be detected by hardness measurements. Three possible reasons can be proposed as possible explanations for this:

- the work hardening occurs only in very thin surface layers, which may be penetrated by the hardness indenter with a load of 0.2 kg. An indication for this reason is the fact that X-ray stress measurements in a surface layer of approximately 10 μm revealed higher tensile maxima in the HAZ than other measurements with a bigger “averaging” depth,
- the indentation by the hardness test itself may produce strong plastic deformation and work hardening in an austenitic steel and consequently a levelling of previously existing small hardness differences,
- it is known that hardness values are lowered by tensile residual stresses. Consequently, higher tensile stresses in the HAZ may lower measured hardness values a bit more than lower tensile stresses in the weld seam, thus resulting in constant measured hardness values.

6 Final remarks and conclusions

6.1 Calculations of residual stresses

The “Round Robin” project with an austenitic steel has shown that a rather rough estimation of the residual stress state after welding is possible without any special distinction of the hardening model to be used. But for a more precise and detailed information, the chosen hardening model is of significant relevance.

Austenitic steels have a high strain hardening exponent and thermal stresses arising during the heating and cooling of the welding process can produce considerable plastic deformation and strain hardening. It could be revealed that calculations of residual stresses due to welding show a high amount of plastic deformation. It is also known that austenitic steels show a pronounced Bauschinger effect if deformations are produced at rather low temperatures. But in the investigated case, more detailed results, which are in good agreement with measured ones, could be found by not taking the Bauschinger effect into account, i.e. the isotropic hardening model instead of the kinematic hardening model gives better results. This finding can be explained by results from literature [19, 20], indicating that in austenitic

steels the Bauschinger effect is not effective – or at least less effective – if deformations are produced at higher temperatures, for instance above 300 °C. As also in the HAZ of weldments sufficiently high temperatures exist, this explanation seems to be quite reasonable for results calculated for the considered type of an austenitic steel. But for a more general statement more detailed information about the effectiveness of the Bauschinger effect at various temperatures in welded joints of different kinds of steels would be really important.

As a result of the “Round Robin” project, it can be recommended to use the isotropic hardening model – instead of the kinematic model – for calculations of residual stresses due to welding of austenitic steels. Further considerations should deal with the question whether more complex models for strain hardening, for instance the Chaboche model, could offer even better calculation results.

6.2 Experimental determination of residual stresses

For choosing an experimental method for the determination of residual stresses, different aspects have to be considered, as instrumental and temporal effort, accuracy, integration volume respectively resolving capacity and of course the question whether the method is destructive or non-destructive. The “Round Robin” project has evaluated special information for welded joints.

6.2.1 Non-destructive measurements

The stress analysis by means of X-rays has proven a good accuracy and the possibility of a rather high resolution concerning the stress distribution, which is important in order to detect details such as local maxima or minima. The fact that, by means of X-rays, stresses are detected in very thin surface layers of approximately 10 µm, can be seen as an advantage or as a disadvantage depending on the aim of the investigation.

In the “Round Robin” investigations, the method has indicated the highest stress maxima in the detected thin layers of the HAZ. In the base material far away from the weld seam, the special feature of the method became obvious, that grinding stresses, superimposing welding stresses in thin layers, may be detected. The method has not been used to detect stress gradients in the “Round Robin” tests. This would be possible in steps with very thin layers, but it would be very time consuming. The big grain size often found in weld seams resulted in problems, which have been solved with a more specialized equipment.

Methods using synchrotron radiation have not been examined in the “Round Robin” tests, but could be promising.

With the method of neutron diffraction measured stresses are integrated over thicker layers, e.g. 3 mm, compared to the X-ray method. This can provide more evidence of the residual stresses due to welding, as disturbing surface effects are at least minimized in the

result. Such a result was obvious in the “Round Robin” test. Measurements by means of neutron diffraction offered a clear description of the residual stress state with tensile and compensating compressive stresses over a wide range. A big advantage of this method is of course the possibility to detect stresses in deeper layers of thick welded plates, as proved in the “Round Robin” tests for instance in a depth of 15 mm, and to get information about the stress gradient down to such a depth below surface. The instrumental effort of this method is of course very important.

6.2.2 Semi-destructive measurements

As semi-destructive measurements various types of the hole drilling methods are commonly used for stress evaluations in welded joints. The advantage of the conventional method is a small instrumental and temporal effort.

In the “Round Robin” investigations, a very specific method using electronic Speckle-interferometry for the measurement of deformations after hole drilling was incorporated. This method provided obviously accurate stress distributions versus distance from the weld centre line averaging residual stresses over the drilling depth of 1 mm. The result is in very good agreement with calculations of residual stresses using the isotropic hardening model. The method has the advantage to offer interesting additional information about the stress state and major stresses.

Results of the conventional incremental hole drilling method in the “Round Robin” tests indicated a good agreement with other measurements of surface stress minima at the weld centre line and maxima in the HAZ. But results of longitudinal residual stresses versus the depth below the surface at the weld centre line described by various laboratories show obviously strong inconsistencies, whereas courses of residual stresses versus the depth below the surface at the positions of stress maxima are mainly consistent with the same tendencies. Differences between some surface stress values could be attributed to the polishing or grinding, which was necessary at the locations of measurements, but it is not sure whether the inconsistencies in the stress gradients below the weld centre line could also be explained with an influence of grinding on stresses in surface layers.

The “Round Robin” tests indicated clearly that with some experience measurements with hole drilling methods offer the possibility of good estimations of the residual stress state after welding with a minimum effort.

Acknowledgements

On behalf of the IIW Commissions X, XIII and XV the authors would like to thank all participating institutions for their fruitful cooperation.

References

- [1] Janosch J.J.: IIW Round Robin protocol for residual stress and distortion prediction, Phase II (Proposal Rev. 1), IIW Doc. X/XV-RSDP-59-00, 2000.
- [2] Janosch J.J.: IIW Doc. X/XV-RSDP-60-01, 2001, IIW Doc. X/XIII/XV-RSDP-68-02 / XV-1121-02 / XIII-1904-02, 2002, IIW Doc. X/XV-RSDP-68-03, 2003, IIW Round Robin Updated Results for Residual Stress and Distortion Prediction, IIW Doc. X/XIII/XV-RSDP-97-04.
- [3] Janosch J.J.: IIW "Round Robin" protocol for 3-dimensional welding residual stress and distortion prediction, IIW Doc. X/XIII/XV-RSDP-75-03.
- [4] Radaj D.: Heat effects of welding: temperature field residual stress distortion, Springer-Verlag, Berlin, 1992.
- [5] Brand M. and Siegele D.: State of the numerical round robin residual stress results, IIW-Document X-1648-08.
- [6] Goldak J., Charkravarti A. and Bibby M.: A new finite element model for welding heat sources Metallurgical and Materials Transactions B, 1984, vol. 15, pp. 299-305.
- [7] Loose T., Sakkiettibutra J. and Wohlfahrt H.: New 3D-calculations of residual stresses consistent with measured results of the IIW Round Robin Programme, Mathematical Modelling of Weld Phenomena 9, Verlag der technischen Universität Graz, Graz, 2010, pp. 369-390.
- [8] Wohlfahrt H.: Report on the Experimental Round Robin Tests on Residual Stresses 2005, IIW Doc. X/XIII/XV-RSDP-112-05, 2005.
- [9] Janosch J.J.: Round Robin phase II – 3D modelling – Updated results, IIW Doc. X/XIII/XV-RSDP-114-05, 2005.
- [10] Janosch J.J.: International Institute of Welding work on residual stress and its application to industry, International Journal of Pressure Vessel and Piping, vol. 85, 2008, pp. 183-190.
- [11] Wohlfahrt H.: New calculations checking an adequate materials law. New results on distortion measurements. Report on the Round Robin Tests on Residual Stresses 2009. IIW Document IIW- X-1668-09, IIW-XIII-2291-09, IIW-XV-1326-09.
- [12] Wohlfahrt H.: Reports on the Experimental Round Robin Tests on Residual Stresses, IIW Doc. XIII-2144-06 / XV-1227-06 / X/XIII/XV-RSDP-115-06, 2006, IIW Doc. X-1633-07 / XIII-2199-07 / XV-1263-07, 2007.
- [13] Wohlfahrt H. and Dilger K.: New results of the IIW Round Robin residual stress measurements, Report on the experimental Round Robin Tests on residual stresses 2008, IIW Doc. XIII-2241-08/XV-1283-08, 2008.
- [14] Lobanov L.M.: Report from E.O. Paton Electric Welding Institute, Kiev, for IIW Report IIW-XIII-2241r-08, IIW-XV-1283r-08, 2008.
- [15] Lobanov L.M., Pivtorak V.A., Savitsky V.V. and Trachuk G.I.: Procedure for determination of residual stresses in welded joints and structural elements using electron speckle-interferometry, The Paton Welding Journal, 1/2006, pp. 24-29.
- [16] Brand M.: Further development of methods of numerical welding simulation, PhD-Thesis, in progress (in German).
- [17] Institute for joining and welding, University of Braunschweig: Additional measurements.
- [18] Georg H. and Benedikt H.: Hinweise zur Bildung, Entstehung und Wirkung von Delta-Ferrit in austenitischen Edelstahllegierungen (Werkstoffnummern 1.4404 / 1.4435), Indications on formation and effect of delta-ferrite in austenitic alloys (Material No. 1.4404 / 1.4435), Henkel-Epol, 2003, Aufsatz Nr. 32 / Rev. 00 (in German).
- [19] Manninen T., Myllykoski P., Taulavuori T. and Korhonen A.S.: Large-strain Bauschinger effect in austenitic stainless steel sheet, Materials Science and Engineering, 2009, vol. A 499, pp. 333-336.
- [20] Mataya M.C. and Carr M.J.: The Bauschinger effect in a nitrogen-strengthened austenitic stainless steel, Materials Science and Engineering, 1983, vol. 57, pp. 205-222.

About the authors

Prof. Dr. Helmut WOHLFAHRT (Hwohlfahrt@gmx.net), Dr. Thomas NITSCHKE-PAGEL (tpagel@tu-braunschweig.de) and Prof. Dr. Klaus DILGER (k.dilger@tu-braunschweig.de) are all with Institute of Joining and Welding, University of Braunschweig, Braunschweig (Germany). Dr. Dieter SIEGELE (dieter.siegele@iwm.fraunhofer.de) and Mr Marcus BRAND (marcus.brand@iwm.fraunhofer.de) are both with Fraunhofer-Institut für Mechanik of Materials, Freiburg (Germany). Mr Jens SAKKIETTIBUTRA, (jens.sakkiettibutra@googlemail.com) is with Bremer Institut für angewandte Strahltechnik GmbH, Bremen (Germany). Dr. Tobias LOOSE (loose@tl-ing.de) is with Ingenieurbüro Tobias Loose GbR, Karlsruhe (Germany).