

Transesterification of Glycerol to Glycerol Carbonate Using KF/Al₂O₃ Catalyst: The Role of Support and Basicity

Swetha Sandesh · Ganapati V. Shanbhag ·
A. B. Halgeri

Received: 11 March 2013 / Accepted: 13 June 2013 / Published online: 27 June 2013
© Springer Science+Business Media New York 2013

Abstract Glycerol carbonate was synthesized by transesterification of glycerol with dimethyl carbonate using KF supported catalyst. KF was impregnated on various oxides and non-oxide supports like Al₂O₃, SiO₂, ZnO, ZrO₂, H-beta, and carbon to study the influence of the support on the catalytic performance. The preparation procedure of supported KF catalysts was modified to remove weakly adsorbed KF from the catalyst surface. The generation of basic sites by KF depends upon the extent of KF interaction with the support. KF/Al₂O₃ catalyst with optimized amount of 3.8 mmol KF, gave the highest activity with 95.8 % glycerol conversion and almost 100 % selectivity for glycerol carbonate. It was truly heterogeneous without any leaching of active sites and also showed good reusability. The catalyst exhibited better performance when compared to conventional solid base catalysts such as MgO, CaO and hydrotalcite.

Keywords Transesterification · Glycerol · Glycerol carbonate · Dimethyl carbonate · Solid base · KF/Al₂O₃

1 Introduction

Depleting crude oil availability all over the world has motivated researchers to look for alternate fuels. Biodiesel is one such fuel synthesized by using vegetable oils or animal fats by transesterification reaction. Glycerol is formed as a byproduct which accounts for one-tenth of

every gallon of biodiesel that is produced. Rapidly increasing production of biodiesel has made glycerol an inexpensive byproduct. To improve the economics of biodiesel synthesis, a lot of research has been carried out to convert glycerol into value-added products like acrolein, propanediols, glycerol carbonate, acrylic acid and glyceric acid [1].

Glycerol carbonate, one such important derivative of glycerol, has high potential applications in various fields. For example, it can be used as a raw material for the synthesis of glycidol, polymers, surfactants, lubricating oils as emulsifiers, moisturizers in cosmetic preparations, lustering agents, washing aids and detergents [2, 3]. Recently, the synthesis of glycerol carbonate from glycerol has gained importance as evidenced by the increasing number of reports in literature. Glycerol carbonate can be synthesized from glycerol using different reactants like carbon dioxide [4], urea [5, 6] and alkyl carbonates [6–8] in the presence of either acid or base catalyst. Aresta et al. [9] reported that glycerol carbonate could be produced from the reaction of glycerol with CO₂ in the presence of *n*-butyl tin methoxide as a catalyst. However, the reaction was carried out at elevated temperatures and pressures and the yield of glycerol carbonate was too low to be used for practical purposes. The carbonylation of glycerol by urea has also been studied using catalysts such as zinc sulfate, hydrotalcite and magnesium sulfate, but the reaction is found to be feasible only under vacuum [5, 6, 10]. Liquid alkyl carbonates such as dimethyl carbonate and ethylene carbonate have gained much attention as carbonate sources for the synthesis of glycerol carbonate from glycerol. Recent studies indicate that the conventional solid base catalysts like CaO [11] and K₂CO₃/MgO [12] showed good conversion for transesterification of glycerol with dimethyl carbonate but suffered from poor reusability. Ebitani and

S. Sandesh · G. V. Shanbhag (✉) · A. B. Halgeri
Materials Science Division, Poornaprajna Institute of Scientific
Research (PPISR), Bidalur Post, Devanahalli,
Bangalore 562110, Karnataka, India
e-mail: shanbhag@poornaprajna.org

co-workers [13] reported hydrotalcite as an active catalyst using dimethyl formamide as a solvent. Mg/Al/Zr mixed oxide catalyst has also been used as a base catalyst with high glycerol carbonate yield but excess of dimethyl carbonate has been utilized [14]. KF/hydroxyapatite has been reported as a catalyst for transesterification of glycerol with dimethyl carbonate [15]. Recently, NaOH/ γ -Al₂O₃ has also been used for the same reaction but the leaching of ionic Na species was observed with successive reuse of the catalyst [16].

KF/Al₂O₃ was first reported as a solid base catalyst by Ando et al. [17, 18]. This catalyst has been successfully applied to a variety of organic transformations such as aldol condensation [19], transesterification [20], Michael addition [21] and Tishchenko reaction [22]. Hattori co-workers [23] reported the formation of K₃AlF₆ and AlO₄²⁻ type of phases by the interaction of KF on alumina support with the formation of OH⁻ species on the catalyst surface.

In the current work, the transesterification reaction of glycerol with dimethyl carbonate has been investigated using KF impregnated on different oxide and non-oxide supports like α - and γ -Al₂O₃, SiO₂, zeolite beta, ZnO, ZrO₂ and carbon to understand the KF and support interaction. All the synthesized catalysts have been characterized by XRD, AAS, N₂ adsorption and CO₂-TPD measurements. The physicochemical properties of the catalyst has been correlated with the activity and selectivity of catalysts. The catalytic activity of KF/Al₂O₃ catalyst has also been compared with conventional solid base catalysts such as MgO, CaO and hydrotalcite.

2 Experimental

2.1 Materials

Glycerol, dimethyl formamide (DMF), potassium fluoride, zinc nitrate, zirconium oxy chloride, activated charcoal (carbon source), aluminum nitrate, urea, calcium oxide (CaO), magnesium oxide (MgO), magnesium nitrate, sodium hydroxide pellets and sodium carbonate were purchased from Merck India Ltd. Pseudoboehmite (alumina source) and H-beta zeolite (SAR = 25) were kindly donated by Süd-Chemie India Pvt Ltd. Fumed silica as a silica source was purchased from Alfa Aesar. Dimethyl carbonate (DMC) was purchased from SRL Chemicals Pvt Ltd. All the chemicals were of research grade and used without any further purification.

2.2 Catalyst Preparation

KF was loaded on different supports by the wet impregnation method. Supports used in this study were α -Al₂O₃

(synthesized by combustion method using aluminum nitrate and urea) and γ -Al₂O₃, SiO₂, H-beta zeolite, ZnO (zinc nitrate was decomposed at high temperature), ZrO₂ (synthesized by zirconium oxy chloride) and carbon. Moreover, the catalysts with different KF content were prepared by loading KF (in the range 1–24 mmol) on γ -alumina. In a typical procedure, 10 ml of aqueous solution containing 17 mmol KF was mixed with 1 g of support under vigorous stirring at room temperature for 2 h followed by the evaporation of water at 80 °C in a water bath. Then the catalyst was dried in an oven at 120 °C overnight and calcined under air at 600 °C for 4 h. After calcination, the catalyst was placed in 50 ml distilled water, stirred well and filtered to remove any physisorbed KF present on the support, and dried at 120 °C. Different KF loaded Al₂O₃ catalysts are designated as XKF/Al₂O₃, where X is the mmol loading of KF (measured by AAS). The alumina used was in gamma form unless otherwise stated. Other solid base catalysts like CaO and MgO were calcined at 850 °C before use and MgAl hydrotalcite (HTc) was synthesized by literature method [24].

2.3 Catalyst Characterization

The powder X-ray diffraction (XRD) patterns were recorded for all the catalysts on a Bruker D2 phaser X-ray diffractometer using Cu K α radiation with high resolution Lynxeye detector. All the samples were scanned in the 2 θ range of 5°–60° with step size of 0.02°/min.

The specific surface areas of the catalysts were measured by N₂ physisorption at liquid nitrogen temperature on Quantachrome Nova 1000 at 77 K and determined by using the standard BET method on the basis of adsorption data.

Basicity of the samples was measured by the temperature programmed desorption of CO₂ (CO₂-TPD) using Quantachrome Autosorb iQ (automated gas sorption analyser). The sample was preheated at 300 °C under the flow of He for 3 h, then cooling to 80 °C. Later, the CO₂ from a stream of He (10 % CO₂) was fed into the sample for 30 min. Then the sample was purged with He at 100 °C for 1 h in order to eliminate physisorbed CO₂. A TPD analysis was carried out from ambient temperature to 600 °C at a heating rate of 10 °C/min. CO₂ concentration in the effluent stream was monitored by using a thermal conductivity detector (TCD) and the areas under the peaks were integrated to determine the amount of CO₂ desorbed. TCD calibration was performed by passing known volumes of CO₂.

The KF concentration on alumina support was determined by analyzing potassium content (sample dissolved in aqua regia) from Perkin Elmer AAnalyst 200 atomic absorption spectrophotometer (AAS) using potassium nitrate as a reference standard. Surface density (SD) of

potassium (K) (which indirectly represents the active sites) on the catalyst surface was calculated using the formula,

$$SD \text{ (K nm}^{-2}\text{)} = (\text{mmol K} \times 6.023 \times 10^{23}) / \text{BET surface area (m}^2 \text{ g}^{-1}\text{)} \times 10^{18}$$

2.4 Catalytic Activity Studies

Transesterification reaction of glycerol with DMC was carried out in a 100 ml two-necked glass reactor equipped with a magnetic stirring bar, a Liebig condenser, and a thermometer. The required amounts of glycerol and DMC were taken in the reactor and 5 wt% of preactivated catalyst was added into it along with the diluent DMF. The reaction was performed under stirring at a desired temperature. After the reaction, the mixture was taken out and centrifuged for 10 min to separate the catalyst from the liquid phase. The thus obtained product was analyzed in gas chromatography (Shimadzu, GC-2014) with flame ionization detector (FID) equipped with a capillary column (0.25 mm I.D and 30 m length, Stabilwax, Restek). All the products were confirmed by gas chromatography with mass spectroscopy (Shimadzu, GCMS QP 2010). The product yield was calculated by the GC analysis using the formula,

$$\text{Product yield (mol\%)} = [\text{conversion (mol\%)} \times \text{selectivity (mol\%)}] / 100.$$

3 Results and Discussion

The synthesized catalysts were characterized by various techniques and the properties were correlated to the catalyst performance based on the glycerol conversion and product yield.

3.1 Catalyst Characterization

The KF impregnated catalysts were prepared by the commonly used procedure for the preparation of KF/Al₂O₃ except for the additional washing step after calcination. This additional step removes the weakly adsorbed KF from the catalyst. The remaining KF on the catalyst after water wash can be strongly adsorbed by the interaction with the support. The XRD patterns of different KF loadings on γ -alumina and KF on various supports are shown in Figs. 1 and 2 respectively. The characteristic crystalline phases of supported KF catalysts were identified with Inorganic Crystal Structure Database (ICSD). The peaks at $2\theta = 17.4^\circ$, 27.5° corresponds to KF phase and peaks at $2\theta = 29.7^\circ$, 36.4° , 42.4° and 52.3° correspond to K₃AlF₆ phase [18, 19]. It is seen that the intensity of the peaks including major peak (29.7°) increased with increase in KF loading up to 3.8 mmol and decreased thereafter (Fig. 1). Intensity of a broad peak at 46°

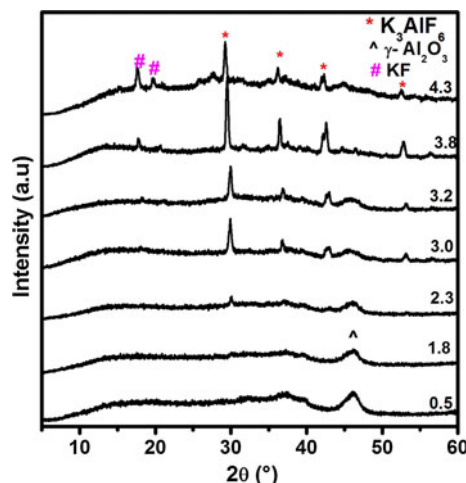


Fig. 1 XRD data of different amount of KF loading on alumina

corresponds to the γ -alumina phase decreased with increase in the KF loading from 0.5 to 3.2 mmol, whereas at higher loadings of KF (3.8 and 4.3 mmol), the alumina phase was completely replaced with the K₃AlF₆ phase. The crystalline phases of KF were formed on the amorphous SiO₂ and carbon supports whereas the crystallinity of ZrO₂ and ZnO improved after impregnating with KF. In case of alumina supports, the phase formation on γ -alumina due to the KF impregnation was different from that of α -alumina (Fig. 2). Interestingly, the XRD pattern of KF/H-beta was similar to that of KF/ γ -alumina. This indicates that KF preferentially interacts with Al sites of the zeolite forming KF and K₃AlF₆ phases.

The BET specific surface areas of different KF supported catalysts are represented in Table 1. The KF/SiO₂ and KF/ZrO₂ catalysts showed low surface areas of 7.32 and 12.4 m²/g respectively whereas other KF impregnated catalysts showed similar surface areas in the range 20–33 m²/g. The BET surface area of pure γ -alumina was 250 m²/g which decreased with increase in KF loading as shown in Table 2. This decrease in surface area could be due to the blockage of alumina pores by KF resulting in the inaccessibility of N₂ molecules to the internal surface.

Surface density of potassium on Al₂O₃ (in K nm⁻²) was calculated using mmol of K and surface area of the catalyst (Table 2). Surface density (SD) of K indirectly represents the active sites on the alumina surface. It is found that SD of K increased with increase in KF loading up to 3.8 mmol (SD = 11.8 K nm⁻²) and remained almost constant at higher loadings. This indicates that most of the Al sites of Al₂O₃ interacted with KF at 3.8 mmol loading and further loading of KF leads to a weak or no interaction with the support, and hence removed by water wash.

The amount of KF on the support was determined by analyzing the concentration of potassium from AAS. KF content in the final catalyst depends on the nature of

Fig. 2 XRD data of KF loading on different supports. (a) KF/ α -Al₂O₃, (b) KF/ γ -Al₂O₃, (c) KF/H-beta, (d) KF/SiO₂, (e) KF/C, (f) KF/ZrO₂, (g) KF/ZnO

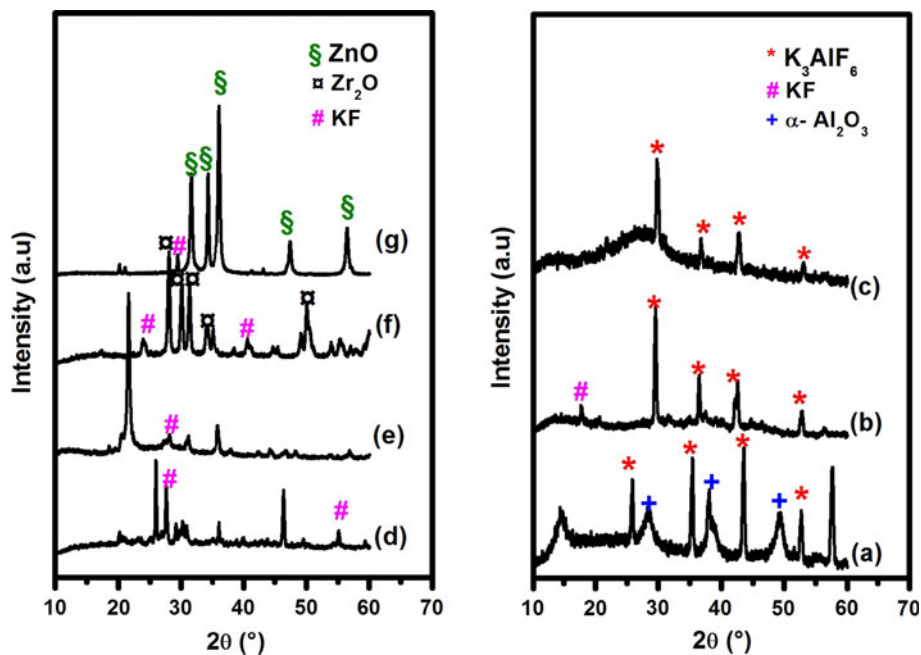


Table 1 Structural characteristics and basicity of different catalysts and their catalytic activities

Catalyst	KF loading measured ^a (mmol/g)	Basicity (mmol/g)	BET surface area (m ² /g)	Conversion of glycerol (mol%)	Selectivity for glycerol carbonate (mol%)	Yield of glycerol carbonate (mol%)
γ -Al ₂ O ₃	–	n.e	250	NR	NR	NR
KF/ γ -Al ₂ O ₃ uncalc ^b	17	n.e	n.e	2	100	2
KF/ γ -Al ₂ O ₃	3.8	2.17	20.4	96	99.8	95.8
KF/ α -Al ₂ O ₃	n.e	n.e	n.e	53	98.1	52
KF/SiO ₂	2.6	0.76	7.3	50.2	99.6	50.0
KF/ZnO	1.6	1.16	24.3	58.3	99.8	58.2
KF/H-beta	2.7	1.09	32.4	65	98.8	64.2
KF/Carbon	0.3	0.04	28.3	NR	NR	NR
KF/ZrO ₂	0.5	0.07	12.4	NR	NR	NR

Reaction conditions: glycerol: DMC: DMF; mole ratio = 1:2:0.5; catalyst = 5 wt% of total reactant weight; temp = 75 °C; time = 2 h

n.e not evaluated, NR no reaction

^a Measured by AAS (weakly adsorbed KF was removed by water wash)

^b Uncalcined and unwashed after KF impregnation

support because the interaction of KF varies with the type of support. It is observed that, even though different supports are treated with same amount of KF (17 mmol/g), KF content after water wash is different for different supports (Table 1). Among all, inert carbon, contained the lowest amount of KF (0.3 mmol/g) whereas γ -alumina consisted of the highest KF (3.8 mmol) among different supports taken for this study.

The basicity of the catalysts was measured by CO₂-TPD and the graphs are depicted in Fig. 3. The total basicity data of all the KF supported catalysts expressed in mmol/g of desorbed CO₂ are listed in Table 1. In order to evaluate the amount of different types of basic sites, the desorption curve

was differentiated into 3 peaks corresponding to <200 °C (weak), 200–350 °C (moderate), >350 °C (strong) as represented in Table 3. Comparison of TPD curves of different supported KF catalysts showed an increase in total basicity in the order, KF/carbon < KF/ZrO₂ < KF/SiO₂ < KF/H-beta < KF/ZnO < KF/Al₂O₃. The basicity found to have a linear correlation with the amount of KF on the support except for KF/ZnO which was more basic compared to SiO₂ and H-beta supported catalysts. KF/Al₂O₃ catalyst with total basicity = 2.17 mmol/g, showed high amounts of moderate (1.2 mmol/g) and strong (0.88 mmol/g) basic sites compared to all other supported KF catalysts (Table 3). The amount of strong basic sites increased in the order KF/

Table 2 Properties of alumina with different KF loading

Catalyst	KF loading (mmol/g)		Basicity (mmol/g)	BET SA (m ² /g)	Surface Density ^c (K nm ⁻²)	Glycerol conversion (mol%)	Selectivity for glycerol carbonate (mol%)	Yield of glycerol carbonate (mol%)
	Amount taken ^a	Measured ^b						
γ -Al ₂ O ₃	—	—	—	250	—	NR	96.9	NR
0.5KF/Al ₂ O ₃	1.0	0.5	0.05	206.7	0.2	NR	NR	NR
1.8KF/Al ₂ O ₃	3.0	1.8	n.e	154.3	0.8	10	98	9.8
2.3KF/Al ₂ O ₃	6.0	2.3	n.e	78.4	1.9	36.5	99.5	36.3
3.0KF/Al ₂ O ₃	8.0	3.0	0.57	42.6	4.3	35	99.4	34.8
3.2KF/Al ₂ O ₃	12.0	3.2	n.e	34.4	6.1	52	99.6	51.8
3.8KF/Al ₂ O ₃	17.0	3.8	2.17	20.4	11.8	72	99.9	71.9
4.3KF/Al ₂ O ₃	24.0	4.3	1.03	23.3	11.6	59.7	99.7	59.5


Reaction conditions: glycerol: DMC: DMF; mole ratio = 1:2:0.5; catalyst = 5 wt% of total reactant weight; temp = 75 °C; time = 1 h

n.e not evaluated, NR no reaction

^a mmol of KF taken per gram of support

^b Measured by AAS (weakly adsorbed KF was removed by water wash)

^c Surface density = (mmol K × 6.023 × 10²³)/BET surface area (m²/g) × 10¹⁸

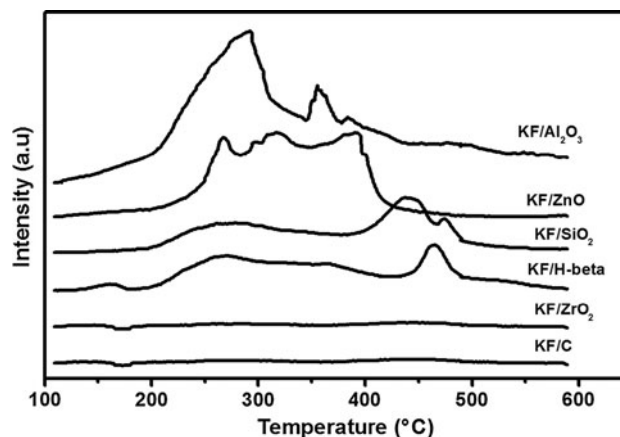**Fig. 3** Temperature programmed desorption of CO₂ patterns of KF on different supported catalysts**Table 3** Total amounts of weak, medium, and strong surface basic sites of all KF loaded catalysts

Catalyst	Basicity (mmol/g) ^a			Total basicity (mmol/g)
	Weak	Medium	Strong	
KF/ γ -Al ₂ O ₃	0.09	1.20	0.88	2.17
KF/SiO ₂	0.03	0.30	0.43	0.76
KF/ZnO	0.04	0.68	0.45	1.17
KF/H-beta	0.04	0.51	0.53	1.09
KF/Carbon	0.00	0.01	0.02	0.04
KF/ZrO ₂	0.01	0.03	0.04	0.07

^a Types of basicity were determined by considering the TPD (CO₂) curve area <200 °C (weak), 200–350 °C (medium) and >350 °C (strong)


carbon < KF/ZrO₂ < KF/SiO₂ < KF/ZnO < KF/H-beta < KF/Al₂O₃. The KF/carbon and KF/ZrO₂ catalysts exhibited negligible basicity. This indicates that the nature and strength of basic sites depends mainly on the type of support.

3.2 Transesterification of Glycerol with Dimethyl Carbonate

3.2.1 Comparison of KF/ γ -Al₂O₃ with Different Catalysts

Glycerol undergoes transesterification with a cyclic carbonate ester, DMC to give glycerol carbonate and methanol (Scheme 1). Different metal oxides, non-metal oxide (silica) and non-oxide (activated carbon) supports modified by KF were studied for the transesterification of glycerol with DMC in the liquid phase (Table 1). The reaction was conducted at 75 °C with glycerol: DMC: DMF mole ratio of 1:2:0.5. The 5 wt% catalyst with respect to the total reactant weight was taken for this study. Among the

Scheme 1 Transesterification of glycerol by dimethyl carbonate

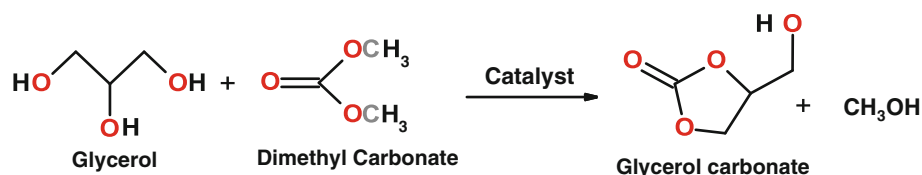

catalysts, 3.8KF/Al₂O₃ showed the highest activity, producing glycerol carbonate with 95.8 % yield. The activities of KF/H-beta, KF/ZnO and KF/SiO₂ were lower than 3.8KF/Al₂O₃, producing 64.2, 58.2 and 50 % of glycerol carbonate respectively whereas, KF/carbon and KF/ZrO₂ exhibited no activity. The basicity measurement indicated that the impregnation of KF on carbon and ZrO₂ led to a negligible generation of basic sites. In case of alumina support, it is shown by Hattori and co-workers [23] through ¹⁹F solid state NMR that K₃AlF₆ phase forms by the interaction of KF with alumina which leads to the formation of basic sites like F- and OH- species. The similar interaction is also possible with the Al sites of H-beta zeolite. KF supported on non-metal oxide like silica also showed basic sites as evident by CO₂-TPD (Fig. 3). However, the amount of basicity was much lower compared with 3.8KF/Al₂O₃ which resulted in low activity. KF on metal oxide support such as ZnO showed higher activity compared to silica support but lower than alumina support. Among two types of alumina supports, γ -alumina exhibited maximum yield (95.8 %) of glycerol carbonate compared to α -alumina (52 %). The catalytic activity was best correlated to the strong basic sites of different supported KF catalysts as shown in Fig. 4. The glycerol conversion linearly increased with increase in strong basic sites indicating that strong basicity generated by KF was necessary for glycerol transesterification with DMC. The activity of 3.8KF/Al₂O₃ was compared with well-known conventional solid base catalysts such as MgO, CaO and HTc. Among

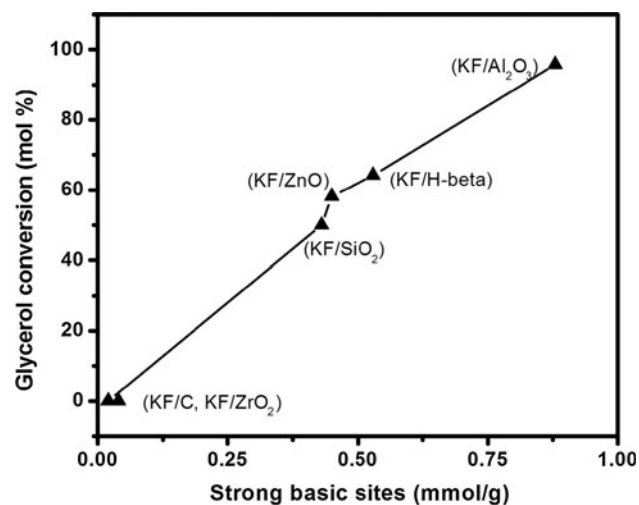


Fig. 4 Correlation of basicity with activity for KF loaded catalyst

these catalysts, 3.8KF/Al₂O₃ exhibited highest activity (95.8 % yield) followed by HTc (94 %), CaO (70.5 %) and MgO (68 %) (Table 4).

3.2.2 Influence of KF Loading on γ -Alumina Support

The different amounts of KF loaded on alumina support in the mmol range of 0.5 to 4.3 were tested for glycerol transesterification and the performance was compared (Table 2). As the loading increased from 0.5 to 3.8 mmol, the glycerol conversion increased to the maximum (95.8 %) whereas further increase in the KF loading on alumina (4.3 mmol) resulted in the decrease of glycerol conversion. Surface density of K was maximum for 3.8 KF/Al₂O₃ which resulted in highest activity. These results were supported by XRD where the peak intensity of the major peak at $2\theta = 29.7^\circ$ increased with increase in KF content up to 3.8 mmol and decreased thereafter. Also, the basicity increased as the KF loading increased up to 3.8 mmol KF loading (basicity = 2.17 mmol/g) and decreased at higher loadings. It is interesting to note that KF/Al₂O₃ uncalcined catalyst showed poor activity with just 2 % conversion indicating the importance of calcination step. The basicity is created on the alumina support by the interaction of KF during calcination at 600 °C.

3.2.3 Influence of Reaction Parameters on Transesterification Reaction

Influence of reaction conditions like temperature, mole ratio and catalyst concentration was studied for 3.8KF/Al₂O₃ and depicted in Fig. 5. The effect of temperature on the transesterification was investigated in the range of 55–85 °C with catalyst concentration of 5 wt% and glycerol: DMC: DMF mole ratio of 1:2:0.5. The conversion of glycerol carbonate increased with increase in the temperature from 55 to 75 °C and then remained almost constant with further increase to 85 °C. Selectivity for the transesterification product was 99.9 % at all temperatures indicating high efficiency of the catalyst for this reaction.


The effect of molar ratio of glycerol to DMC was also investigated at 75 °C as shown in Fig. 5. The glycerol conversion was low (25 % in 1 h) for 1:1 mol ratio and it increased to 75 % upon increasing the mole ratio to 1:2. Further increase in DMC concentration did not affect the

Table 4 Catalytic activity of different solid base catalysts

Catalyst	Calcination temperature (°C)	Conversion of glycerol (mol%)	Selectivity for glycerol carbonate (mol%)	Yield of glycerol carbonate (mol%)
γ -Al ₂ O ₃	600	NR	NR	NR
3.8KF/ γ -Al ₂ O ₃	600	96.0	99.8	95.8
CaO	850	70.8	99.6	70.5
MgO	850	68.4	99.4	68.0
HTc (Mg/Al)	120	94.2	99.8	94.0

Reaction conditions: gly: DMC: DMF mole ratio = 1:2:0.5, catalyst = 5 wt% catalyst, temp = 75 °C, time = 2 h

Fig. 5 Influence of reaction conditions. **a** Effect of temperature: conditions: catalyst = 3.8 KF/Al₂O₃, catalyst amount = 5 wt%, gly: DMC: DMF mole ratio = 1:2:0.5, time = 1 h. **b** Effect of glycerol to DMC mole ratio: conditions: catalyst = 3.8KF/Al₂O₃, catalyst amount = 5 wt%, DMF = 0.5 mol, time = 1 h, temperature = 75 °C. **c** Effect of catalyst concentration: conditions: catalyst = 3.8KF/Al₂O₃, gly: DMC: DMF mole ratio = 1:2:0.5, time = 1 h, temperature = 75 °C

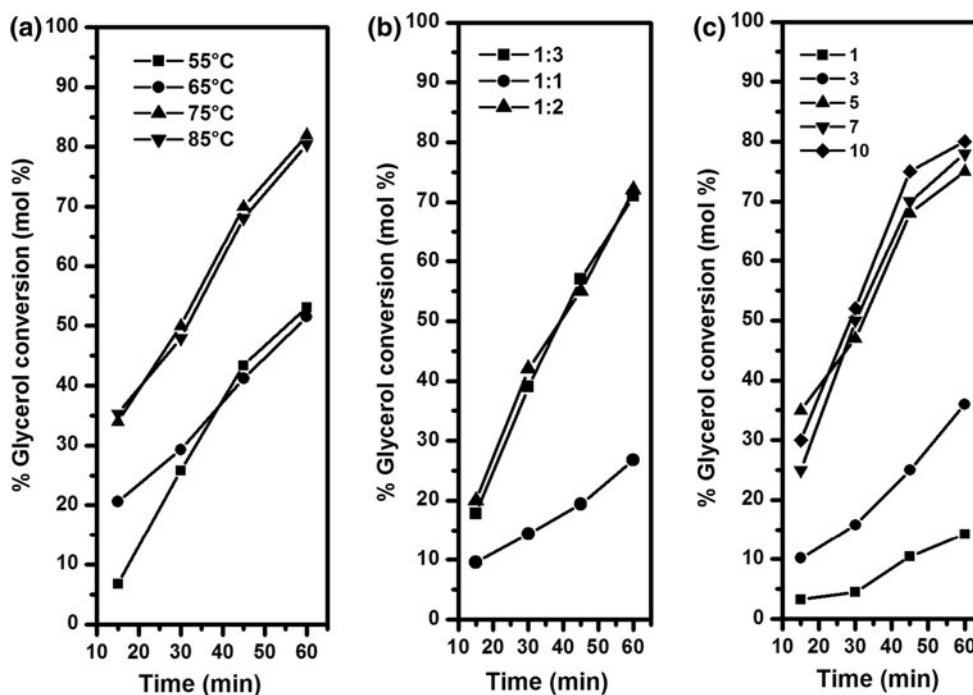

catalytic activity. Glycerol, due to its high polarity, preferentially adsorbs on to the active sites and hence more DMC is needed for obtaining high conversion.

The effect of catalyst concentration on the conversion of glycerol was studied on 3.8 KF/Al₂O₃ catalyst. The conversion of glycerol increased as the catalyst concentration increased from 1 to 5 wt% with respect to the total weight of the reactants. However, further increase of active sites with the increase in catalyst concentration from 5 to 10 wt% improved the activity only marginally. Based on the above optimization studies, the best suitable conditions viz. reaction temperature of 75 °C, glycerol: DMC mole ratio of 1:2 and 5 wt% catalyst were employed to get high catalytic performance.

3.2.4 Leaching and Reusability

Leaching test was carried out to investigate the leaching of any KF species from the catalyst into reaction media. The

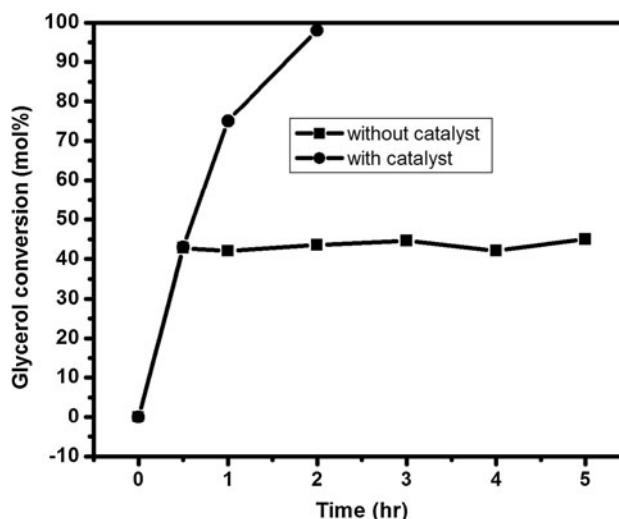
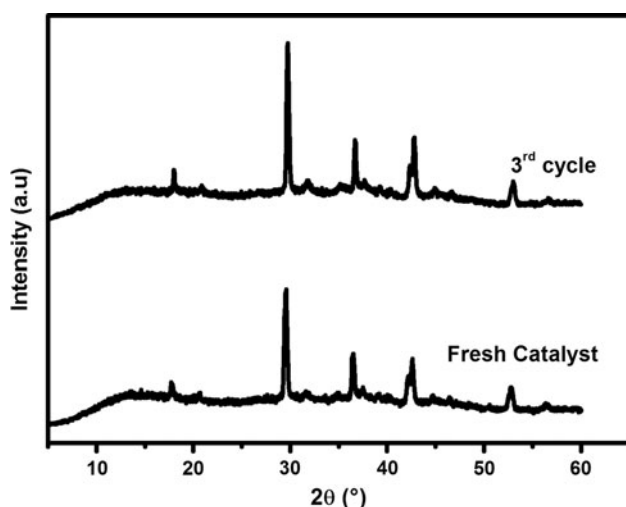


Fig. 6 Leaching test of KF/Al₂O₃ catalyst

Table 5 Catalyst reusability

Catalyst	Conversion of glycerol (mol%)	Selectivity for glycerol carbonate (mol%)	Yield of glycerol carbonate (mol%)
First run	96	99.8	95.8
Second run	94.6	99.6	94.2
Third run	93.2	99.8	93.0

Reaction conditions: gly: DMC: DMF mole ratio = 1:2:0.5, catalyst = 5 wt% catalyst, temp = 75 °C, time = 2 h

**Fig. 7** XRD pattern of recycled catalyst

reaction was carried out using $\text{KF}/\text{Al}_2\text{O}_3$ catalyst at a reaction temperature of 75 °C with glycerol to dimethyl carbonate mole ratio of 1:2 with DMF as a solvent. Reaction was stopped after 30 min (40 % conversion) and the hot reaction mixture containing catalyst was centrifuged. Supernatant liquid was taken and reaction was continued for next 5 h. The conversion remained constant even after 5 h of reaction time, indicating no leaching of active sites into the reaction media (Fig. 6). Even the analysis of reaction mixture with AAS for potassium showed a negligible K content (<0.002 mmol/g catalyst) proving that the water wash during catalyst synthesis has an effective role in removing the weakly adsorbed KF species.

For a recycling test after the first run, the catalyst was filtered, washed thoroughly with methanol, dried at 120 °C and reused with fresh reactants under the same reaction conditions (Table 5). The catalyst showed good reusability with a marginal decrease in activity (3 %) after 3 cycles. It is important to note that catalyst was not calcined before each recycle. Furthermore, XRD patterns of both fresh and

recycled catalysts indicated that there was no change in phase purity after the two recycles (Fig. 7).

4 Conclusions

Transesterification of glycerol with dimethyl carbonate to form glycerol carbonate has been carried out using various solid base catalysts. Different supported KF catalysts showed an increase in total basicity in the order, $\text{KF}/\text{carbon} < \text{KF}/\text{ZrO}_2 < \text{KF}/\text{SiO}_2 < \text{KF}/\text{H-beta} < \text{KF}/\text{ZnO} < \text{KF}/\text{Al}_2\text{O}_3$. The generation of basicity and the total basic sites depend on the type of the support and its interaction with KF. The additional step of water wash of the supported KF catalyst helps in removing the weakly adsorbed KF from the catalyst surface. The $\text{KF}/\text{Al}_2\text{O}_3$ catalyst with optimized amount of 3.8 mmol KF, gave the highest activity with 95.8 % glycerol conversion and almost 100 % selectivity for glycerol carbonate. The catalyst showed better performance compared to conventional solid base catalysts such as MgO, CaO and HTc. In conclusion, $\text{KF}/\text{Al}_2\text{O}_3$ was found to be an efficient and reusable solid base catalyst for the transesterification of glycerol to glycerol carbonate.

Acknowledgments Swetha S acknowledges Admar Mutt Education Foundation (AMEF) for providing the fellowship and also thankful to Manipal University for permitting this research as a part of the Ph.D programme. The authors thank Bangalore Institute of Technology, India and Indian Institute of Chemical Technology (IICT), Hyderabad, India for providing surface area measurements and CO_2 -TPD respectively.

References

- Guerrero-Perez MO, Rosas JM, Bedia J, Rodriguez-Mirasol J, Cordero T (2009) *Green Chem* 11:21
- Uno M, Okutsu M (2011) US patent 6495703 B2
- Herault D, Boutty B, Zander L, Strube A (2005) US patent 2005/0038266 A1
- George J, Patel Y, Pillai M, Munshi P (2009) *J Mol Catal A* 304:1
- Jean-Luc Dubois, Aresta M, Dibenedetto A, Ferragina C, Nocito F (2011) US patent 2011/0245513 A1
- Climent MJ, Corma A, Frutos PD, Iborra S, Noy M, Velty A, Concepcion P (2010) *J Catal* 269:140
- Ochoa-Gomez JR, Gomez-Jimenez-Aberasturi O, Madurga BM, Rodriguez AP, Ramirez-Lopez C, Ibarreta LL, Torrecilla-Soria J, Velasco MCV (2009) *Appl Catal A Gen* 366:315
- Alvarez MG, Sagarra AM, Contreras S, Sueiras JE, Medina F, Figueras F (2010) *J Chem Eng* 161:340
- Aresta M, Dibenedetto A, Nocito F, Ferragina C (2006) *J Mol Catal A* 257:149
- Aresta M et al (2011) US patent 2011/0245513 A1
- Simanjuntak FSH, Kim TK, Lee SD, Ahn BS, Kim HS, Lee H (2011) *Appl Catal A Gen* 401:220
- Du M, Li Q, Dong W, Geng T, Jiang Y (2011) *Res Chem Intermediat* 38:1069
- Takagaki A, Iwatani K, Nishimura S, Ebitani K (2010) *Green Chem* 12:578
- Malyaadi M, Jagadeeswaraiiah K, Sai Prasad PS, Lingaiah N (2011) *Appl Catal A Gen* 401:153

15. Bai R, Wang S, Mei F, Li T, Li G (2011) *J Ind Eng Chem* 17:777
16. Bai R, Wang Y, Wang S, Mei F, Li T, Li G (2013) *Fuel process. Technology* 106:209
17. Yamawaki J, Ando T (1979) *Chem Lett* 8:755
18. Ando T, Yamawaki J (1979) *Chem Lett* 45:755
19. Raju V, Radhakrishnan R, Jaenicke S, Chuah GK (2011) *Catal Today* 164:139
20. Murugan C, Bajaj HC (2011) *Fuel Proc Tech* 92:77
21. Clacens JM, Genuit D, Delmotte L, Ruiz AG, Bergeret G, Montiel R, Lopez J, Figueras F (2004) *J Catal* 221:483
22. Baba T (2000) *Catal Survey Jpn* 4:17
23. Kabashima H, Tsuji H, Nakata S, Tanaka Y, Hattori H (2000) *Appl Catal A Gen* 195:227
24. Reichle WT (1985) *J Catal* 94:547