



Niobium- and antimony-doped tin dioxide aerogels as new catalyst supports for PEM fuel cells

G. Ozouf¹ and C. Beauger^{1,*}

¹ MINES ParisTech, PSL Research University, PERSEE - Centre procédés, énergies renouvelables et systèmes énergétiques, CS 10207 rue Claude Daunesse, 06904 Sophia Antipolis Cedex, France

Received: 30 November 2015

Accepted: 12 February 2016

Published online:

24 February 2016

© Springer Science+Business Media New York 2016

ABSTRACT

In order to tackle the problem of low durability, tin dioxide was studied to replace carbon black as a catalyst support in proton exchange membrane fuel cells (PEMFCs). SnO₂ is a well-known *n*-type semi-conductor whose electronic conductivity can be improved by doping with hypervalent cations such as Nb⁵⁺ or Sb⁵⁺. In addition, as a catalyst support, this material has to develop a high specific surface area with an adequate mesoporous morphology to allow both good dispersion and activity of the catalyst (Pt). To this end, our objective was to develop doped SnO₂ aerogels in order to gather in a same material both a high electronic conductivity and an adapted morphology. In this study, SnO₂ xerogels and aerogels were successfully synthesized following an acid-catalyzed sol-gel route starting with metal alkoxides as precursors. Dried gels were calcined for 5 h at 600 °C in flowing air. The effect on both the structure and the morphology of the material resulting from doping with niobium or antimony was investigated by XRD, SEM, and nitrogen sorption. The electronic conductivity of pure and doped SnO₂ materials was obtained from impedance spectroscopy and resistance measurements. Our materials showed a very interesting airy morphology adapted for the foreseen application: a reasonable specific surface area (80–90 m²/g) with a bimodal pore size distribution centered on around 25 and 45 nm. Moreover, all Sb-doped samples exhibited significant improvement in electronic conductivity. 5 at.% Sb-doped SnO₂ even showed an electronic conductivity of 1 S/cm, very similar to that of Vulcan XC-72 (4 S/cm) and representing a 5 orders of magnitude increase compared to that of pure SnO₂.


Introduction

Fuel cells are environmentally friendly electrochemical energy converters that produce electricity and heat mainly from hydrogen and air [1–3]. Among the

many existing types of fuel cells, proton exchange membrane fuel cells (PEMFCs) have the advantage of providing a large range of power, from a few W to hundreds of kW. Operating at low temperatures (80 °C), PEMFCs allow quick starts what makes them

Address correspondence to E-mail: christian.beauger@mines-paristech.fr

particularly interesting for transport applications. Low temperature operation limits the choice of catalysts for electrochemical reactions (H_2 oxidation, HOR and O_2 reduction, ORR) to noble metals, mostly platinum. To reduce the amount of platinum while maintaining good performance, platinum nanoparticles are dispersed on a support. Because they have both a high electronic conductivity and a high specific surface area (respectively, about 4 S/cm and 254 m^2/g for Vulcan XC-72 [4]), current electrocatalysts are based on carbon blacks (Vulcan XC-72R or TKK TEC10E40E for instance). However, the corrosion of carbon black on the cathode side in fuel cell operating conditions ($E = 1.2$ V, $T = 80$ °C, high relative humidity and strongly acidic environment) is responsible for contact losses between the conductive carbon support and the catalyst, thus limiting the durability of PEMFC. This phenomenon is particularly marked for transport applications, during start/stop cycles [4, 5]. They may indeed cause a reverse current compared to the normal operation of the fuel cell, leading to an increase in the cathode potential of up to 1.44 V. In the presence of platinum nanoparticles, such high potential causes severe corrosion of the cathode following the reaction:



Degradation mechanisms include dissolution as well as coalescence of platinum particles, thus limiting their activity [6].

According to thermodynamic calculations derived from Pourbaix pH-potential diagrams, tin dioxide is expected to be very stable in PEMFC operating conditions. Its utilization as a catalyst support should improve PEMFC durability [7]. Tin dioxide is an *n*-type semi-conductor ($E_g = 3.6$ eV). Doping SnO_2 with hypervalent donor components like Nb^{5+} or Sb^{5+} leads to a significant increase of the electronic conductivity [8, 9]. Due to its remarkable bulk and surface properties, this material is already used as a transparent conductive oxide (TCO) [10], an electrode material in Li-ion batteries [11, 12], a catalyst for oxidation reaction [13–15] and a sensing material in gas sensors [16–18].

Several authors have shown that using pure SnO_2 as a catalyst support effectively improves the durability of PEMFC, mostly thanks to improved

corrosion resistance [19–21]. Moreover, it reduces polymer membrane degradation by neutralizing the formation of H_2O_2 formed during ORR [22]. It also allows better tolerance to CO than Pt/C electrocatalysts [14, 23, 24]. This can be explained by the oxidation of CO adsorbed at the Pt surface by the hydroxyl groups covering the surface of SnO_2 [25]. However, electrochemical characteristics, like the electrochemical surface area (ECSA) or the oxygen reduction reaction (ORR) mass and specific activities of Pt/ SnO_2 electrocatalysts, are relatively low compared to those of Pt/C, mostly due to their poor electronic conductivity and low specific surface area. Recent studies have shown the potential of doping SnO_2 by Nb^{5+} [26–29] or Sb^{5+} [26, 27, 30–36]. In addition to improving electronic conductivity, dopants are known to inhibit particle growth [37] and modify the material's morphology. Although improvements have been observed compared to pure SnO_2 , experimental results generally show lower performance than carbon black, particularly regarding mass catalytic activity. In some cases, depending on the SnO_2 morphology, mass catalytic activities were improved, even surpassing those of Pt/C electrocatalysts [27, 35]. This has been ascribed to the sometimes contested strong metal-support interaction (SMSI) [38, 39]. It has been proposed that this strong interactions between SnO_2 and Pt may change the Pt electronic structure and lower the activation barrier for oxygen dissociation [40]. However, a recent study has shown that steric effects are more likely the cause of this lower activation barrier [41].

The morphology of the support is primordial to limit concentration polarization and ease fluids management in volume electrode. Aerogels are to this end particularly interesting materials. Carbon aerogels have already proven their ability to efficiently support catalysts for PEMFC application [42, 43]. Their morphology can be adjusted by playing on the sol-gel parameters for higher specific surface areas with adequate mesoporosity.

In this study, SnO_2 aerogels were thus synthesized to be used as a catalyst support for PEMFC in order to overcome the reported limitations regarding morphology and durability. The effect of doping SnO_2 with niobium or antimony on the electronic conductivity as well as on the morphology has also been investigated.

Experimental

SnO₂ synthesis route

Metal oxides were synthesized following a sol–gel route, starting with metal alkoxide precursors: Sn(OiPr)₄, Nb(OiPr)₅, and Sb(OiPr)₃ all purchased from Alfa Aesar. Two solutions (A & B) were prepared. Solution A, consisting of tin isopropoxide in isopropanol (Acros Organics, 99.5 %) with a corresponding amount of the doping element, was placed under magnetic stirring. Solution B, consisting of nitric acid (Alfa Aesar, 2N) (HNO₃/Sn = 0.072 mol/mol) in water (H₂O/Sn = 3.06 mol/mol) and isopropanol (iPrOH/Sn = 119 mol/mol), was also mixed under magnetic stirring. Solution B was then slowly dripped into solution A and a gel formed after a few minutes. The gel was then covered with isopropanol to prevent any drying and aged for 48 h at room temperature before being washed with isopropanol three times a day for 2 days. After washing, the resulting gels were dried either by conventional evaporation to obtain xerogels, or under CO₂ in supercritical conditions (80 bars, 40 °C) to obtain aerogels. The resulting solids were heat treated under air for 5 h.

After calcination, the sample color turned blue or black, respectively, for SnO₂: Sb aerogels or xerogels. The SnO₂: Nb xerogels turned light green, whereas the SnO₂: Nb aerogels remained white. Compared to aerogels, xerogels are likely to be darker in color due to a higher density resulting from the drying route.

Samples were labeled according to a dedicated nomenclature. For example, the SnO₂: Nb (10 at.%) aerogel sample is labeled A6SN100, where A stands for aerogel (X for xerogels), 6 for calcination at 600 °C in air, S for SnO₂, N for Nb dopant (S for Sb), and 100 for 10 at.% doping.

Characterization

XRD measurements were performed using an X'Pert pro, Philips diffractometer (Cu K α of $\lambda = 1.5405 \text{ \AA}$). The diffractometer was operated at 45 kV and 30 mA. Data were collected at steps of 0.05° from 20° to 90° in 2- θ mode with a Pixel counter.

Morphologies were analyzed by SEM using a Supra 40 with Gemini column operated at 3.00 kV. The oxide powders were deposited on adhesive conducting carbon tapes and coated with a 7 nm-thick platinum layer, using a Quorum (Q150 T).

In addition, nitrogen sorption analysis was performed with a Micromeritics ASAP 2020. Samples were first degassed for 120 min at 100 °C and 10 μmHg . The Brunauer–Emmett–Teller (BET) model was applied to determine the specific surface area. The pore size distributions were calculated applying the Barret-Joyner-Halenda (BJH) method to the desorption branch of the isotherms. The assessments of microporosity were made from t-plot construction using the Harkins–Jura correlation.

Concerning the pore size distribution determination using this technique, we assumed that the samples were mechanically strong enough after calcination to withstand the pressure applied during the experiment.

The bulk chemical composition was analyzed by energy dispersive X-ray spectroscopy (EDX) performed during SEM observation with a Philips XL30 operated at 15 kV.

The surface chemical composition was analyzed by X-ray photoelectron spectroscopy (XPS) using a Thermo Scientific K-Alpha system. The spectrometer was equipped with an AlK α monochromated source and a low energy flood-gun for charge compensation.

The ellipsoid spot size is about $350 \times 700 \mu\text{m}^2$.

The electronic conductivity was investigated by impedance spectroscopy and direct resistance measurements.

For impedance spectroscopy, the frequency ranged from 100 Hz to 1 MHz with a potential of 200 mV and an amplitude of 100 mV. Since pellet formation was difficult for SnO₂ samples, impedance spectroscopy measurements were only performed on xerogel sample parts. Due to their powder form, it was actually not possible to perform impedance spectroscopy measurements on aerogels. Next, a homemade conductivity cell was developed, made up of two copper electrodes ($S = 0,785 \text{ cm}^2$) surrounded with a Teflon ring. Samples were introduced between these two electrodes (see Fig. 1). A

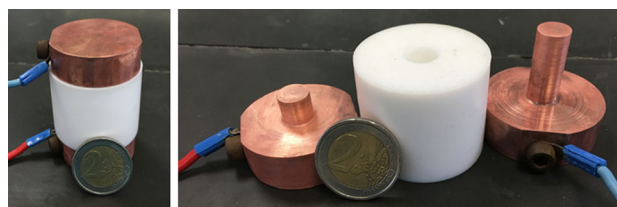


Figure 1 Homemade conductivity cell picture assembled (left) and disassembled (right).

potentiostat was used to apply a current of 105, -105 , or 400 mA, and the voltage was measured for each current. The homemade conductivity cell was placed in a press, and measurements were made at room temperature, without and with pressure at 6.5×10^2 and 13×10^2 kg/cm².

The conductivity (σ) was calculated with the formula $\sigma = e/(R \times S_{\text{electrode}})$, where e is the thickness of the sample, R the measured resistance, and $S_{\text{electrode}}$ the surface of the electrode.

Results and discussion

Structural and morphological characterization

In this section, we present the structural and morphological characterization results. These results highlight specific properties such as crystallinity and specific surface areas or pore size distributions, which are crucial in selecting the most appropriate sample for the foreseen application.

Since the electronic conductivity in semi-conductors is strongly related to the periodic crystal structure, materials were calcined at different temperatures in air. The resulting XRD diagrams are shown in Fig. 2.

All calcined samples show characteristic peaks of rutile SnO₂. After calcination at 400 °C, the XRD peaks are relatively wide with very weak intensity, showing

low crystallinity, with the material remaining partially amorphous. The crystallinity improves following calcination at 700 °C. SnO₂ xerogels then exhibit good crystallinity, the peaks are intense, and the Full Width at Half Maximum is small. Both the electronic conductivity and the specific surface area are important for catalyst support. Given that the higher the calcination temperature the better the crystallinity but the lower the specific surface area, we needed to find a compromise. In order to avoid too severe a decrease in the specific surface area, materials were calcined at 600 °C.

Nb- and Sb-doped SnO₂ samples were prepared following a similar synthesis route, simply adding the dopant precursor to the alkoxide solution. Samples were calcined in air for 5 h at 600 °C.

Whatever the amount of dopant between 5 and 15 at.%, XRD diffractograms of doped SnO₂ aerogels also only showed the characteristic peaks of the SnO₂ rutile phase (see Fig. 3 for pure and 10 at.% doped samples). No new crystal phase was detected, and we observed a peak shift over smaller angle. This shift is more pronounced for Sb-doped samples than for Nb-doped ones (insert in Fig. 3), resulting from a greater modification of the SnO₂ lattice parameters. Both the absence of a new phase and the observation of XRD peak shifts are good indications of proper doping.

SEM analyses of the samples calcined at 600 °C were then performed to visualize the morphology of the aerogels and xerogels (Figs. 4 and 5) and possibly check the impact of doping.

Figure 2 X-ray diffraction diagrams of pure SnO₂ xerogels before and after calcination at 200, 400, 600, and 700 °C for 5 h in air.


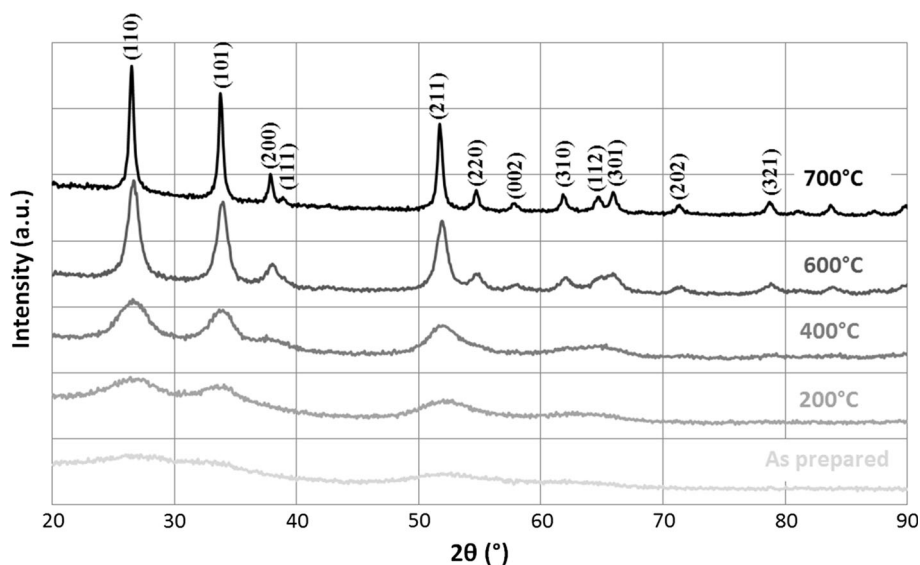


Figure 3 X-ray diffractogram of aerogels: pure SnO₂ (A6S), SnO₂: Sb (10 at.%) (A6SS100) and SnO₂: Nb (10 at.%) (A6SN100). All samples were calcined for 5 h at 600 °C in air.

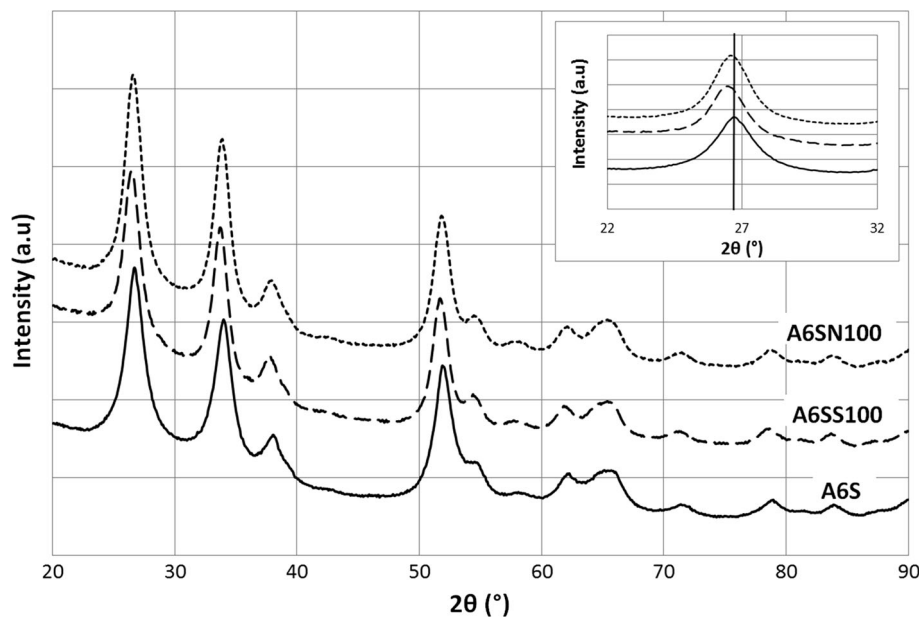

The morphology of pure SnO₂ aerogel (A6S) results from the agglomeration or aggregation of rather small particles (about 13 nm). The organization of such agglomerates results in the formation of large pores.

Doping seems to inhibit particle growth during the sol–gel process. Nb- or Sb-doped aerogels are indeed made up of smaller particles than pure SnO₂ aerogels. Nucleation and growth control of SnO₂ particles with dopant has already been observed and reported [9, 28, 37].

The overall picture of Nb-doped SnO₂ aerogel (A6SN100) is quite similar to that of pure SnO₂ (A6S) although the agglomerates look slightly smaller.

On the contrary, the morphology of Sb-doped SnO₂ aerogels (A6SS050 and A6SS100) is significantly different. They show a very interesting airy morphology lying on a three-dimensional network made up of interconnected particles. It is noteworthy that this morphology is quite similar to that of carbon aerogels previously synthesized in our group [43]. Sb-doped SnO₂ aerogels are from this point of view more interesting than Nb-doped ones.

As expected from the drying route, xerogel samples showed a very different morphology. X6SS050 and X6SS100, presented in Fig. 5, are much denser and show less apparent porosity than their aerogel counterparts.

To obtain additional morphological data, we performed nitrogen sorption analysis. The results are

reported in Table 1 and Fig. 6 for aerogels and in Table 2 and Fig. 7 for xerogels.

First of all, the type-IV isotherms obtained are representative of mesoporous materials.

Specific surface areas were calculated based on the BET model. Pore size distributions and mesoporous volumes were calculated based on the BJH model, assuming that all calcined samples are mechanically strong enough to withstand applied forces during analysis.

It is interesting to note that the doping rate impacts both the specific surface area and the mesoporous volume. A maximum was observed for 10 at.% doping rate. Values are actually relatively high for pure and 10 at.% doped materials, reaching almost 90 m²/g for the specific surface area, and 0.3 cm³/g for the mesoporous volume, whatever the dopant used (Sb or Nb).

The microporous volume of aerogel samples is negligible compared to their mesoporous volume. This is of utmost importance for the foreseen application, since most of the porosity will thus be accessible for Pt deposition and utilization. Here again, Sb-doped aerogels are more promising than pure or Nb-doped ones, showing an even smaller microporous volume.

The pore size distribution, calculated using the BJH method from isotherms, shows, for pure SnO₂ aerogels, a multimodal distribution with quite a narrow

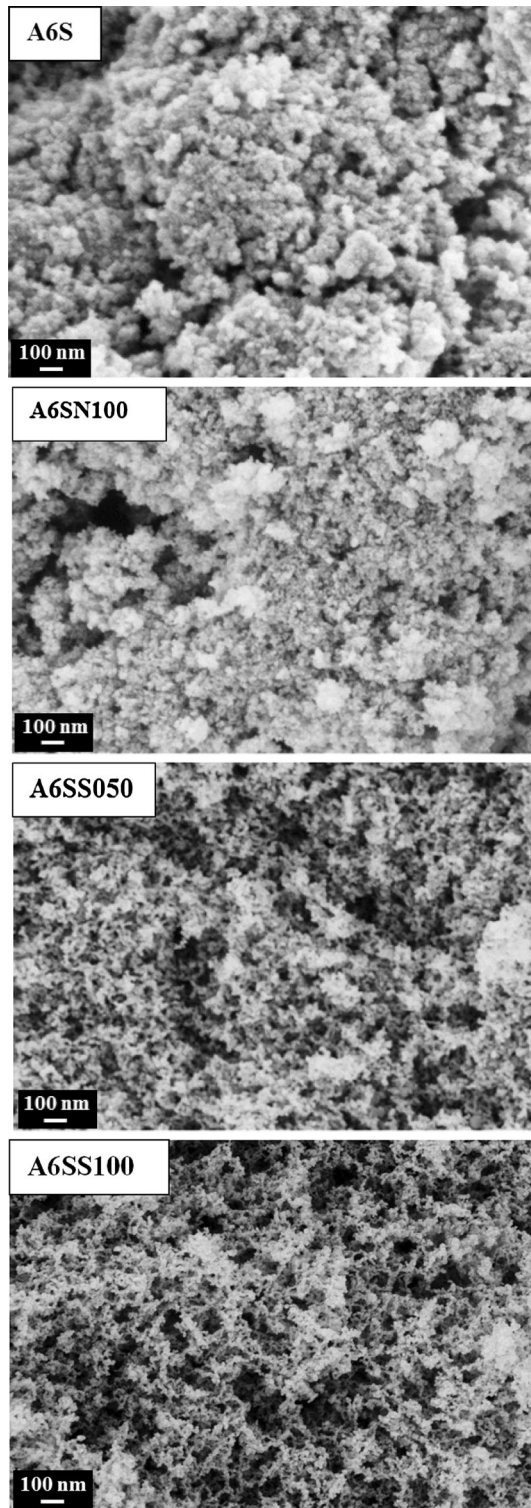


Figure 4 SEM images of aerogels: pure SnO₂ (A6S), SnO₂: Nb (10 at.%) (A6SN100), SnO₂: Sb (5 at.%) (A6SS050) and SnO₂: Sb (10 at.%) (A6SS100) (All samples calcined for 5 h at 600 °C in air).

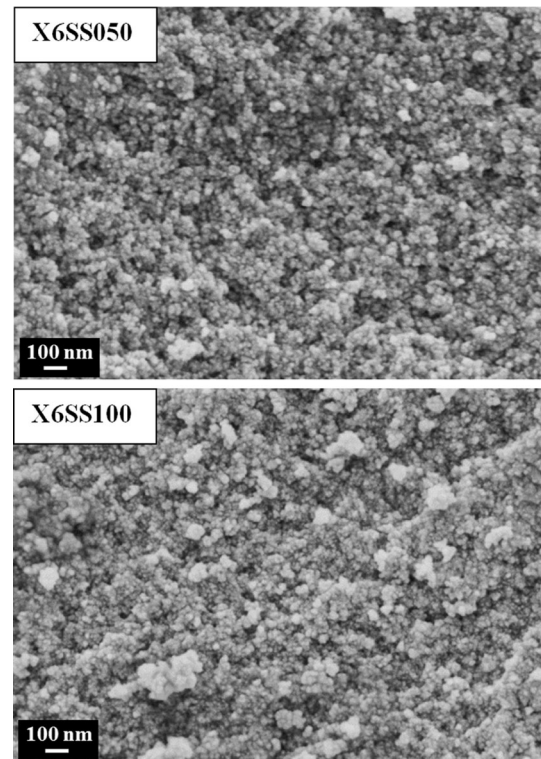


Figure 5 SEM images of xerogels: SnO₂: Sb (5 at.%) (X6SS050) and SnO₂: Sb (10 at.%) (X6SS100). All samples calcined for 5 h at 600 °C in air.

peak at around 15 nm and broader ones centered on 20 and 40 nm (Fig. 6).

Looking at Fig. 6, N₂ sorption should be complemented by mercury porosimetry analysis to fully characterize the pore size distribution, especially in the macroporous domain. Due to the nature of the samples, such an analysis could not be performed. Still, N₂ sorption analysis allowed to highlight morphology differences between aerogels samples.

The pore size distribution observed for doped samples is notably modified. First, the main peaks at 15, 20, and 40 nm observed for pure SnO₂ have shifted to larger diameters, namely 20, 30, and 45 nm. Second, the contributions at 30 and 45 nm are significantly lower for Nb- and Sb-doped samples than for pure SnO₂. The peak at 45 nm is even smaller for Sb-doped samples. The decrease in porosity around 45 nm may be related to the SEM observations and the change in size of the particle agglomerates.

To sum up, a multimodal distribution with broad peaks centered around 25 and 45 nm was observed for Sb- and Nb-doped SnO₂.

Table 1 Nitrogen sorption measurement results—SnO₂ aerogel samples (calcined for 5 h at 600 °C in air)

Sample	Dopant rate (at.%)	S BET (m ² /g)	PSD (BJH) (nm)	Pore volume (BJH) (cm ³ /g)	μ pore volume (t-plot) (cm ³ /g)
A6S	x-x	81	15–20–40	0.31	1.5 × 10 ⁻²
A6SN050	Nb-5	76	20–30–45	0.21	1.2 × 10 ⁻²
A6SN100	Nb-10	87	20–30–45	0.29	1.3 × 10 ⁻²
A6SS050	Sb-5	56	20–30–45	0.21	0.4 × 10 ⁻²
A6SS100	Sb-10	85	20–45	0.27	0.8 × 10 ⁻²
A6SS150	Sb-15	42	15–25–40	0.13	0.5 × 10 ⁻²

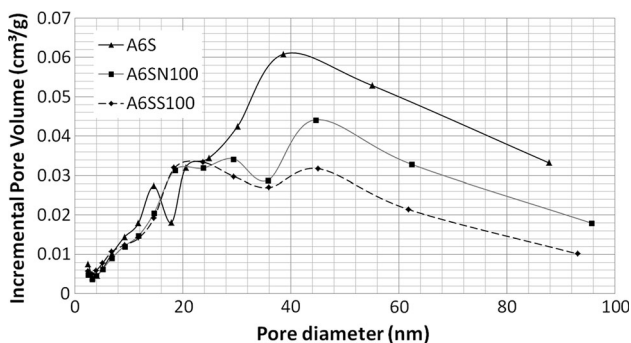


Figure 6 Pore size distribution for pure and doped SnO₂ aerogels (A6S = pure SnO₂, A6SN100 = SnO₂: Nb 10 at.%, A6SS100 = SnO₂: Sb 10 at.%).

In line with SEM observations, xerogel samples showed smaller specific surface areas than aerogel samples and much smaller porous volumes (0.1 cm³/g vs. 0.3 cm³/g). Accordingly, the microporous volume is also negligible, at two orders of magnitude smaller than that of aerogels.

In the case of xerogels, the specific surface area clearly increases with the Sb content. It is noteworthy that the 10 and 15 at.% doped xerogel samples showed surprisingly high specific surface areas of around 60 m²/g, close to the aerogel one.

Xerogel pore size distribution is also significantly different. Only one peak is observed for pure SnO₂, centered at around 13 nm. This peak shifts toward smaller diameters with the increase in Sb content. It is centered at around 4 nm for SnO₂: Sb 15 at.%. Such

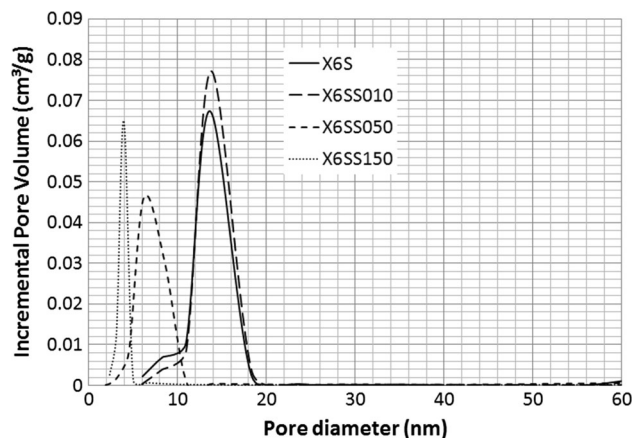


Figure 7 Pore size distribution for pure and doped SnO₂ xerogels (X6S = pure SnO₂, X6SS010 = SnO₂: Sb 1 at.%, X6SS050 = SnO₂: Sb 5 at.%, X6SS150 = SnO₂: Sb 15 at.%).

behavior is consistent with our SEM observations and literature that reports a decrease in particle size after doping.

So, despite negligible microporous volume and quite high specific surface area, due to pore size distributions centered on small mesopores (all <15 nm), xerogels appear less appropriate for the application.

Chemical composition

Chemical composition obviously impacts electronic conductivity. Although the amount of dopant

Table 2 Nitrogen sorption measurement results—SnO₂ xerogel samples (calcined for 5 h at 600 °C in air)

Sample	Dopant rate (at.%)	S BET (m ² /g)	PSD (BJH) (nm)	Pore volume (BJH) (cm ³ /g)	μ pore volume (t-plot) (cm ³ /g)
X6S	x-x	21	13	0.10	1.6 × 10 ⁻⁴
X6SS010	Sb-1	20	13	0.09	1.0 × 10 ⁻⁴
X6SS020	Sb-2	23	11	0.09	1.7 × 10 ⁻⁴
X6SS050	Sb-5	32	7	0.09	1.6 × 10 ⁻⁴
X6SS100	Sb-10	57	6	0.09	1.6 × 10 ⁻⁴
X6SS150	Sb-15	63	4	0.08	1.6 × 10 ⁻⁴

Table 3 Chemical composition of aerogels from EDX and XPS measurements

Sample	Dopant rate (at.%)	$x/(x + \text{Sn})^*$	
		EDX (at.%)	XPS (at.%)
A6SN050	Nb-5	5.5	7
A6SN100	Nb-10	10	13
A6SS050	Sb-5	7.5	8
A6SS100	Sb-10	12.0	13.5

* $x = \text{Nb}$ or Sb


precursor can be perfectly controlled during the sol-gel process, the exact concentration of dopant and its repartition in the final material has to be analyzed. The homogeneity of the sol may indeed not be optimal and some precursors could also partially precipitate during the sol-gel transition, thus modifying the real dopant amount within samples. Moreover, during calcination, the thermal energy can induce some atomic diffusion of the dopant within the SnO_2 matrix.

Thus, both bulk and surface chemical compositions were measured by EDX and XPS, respectively. These two methods are semi-quantitative and are used to compare different samples rather than to provide their real chemical composition.

According to the EDX measurements (Table 3), the niobium bulk concentrations correspond to the expected values for 5 and 10 at.% doped SnO_2 samples. The surface niobium concentration, measured by XPS, is, however, slightly higher than the bulk concentration (respectively, 7 and 13 at.% vs. 5 and 10 at.% expected for A6SN050 and A6SN100). The chemical composition does not seem to be perfectly homogenous in all SnO_2 : Nb samples. Such surface enrichments have already been reported by Szczuko et al. [9].

Regarding Sb-doped samples, the EDX peaks of Sn and Sb are very close due to the similar electronic structure of these two elements (Fig. 8). The doping rate calculation is thus more difficult. According to the EDX analysis, the Sb bulk concentration is higher than expected. This may, however, be a simple overestimation due to the Sn and Sb peaks overlapping. The trend is consistent for 5 and 10 at.% doped samples whose dopant concentration was calculated, respectively, to 7.5 and 12 at.%.

XPS survey spectra of SnO_2 : Nb and SnO_2 : Sb aerogels are shown on Fig. 9. Similar difficulties than for EDX analysis arose to quantify Sb rate at the surface, since the most intense peak of Sb (Sb 3d5) stands at the same binding energy as the O 1s peak. Thus, we performed measurements considering a less intense Sb peak (Sb 3d3) (Fig. 10). As for EDX, the characterization accuracy of Sb-doped samples is rather poor but comparison is still possible. As shown in Table 3, the Sb rate is also higher than expected on the surface, whatever the expected amount of Sb. The surface concentrations are still slightly larger than the bulk ones. They may also have been overestimated. As already observed [44, 45], Sb seems also prone to segregation in our SnO_2 aerogels (about 10 % more Sb measured on surface vs. volume), however, in a

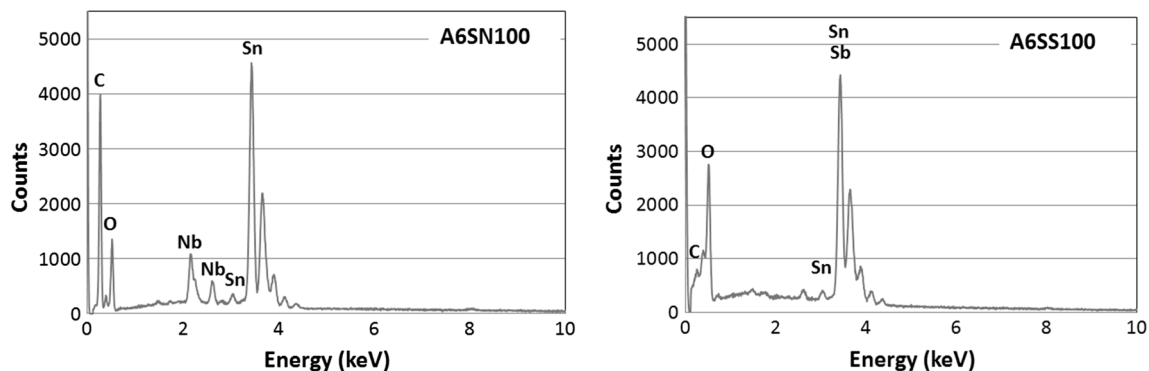**Figure 8** EDX typical spectra obtained for SnO_2 : Nb (A6SN100) and SnO_2 : Sb (A6SS100) aerogels.


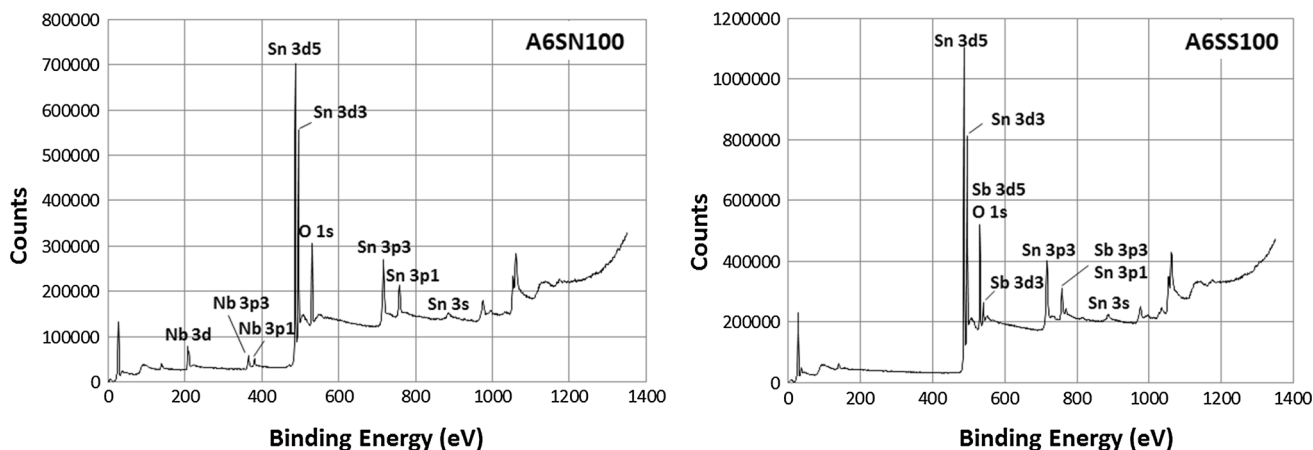


Figure 9 XPS survey spectra obtained for SnO₂: Nb (A6SN100), SnO₂: Sb (A6SS100) aerogels.

Figure 10 XPS spectra focusing on Nb 3d (left) and Sb 3d (right).

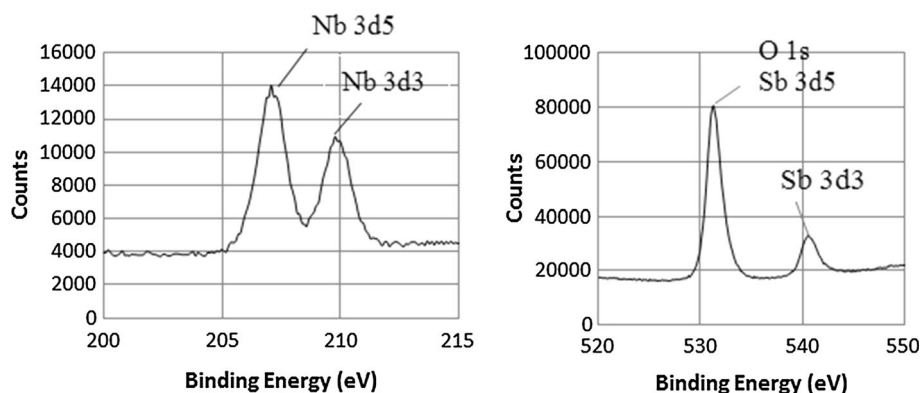

lesser extent than Nb (30 % more Nb measured on surface vs. volume).

If such segregations reveal to be problematic in fuel cell operating conditions, we will try to mitigate them through accurate selection or modification of metal precursors. Segregation may indeed result from different hydrolysis or condensation kinetics with the precursors used. In our case, tin isopropoxide may be more reactive than niobium and antimony isopropoxide. Segregation can probably be mitigated selecting or even synthesizing precursors with similar hydrolysis/condensation kinetics.

Electronic conductivity measurement

High electronic conductivity is essential for a material to be a good catalyst support in PEMFC. As metal oxides are by definition dielectric, high conductivity can only be obtained by modifying their electronic configuration. Doping is one option, as followed in this work. It is of paramount importance to check how the dopant type and concentration influence the electronic conductivity of doped samples. In this section, the electronic conductivity was measured for different Nb and Sb concentrations and compared to

Table 4 SnO₂: Nb conductivities obtained from impedance spectroscopy measurements on xerogel samples

Samples	Dopant rate (at.%)	Bulk conductivity 10 ⁻⁵ (S/cm)	Global conductivity 10 ⁻⁵ (S/cm)
X6S	–	53 ± 2	1.9 ± 1.3
X6SN020	Nb-2	63 ± 11	1.0 ± 0.4
X6SN100	Nb-10	490 ± 360	4.5 ± 3.6

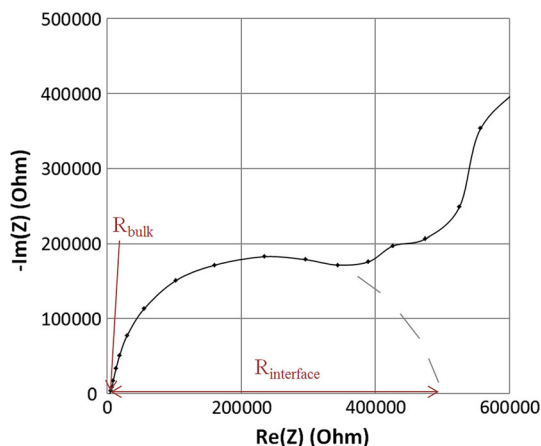


Figure 11 Nyquist plot obtained for SnO₂: Nb 10 at.% xerogel.

that of pure SnO₂ on one hand and carbon on the other hand. All materials were analyzed in the same conditions. In order to limit the impact of interface resistance between particles, measurements were first performed on xerogel sample pieces. This allowed us to study the influence of both the dopant type and its concentration. Measurement errors are quite high due to surface roughness of the samples, which was not possible to improve.

Nb⁵⁺ doping was first selected to increase the SnO₂ conductivity (Table 4). Typical impedance curves obtained for Nb-doped SnO₂ exhibit a characteristic half circle arc that is representative of a semi-conductor behavior (Fig. 11). The high frequency resistance is representative of bulk resistance, and the diameter of the half circle corresponds to that of interface resistances. We used both to analyze the conductivity of our samples.

The bulk conductivity of SnO₂ is considerably low (5×10^{-4} S/cm). The interface resistance between particles is relatively high, resulting in lower global conductivity, even for doped samples.

Compared to pure SnO₂, Nb-doped samples exhibit a significant improvement in bulk electronic conductivity. 5×10^{-3} S/cm was reached for 10 at.% of

Table 5 SnO₂: Sb conductivity obtained from impedance spectroscopy measurements on xerogel samples

Samples	Dopant rate (at.%)	Conductivity (S/cm)
X6S	–	$1.9 \times 10^{-5} \pm 1.3 \times 10^{-5}$
X6SS020	Sb-2	0.41 ± 0.16
X6SS050	Sb-5	0.97 ± 0.14
X6SS100	Sb-10	0.81 ± 0.4
X6SS150	Sb-15	0.71 ± 0.39

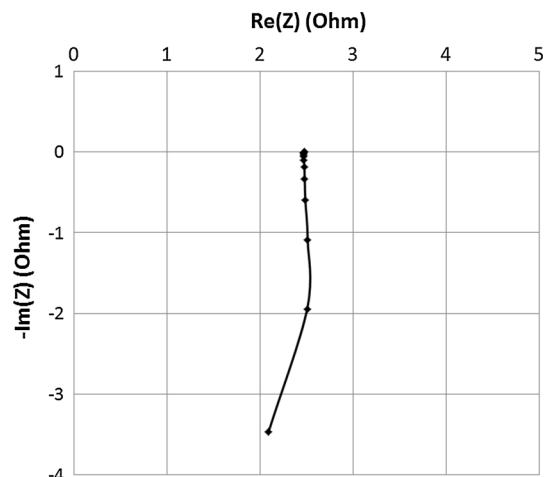


Figure 12 Nyquist plot obtained for SnO₂: Sb 10 at.% xerogel.

Nb, i.e., one order of magnitude higher than that of pure SnO₂. The improvement in global conductivity is very low compared to that of bulk conductivity, here again due to significant interface resistances. The doping inhibits grain growth during the sol gel process, as mentioned above and in agreement with SEM observations and pore size distribution calculations. Hence, the number of interfaces should be greater for doped materials, thus partially accounting for the limited improvement in the global conductivity.

The bulk conductivities of Nb-doped samples are still very low and far from that of Vulcan XC-72.

In agreement with other studies [9, 31, 33, 36, 46, 47], an impressive improvement in conductivity was observed for Sb-doped SnO₂ (Table 5). X6SS100 (10 at.% Sb-doped SnO₂ xerogel) shows indeed the typical behavior of a conducting material (Fig. 12). No impact of grain boundaries can be observed on the Nyquist plot. In agreement with Bruneaux et al. [48], this may result from a higher charge carriers density than in the case of Nb doping. Whatever the Sb rate between 2 and 15 at.%, conductivities were improved by at least 4 orders of magnitude compared to pure SnO₂. The electronic conductivity reached a maximum of about 1 S/cm for 5 at.% Sb, a value very close to that reported for Vulcan XC-72 (4 S/cm).

Based on this first series of results, Sb was selected as the favored dopant to determine the conductivity of doped SnO₂ aerogels.

Aerogel materials are not monolithic enough after calcination to allow impedance spectroscopy measurements and it was difficult to prepare pellets. We thus produced a homemade cell to measure the

Figure 13 Evolution of electronic conductivity with pressure applied on SnO₂: Sb xerogels—(2 at.%-X6SS020, 5 at.%-X6SS050, 10 at.%-X6SS100 and 15 at.%-X6SS150).

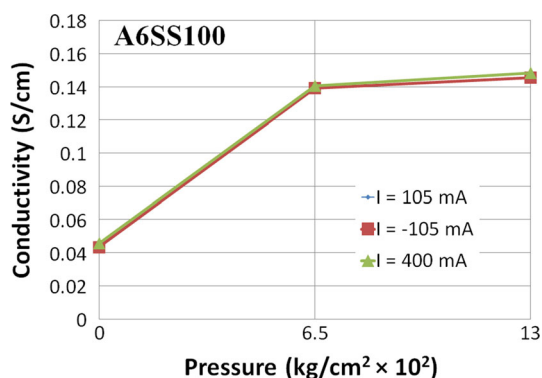
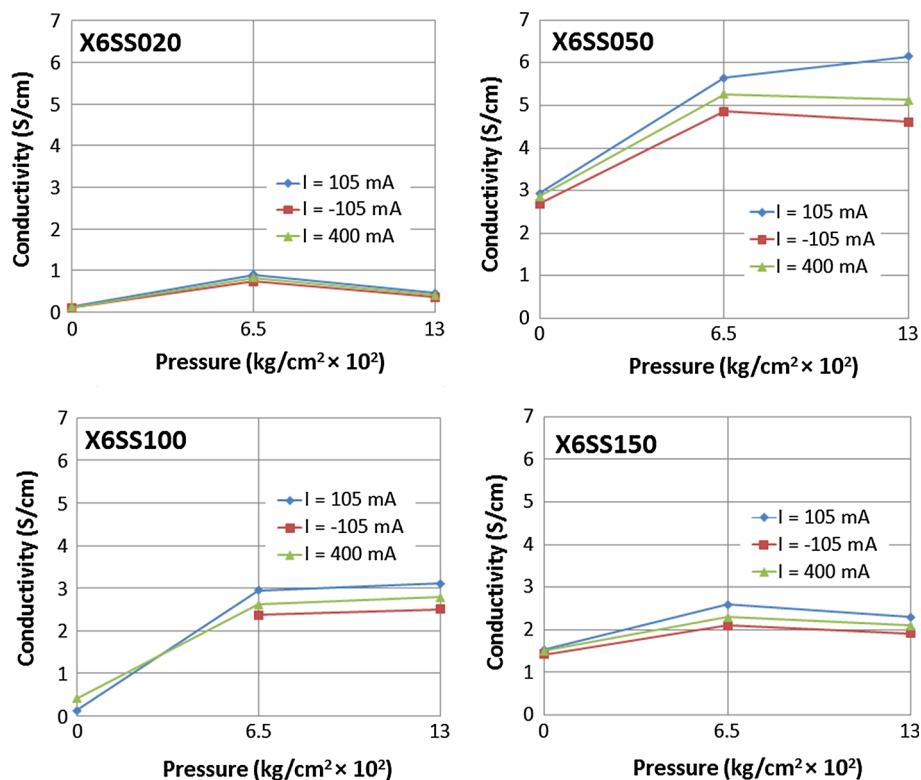


Figure 14 Evolution of electronic conductivity with pressure applied on SnO₂: Sb samples—(5 at.%-A6SS050 and 10 at.%-A6SS100).

resistance of aerogel materials, pressed between two electrodes inserted into a Teflon cylinder. For comparison purposes, we also measured the resistance of xerogels in the same conditions.

The evolution of conductivity with the pressure applied on the sample through the electrodes is shown in Fig. 13 for xerogels and Fig. 14 for aerogels.

As expected, the conductivity increases with the pressure applied. No significant difference was observed following a change in the current (+105,

–105 or 400 mA). In most cases, a plateau is reached from 6.5×10^2 kg/cm² of applied pressure.

Figure 15 represents the evolutions of conductivity for aerogels and xerogels as a function of the antimony doping rate and for the two methods used in this study (1: EIS, 2: direct resistance measurement).

First, conductivity values obtained with the homemade cell (13×10^2 kg/cm² pressure, data referenced (2) on Fig. 15) are 4 times higher than those obtained with impedance spectroscopy (data referenced (1) in Fig. 15). This is probably due to better contact between particles resulting from the relatively high pressure applied.

Then, the conductivity of xerogels is roughly between one and two orders of magnitude higher than that of aerogels.

Finally, whatever the measurement technique, the conductivity reaches a maximum for 5 at.% Sb-doping rate in the case of xerogels and between 5 and 10 at.% in the case of aerogels.

Discussion

The purpose of this study was to synthesize a new corrosion-resistant catalyst support for PEMFC. Both the morphology and the electronic conductivity are of

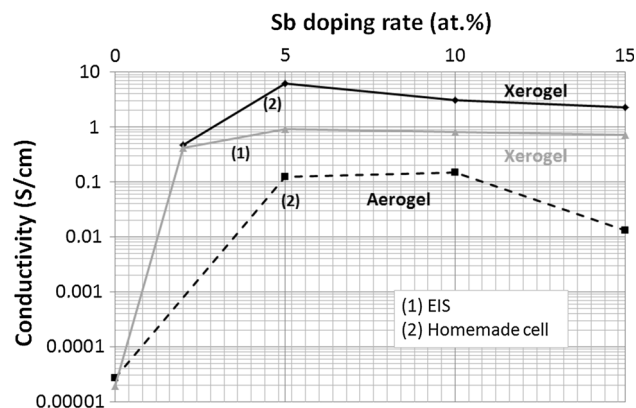


Figure 15 Xerogel and aerogel conductivity for different Sb-doping rates [(2): $P = 13 \times 10^2 \text{ kg/cm}^2$].

major importance considering the foreseen application. In a first part, the unique material morphology will be highlighted in comparison with those reported in the literature. In a second part, the electronic conductivity and its evolution with materials composition will be discussed.

Morphology

Considering the morphology, we have already stated that both the presence of meso and macropores are beneficial to fluid management within electrodes [43]. Moreover, since the optimum Pt particle size was reported to be between 3 and 4 nm in diameter, microporosity should be avoided and may become clogged after the deposition of platinum nanoparticles. Mesopores on the contrary allow good platinum nanoparticle dispersion while avoiding pore obstruction, still leaving room for high gas flow rates. Macropores are also beneficial to efficiently manage water coming from humidified gases and that produced during ORR.

Regarding such considerations, all SnO_2 aerogels show a very interesting morphology. Combining specific surface area close to $90 \text{ m}^2/\text{g}$, adequate pore size distribution revealing medium and large mesopores (25 and 45 nm) and negligible microporous volume, they are particularly well adapted to the foreseen application.

Little research has been reported on such an interesting morphology, mixing a high specific surface area with wide pore size distribution. Our materials show higher values for SnO_2 than most of those reported in literature [26, 27, 33]. Usually, high

specific surface area is developed at the expense of wide pore size distribution and vice versa. Indeed, high specific surface area nanostructured Sb-doped SnO_2 materials have already been synthesized. Lee et al. [49] achieved $100 \text{ m}^2/\text{g}$ from chloride precipitation in basic conditions. Sol-gel route using template, dodecylamine [31, 50], or tetradecylamine [34] also provide high specific surface areas with, respectively, 216 and $263 \text{ m}^2/\text{g}$. However, these materials show a narrow pore size distribution centered on few nm only.

Although the specific surface areas developed by our materials are still lower than that of Vulcan XC-72 ($254 \text{ m}^2/\text{g}$), a general carbon black reference, the difference in bulk density is in favor of SnO_2 . We may actually expect a similar developed surface area for the same volume. Since our aerogels crack after calcination, it was unfortunately not possible to measure their density. This advantage will be checked after electrochemical characterizations.

Thus, from a morphology point of view, the materials developed in this study are promising candidates for PEMFC catalyst support.

Electronic conductivity

High enough electronic conductivities were achieved only after doping with Sb. Doping with Nb allowed improving electronic conductivity by a factor of only 2 compared to undoped SnO_2 , what remains too low for the foreseen application. Doping may actually have been less efficient with Nb than with Sb. On one hand, the degree of segregation seems to be larger for Nb (see Table 3) and on the other hand the repartition of the dopant in the SnO_2 matrix may be less homogeneous, resulting in possible local Nb rich regions. Moreover, we cannot exclude the possibility of amorphous Nb oxide regions which would concentrate Nb at the expense of SnO_2 . Finally, the association of defects due to the introduction of dopant in SnO_2 may be less prone to increase the electronic conductivity in the case of Nb than in the case of Sb.

Most of the conductivities reported in literature [9, 33, 46, 47] were measured using different levels of pressure applied on samples. Since conductivity obviously depends on powder density (the higher the density, the higher the conductivity), it is quite difficult to compare reported conductivity values from one study to another. However, the values obtained

in our study for Sb-doped SnO₂ xerogels are among the highest reported ones.


The observed evolution of electronic conductivity with the antimony dopant rate and the presence of a maximum has already been reported [9, 28, 31, 33, 46, 47]. This may be related to the oxidation state of the dopant.

SnO₂ is known to be an oxygen-deficient non-stoichiometric oxide (SnO_{2-δ}) [51]. Its intrinsic electronic conductivity results from the presence of oxygen vacancies (V_O^{••}) which are compensated with electrons. Hence, the non-stoichiometry of SnO₂ gives rise to an *n*-type conductivity according to the equilibrium (1):



when SnO₂ is doped with Sb, a possible competition between the two antimony oxidation states has been suggested [52–55]. It has been shown that when Sb³⁺ is incorporated into SnO₂, it is oxidized during calcination in air [56]. This oxidation to Sb⁵⁺ is favored in the presence of SnO₂, which acts as a catalyst and a stabilizer of the Sb⁵⁺ state. This results in an increased Sb⁵⁺/Sb³⁺ ratio. The lower the Sb content, the higher the Sb⁵⁺/Sb³⁺ ratio.

For low doping rates, the antimony is agreed to be stabilized in a +5 state after calcination. According to geometrical considerations, the substitution, in the SnO₂ lattice, of Sn⁴⁺ ions with Sb⁵⁺ ions is allowed thanks to compatible ionic radius. Such a substitution leads to the generation of positively charged point defects Sb_{Sn}[•] which can be compensated by creating tin vacancies what can be represented with the Eq. (2):



These tin vacancies may then react with native oxygen vacancies, decreasing their concentration (at constant temperature and O₂ partial pressure). Such a decrease in oxygen vacancy concentration impacts the equilibrium (1) (right shift) resulting in a higher concentration of electrons in the lattice. Hence, the introduction of Sb⁵⁺ results in increased conductivity, as observed up to 5 at.% with xerogel samples.

For higher doping rates, Sb⁵⁺ is no longer favored and Sb³⁺ is stabilized. It substitutes Sn⁴⁺ as possibly represented with the equilibrium (3):



The creation of oxygen vacancies according to equilibrium (3) now impacts equilibrium (1) in the opposite direction, making the electron concentration

decrease. Consequently, the electronic conductivity decreases, as experimentally observed from 5 at.% on xerogel samples.

This hypothesis could partially explain the observed conductivity trend. It is, however, incomplete because it does not account for different parameters, such as the charge carrier mobility, the change in morphology between samples with different doping rates, and the effect of Sn⁴⁺/Sn²⁺ transition. It has also been reported that Sb³⁺ cannot fit in Sn⁴⁺ octahedral coordination as good as Sb⁵⁺, which induces charge defects [48].

All conductivity values obtained here are not really representative of real catalytic layer conductivities. They are useful to compare samples and select the proper dopant and its concentration. The conductivity of aerogels measured here is notably lower than that of xerogels and carbon. It is, however, noteworthy that the doped SnO₂ materials developed in this study are intended to be used as platinum support for fuel cell application. Pt nanoparticles deposited at the surface of SnO₂ may then lower the depletion layer resulting from adsorbed oxygen species (O₂⁻, O⁻ or O₂²⁻) limiting the electronic conductivity [57]. Thus as already reported [35, 58], we might expect an improvement in the conductivity after Pt deposition. This will be checked in a further study.

Conclusion

Antimony and niobium-doped tin dioxide xerogels and aerogels were synthesized by a sol-gel route starting with metal alkoxide precursors. After calcination at 600 °C in air, only the rutile crystal phase of SnO₂ was detected by XRD for all samples, whether pristine or doped.

Due to their unique morphology, our Nb- and Sb-doped SnO₂ aerogels appear to be very promising catalyst supports for PEMFC cathode.

Aerogel samples show an interconnected particle network, particularly pronounced for Sb-doped samples, with bimodal mesoporous pore size distributions.

Doping SnO₂ induces airier morphologies and leads to quite high specific surface areas: 85 m²/g for both SnO₂: Nb (10 at.%) and SnO₂: Sb (10 at.%).

As expected from the drying route, xerogels are denser and present only very small pore diameters (<20 nm). Highly doped xerogel samples, however,

show surprisingly high specific surface areas ($60 \text{ m}^2/\text{g}$ for 10 at.% Sb).

All Sb-doped samples exhibited an impressive improvement in electronic conductivity compared to pure SnO_2 . An increase of at least a 4 orders of magnitude has been recorded after doping SnO_2 xerogels with Sb, to reach electronic conductivities of about 1 S/cm (SnO_2 : Sb (5 at.%)), one order of magnitude less for aerogels. This value is even very close to that of carbon Vulcan XC-72 (4 S/cm).

Only poor conductivities were achieved for Nb-doped samples ($4.5 \times 10^{-5} \text{ S/cm}$ for 10 at.% of Nb versus $2 \times 10^{-5} \text{ S/cm}$ for pure SnO_2).

To conclude, with an adequate morphology (high specific surface area, bimodal pore size distribution centered on 25 and 45 nm, negligible microporous volume) and thanks to a high bulk electronic conductivity close to that of Vulcan XC-72, Sb-doped SnO_2 aerogel samples are very promising candidates as catalyst supports for PEMFC cathodes.

Future work will center on Pt deposition and catalytic performance assessment (activity and durability).

Acknowledgements

The authors wish to thank Pierre Ilbizian for supercritical drying, Frédéric Georgi for XPS analysis, Suzanne Jacomet for SEM/EDX analysis as well as Frédéric Fabry and Matthieu Houllé for their help in manufacturing the homemade conductivity measurement cell. This work was funded by the European Union's Seventh Framework Program for the Fuel Cells and Hydrogen Joint Technology Initiative under Grant Agreement No. 325239 (FCH-JU project Nano-CAT) and the French National Research Agency PROGELEC programme, (ANR-12-PRGE-007 project SURICAT). It was supported by Capenergies and Tenerrdis.

Author contributions The manuscript was written through contributions of all authors.

References

- [1] Rabis A, Rodriguez P, Schmidt TJ (2012) Electrocatalysis for polymer electrolyte fuel cells: recent achievements and future challenges. *ACS Catal* 2(5):864–890
- [2] Costamagna P, Srinivasan S (2001) Quantum jumps in the PEMFC science and technology from the 1960s to the year 2000 Part I. Fundamental scientific aspects. *J Power Sources* 102(1–2):242–252
- [3] Haile SM (2003) Fuel cell materials and components. *Acta Mater* 51(19):5981–6000
- [4] Antolini E (2009) Carbon supports for low-temperature fuel cell catalysts. *Appl Catal B* 88(1–2):1–24
- [5] Maass S, Finsterwalder F, Frank G, Hartmann R, Merten C (2008) Carbon support oxidation in PEM fuel cell cathodes. *J Power Sources* 176(2):444–451
- [6] Yasuda K, Taniguchi A, Akita T, Ioroi T, Siroma Z (2006) Platinum dissolution and deposition in the polymer electrolyte membrane of a PEM fuel cell as studied by potential cycling. *Phys Chem Chem Phys* 8(6):746–752
- [7] Sasaki K, Hayashi S, Kanda K, Takabatake Y, Tsukatsune T, Higashi T, Takasaki F, Noda Z, Hayashi A (2012) Alternative electrocatalyst support materials for polymer electrolyte fuel cells. *The Electrochem Soc Meeting Abstracts*, 1684
- [8] Gokulakrishnan V, Parthiban S, Jeganathan K, Ramamurthi K (2011) Investigations on the structural, optical and electrical properties of Nb-doped SnO_2 thin films. *J Mater Sci* 46(16):5553–5558. doi:10.1007/s10853-011-5504-x
- [9] Szczuko D, Werner J, Oswald S, Behr G, Wetzig K (2001) XPS investigations of surface segregation of doping elements in SnO_2 . *Appl Surf Sci* 179(1–4):301–306
- [10] Bressand JGE, Royer B (2009) Electrochromic device with controlled infrared reflection, european patent 2 307 926 B1
- [11] Megahed S, Ebner W (1995) Lithium-ion battery for electronic applications. *J Power Sources* 54(1):155–162
- [12] Courtney IA, Dunlap RA, Dahn JR (1999) In-situ Sn-119 Mossbauer effect studies of the reaction of lithium with SnO and SnO: 0.25 B_2O_3 : 0.25 P_2O_5 glass. *Electrochim Acta* 45(1–2):51–58
- [13] Fuller MJ, Warwick ME (1972) The catalytic oxidation of carbon monoxide on Tin(IV) oxide. *J Catal* 29:441–450
- [14] Matsui T, Fujiwara K, Okanishi T, Kikuchi R, Takeguchi T, Eguchi K (2006) Electrochemical oxidation of CO over tin oxide supported platinum catalysts. *J Power Sources* 155(2):152–156
- [15] Herniman HJ, Pyke DR, Reid R (1979) An investigation of the relationship between the bulk and surface composition of tin and antimony mixed oxide catalysts and the oxidative dehydrogenation of I-Butene to Butadiene. *J Catal* 58:8–73
- [16] Viricelle JP, Valleron A, Pijolat C, Breuil P, Ott S (2012) Gas sensors based on tin dioxide for exhaust gas application, modeling of response for pure gases and for mixtures. In: 26th European Conference on solid-state transducers, *Eurosensor* 47:655–658

- [17] Shukla S, Patil S, Kuiry SC, Rahman Z, Du T, Ludwig L, Parish C, Seal S (2003) Synthesis and characterization of sol-gel derived nanocrystalline tin oxide thin film as hydrogen sensor. *Sens Actuators, B* 96(1–2):343–353
- [18] Barsan N, Koziej D, Weimar U (2007) Metal oxide-based gas sensor research: How to? *Sens Actuators, B* 121(1):18–35
- [19] Masao A, Noda S, Takasaki F, Ito K, Sasaki K (2009) Carbon-free Pt electrocatalysts supported on SnO₂ for polymer electrolyte fuel cells. *Electrochem Solid State Lett* 12(9):B119–B122
- [20] Takabatake Y, Noda Z, Lyth SM, Hayashi A, Sasaki K (2014) Cycle durability of metal oxide supports for PEFC electrocatalysts. *Int J Hydrog Energy* 39(10):5074–5082
- [21] Zhang P, Huang SY, Popov BN (2010) Mesoporous tin oxide as an oxidation-resistant catalyst support for proton exchange membrane fuel cells. *J Electrochem Soc* 157(8):B1163–B1172
- [22] Andersen SM, Norgaard CF, Larsen MJ, Skou E (2015) Tin dioxide as an effective antioxidant for proton exchange membrane fuel cells. *J Power Sources* 273:158–161
- [23] Matsui T, Kanishi T, Fujiwara K, Tsutsui K, Kikuchi R, Takeguchi T, Eguchi K (2006) Effect of reduction-oxidation treatment on the catalytic activity over tin oxide supported platinum catalysts. *Sci Technol Adv Mater* 7(6):524–530
- [24] Okanishi T, Matsui T, Takeguchi T, Kikuchi R, Eguchi K (2006) Chemical interaction between Pt and SnO₂ and influence on adsorptive properties of carbon monoxide. *Appl Catal A* 298:181–187
- [25] Arenz M, Stamenkovic V, Blizanac BB, Mayrhofer KJJ, Markovic NM, Ross PN (2005) Carbon-supported Pt-Sn electrocatalysts for the anodic oxidation of H₂, CO, and H₂/CO mixtures. Part II: the structure-activity relationship. *J Catal* 232(2):402–410
- [26] Takasaki F, Matsue S, Takabatake Y, Noda Z, Hayashi A, Shiratori Y, Ito K, Sasaki K (2011) Carbon-free Pt electrocatalysts supported on SnO₂ for polymer electrolyte fuel cells: electrocatalytic activity and durability. *J Electrochem Soc* 158(10):B1270–B1275
- [27] Kakinuma K, Chino Y, Senoo Y, Uchida M, Kamino T, Uchida H, Deki S, Watanabe M (2013) Characterization of Pt catalysts on Nb-doped and Sb-doped SnO₂-delta support materials with aggregated structure by rotating disk electrode and fuel cell measurements. *Electrochim Acta* 110:316–324
- [28] Cavaliere S, Subianto S, Savych I, Tillard M, Jones DJ, Roziere J (2013) Dopant-driven nanostructured loose-tube SnO₂ architectures: alternative electrocatalyst supports for proton exchange membrane fuel cells. *J Phys Chem C* 117(36):18298–18307
- [29] Shahgaldi S, Hamelin J (2015) The effect of low platinum loading on the efficiency of PEMFC's electrocatalysts supported on TiO₂-Nb, and SnO₂-Nb: an experimental comparison between active and stable conditions. *Energy Convers Manag* 103:681–690
- [30] Kakinuma K, Uchida M, Kamino T, Uchida H, Watanabe M (2011) Synthesis and electrochemical characterization of Pt catalyst supported on Sn 0.96 Sb 0.04 O₂-delta with a network structure. *Electrochim Acta* 56(7):2881–2887
- [31] Gurrola MP, Guerra-Balcazar M, Alvarez-Contreras L, Nava R, Ledesma-Garcia J, Arriaga LG (2013) High surface electrochemical support based on Sb-doped SnO₂. *J Power Sources* 243:826–830
- [32] You DJ, Kwon K, Pak C, Chang H (2009) Platinum-antimony tin oxide nanoparticle as cathode catalyst for direct methanol fuel cell. *Catal Today* 146(1–2):15–19
- [33] Yin M, Xu JY, Li QF, Jensen JO, Huang YJ, Cleemann LN, Bjerrum NJ, Xing W (2014) Highly active and stable Pt electrocatalysts promoted by antimony-doped SnO₂ supports for oxygen reduction reactions. *Appl Catal B* 144:112–120
- [34] Oh HS, Nong HN, Strasser P (2015) Preparation of mesoporous Sb-, F-, and In-doped SnO₂ bulk powder with high surface area for use as catalyst supports in electrolytic cells. *Adv Func Mater* 25(7):1074–1081
- [35] Senoo Y, Taniguchi K, Kakinuma K, Uchida M, Uchida H, Deki S, Watanabe M (2015) Cathodic performance and high potential durability of Ta-SnO₂-delta-supported Pt catalysts for PEFC cathodes. *Electrochem Commun* 51:37–40
- [36] Avila-Vazquez V, Galvan-Valencia M, Ledesma-Garcia J, Arriaga LG, Collins-Martinez VH, Guzman-Martinez C, Escalante-Garcia IL, Duron-Torres SM (2015) Electrochemical performance of a Sb-doped SnO₂ support synthesized by coprecipitation for oxygen reactions. *J of Appl Electrochem* 45(11):1175–1185
- [37] Leite ER, Weber IT, Longo E, Varela JA (2000) A new method to control particle size and particle size distribution of SnO₂ nanoparticles for gas sensor applications. *Adv Mater* 12(13):965–968
- [38] Tauster SJ, Fung SC (1978) Strong metal-support interactions—occurrence among binary oxides of groups IIA-VB. *J Catal* 55(1):29–35
- [39] Kamiuchi N, Matsui T, Kikuchi R, Eguchi K (2007) Nanoscopic observation of strong chemical interaction between Pt and tin oxide. *J Phys Chem C* 111(44):16470–16476
- [40] Spencer MS (1985) Models of strong metal support interaction (SMSI) in Pt on TiO₂ catalysts. *J Catal* 93(2):216–223
- [41] Daio T, Staykov A, Guo LM, Liu JF, Tanaka M, Lyth SM, Sasaki K (2015) Lattice strain mapping of platinum nanoparticles on carbon and SnO₂ supports. *Sci Rep* 5:13126
- [42] Ouattara-Brigaudet M, Beauger C, Berthon-Fabry S, Achard P (2011) Carbon aerogels as catalyst supports and first insights on their durability in proton exchange membrane fuel cells. *Fuel Cells* 11(6):726–734

- [43] Ouattara-Brigaudet M, Berthon-Fabry S, Beauger C, Chatenet M, Job N, Sennour M, Achard P (2012) Influence of the carbon texture of platinum/carbon aerogel electrocatalysts on their behavior in a proton exchange membrane fuel cell cathode. *Int J Hydrog Energy* 37(12):9742–9757
- [44] Fabbri E, Rabis A, Kotz R, Schmidt TJ (2014) Pt nanoparticles supported on Sb-doped SnO₂ porous structures: developments and issues. *Phys Chem Chem Phys* 16(27):13672–13681
- [45] Rabis A, Kramer D, Fabbri E, Worsdale M, Kotz R, Schmidt TJ (2014) Catalyzed SnO₂ thin films: theoretical and experimental insights into fabrication and electrocatalytic properties. *J Phys Chem C* 118(21):11292–11302
- [46] Muller V, Rasp M, Stefanic G, Ba JH, Gunther S, Rathousky J, Niederberger M, Fattakhova-Rohlfing D (2009) Highly conducting nanosized monodispersed antimony-doped tin oxide particles synthesized via nonaqueous sol-gel procedure. *Chem Mater* 21(21):5229–5236
- [47] Mulla IS, Soni HS, Rao VJ, Sinha APB (1986) Deposition of improved optically selective conductive tin oxide-films by spray pyrolysis. *J Mater Sci* 21(4):1280–1288. doi:[10.1007/BF00553263](https://doi.org/10.1007/BF00553263)
- [48] Bruneaux J, Cachet H, Froment M, Messad A (1994) Structural, electrical and interfacial properties of sprayed SnO₂ films. *Electrochim Acta* 39(8–9):1251–1257
- [49] Lee KS, Park IS, Cho YH, Jung DS, Jung N, Park HY, Sung YE (2008) Electrocatalytic activity and stability of Pt supported on Sb-doped SnO₂ nanoparticles for direct alcohol fuel cells. *J Catal* 258(1):143–152
- [50] Gurrola MP, Gutierrez J, Rivas S, Guerra-Balcazar M, Ledesma-Garcia J, Arriaga LG (2014) Evaluation of the corrosion of Sb-doped SnO₂ supports for electrolysis systems. *Int J Hydrog Energy* 39(29):16763–16770
- [51] Godinho KG, Walsh A, Watson GW (2009) Energetic and electronic structure analysis of intrinsic defects in SnO₂. *J Phys Chem C* 113(1):439–448
- [52] Terrier C, Chatelon JP, Berjoan R, Roger JA (1995) Sb-doped SnO₂ transparent conducting oxide from the sol-gel dip-coating technique. *Thin Solid Films* 263(1):37–41
- [53] Terrier C, Chatelon JP, Roger JA (1997) Electrical and optical properties of Sb:SnO₂ thin films obtained by the sol-gel method. *Thin Solid Films* 295(1–2):95–100
- [54] Lekshmy SS, Daniel GP, Joy K (2013) Microstructure and physical properties of sol gel derived SnO₂: Sb thin films for optoelectronic applications. *Appl Surf Sci* 274:95–100
- [55] Las WC, Dolet N, Dordor P, Bonnet JP (1993) Influence of additives on the electrical-properties of dense SnO₂-based ceramics. *J Appl Phys* 74(10):6191–6196
- [56.] Caldaru M, Thomas MF, Bland J, Spranceana D (2001) Redox processes in Sb-containing mixed oxides used in oxidation catalysis I. Tin dioxide assisted antimony oxidation in solid state. *Appl Catal A* 209(1–2):383–390
- [57] Barsan N, Weimar U (2001) Conduction model of metal oxide gas sensors. *J Electroceramics* 7(3):143–167
- [58] Senoo Y, Kakinuma K, Uchida M, Uchida H, Deki S, Watanabe M (2014) Improvements in electrical and electrochemical properties of Nb-doped SnO₂-delta supports for fuel cell cathodes due to aggregation and Pt loading. *RSC Adv* 4(61):32180–32188