



# Influence of agro-based reinforcements on the properties of aluminum matrix composites: a systematic review

Bisma Parveez<sup>1</sup>, Md Abdul Maleque<sup>1,\*</sup> , and Nur Ayuni Jamal<sup>1</sup>

<sup>1</sup>Department of Manufacturing and Materials Engineering, International Islamic University Malaysia, 53100 Kuala Lumpur, Malaysia

**Received:** 1 March 2021

**Accepted:** 29 June 2021

**Published online:**  
13 July 2021

© The Author(s), under exclusive licence to Springer Science+Business Media, LLC, part of Springer Nature 2021

## ABSTRACT


Aluminum matrix composites (AMCs) have been extensively studied primarily due to higher strength-to-weight ratio, lower cost, and higher wear resistance properties. However, increasing demand for economical and energy-efficient materials in the automotive, aerospace and other applications is tailoring research area in the agro-based composite materials. Therefore, the aim of this systematic review work is to study the influence of agro-based reinforcements on the tribological and mechanical properties of AMC's processed by various techniques. It was observed that the processing conditions can be designed to obtain uniform structures and better properties AMCs. The agro-waste reinforcement materials, such as rice husk ash, bamboo stem ash, coconut and shell ash can result in a reduction in the density of AMC's without compromising mechanical properties. Moreover, the efficient utilization of the agro-waste leads to a decrease in manufacturing cost and prevents environmental pollution, hence, can be considered as a sustainable material. The state-of-the-art revealed that the agro-based reinforcements do not form brittle composites, as in the case of ceramic reinforced composites. Hence, the study concludes that the agro-based AMCs have great potential to act as a replacement for costly and environmentally hazardous ceramic reinforced-AMCs which can especially be used in various automotive applications that demand higher strength-to-weight ratio, lower cost, and higher wear resistance.

Handling Editor: P. Nash.

Address correspondence to E-mail: maleque@iiium.edu.my

<https://doi.org/10.1007/s10853-021-06305-2>

## GRAPHICAL ABSTRACT

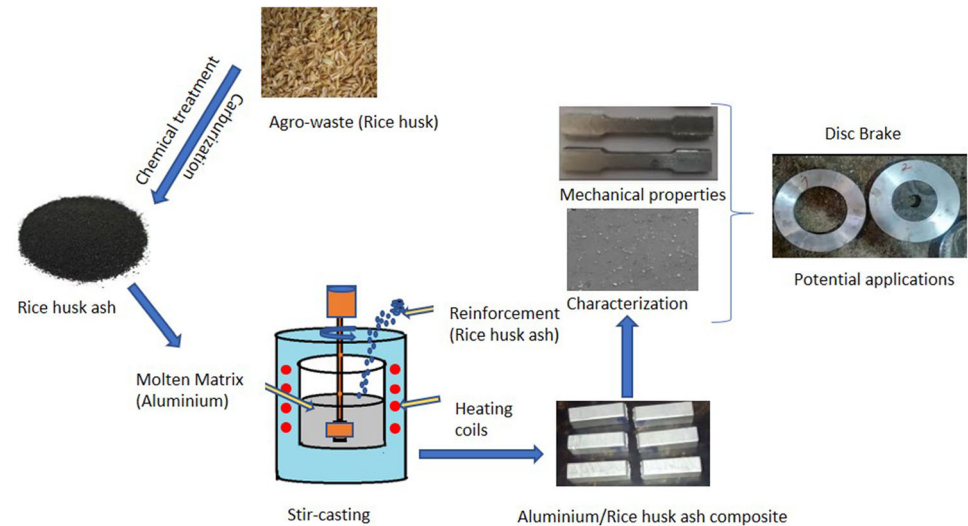

## Introduction

Due to the increasing demand for economical and energy-efficient materials in the automotive, aerospace and numerous applications, the industrial sectors are concentrating on the development of lightweight, low cost and eco-friendly materials. Preceding work has conveyed that AMC's exhibit superior features such as lower density, higher stiffness, and low coefficient of thermal expansion, specific strength, and superior wear resistance [1–3]. Presently, researchers and scientists are paying more attention toward the development of discontinuously reinforced AMC's. This is due to the simpler production techniques that are economically feasible and result in the development of the homogeneous structure of particulate reinforced AMC's. The homogeneity of reinforcement particles and their interfacial bonding in the composites are further improved by subjecting them to several forming processes like forging, extrusion, and rolling [4]. Also, it has been reported that the type and fraction of reinforcement materials influence the characteristics of the Al composites. It has been reported that the significant improvement in the properties of Al composites can be achieved by the addition of even a

small quantity of ceramic reinforcements [5–7]. These particulate materials are silicon carbide (SiC), boron carbide ( $B_4C$ ), titanium carbide (TiC),  $Al_2O_3$ , and silica ( $SiO_2$ ) particles. With the addition of ceramic reinforcements the physical and mechanical properties of materials can be improved, and such materials can be used as a replacement to the bulky cast iron in automobile applications such as brake rotor [8].

In addition, properties of these materials can be adjusted by the selection of suitable fabrication techniques such as coating reinforcements [9], precipitate strengthening [10], mechanical and thermal activation reactions [11] and varying percentage of reinforcements in AMC's. The addition of these hard particles into soft Al-matrices improve their hardness and wear resistance. However, the production of these ceramic materials is neither economical nor environmentally friendly. Taking these factors into consideration, researchers have found huge potential in agro-waste based reinforcements due to their economic viability and abundance availability [12, 13]. Furthermore, these materials are frequently disposed in an open land resulting in environmental contamination. Agro-waste materials such as rice husk ash (RHA) [14–16], groundnut shell ash (GSA) [17, 18], coconut shell ash (CSA) [18, 19], melon shell ash (MSA) [20] have been utilized by the

researchers as reinforcing materials for improving the properties of AMC's. These AMC's can find application in automotive, aerospace, and construction materials [21, 22].

Thus, the utilization of agro-waste materials in the AMC industry can be beneficial in the reduction in environmental degradation resulting from their disposal [23, 24]. Although the addition of the ceramic particles improves stiffness, specific strength, and wear resistance of Al-alloys considerably, several drawbacks regarding the use of Al/ceramics composites have also been reported [23]. It has been observed that ceramic reinforcements increase the density of the developed composites. This can be attributed to a higher density of ceramic reinforcements such as SiC (3.22 g/cm<sup>3</sup>) and Al<sub>2</sub>O<sub>3</sub> (3.9 g/cm<sup>3</sup>) in comparison to Al-matrices (2.7–2.8 g/cm<sup>3</sup>). Also the ceramic particles have higher elastic modulus (400 GPa) in comparison to Al alloys (70 GPa). This degrades the aggregate properties leading to brittleness, poor machinability, and reduced fracture toughness of the AMC's [25, 26]. In addition to this, ceramic reinforcements in Al composites reduce the impact strength of the composites by reducing strain energy and forms regions of stress concentration [27]. Under these conditions, the development of agro-waste AMC's is quite beneficial. The use of agro-waste materials results in formation of low cost and lightweight composites without compromising their mechanical and tribological properties [28, 29]. However, there is a limited understanding of their service performance, thus restricts their utilization options for their wider use in applications. Consequently, it is important to review the morphological, mechanical, and tribological properties of these materials containing various agro-based reinforcements to conclude the advancements done so far and to look the way forward for the improvement of properties of AMC's by addition of such agro-based reinforcements.

Considering all these issues, this paper presents the overview of low-cost agro-based Al-composites using various processing technique i.e., stir casting, compo-casting, powder metallurgy as well as additive manufacturing. The morphological, mechanical, and tribological analysis of fabricated agro-waste based materials have been extensively reviewed to find the best possible fabrication techniques for the development of agro-based AMC's. In general, this paper has been presented in six sections. The first section

introduces the AMC's state-of-the-art and their strength improving efforts by the researchers. The second section describes briefly the various agro-based materials used by the researchers and their chemical compositions. In the third section, the properties of agro-based AMC's reinforced with agro-based materials have systematically been reviewed. The fourth section explains the various production techniques for the development of such agro-based AMC's. The fifth section includes the challenges and the way forward for the agro-based AMC's. In sixth section, the conclusion and remarks of the review have been elucidated.

## Agro-waste reinforcement materials

Several agro-based materials are promising to be used as reinforcements in Al matrix composites development and some of them are mentioned in Table 1. The following are the agro-wastes recognized as potential reinforcing material:

### Rice husk ash (RHA)

This agro-waste material is obtained from rice mills during the process of milling of the paddy. Usually, it is used as a fuel for generating electricity in the rice mills. However, it has been observed that about 25% of the total weight of rice husk forms ash during the steam generation process, thus not an efficient fuel [30]. Moreover, dumping it in an open land has resulted into a major impact on the environment.

**Table 1** Various Al alloys matrices and agro-based reinforced composites

| Matrix        | Reinforcement                 | References |
|---------------|-------------------------------|------------|
| AA6063        | Rice husk ash                 | [37]       |
| AlSi10Mg      | Rice husk ash                 | [38]       |
| Al            | Groundnut shell ash           | [39]       |
| Al6082        | Coconut shell ash             | [40]       |
| AA6061        | Palm sprout shell ash         | [41]       |
| Al6061        | Sugarcane bagasse ash         | [42]       |
| Al            | Palm shell activated carbon   | [43]       |
| Al0.3Si0.1 Mg | Horse eye bean seed shell ash | [44]       |
| Al            | Mustard husk ash              | [45]       |
| Al6063        | Corn cob ash                  | [46]       |
| Al6063        | Palm kernel shell ash         | [47]       |
| Al356.2       | Bamboo leaf ash               | [48]       |

**Table 2** Chemical composition of agro-based reinforcements

| Agro-Waste                     | Composition               |   |              |   |              |                           |                          |  |
|--------------------------------|---------------------------|---|--------------|---|--------------|---------------------------|--------------------------|--|
|                                | SiO <sub>2</sub><br>(wt%) | Al <sub>2</sub> O <sub>3</sub><br>(wt%) | MgO<br>(wt%) | Fe <sub>2</sub> O <sub>3</sub><br>(wt%) | CaO<br>(wt%) | K <sub>2</sub> O<br>(wt%) | SO <sub>3</sub><br>(wt%) | P <sub>2</sub> O <sub>5</sub><br>(wt%) |
| RHA -Rice husk ash<br>[57, 58] | 97.09                     | 1.135                                   | 0.825        | 0.31                                    | –            | –                         | –                        | –                                      |
| CSA-Coconut Shell Ash<br>[59]  | 45.05                     | 15.6                                    | 16.2         | 12.4                                    | –            | –                         | –                        | –                                      |
| BLA-Bamboo leaf ash[60]        | 75.9                      | 3.5                                     | –            | 1.22                                    | 7.47         | –                         | –                        | –                                      |
| POFA-Palm Oil Fuel Ash<br>[61] | 49.20                     | 35.45                                   | 3.93         | –                                       | 7.5          | 5.3                       | 1.73                     | 6.41                                   |
| POC-Palm Oil Clinkers [62]     | 81.8                      | 3.5                                     | 1.24         | 5.18                                    | 2.3          | 4.66                      | –                        | 0.76                                   |

Therefore, researchers started utilizing this material most efficiently as reinforcement in high-performance AMC's as it offers lower density (0.3–1.9 gm/cm<sup>3</sup>) and ease of availability [28, 31]. RHA consists of a higher percentage of SiO<sub>2</sub> along with other elements such as Al<sub>2</sub>O<sub>3</sub>, Fe<sub>2</sub>O<sub>3</sub>, and MgO, as shown in Table 2. Kumar [32] reinforced RHA and mica in Al7075 matrix composites and found an improvement in hardness, tensile strength as well as the toughness of the developed composites. Further some researches have extracted SiC from rice husk [33, 34] and used that as a reinforcing material due to their better properties as comparison to RHA [35]. Joharudin et al. [36], extracted silica from RHA through heat treatments and reinforced them in recycled Al7075 chip resulting into enhancement of the hardness of the developed composites.

### Coconut Shell Ash (CSA)

This agro-waste material is mostly available in tropical regions in abundance and often used as fuel in boilers and furnaces [49]. But the combustion of CSA results in the release of CO<sub>2</sub> and methane in large quantities and hence, leads to significant environmental pollution [50]. It is preferred to use them as reinforcement in the production of Al-composites taking these considerations [51]. The density of CSA was found to be 2.05 gm/cm<sup>3</sup> and its constituents of elements are like SiO<sub>2</sub>, MgO, Al<sub>2</sub>O<sub>3</sub>, and Fe<sub>2</sub>O<sub>3</sub>, as mentioned in Table 2.

The coconut shell when added as particles have proved to enhance the properties of Al composites. Kaladgi et al. [52] developed coconut shell micro particles (CMP) and Al<sub>2</sub>O<sub>3</sub> reinforced Al6061 composites via stir casting technique. There was an

increase in hardness and tensile strength with increasing reinforcement content. Also, Bello et al. [53] incorporated CMP in Al alloy developed by compo-casting technique and observed an increase in tensile properties as a result of good interfacial bonding between the matrix and reinforcement and due to formation of harder phases.

### Bamboo leaf ash (BLA)

The bamboo trees are found in abundance in various sections of the world. These trees often litter their leaves in these regions; however, these can be used as BLA for economic purposes. It mainly constituents of ceramic oxides like SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, CaO, K<sub>2</sub>O, and Fe<sub>2</sub>O<sub>3</sub>, as shown in Table 2; thus, it can be used as reinforcements in the AMC's [54, 55]. Aleneme et al., [56] reinforced BLA in Al alloy and observed an improvement in the wear behavior of the resultant composites.

### Palm Oil Fuel Ash (POFA)

This is agricultural waste abundantly found in Malaysia, and it contains a higher content of siliceous material. It is obtained on the combustion of oil palm fiber, mesocarp, and empty fruit bunch as boiler fuel to produce steam for palm oil mill, and the end product remaining after combustion is POFA [63]. This can be later used as reinforcing material [64]. Silica or silicon dioxide (SiO<sub>2</sub>) is the main constituent found in POFA, mostly up to 40%, besides silica, other chemical components found in POFA are potassium oxide, magnesium oxide, calcium oxide, aluminum oxide, and iron oxide. The composition is shown in Table 2. The study of the effect of POFA on

the mechanical and tribological properties revealed that addition of POFA improved the hardness, tensile strength, wear and coefficient of friction of the resultant composites [64].

### Palm Oil Clinkers (POC)

The palm oil is primarily produced in Indonesia and Malaysia, contributes to 83% of total world production in 2015 [65]. The extraction process of this palm oil results in the production of waste in large quantities in the form of POC [66]. The disposal of these can be hazardous for the environment. Thus, it can find its usage as reinforcements in the Al composites [67]. Table 2 shows the chemical compositions of POC.

### Sugarcane Bagasse ash (SCBA)

Bagasse is the waste product obtained after processing of sugarcane for extraction of juice. It is one of the largest agricultural wastes in the world. Many researchers have used this residue due to its versatility but not limited to feedstock, biofuel (ethanol), and paper [68]. The main elements of SCB are hemicellulose, cellulose, wax lignin, and ash [69]. Their presence makes SCB an ultimate material as a reinforcement fiber in the development of new material with exceptional physical and chemical properties [70, 71]. Chandla et al., [72] reinforced varying content of bagasse ash in Al6061/5wt% Al<sub>2</sub>O<sub>3</sub> based composites via stir casting technique and observed an increase in hardness as well as the tensile strength of the composites with increasing bagasse ash content.

### Properties of agro-waste reinforced composites

The structure, properties and processing analysis of various agro-wastes such as rice husk ash, breadfruit seed, corn cob ash, groundnut shell ash, bamboo leaf ash, coconut shell ash, maize stalk ash, lemongrass ash, aloe vera, and SiO<sub>2</sub> (agro-based)-reinforced Al composites are shown in Table 3. The effect of these agro-based reinforcements on the microstructure, mechanical and tribological properties of Al composites also discussed in the following sub-sections.

### Microstructure of agro-waste reinforced composites

Oghenevweta et al. [89] carried out the microstructural analysis of the developed Al–Si–Mg-based composites reinforced with carbonized maize stalk waste by a stir casting technique. They claimed that a uniform distribution of reinforcements was obtained along the grain boundaries resulting grain refinement thereby forming better bonding. This in turn improved tensile strength and hardness value with the increased percentage of carbonized maize stalk. However, it was also mentioned that the impact energy, elongation and densities slightly decreased. Atuanya et al. [90] studied the influence of breadfruit seed hull ash as reinforcement on the microstructures and mechanical properties of Al–Si–Fe based composites fabricated via stir casting technique. The reduction in the grain size of the matrix and good interfacial bonding between the matrix and the reinforced particles was observed as evident from Fig. 1, leading to improvement in the hardness and strength; however, there was a slight decrease in impact energy.


Further, Saravanan and Kumar [91] observed good dispersibility of RHA in AlSi10Mg matrix causing improvement in the hardness, compressive strength, and tensile strength. The homogeneous dispersion of reinforced particles throughout the Al matrix and grain refinement is shown in Fig. 2. Gladston et al. [92] noticed that there was a unique distribution of RHA particles into AA6061 alloy matrix, developed through compo-casting technique leading to increased ultimate tensile strength and microhardness of the AMC's. This behavior can be attributed to the uniform distribution of RHA particles in the matrix material as shown in Fig. 3.

Jerin et al. [93] found a uniform dispersion of lemon grass ash (LGA) particles in the composite matrix manufactured via a compo-casting technique. The microhardness and the tensile properties of the composites were also improved. Furthermore, Kumar and Birru [94] observed that the Al composites reinforced with BLA exhibited superior properties due to their effective bonding with the matrix alloy and homogeneous distribution of BLA particles in composites. However there was reduction in the density and increased porosity values with increase in mass fraction of BLA particles. Also, Venkatesh et al. [95] studied microstructural characteristics of GSA and


**Table 3** Agro-waste reinforced Al composites

| Reinforcement                  | Matrix    | Study (Properties)                          | Characterization and testing                           | Fabrication technique    | Reference year |
|--------------------------------|-----------|---|--|--------------------------|----------------|
| Palm kernel shell              | AA 6063   | -Microstructure<br>-Physical<br>-Mechanical | -XRF<br>-XRD<br>-Density,<br>-Porosity<br>-SEM<br>-EDX | Stir-casting             | [73]<br>2020   |
| Rice husk (Si-compound)        | AA 6063   | -Tribological                               | -Coefficient of friction (CoF)<br>-Wear rate           | Two-step stir-casting    | [74]<br>2020   |
| Aloe vera ash                  | AA7075-T6 | -Mechanical<br>-Tribological                | -CoF<br>-Wear rate<br>-UTS                             | Friction stir processing | [75]<br>2020   |
| RHA                            | AA7075    | -Physical and<br>-Morphological             | -SEM<br>-Density<br>-Porosity<br>-Hardness             | Powder metallurgy        | [76]<br>2020   |
| Rice husk (silica)             | AA7075    | -Physical                                   | -Density<br>-Porosity<br>-Hardness                     | Powder metallurgy        | [77]<br>2020   |
| BLA-SiC                        | AA 6063   | -Mechanical                                 | -Stress-strain   | Stir-casting             | [78]<br>2020   |
| Rice husk(silica) and graphite | Al        | -Physical<br>- Mechanical<br>- Thermal      | -FESEM<br>-FTIR<br>-XRD<br>-Hardness<br>-Density       | Powder metallurgy        | [79]<br>2020   |
| RHA                            | AA6061    | -Tribological                               | -Wear rate   | Friction stir processing | [80]<br>2020   |
| RHA                            | AA6061    | -Physical<br>- Mechanical                   | -SEM<br>-Density<br>-Hardness                          | Two-step casting         | [81]<br>2020   |
| Pine leaf ash                  | Al        | -Tribological                               | -SEM<br>-Hardness<br>-Wear rate                        | Friction stir processing | [82]<br>2020   |
| RHA                            | Al6061    | -Mechanical                                 | -Hardness  | Stir-casting             | [83]<br>2019   |
| Bagasse ash and graphite       | AA7075    | -Physical<br>-Mechanical                    | -Density<br>-Hardness<br>- tensile                     | Squeeze casting          | [84]<br>2020   |
| CSA and SiC                    | LM24      | -Microstructure<br>-Tribological            | -XRD<br>-Wear rate                                     | Squeeze casting          | [85]<br>2019   |
| RHA -fly ash                   | A356      | -Tribological                               | -Wear rate<br>-Wear mechanism                          | Double stir-casting      | [86]<br>2019   |
| Bagasse ash and SiC            | Al 5056   | -Tribological                               | -Wear rate<br>-Hardness                                | Stir-casting             | [87]<br>2019   |
| RHA                            | AA7075    | -Microstructure<br>-Mechanical              | -SEM<br>-EDX,<br>-Microhardness                        | Friction stir processing | [88]<br>2018   |

**Figure 1** The microstructure of aluminum alloy reinforced with, **a** 2 wt%, **b** 6 wt% and **c** 8 wt%, breadfruit seed hull ash. Reproduced with permission from [90].

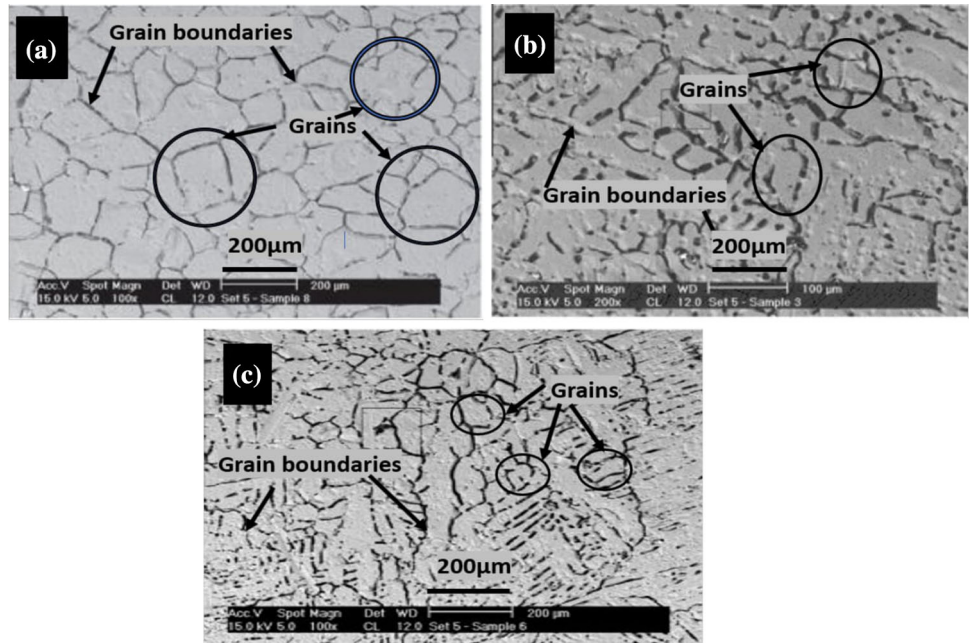


**Figure 2** SEM images showing microstructure of **a** AlSi<sub>10</sub>Mg, **b** AlSi<sub>10</sub>Mg + 6% RHA, **c** AlSi<sub>10</sub>Mg + 12% RHA composites. Reproduced with permission from [91].

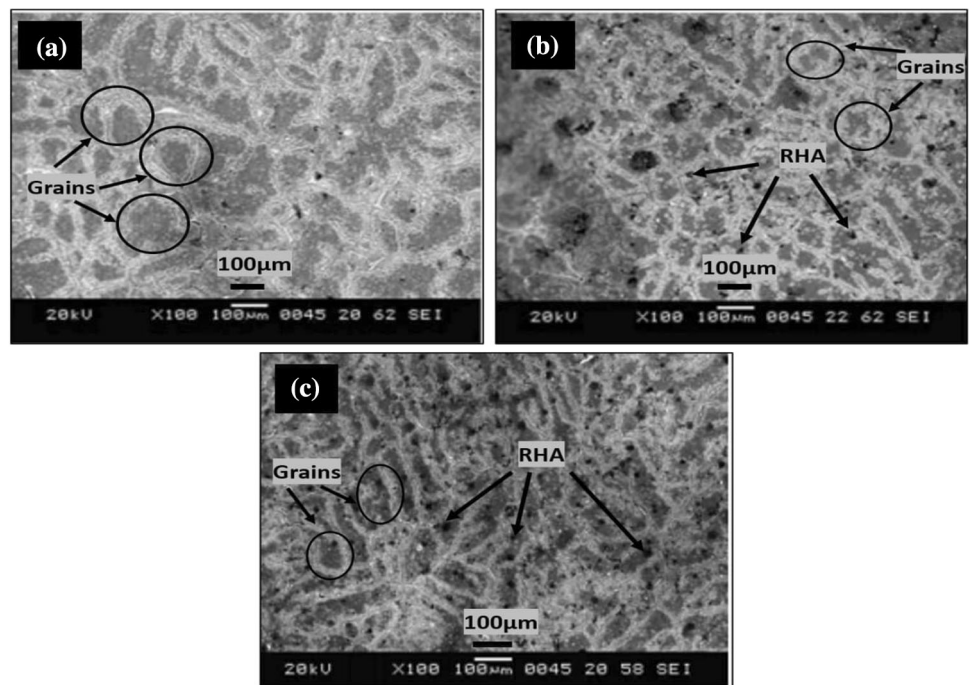

boron carbide reinforced Al composites developed via squeeze casting technique and revealed the uniform distribution and better bonding of reinforcements with the matrix materials forming clear interfaces in the reinforced composite, however, agglomeration and cluster formation takes place with increased GSA particles.

### Mechanical properties of agro-waste reinforced composites


Many researchers studied the influence of these agro-waste reinforcements on the mechanical properties of Al based composites. Ahamed et al. [96] observed the decrease in densities of Al composites reinforced with RHA fabricated by stir casting technique;

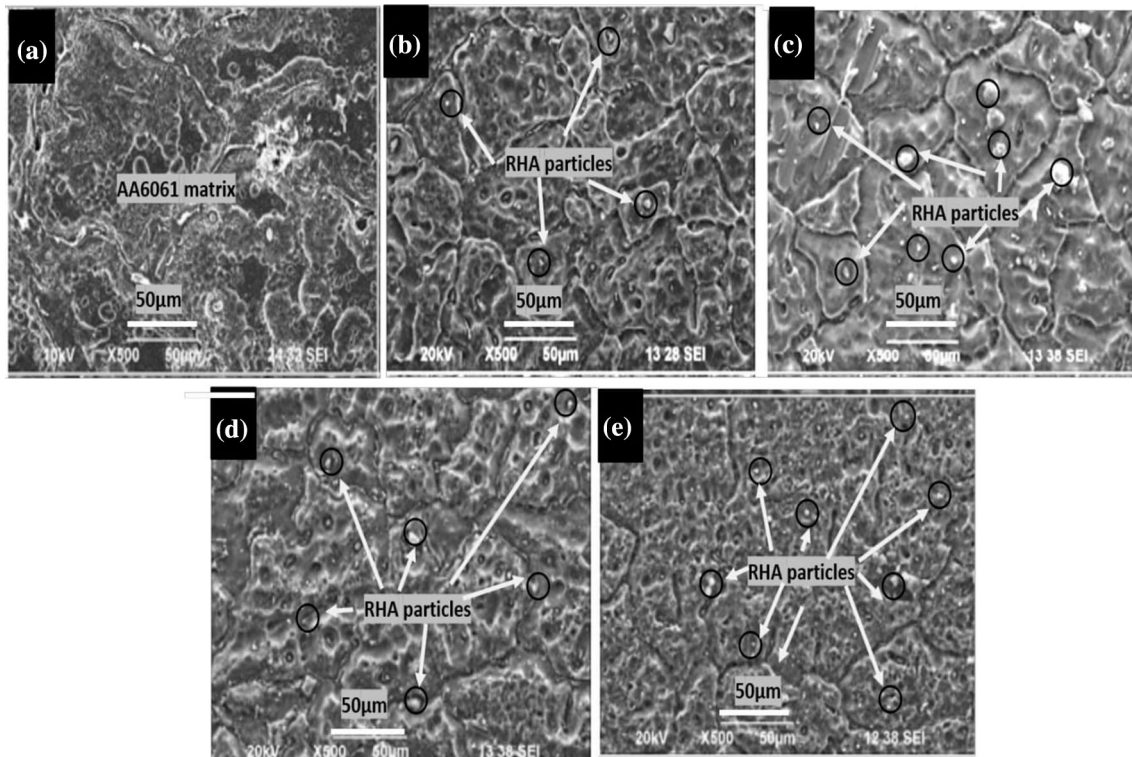

**Figure 3** SEM images of AA6061 composites with varying RHA content, **a** 0wt%, **b** 2wt%, **c** 4wt%, **d** 6wt%, and **e** 8wt%. Reproduced with permission from [92].

however, yield strength, ultimate strength, and hardness of the composites increased, as shown in Fig. 4. Agro-waste reinforcements are found to reduce densities of composites without conceding the mechanical properties of composites. Varalakshmi and Kumar [97] fabricated Al 6061-coconut shell ash metal matrix composites using a stir casting technique. There was an increase in the ultimate tensile strength and hardness of the composites even though the density of the CSA reinforced composites decreased. It has been observed by the researchers that small percentages of ceramic reinforcements when replaced by agro-waste particles in the Al composites there was a significant improvement in properties.


Prasad et al. [98] employed two step stir casting technique for the fabrication of Al composites reinforced with RHA and SiC particulates and reported an increase in hardness, ultimate tensile strength, and yield strength with an increase in weight fraction however the densities decreased. Although double stir casting techniques allow improvement in

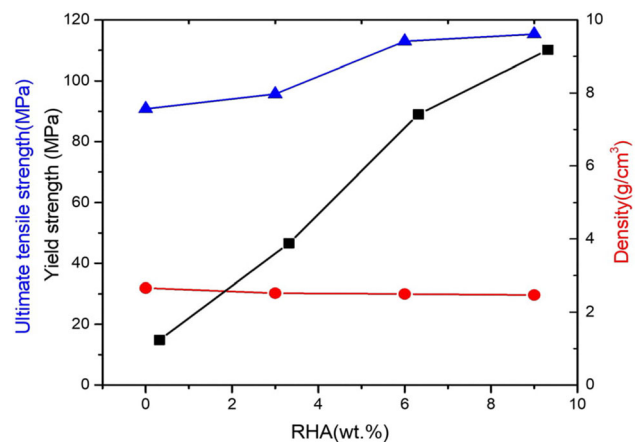

**Figure 4** Variation of yield strength, ultimate tensile strength, and density with the wt % of RHA in Al composite. Reproduced with permission from [96].

wettability, even though it remains still a challenge to overcome. However, this problem can be solved by using the vortex method for the development of AMC's. Gireesh et al. [99] developed aloe vera, and



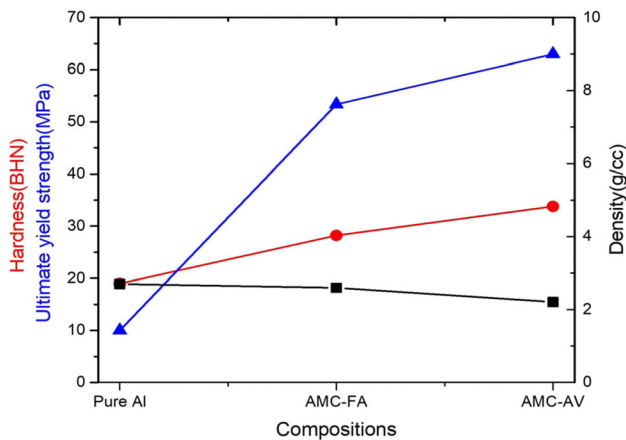

**Figure 5** Comparison of mechanical properties, ultimate yield strength (MPa), hardness (BHN), and density (g/cc) of AMC's on the addition of fly ash (FA) and aloe vera (AV). Reproduced with permission from [99].

fly ash reinforced AMC's and compared their mechanical properties. They concluded that the mechanical properties improved more by the addition of aloe vera as compared to fly ash, as evident from Fig. 5. Devanathan et al. [100] fabricated AMC's reinforced with CSA and FA via stir casting technique and observed an improved hardness, tensile strength and percentage elongation of the composites with increase in weight percentage of CSA.

Gupta et al. [101] studied mechanical properties of RHA and  $Al_2O_3$  reinforced Al/Si12 composites and observed an improvement in the microhardness, tensile strength, and flexural strength of the composites. Moreover, Shankar et al. [102] fabricated AlSi10Mg composites reinforced with SCBA particles via stir casting process and observed an increase in their hardness, tensile, and impact strength, however, their ductility decreased with increase in the weight percentage of SCBA. Table 4 showed the effect of agro-based reinforcements on the mechanical properties of Al composites. The hardness, tensile strength, yield strength, impact strength and compressive properties were found to increase in the agro-based content however only upto certain limit.

### Tribological properties of agro-waste reinforced composites

An attempt has been made by Gupta et al. [101] to develop Al-Si12 matrix composites reinforced with RHA and  $Al_2O_3$  and evaluate their tribological

performance. There was an improvement in the weight loss with increase in weight percentages of reinforcements as shown in Fig. 6. Also, Shaikh et al. [112] fabricated Al-based composites reinforced with SiC and RHA using the powder metallurgy technique. The study revealed the decrease in hardness and wear loss of the composites with an increase in RHA contents up to 10%. However, the corrosion and wear study by Kanayo and Olubambi [113] revealed that there was an increment in both the corrosion as well as wear rate by increasing the percentage of RHA and alumina reinforced Al-Mg-Si composites. The wear behavior was observed changing from abrasive wear to both the adhesive and abrasive wear with increase in RHA content.

Bodunrin et al. [114] developed silica sand, and BLA reinforced Al composites via stir casting technique. The porosity measurement and study of wear performance concluded that the composites became lesser denser with increasing BLA content. There was also a reduction in hardness; however, composite with silica sand and BLA reinforcements had higher wear resistance than single reinforced Al6063-silica sand composite. In addition, Alaneme et al. [115] also fabricated Al-Mg-Si alloy matrix composites with RHA and SiC as reinforcements by double stir casting technique and observed improvement in corrosion resistance, coefficient of friction and wear behavior of composites. Prasad and Shoba [116] investigated the dry sliding wear behavior of AMC's reinforced with RHA and SiC particulates fabricated via vortex method. The study revealed that the reinforced composites exhibited higher wear resistance as compared to unreinforced composites. Deshmukh and Pathak [117] studied the influence of varying wt% of rice husk based  $SiO_2$  on the mechanical and wear properties of AMC developed by stir casting technique. It was concluded that the wettability of the matrix with reinforcement was improved due to the addition of Mg during the stir casting process, and better wear resistance was achieved due to the higher Vickers hardness.

Kumar and Birru [118] studied the tribological properties of BLA reinforced Al composites and observed decreased wear rate values with increased BLA content in the composites. Similarly, Bodourin et al. [119] reinforced BLA in Al6063 alloy matrix and found an improvement in the hardness and the wear resistance of the material. Furthermore, Shankar et al. [102] evaluated the tribological properties of SCBA

**Table 4** Properties of agro-waste reinforced aluminum composites

| Compositions           | Hardness                | Tensile strength (MPa) | Compressive strength (MPa) | References (Year) |
|------------------------|-------------------------|------------------------|----------------------------|-------------------|
|                        | Brinell hardness (BHN)  |                        |                            |                   |
| A-356.2/2wt.%RHA       | 77                      | 175                    | 233                        |                   |
| A-356.2/4wt.%RHA       | 83                      | 239                    | 261                        | [103] (2016)      |
| A-356.2/8wt.%RHA       | 84                      | 278                    | 268                        |                   |
|                        | (VHN)                   |                        |                            |                   |
| Al6063                 | 58                      | 135                    | 154                        | [104]             |
| Al6063/3GSA            | 60                      | 138                    | 188                        | (2015)            |
| Al6063/6GSA            | 65                      | 152                    | 200                        |                   |
| Al6063/9GSA            | 67                      | 156                    | 212                        |                   |
| Al6063/12GSA           | 68                      | 147                    | 240                        |                   |
|                        | Yield strength (MPa)    |                        |                            |                   |
| Al-Si-Mg/10SiC         | 93                      | 185                    | 144                        |                   |
| Al-Si-Mg/9SiC/1CCA     | 91                      | 182                    | 142                        |                   |
| Al-Si-Mg/8SiC/2CCA     | 90                      | 174                    | 136                        | [105] (2014)      |
| Al-Si-Mg/7SiC/3CCA     | 86                      | 170                    | 133                        |                   |
| Al-Si-Mg/6SiC/4CCA     | 81                      | 162                    | 126                        |                   |
|                        | Impact Energy (j)       |                        |                            |                   |
| Al                     | 38                      | 55                     | 13                         |                   |
| Al + 3CSA + 5 SiC      | 40                      | 120                    | 11.5                       | [106] (2017)      |
| Al + 5CSA + 5 SiC      | 43                      | 122                    | 9.5                        |                   |
| Al + 10CSA + 5 SiC     | 45                      | 125                    | 8.5                        |                   |
|                        | Yield strength (MPa)    |                        |                            |                   |
| AA6061                 | 130                     | 120                    | 98                         |                   |
| AA6061/1.5SiC          | 140                     | 132                    | 102                        |                   |
| AA6061/0.75SiC/BLA     | 185                     | 154                    | 128                        | [107] (2018)      |
| AA6061/0.75SiC/NLA     | 158                     | 140                    | 115                        |                   |
| AA6061/0.75SiC/TLA     | 170                     | 137                    | 120                        |                   |
|                        | Rockwell Hardness (HRA) |                        |                            |                   |
| Al-Si-Mg               | 50                      | 100                    | 78                         |                   |
| Al-Si-Mg/6SiC          | 57                      | 135                    | 115                        |                   |
| Al-Si-Mg/4.5SiC/1.5GSA | 55                      | 130                    | 105                        |                   |
| Al-Si-Mg/3SiC/3GSA     | 53                      | 125                    | 100                        | [18] (2018)       |
| Al-Si-Mg/1.5SiC/7.5GSA | 52                      | 120                    | 90                         |                   |
| Al-Si-Mg/6GSA          | 51                      | 115                    | 86                         |                   |
| Al-Si-Mg/10SiC         | 64                      | 160                    | 130                        |                   |
| Al-Si-Mg/7.5SiC/2.5GSA | 63                      | 150                    | 120                        |                   |
| Al-Si-Mg/5SiC/5GSA     | 58                      | 147                    | 118                        |                   |
| Al-Si-Mg/2.5SiC/7.5GSA | 56                      | 140                    | 117                        |                   |
| AlSiMg10GSA            | 5                       | 136                    | 115                        |                   |
|                        | Energy absorbed(j)      |                        |                            |                   |
| Al7075                 | 127                     | 114                    | 0.6                        |                   |
| Al7075/3CSFA           | 134                     | 121                    | 1.3                        |                   |


Table 4 continued

| Compositions                                  | Hardness           | Tensile strength (MPa) | Compressive strength (MPa) | References (Year) |
|---|--------------------|------------------------|----------------------------|-------------------|
| Al7075/3B <sub>4</sub> C/ 3CSFA               | 142                | 135                    | 1.8                        |                   |
| Al7075/6B <sub>4</sub> C/ 3CSFA               | 149                | 155                    | 2.1                        | [108] (2018)      |
| Al7075/9B <sub>4</sub> C/ 3CSFA               | 155                | 189                    | 2.3                        |                   |
| Al7075/12B <sub>4</sub> C/ 3CSFA              | 169                | 177                    | 2                          |                   |
|   | (HRA)              |                        | Young's modulus (GPa)      |                   |
| Al 6063 Alloy                                 | 62                 | 110                    | 15                         |                   |
| Al6063/2 SiO <sub>2</sub> (rice husk derived) | 65                 | 130                    | 25                         |                   |
| Al6063/4 SiO <sub>2</sub> (rice husk derived) | 67                 | 150                    | 37                         | [109] (2018)      |
| Al6063/6 SiO <sub>2</sub> (rice husk derived) | 69                 | 160                    | 43                         |                   |
| Al6063/8 SiO <sub>2</sub> (rice husk derived) | 72                 | 200                    | 50                         |                   |
|   | (BHN)              |                        | Elongation%                |                   |
| A6061   | 152                | 6                      | 2                          |                   |
| A6061/2RHA                                    | 170                | 6.03                   | 2.4                        | [110] (2020)      |
| A6061/4RHA                                    | 175                | 6.13                   | 2.5                        |                   |
| A6061/6RHA                                    | 178                | 6.23                   | 2.7                        |                   |
| A6061/8RHA                                    | 188                | 6.34                   | 2.9                        |                   |
|   | (HV)               |                        | Impact strength(J)         |                   |
| Al/1.6RHA(150 μm)                             | 92                 | 100                    | 2.5                        |                   |
| Al/1.6RHA(300 μm)                             | 88                 | 80                     | 5.2                        |                   |
| Al/1.6RHA(600 μm)                             | 85                 | 90                     | 6.8                        | [111] (2020)      |
| Al/0.4graphite/1.6RHA(150 μm)                 | 115                | 130                    | 5.5                        |                   |
| Al/0.4graphite/1.6RHA(300 μm)                 | 96                 | 120                    | 7                          |                   |
| Al/0.4graphite/1.6RHA(600 μm)                 | 105                | 125                    | 8.2                        |                   |
|   | (BHN)              |                        | Impact strength(J)         |                   |
| Al7075/3mica                                  | 107                | 244                    | 8.2                        |                   |
| Al7075/3mica/5RHA                             | 128                | 260                    | 9                          | [32] (2020)       |
| Al7075/3mica/10RHA                            | 139                | 268                    | 8.5                        |                   |
| Al7075/3mica/15RHA                            | 146                | 262                    | 7.8                        |                   |
| BLA: Bamboo leaf ash                          | CCA: Corn cob ash  |                        | TLA: Tamarind leaf ash     | FA: Fly ash       |
| RHA: Rice husk ash                            | NLA: Neem leaf ash |                        | GSA: Groundnut shell ash   | AV: Aloe vera     |
| CSFA: Coconut shell fly ash                   |                    |                        |                            |                   |

particles reinforced AlSi10Mg alloy matrix composites. The wear rate and coefficient of friction(COF) of the developed composites decreased with increase in the weight percentage of ash content, however, it increased on increasing applied load. Also, Lakshmiathan and Prabu [120] developed Al(6061) alloy composites reinforced with CSA by stir casting technique and observed that the wear rate decreases upto 6wt % of CSA, on further addition their values

increased, however, COF increased on addition of CSA as evident from Fig. 7.

Prasad and Krishna [121] observed an increase in the wear rate and the COF of A356.2 matrix composites on addition of RHA. Furthermore, Panda et al., [122] investigated the COF and wear rate of AMC reinforced with CSA. The COF as well as wear rate decreased with increased CSA content. Therefore, these agro-waste AMC's also influence the

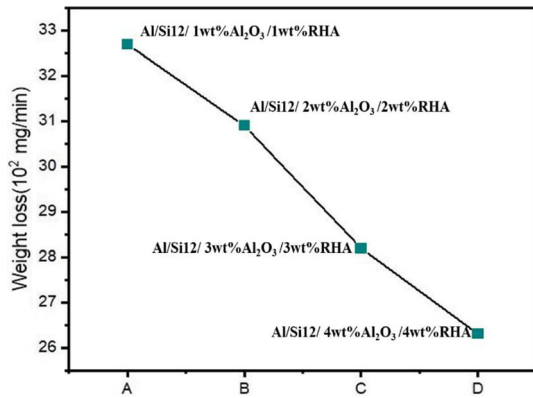



**Figure 6** Weight loss of RHA and Al<sub>2</sub>O<sub>3</sub> reinforced Al/Si12matrix composites at a velocity of 1.5 m/s at a load of 9.8 N and sliding distance of 1000 m. Reproduced with permission from [101].

tribological properties of the composites [123, 124]. From the literature review, it can be seen that the researchers have used agro-waste ash as reinforcements in the Al matrix. This ash has low strength, thus improves the mechanical properties of Al matrix insignificantly. There is a need to improvise the characteristics of agro-waste materials by carrying out various processing techniques in order to get better reinforcing material out of them. Table 5 shows the effect of agro-waste reinforcements on the

tribological properties of AMC's developed by various techniques. It reveals that the hardness of composites increase while as their wear rates decrease on addition of agro-based reinforcement, however, COF increases in certain cases. These properties are favorable for several applications. Since agro-wastes have potential in providing high strength, cost-effective, and environmental-friendly material, their improvement can enhance properties of Al composites to greater degrees; therefore, these cannot be ignored and need further investigation.

### Limitation of agro-based AMC's

The issue of wettability and the interfacial bonding between the reinforcement and Al matrix is a matter of concern in case of agro-based reinforcements that forms solid liquid interface during fabrication process, especially when liquid state or semi-liquid state manufacturing process is employed. The dispersion of agro-wastes particles with Al matrix material is another important issue. The strength of the reinforced composites depends upon the wetting action between the agro-based reinforcements and Al matrix. Many researchers have used various techniques to improve this, but still requires more extensive research to overcome this problem. Although agro-based reinforcements have proven to

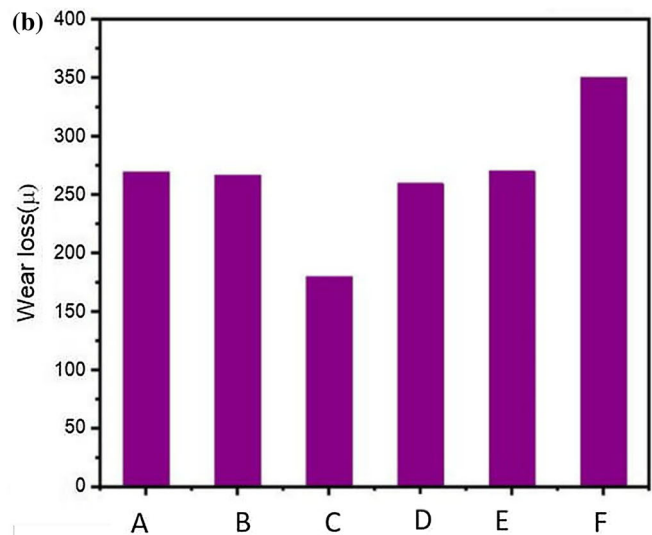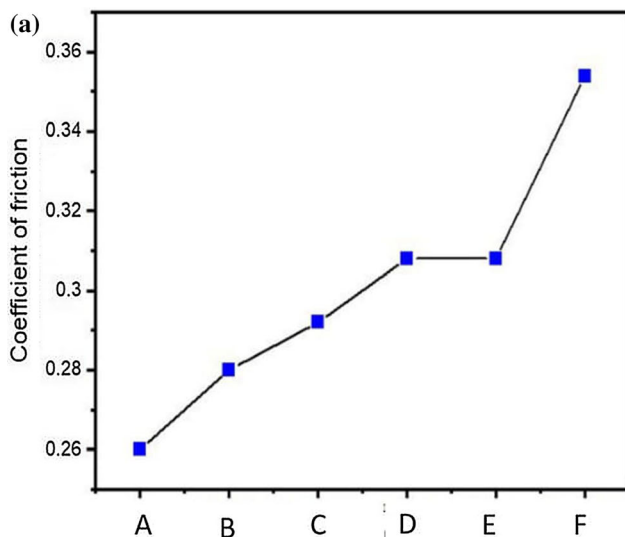

**Figure 7** Effect of CSA content on the **a** Coefficient of friction, and **b** wear loss of composites at under constant sliding distance, sliding velocity and load of 1000 m, 1.5 m/s, 10 N,

respectively (A, B, C, D, E, and F indicate 0, 3, 6, 9, 12 and 15 wt.% CSA, respectively). Reproduced with permission from [120].

**Table 5** Tribological properties of agro-based aluminum composites


| Compositions                      | Hardness (HV)     | Wear rate (gms)        | Coefficient of friction    | Processing technique | Ref. (Year) |
|-----------------------------------|-------------------|------------------------|----------------------------|----------------------|-------------|
| Al                                | 48                | 0.0531                 | 0.34                       |                      |             |
| Al + 3.4wt.%SiC                   | 66                | 0.0115                 | 0.298                      | Stir- casting        | [125]       |
| Al + 0.9 wt.%JA                   | 59                | 0.015                  | 0.313                      |                      | 2020        |
| Al + 3.4wt.%SiC + 0.9 wt.%JA      | 57                | 0.0165                 | 0.326                      |                      |             |
|                                   |                   | μm                     |                            |                      |             |
| AA7075                            | 115               | 38                     | 0.24                       |                      |             |
| AA7075 + 5 wt.%CSA                | 136               | 42                     | 0.19                       |                      |             |
| AA7075 + 10wt.%CSA                | 162               | 32                     | 0.20                       |                      |             |
| AA7075                            | 115               | 45                     | 0.27                       |                      | [126]       |
| AA7075 + 5 wt.%CSA                | 136               | 48                     | 0.28                       | Stir- casting        | 2019        |
| AA7075 + 10wt.%CSA                | 162               | 38                     | 0.29                       |                      |             |
| AA7075                            | 115               | 55                     | 0.30                       |                      |             |
| AA7075 + 5 wt.%CSA                | 136               | 50                     | 0.36                       |                      |             |
| AA7075 + 10wt.%CSA                | 162               | 49                     | 0.37                       |                      |             |
|                                   |                   | Mm <sup>3</sup> /N-m   |                            |                      |             |
| A7075                             | 60                | $1.8 \times 10^{-4}$   | –                          |                      |             |
| A7075 + 2wt.%B <sub>4</sub> C/RHA | 70                | $1.9 \times 10^{-4}$   | –                          | High vacuum casting  | [127]       |
| A7075 + 4wt.%B <sub>4</sub> C/RHA | 90                | $2 \times 10^{-4}$     | –                          |                      | 2019        |
| A7075 + 6wt.%B <sub>4</sub> C/RHA | 110               | $2.3 \times 10^{-4}$   | –                          |                      |             |
| A7075 + 8wt.%B <sub>4</sub> C/RHA | 127               | $2.4 \times 10^{-4}$   | –                          |                      |             |
|                                   | HRF               |                        |                            |                      |             |
| A356 + 2wt.%LBWA                  | 8.8               | 0.13                   | –                          |                      |             |
| A356 + 4wt.%LBWA                  | 10.9              | 0.12                   | –                          | Stir-casting         | [128]       |
| A356 + 6wt.%LBWA                  | 11                | 0.166                  | –                          |                      | 2020        |
| A356 + 8wt.%LBWA                  | 14.2              | 0.11                   | –                          |                      |             |
| A356 + 10wt.%LBWA                 | 15.3              | 0.034                  | –                          |                      |             |
| AA7075-T651(20 N)                 | –                 | 0.832                  | 0.4680                     |                      |             |
| FSPed AA7075- T651(20 N)          | –                 | 0.7052                 | 0.4568                     | Stir casting         |             |
| AA7075- T651/WFA (20 N)           | –                 | 0.646                  | 0.4181                     | and                  | [129]       |
| AA7075-T651(50 N)                 | –                 | 0.113                  | 0.1969                     | Friction stir        | 2019        |
| FSPed AA7075- T651(50 N)          | –                 | 0.0575                 | 0.1320                     | processing           |             |
| AA7075- T651/WFA (50 N)           | –                 | 0.0403                 | 0.1119                     |                      |             |
| AA7075-T651/PKSA(20 N)            | –                 | 0.7051                 | 0.4507                     | Friction stir        | [130]       |
| AA7075-T651/PKSA(50 N)            | –                 | 0.0277                 | 0.1158                     | processing           | 2019        |
| Al6061(RT)                        | –                 | $0.2 \times 10^{-3}$   | –                          |                      |             |
| Al6061 + RHA(RT)                  | –                 | $0.15 \times 10^{-3}$  | –                          |                      |             |
| Al6061 + FA(RT)                   | –                 | $0.09 \times 10^{-3}$  | –                          | Casting              |             |
| Al6061(150°)                      | –                 | $0.14 \times 10^{-3}$  | –                          | And                  |             |
| Al6061 + RHA (150°)               | –                 | $0.064 \times 10^{-3}$ | –                          | Forging              | [131]       |
| Al6061 + FA (150°)                | –                 | $0.048 \times 10^{-3}$ | –                          |                      | 2019        |
| Al6061(Forged)                    | –                 | $0.139 \times 10^{-3}$ | –                          |                      |             |
| Al6061 + RHA(Forged)              | –                 | $0.130 \times 10^{-3}$ | –                          |                      |             |
| Al6061 + FA(Forged)               | –                 | $0.09 \times 10^{-3}$  | –                          |                      |             |
| JA-Jute ash                       | RHA-Rice husk ash |                        | LBWA-Locust bean waste ash |                      |             |
| RT -room temperature              |                   | WFA-Wood fly ash       |                            |                      | FA-fly ash  |

improve the morphology, mechanical and tribological properties of AMC's as mentioned in the previous sections however, limitations with respect to some properties are also observed. Arora and Sharma [132] developed RHA and SiC reinforced Al composites via stir casting technique and observed that with the increasing of RHA content, hardness and tensile strength decreased with the increment in wear rate. Similar trends were observed with the addition of BLA [133] and CCA [105] in Al–Mg–Si matrix material.

The incorporation of agro-based reinforcements also reduces the elongation at break thus affecting the elasticity of material. Hossain et al., [134] noticed decrease in elongation at break with increase in RHA content in Al alloy. Also, Sarkar et al., [135] found that the increasing RHA content in Al composites reduces their hardness, tensile strength as well as elongation at break. The limitations were not only specific to mechanical properties but were also observed for tribological properties of the resultant agro-based Al composites. Kamal and Siddiqui [45] reported that there was a decline in the hardness, and increment in the wear rate of the mustard husk ash (MSH) reinforced Al composites developed by powder metallurgy technique, with increase in MHS content. The coefficient of friction was found to be higher with higher content of CSA in Al matrix composite due to more CSA particles at the interface causing abrasive wear as a result of more rubbing action [122]. However, agro-wastes aluminum composites have very limited data on the utilization of additive manufacturing (AM) approach for the development of new composite that pose other challenges thus, it stresses importance of such amazing technique in verifying new set of results for advanced and wider applications of this material.

### Fabrication of agro-based AMC's

AMC's are generally developed through two routes, liquid and solid route. The liquid route involves stir casting, friction stir processing, and compo-casting techniques, while solid route includes powder metallurgy technique. The brief idea about these techniques are described as follows:

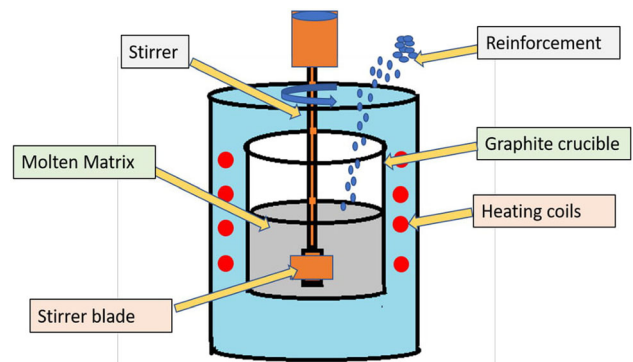

**Figure 8** Schematic diagram of stir casting technique.

### Stir casting technique

Owing to the flexibility, simplicity, and economic viability of the technique, it is mostly considered for fabricating AMC's [37, 136]. Figure 8 shows the stir casting technique that is commonly used for aluminum-composite fabrication. Even though concerns of uniform distribution of reinforcing particles, wettability, porosity, interfacial reactions particle agglomeration, isolation, and formation of unwanted secondary phases have been observed, however, the methods to overcome them have also been reported [136, 137]. The optimization of mixing parameters such as stirring speed, rotation of stirrer, blade angle to stirrer axis can lead to reduced particle clustering and segregation [138, 139], and also can be further reduced by employing a two-step stir casting technique [140, 141].

In stir casting technique, it is hard to get proper dispersion of reinforced particles due to the specific gravity of reinforcements that allow them to settle at the bottom during the process of fabrication. Numerous researchers have employed stir casting method for developing Al composites reinforced with agro-waste as mentioned in Table 6. The two-step stir casting technique was employed by researchers to improve the wettability of agro-based reinforcement in Al matrix thereby improving the properties of composites [142]. Also, wettability between the Al matrix and reinforcing materials was improved by coatings the reinforcing materials [143] or by using wetting agents such as magnesium and borax [144]. Another problem of interfacial reaction and formation of unwanted secondary phases that deteriorate the properties of the composites can be avoided by choosing reinforcing materials that inhibit the

**Table 6** Agro-waste reinforced aluminum composites and their fabrication techniques

| Agro-based reinforcement    | Composition            | Fabrication technique         | References |
|-----------------------------|------------------------|-------------------------------|------------|
| Rice husk ash (RHA)         | Al-6061/SiC/RHA        | Stir casting process          | [135]      |
|                             | AA6351/SiC /RHA        | Stir casting technique        | [147]      |
|                             | AA6082/ B4C/RHA        | Stir casting technique        | [148]      |
|                             | Al64430/SiC/RHA        | Stir casting technique        | [149]      |
|                             | Al6061/TiC/RHA         | Stir casting technique        | [150]      |
| Coconut shell ash(CSA)      | Al-Si-Fe/ CSA          | Double stir-casting technique | [151]      |
|                             | Al-Si-Fe alloy/CSA     | Double stir-casting technique | [152]      |
|                             | Al7079/CSA             | Stir casting technique        | [153]      |
| Bamboo char(BC)             | Al-6061/ B4C/BC        | Stir casting technique        | [154]      |
| Groundnut shell ash         | A356/ GSA              | Stir casting technique        | [155]      |
| Sugarcane bagasse ash(SCBA) | AlSi10Mg/SCBA          | Stir casting technique        | [156]      |
|                             | Al-7%Si/BA             | Stir casting technique        | [157]      |
|                             | Al-7075/ graphite/SCBA | Stir casting technique        | [158]      |
| Melon shell ash(MSA)        | Al-12%Si/MSA           | Stir casting technique        | [159]      |
| Bean pod ash(BPA)           | Al/BPA                 | Stir casting technique        | [160]      |
| Palm Kernel shells (PKS)    | Al6063/PKS             | Stir casting technique        | [161]      |
| Bagasse ash (BA)            | Al/ Graphite/ BA       | Friction stir processing      | [162]      |
|                             | Al/Boron nitride/BA    | Friction stir processing      | [163]      |


interfacial reaction, such as boron carbide and alumina [145, 146]. The porosity can be controlled by optimizing several process parameters during casting process of AMC's. Various researchers have developed Al composites with agro-based reinforcements via stir casting techniques and the fabricated composites exhibiting improved microstructure as well as better properties as evident in Table 6.

### Compo-casting technique


Although fabrication of composites by stir casting is highly discouraged owing to poor wettability of ceramic particles during the fabrication process [164]. Numerous methods were anticipated to improve the wettability by the addition of wettability agents [165], by preheating [166], oxidation [167], and coating [168]

of ceramic reinforcements. However, such methods result in an increase in the overall production cost. Thus, a technique in which casting temperature is lowered and ceramic particles are added when the aluminum is in a semi-solid state. This is the most economically viable technique for enhancing wettability and is called as compo-casting or slurry casting [169] as demonstrated in Fig. 9. Compo-casting is widely employed for the fabrication of composites due to its low cost, easiness, close to net shape, and large-scale production [170]. In addition, this technique has been successively employed for the fabrication of various agro-based AMC's [171]. Several investigations have revealed improved wettability and uniform distribution of ceramic particles in the AMC's produced through compo-casting compared to stir casting. Therefore, compo-casting is regarded

**Figure 9** Schematic diagram of compocasting technique.

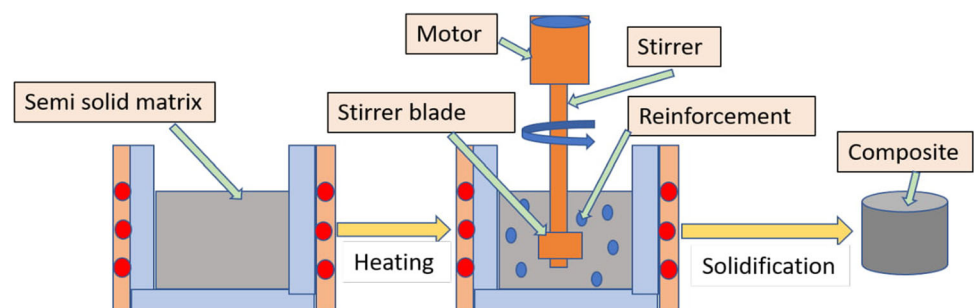

**Figure 10** Powder metallurgy process.

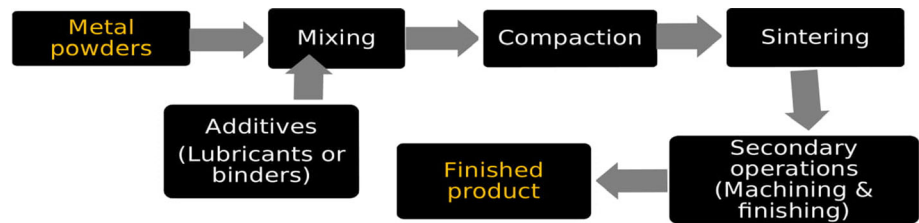


as the most appropriate method for the development of low-cost composites efficiently. Some researchers have used this technique in the fabrication of aluminum-based agro-waste composites to overcome the issue of wettability encountered in the stir casting technique.

### Powder metallurgy technique

Powder metallurgy technique is a recent preferred technology due to its various benefit of fabricating composites to near net shape characteristics, controlled homogeneity of structure, highly efficient use of the initial metals (95–98%), high productivity, a unique capability of producing porous materials, minimum consumption of energy and raw materials. Powder metallurgy is a recently growing technique advantageous for composites with ceramic and other reinforcement [172]. In this process, powders are transformed into materials through various methods, as shown in Fig. 10. It enables uniform distribution of reinforcements throughout the composite substrate. Powder metallurgy involves multiple steps such as mixing of powders, compaction, and sintering, as shown in Fig. 10. The process is not confined to any material, and it can be used to fabricate composites of


a wide range of materials [173]. This technique results in the development of products of near-net-shape that does not require machining after fabrication. This technique is mostly preferred due to its advantages over other techniques as particle agglomeration, low wettability, and formation of detrimental phases, which are some of the complications linked with liquid metallurgy route are easily evaded [174]. Yusoff et al., [175] developed Palm shell activated carbon-reinforced aluminum composites via powder metallurgy technique and investigated the effect of factors such as applied load, sliding distance and reinforcement content (wt.%) on the wear properties analysis of variance (ANOVA). The improvement of wear resistance was found to be strongly dependent on the reinforcement content.

Additive manufacturing (AM) can be considered as an advanced powder metallurgy process if powder is used as input raw material. It is the process of making objects from 3D model data by joining materials mostly layer upon layer [176]. This technology can be applied to develop agro-wastes reinforced composite parts. The two basic parameters of metal AM process are the input raw material and energy source used to form the part [177]. Input raw material includes metal powder, whereas wire and

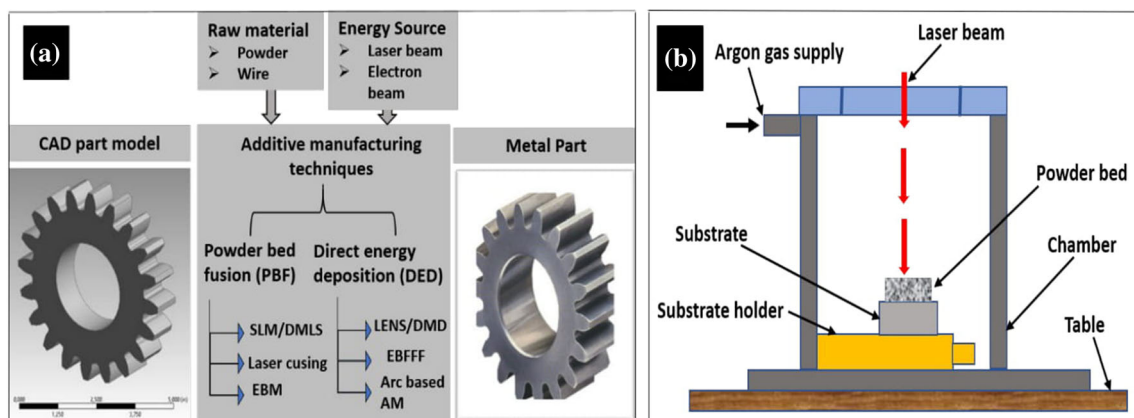

**Figure 11** a Additive manufacturing processes, b Schematic diagram of apparatus for power fusion technology proposed for agro-based AMC's fabrication.



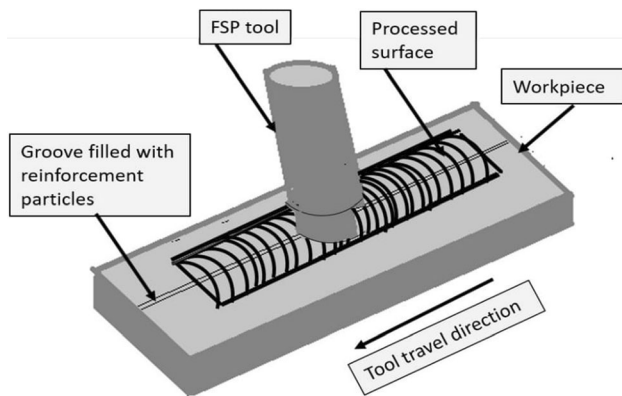

**Figure 12** Schematic diagram of friction stir casting technique.

laser or electron beam can be utilized as energy source as shown in Fig. 11(a). AM machine requires CAD model of the part in the stereo lithography file format. Specialized slicing software then slices this model into number of cross-sectional layers. AM machine builds these layers one by one to manufacture complete part [178]. Thickness of these layers depends on the type of raw material and the AM process used to manufacture the finished part. Metal AM processes can be developed by two categories: Powder-bed fusion (PBF) and Directed energy deposition (DED) AM. In PBF as illustrated by Fig. 11(b), the thermal energy selectively fuses regions of powder bed to form the final composite part [176]. The PBF approach involves processes selective laser sintering/melting (SLS/SLM), laser curing and electron beam melting (EBM), etc. In DED, thermal energy is used to fuse materials (powder or wire form) by melting as they are being deposited [176]. Although this technology has been applied by the researchers for the development of the Al alloys (SLM and DMLS) [179, 180] and AMC's (DMLS process) and studied their microstructure, properties and wear behavior [181–183] but it is yet not utilized for the development of agro-based AMC's. This technology can find huge potential in this area thus, needs to be explored further.

### Friction stir processing

Friction stir processing is a unique technique that modifies the surfaces and effects the surface of the composites by transforming them into a more homogeneous microstructure and thus improves their properties. This technique as shown in Fig. 12 has benefits over stir casting, and powder metallurgy

techniques as these techniques result in an increase in stiffness and strength at the expense of toughness and ductility. Friction stir processing results in the development of surface metal matrix composites (SMMC's) with higher surface hardness [184, 185] and enhanced creep resistance while retaining the toughness and ductility of the metallic substrates [186]. This technique improves the reinforcing particulate distribution in the composites. It has been employed as a post-fabrication process on the AMC's fabricated by powder metallurgy route in order to improve their properties [187]. This technique was also used to develop nanocomposites surfaces on metallic substrates [188].

This technique has made fabrication of bulk MMC's possible [189, 190], but it requires further research work in order to get adequate information for commercializing the process. FSP technique was adopted by Dinaharan et al. [191] to fabricate rice husk reinforced Al6061 composites. The morphological characterization revealed the absences of agglomerations or segregations. Moreover, increment in tensile strength from 220 to 285 MPa was also reported. Also, Fatchurrohman et al. [192] studied the effect of parameters of FSP on the microstructure and microhardness of Al6061 based RHA-reinforced composites and thus, found the optimum process parameters at which the composites exhibited better properties. Abdulmalik and Ahmad [193] fabricated RHA-reinforced Al 6061 based composite by FSP technique, and the composites exhibited homogeneous distribution of reinforcements with increased hardness values.

### Research Gap

From the above literatures we have found the following gaps:

1. There is a scope on improvement of agro-based reinforcements by chemical and heat treatments to replace costly reinforcements like SiC, Al<sub>2</sub>O<sub>3</sub> etc., as the agro-based reinforcements such as rice husk ash, coconut shell ash consists of such elements.
2. More research need to focus on the fabrication techniques that can overcome the challenges of improving the interfacial bonding between the Al matrix and agro-based reinforcements.

3. Optimization of process parameters for the development of agro-based reinforced Al composites with their optimum property attainment have not been studied so far.
4. Study on optimization of wear resistance property for agro-based AMC's at elevated temperature have not been explored yet.
5. Work needs to be focused on the production of high-quality and low-production-cost agro-based AMC's. Technologies such as additive manufacturing need to be explored for the development of components for various applications.

### Challenges and way forward

Presently, the low cost and high-performance engineering components are getting much consideration from material scientists. The replacement of hazardous reinforcement to agro-based has played an important role in improving the sustainability and environmental degradation. Thus, material scientists are paying more attention toward improvement of such reinforcements. In addition, the disposal of such materials otherwise cause environmental issues; thus, their usage as reinforcements can solve this problem. As such, agro-waste based AMC's are potential candidate materials but advancements are still challenging for their efficient utilization as a reinforcement for composite. Some of them are:

1. The microstructure studies of agro-based AMC's fabricated via stir casting route revealed non-homogeneous distribution of reinforcing particles and face the issue of wettability. Accordingly, the agro-based AMC's fabricated by using different techniques can overcome this issue and help in achieving uniform distribution of reinforced particles as well as good bonding between matrix and reinforcing particles. These techniques are compo-casting, vortex method, powder metallurgy, friction stir processing, etc. Additionally, agro-based AMC's and their techniques can be tailored to get the required morphology of the composites with better wettability and bonding strength thereby leading to enhancement of properties.
2. These agro-based reinforcements insignificantly improve the properties of composites thus there arises a need of improving their strength either by their surface modification or by further processing them into better quality reinforcements, such as silica derived from rice husk as compared to rice husk ash can be considered as a better reinforcement.
3. Their potential in improving the wear rates have not been yet explored extensively. Thus, the study of wear properties of these composites requires further investigation at different operating conditions. For e.g., to replace the hazardous lead and asbestos, fiber is used as a friction material in automobile brakes and clutches. In addition, these agro-wastes due to their availability in abundance can also reduce the production cost and thus can led to a reduction in component cost; therefore, we can get a low-cost technology.
4. The reuse and recycle of of the agro-waste material is an issue to be dealt with, thus an appropriate processing route would be the focus of immediate future work. Their remarkable advantages are that they are comparatively cheaper, lightweight, and possess higher strength to weight ratio as compared to ceramic reinforced composites.
5. Lightweight and high strength agro-based AMC's can be used as a replacement of the conventional materials in various applications. However, more investigation of the potential of agro-waste is crucial, focusing on optimizing the production process for obtaining better reinforcing materials and determining the optimum processing parameters. This can encourage the production of agro-based AMC's on a large-scale using agro-waste.
6. Additive manufacturing techniques can be used for the fabrication of agro-based AMC's. It is a novel method of developing parts to near net shape using layer by layer addition of materials which reduces: fly ratio (input material weight to final part weight) up to 1:1 [194, 195] as compared to 10:1 or 20:1 in case of conventional manufacturing processes. It provides freedom in part designing and can produce complex parts with low density, high strength, good thermal properties, and good energy absorption for applications like heat exchangers in automobile, computer, and aerospace industries [196]. It can allow mass production as it eliminates the processes like casting, forging, rolling, drilling, machining and welding, etc. and produces part in single

processing step. In addition, it reduces assembly requirements by combining number of parts into a single part. This technology has not been yet applied to develop agro-based AMC's. However, it has great potential to be used for the fabrication of low cost and high strength agro-based AMC's. For the fabrication of agro-based AMC's, powder bed fusion process will be preferred. Initially, the homogeneous mixture of Al powder and agro-based reinforcement will be prepared. Then this powdered mixture will be layered on the substrate as shown in Fig. 11(b) and laser pulse or electron beam will be fired at the particular location depending upon the cross section to be formed from the CAD model. An energy source either in the form of laser beam or electron beam melts the powder by scanning powder layer in an inert atmosphere. After scanning one layer another layer will be deposited on the formed layer which will be again scanned by an energy source. Repeating this cycle layer by layer the complete part will be formed. It can reduce the overall cost and leads to material conservation and sustainability. In combination with the utilization of agro-based materials this technology has a huge prospect in lightweight and low-cost manufacturing.

To sum up, it can be said that due to energy efficiency, cost-effectiveness, and environmental friendliness, these materials can find application as a reinforcing material in the composites and have vast potential, scope, and prospects for the researchers in the field of expectation and enrichment of characteristics of the agro-based AMC's. However, there is still the need to characterize the potentials of agro-waste by converting them into better reinforcing particles that can enhance the properties of AMC's.

## Conclusion

This review has systematically discussed various agro-based reinforcements and their influence on the microstructural, mechanical, and tribological properties and the processing techniques involved. Some of the key findings are:

1. Addition of various combinations of reinforcements in the composites are developed to attain desirable mechanical properties that are difficult to achieve in ceramic reinforced composites.
2. The agro-based AMC's reinforced with agro-waste products have revealed that the better performance of AMC's can be reached at lower production cost even though replacement of about 50% synthetic reinforcement by the agro-waste is possible without compromising any property. As revealed by the literature that replacing SiC or alumina by the agro-waste in small quantity results in an improvement in properties of the composite.
3. The agro-based reinforcements like, maize stalk ash, coconut shell ash, rice husk ash, etc. reduce the density of AMC's on their addition to composites. However, acceptable porosity levels are obtained in these composites.
4. The mechanical properties of agro-based AMC's revealed that the mechanical properties can be controlled by varying composition and reinforcements.
5. Various research works include agro-based materials as reinforcements and have studied influence, characteristics and properties of the AMC's; however, these also depend on the production technique employed.
6. Among all the techniques stir casting has been used extensively, however, it has various limitations associated, such as wettability and nonuniform dispersion of reinforcements. Thus, other techniques are now considered such as friction stir casting, compocasting and powder metallurgy.
7. These agro-waste materials have the potential to replace the hazardous reinforcements such as asbestos fiber used as a friction material in automobiles; coir fiber, when reinforced in the aluminum composite, has proved to be better candidate material as filler materials in brake pad applications and thus expand their scope of applications.

## Acknowledgements

The authors greatly acknowledge Department of Manufacturing & Materials Engineering, International Islamic University Malaysia, Malaysia for technical support.

## Declarations

**Conflict of Interest** We have no objection to share research data with other researchers who can evaluate our findings, and increase trust in our article. Here, mainly the research data are taken from different sources with appropriate citation for elaborating the review article.

## References

- [1] Macke A, Schultz BF. Metal matrix composites offer the automotive industry an opportunity to reduce vehicle weight, improve performance. *Adv Mater Process* 2012:19–23.
- [2] Miracle DB (2005) Metal matrix composites – From science to technological significance. *Compos Sci Technol* 65:2526–2540. <https://doi.org/10.1016/j.compscitech.2005.05.027>
- [3] Tung SC, McMillan ML (2004) Automotive tribology overview of current advances and challenges for the future. *Tribol Int* 37:517–536. <https://doi.org/10.1016/j.triboint.2004.01.013>
- [4] Sun C, Song M, Wang Z, He Y (2011) Effect of particle size on the microstructures and mechanical properties of SiC-reinforced pure aluminum composites. *J Mater Eng Perform* 20:1606–1612. <https://doi.org/10.1007/s11665-010-9801-3>
- [5] Surappa MK (2003) Aluminium matrix composites: challenges and opportunities. *Sadhana* 28:319–334
- [6] Rohatgi BPPK, Schultz B, Matters M (2011) Lightweight metal matrix nanocomposites - stretching the boundaries of metals. *Mater Matters* 2(4):1–6
- [7] Surappa MK, Rohatgi PK (1981) Preparation and properties of cast aluminium-ceramic particle composites. *J Mater Sci* 16:983–993. <https://doi.org/10.1007/BF00542743>
- [8] Maleque MA, Atiqah A, Talib RJ, Zahurin H (2012) New natural fibre reinforced aluminium composite for automotive brake pad. *Int J Mech Mater Eng* 7:166–170
- [9] Rajan TPD, Pillai RM, Pai BC (1998) Reinforcement coatings and interfaces in aluminium metal matrix composites. *J Mater Sci* 33:3491–3503. <https://doi.org/10.1023/A:1004674822751>
- [10] Panigrahi SK, Jayaganthan R (2010) Effect of annealing on precipitation, microstructural stability, and mechanical properties of cryorolled Al 6063 alloy. *J Mater Sci* 45:5624–5636. <https://doi.org/10.1007/s10853-010-4627-9>
- [11] Reddy BSB, Das K, Das S (2007) A review on the synthesis of in situ aluminum based composites by thermal, mechanical and mechanical-thermal activation of chemical reactions. *J Mater Sci* 42:9366–9378. <https://doi.org/10.1007/s10853-007-1827-z>
- [12] Taylor P (2016) Development of metal-matrix composites from industrial/agricultural waste materials and their derivatives. *Crit Rev Environ Sci Technol* 46:143–208. <https://doi.org/10.1080/10643389.2015.1077067>
- [13] Lancaster L, Lung MH, Sujana D, Ash ACS (2013) Utilization of agro-industrial waste in metal matrix composites : towards sustainability. *World Acad Sci Eng Technol* 73:1136–1144
- [14] Das S, Dan TK, Prasad SV, Rohatgi PK (1986) Aluminium alloy-rice husk ash particle composites. *J Mater Sci Lett* 5:562–564. <https://doi.org/10.1007/BF01728691>
- [15] Siddharth D, Rao JB (2017) Synthesis and characterization of RHA (rice husk ash) particulates reinforced A7075 composites. *Int J Adv Mech Civ Eng* 4:105–110
- [16] Dwivedi SP, Saxena A, Kumaraswamy A, Sahu R (2021) Synthesis and characterisation of waste SAC-and RHA-reinforced aluminium-based composite. *Green Mater*. <https://doi.org/10.1680/jgrma.20.00042>
- [17] Alaneme KK, Eze HI, Bodunrin MO (2015) Corrosion behaviour of groundnut shell ash and silicon carbide hybrid reinforced Al-Mg-Si alloy matrix composites in 3.5% NaCl and 0.3M H<sub>2</sub>SO<sub>4</sub> solutions. *Leonardo Electron J Pract Technol* 14:141–158
- [18] Alaneme KK, Bodunrin MO, Awe AA (2018) Microstructure, mechanical and fracture properties of groundnut shell ash and silicon carbide dispersion strengthened aluminium matrix composites. *J King Saud Univ - Eng Sci* 30:96–103. <https://doi.org/10.1016/j.jksues.2016.01.001>
- [19] Poornesh M, Saldanha JX, Singh J, Pinto GM (2017) Comparison of mechanical properties of coconut shell ash and SiC reinforced hybrid aluminium metal matrix composites. *Am J Mater Sci* 7:116–119. <https://doi.org/10.5923/j.materials.20170704.10>
- [20] Abdulwahab M, Umaru OB, Bawa MA, Jibo HA (2017) Microstructural and thermal study of Al-Si-Mg/melon shell ash particulate composite. *Results Phys* 7:947–954. <https://doi.org/10.1016/j.rinp.2017.02.016>
- [21] Safiuddin M, Jumaat MZ, Salam MA, Islam MS, Hashim R (2010) Utilization of solid wastes in construction materials. *Int J Phys Sci* 5:1952–1963
- [22] Atiqah MAM (2012) Development and characterization of coir fibre reinforced composite brake friction materials. *Arab J Sci Eng* 38:3191–3199. <https://doi.org/10.1007/s1369-012-0454-4>

- [23] Siva Prasad D, Rama Krishna A (2011) Production and mechanical properties of A356. 2 / RHA composites. *Int J Adv Sci Technol Prod* 33:51–58
- [24] Zuhailawati H, Samayamuththirian P, Haizu CHM, Campus E, Pinang P (2007) Fabrication of low cost of aluminium matrix composite reinforced with silica sand. *J Phys Sci* 18:47–55
- [25] Kanthavel K, Sumesh KR, Saravanakumar P (2016) Study of tribological properties on Al / Al<sub>2</sub>O<sub>3</sub> / MoS<sub>2</sub> hybrid composite processed by powder metallurgy. *Alexandria Eng J* 55:13–17. <https://doi.org/10.1016/j.aej.2016.01.024>
- [26] Baradeswaran A, Perumal AE (2014) Study on mechanical and wear properties of Al7075 / Al<sub>2</sub>O<sub>3</sub> / graphite hybrid composites. *Compos Part B* 56:464–471. <https://doi.org/10.1016/j.compositesb.2013.08.013>
- [27] Adebisi AA, Maleque A, Ali MY (2016) Effect of variable particle size reinforcement on mechanical and wear properties of 6061Al – SiC p composite. *Compos InterfaCes* 23:533–547. <https://doi.org/10.1080/09276440.2016.1167414>
- [28] Tiwari S, Pradhan MK (2017) Effect of rice husk ash on properties of aluminium alloys: A review. *Mater Today Proc* 4:486–495. <https://doi.org/10.1016/j.matpr.2017.01.049>
- [29] Kulkarni PP, Siddeswarappa B, Kumar KSH (2019) A survey on effect of agro waste ash as reinforcement on aluminium base metal matrix composites. *Open J Compos Mater* 09:312–326. <https://doi.org/10.4236/ojcm.2019.93019>
- [30] Bhattacharya SC (1993) State-of-the-art of utilizing residues and other types of biomass as an energy source. *RERIC Int Energy J* 15:1–23
- [31] Aigbodion V (2012) Development of Al-Si-Fe/Rice husk ash particulate composites synthesis by double stir casting method. *Usak Univ J Mater Sci* 1:187–197
- [32] Sathiesh Kumar N (2020) Fabrication and characterization of Al7075 / RHA /Mica composite by squeeze casting. *Mater Today Proc*. <https://doi.org/10.1016/j.matpr.2020.05.769>
- [33] Bakar RA, Yahya R, Gan SN (2016) Production of high purity amorphous silica from rice husk. *Procedia Chem* 19:189–195. <https://doi.org/10.1016/j.proche.2016.03.092>
- [34] Bazargan A, Bazargan M, McKay G (2015) Optimization of rice husk pretreatment for energy production. *Renew Energy* 77:512–520. <https://doi.org/10.1016/j.renene.2014.11.072>
- [35] Verma N, Vettivel SC (2018) Characterization and experimental analysis of boron carbide and rice husk ash reinforced AA7075 aluminium alloy hybrid composite. *J Alloys Compd* 741:981–998. <https://doi.org/10.1016/j.jallcom.2018.01.185>
- [36] Joharudin NFM, Latif NA, Mustapa MS, Badarulzaman NA, Mahmud MF (2020) Effect of burning temperature on rice husk silica as reinforcement of recycled aluminium chip AA7075. *J Adv Res Fluid Mech Therm Sci* 68 <https://doi.org/10.37934/ARFMTS.68.1.125132>
- [37] Alaneme KK, Sanusi KO (2015) Microstructural characteristics, mechanical and wear behaviour of aluminium matrix hybrid composites reinforced with alumina, rice husk ash and graphite. *Eng Sci Technol an Int J* 18:416–422. <https://doi.org/10.1016/j.jestch.2015.02.003>
- [38] Narasaraju G, Raju DL (2015) Characterization of hybrid rice husk and fly ash-reinforced aluminium alloy (AlSi10Mg) composites. *Mater Today Proc* 2:3056–3064. <https://doi.org/10.1016/j.matpr.2015.07.245>
- [39] Usman AM, Rajil A, Hassan MA, Waziri and NH. Influence of particulate loading on the mechanical properties of Al-4.5 Cu/GSA composite. *Int J Eng Sci* 2014;3:1–7.
- [40] Ravi Kumar K, Pridhar T, Sree Balaji VS (2018) Mechanical properties and characterization of zirconium oxide (ZrO<sub>2</sub>) and coconut shell ash(CSA) reinforced aluminium (Al 6082) matrix hybrid composite. *J Alloys Compd* 765:171–179. <https://doi.org/10.1016/j.jallcom.2018.06.177>
- [41] Babu RBMR (2019) Effect of mechanical properties on palm sprout shell ash reinforced with Al-6061 alloy metal matrix composites. *Int J Sci Res Eng Trends* 5:2395–2566
- [42] Virkunwar AK, Ghosh S, Basak R (2019) Study of mechanical and tribological characteristics of aluminium alloy reinforced with sugarcane bagasse ash. *SSRN Electron J*. <https://doi.org/10.2139/ssrn.3313510>
- [43] Baharin S, Universiti J (2011) Analysis of worn surfaces of palm shell activated carbon (Pscac) reinforced aluminium matrix. *Eng e-Trans* 6:156–160
- [44] Emeruwa OE, Nnakwo KC, Atuanya CU (2017) Investigative study of the structure and mechanical behaviour of horse eye bean seed shell ash reinforced aluminium alloy matrix composite. *Int J Sci Res Sci Eng Technol* 3:8–13
- [45] Tafzeelul Kamal MAS (2018) Evaluation of mustard husk ash as reinforcement for aluminium matrix composite. *Mater Res Express* *Accept* 5:1–16
- [46] Odoni BU, Odikpo F, Chinasa NC, Akaluzia RO (2020) Experimental analysis, predictive modelling and optimization of some physical and mechanical properties of aluminium 6063 alloy based composites reinforced with corn cob ash. *J Mater Eng Struct* 7:451–465
- [47] Ikubanni PP, Oki M, Adeleke AA, Adediran AA, Agboola OO, Babayeju O, Egbo N, Omiogbemi IMB (2021) Tribological and physical properties of hybrid reinforced

- aluminium matrix composites. *Mater Today Proc.* <https://doi.org/10.1016/j.matpr.2021.03.537>
- [48] Ebenezer NS, Vinod B, Jagadesh HS (2021) Corrosion behaviour of bamboo leaf ash-reinforced nickel surface-deposited aluminium metal matrix composites. *J Bio-Tribo-Corrosion* 7:1–7. <https://doi.org/10.1007/s40735-021-00510-x>
- [49] Yevich R, Logan JA (2003) An assessment of biofuel use and burning of agricultural waste in the developing world. *Global Biogeochem Cycles.* <https://doi.org/10.1029/2002gb001952>
- [50] Sarkar JK, Wang Q (2020) Different pyrolysis process conditions of South Asian waste coconut shell and characterization of gas, bio-char, and bio-oil. *Energies.* <https://doi.org/10.3390/en13081970>
- [51] Satheesh M, Pugazhivadiv M (2019) Investigation on physical and mechanical properties of Al6061-Silicon Carbide (SiC)/Coconut shell ash (CSA) hybrid composites. *Phys B Condens Matter* 572:70–75. <https://doi.org/10.1016/j.physb.2019.07.058>
- [52] Kaladgi ARR, Rehman KF, Afzal A, Baig MA, Soudagar MEM, Bhattacharyya S (2021) Fabrication characteristics and mechanical behaviour of aluminium alloy reinforced with Al<sub>2</sub>O<sub>3</sub> and coconut shell particles synthesized by stir casting. *IOP Conf Ser Mater Sci Eng* 1057:12017. <https://doi.org/10.1088/1757-899X/1057/1/012017>
- [53] Bello SA, Raheem IA, Raji NK (2017) Study of tensile properties, fractography and morphology of aluminium (1xxx)/coconut shell micro particle composites. *J King Saud Univ - Eng Sci* 29:269–277. <https://doi.org/10.1016/j.jksues.2015.10.001>
- [54] Bannaravuri PK, Birru AK. Strengthening of Al-4.5%Cu alloy with the addition of Silicon Carbide and Bamboo Leaf Ash. *Int J Struct Integr* 2019;10:149–61. <https://doi.org/10.1108/IJSI-03-2018-0018>.
- [55] Shridhara K. T, Hanumthlhal S, Annoji Rao T. M. Characterisation of Aluminium-Copper Alloy with Bamboo Leaf Ash and Graphite Metal Matrix Composites. *Int J Eng Res* 2015;V4:446–50. <https://doi.org/10.17577/ijertv4is070374>.
- [56] Alaneme KK, Olubambi PA, Afolabi AS, Bodurin MO (2014) Corrosion and tribological studies of bamboo leaf ash and alumina reinforced Al-Mg-Si alloy matrix hybrid composites in chloride medium. *Int J Electrochem Sci* 9:5663–5674
- [57] Usman AM, Raji A, Waziri N, Hassan MA (2014) Aluminium alloy - rice husk ash composites production and analysis. *Leonardo Electron J Pract Technol* 25:84–98
- [58] De SC, Khosrow R (2010) Rice Husk Ash as a supplementary raw material for the production of cellulose – cement composites with improved performance. *Waste Biomass Valor* 1:241–249. <https://doi.org/10.1007/s12649-010-9017-7>
- [59] Madakson PB, Yawas DS, Apasi A (2012) Characterization of coconut shell ash for potential utilization in metal matrix composites for automotive applications. *Int J Eng Sci Technol* 4:1190–1198
- [60] Amu OO, Adetuberu AA (2010) Characteristics of bamboo leaf ash stabilization on lateritic soil in highway construction. *Int J Eng Technol* 2:212–219
- [61] Zainudin NF, Lee KT, Kamaruddin AH, Bhatia S, Mohamed AR (2005) Study of adsorbent prepared from oil palm ash ( OPA ) for flue gas desulfurization. *Sep Purif Technol* 45:50–60. <https://doi.org/10.1016/j.seppur.2005.02.008>
- [62] Robani R, Chan C. Reusing soft soils with cement-palm oil clinker ( POC ) stabilisation. *Int Conf Eng Educ 21st Century* 2009:1–4.
- [63] Ahmadi R, Saiful MS, Zawawi DF, Rahman SZA, Ismail I, Mannan AB, et al. Production and Characterisation of Microfine Sized Palm Oil Fuel Ash (POFA) Originated from Bau, Lundu Palm Oil Mill. *MATEC Web Conf* 2016;87. <https://doi.org/10.1051/mateconf/20178701011>.
- [64] Hashimah N, Mohamad B. The utilization of Palm Oil Fuel Ash in Aluminium Metal Matrix Composites Materials. 2019.
- [65] Shigetomi Y, Ishimura Y, Yamamoto Y (2020) Trends in global dependency on the Indonesian palm oil and resultant environmental impacts. *Sci Rep* 10:1–11. <https://doi.org/10.1038/s41598-020-77458-4>
- [66] Ahmad MH, Noor NM. Physical Properties of Local Palm Oil Clinker And Fly Ash. *1st Eng Conf Energy Environ* 2007:1–6.
- [67] Zamri YB, Shamsul JB, Amin MM (2011) Potential of palm oil clinker as reinforcement in aluminium matrix composites for tribological applications. *Int J Mech Mater Eng* 6:10–17
- [68] Herna'ndez-Salas J.M., Villa-Ram' rez M.S, Veloz-Rendó'n J.S, Rivera-Herna'ndez K.N, Gonza'lez-Ce'sar R.A, Plascencia-Espinosa M.A T-ES. Comparative hydrolysis and fermentation of sugarcane and agave bagasse. *Bioresour Technol* 2009;100:1238–45. <https://doi.org/10.1016/j.biortech.2006.09.062>.
- [69] Sn W (2008) Sugarcane bagasse: how easy is it to measure it's constituents? *Proc S Afr Sug Technol Ass* 81:266–273
- [70] Usman AM, Raji A, Hassan MA, Waziri NH (2014) A comparative study on the properties of Al-7%Si-rice husk ash and Al-7%Si-bagasse ash composites produced by stir casting. *Int J Eng Sci* 3:1–7
- [71] Kamble A, Kulkarni SG (2019) Microstructural examination of bagasse ash reinforced waste aluminium alloy

- matrix composite. AIP Conf Proc 2105:1–8. <https://doi.org/10.1063/1.5100696>
- [72] Chandla NK, Yashpal, Kant S, Goud MM, Jawalkar CS. Experimental analysis and mechanical characterization of Al 6061/alumina/bagasse ash hybrid reinforced metal matrix composite using vacuum-assisted stir casting method. *J Compos Mater* 2020;54:4283–97. <https://doi.org/10.1177/0021998320929417>.
- [73] Odikpo F, Adesoji A, Ufuoma B, Goodluck O, Olayanju A. Physico-chemical and morphological evaluation of palm kernel shell particulate reinforced aluminium matrix composites. *Mater Today Proc* 2020:1–6. <https://doi.org/10.1016/j.matpr.2020.03.641>.
- [74] Adediran AA, Alaneme KK, Oladele IO, Akinlabi ET (2020) Wear characteristics of aluminium matrix composites reinforced with Si-based refractory compounds derived from rice husks. *Cogent Eng* 7:1–19. <https://doi.org/10.1080/23311916.2020.1826634>
- [75] Tyagi L, Butola R, Jha AK (2020) Mechanical and tribological properties of AA7075-T6 metal matrix composite reinforced with ceramic particles and aloe vera ash via Friction stir processing. *Mater Res Express* 7:1–13. <https://doi.org/10.1088/2053-1591/ab9c5e>
- [76] Farahin N, Joharudin M, Latif NA, Sukri M, Badarulzaman NA (2020) Effects of untreated and treated Rice Husk Ash (RHA) addition on physical properties of recycled aluminium chip. *Int J Integr Eng* 12:132–137
- [77] Farahin N, Joharudin M, Latif NA, Sukri M (2020) Physical properties and hardness of treated amorphous silica as reinforcement of AA7075 recycled aluminum chip. *IOP Conf Ser Sci Eng* 824:1–5. <https://doi.org/10.1088/1757-899X/824/1/012015>
- [78] Alaneme KK, Babalola SA, Chown LH, Bodunrin MO (2020) Hot deformation behaviour of bamboo leaf ash – silicon carbide hybrid reinforced aluminium based composite. *Manuf Rev* 17:1–14
- [79] Saini S, Gupta A, Jyoti A, Sumit M (2020) Rice husk - extracted silica reinforced graphite / aluminium matrix hybrid composite. *J Therm Anal Calorim*. <https://doi.org/10.1007/s10973-020-10404-8>
- [80] Marini CD, Fatchurrohman N, Zulkfli Z (2020) Investigation of wear performance of friction stir processed aluminium metal matrix composites. *Mater Today Proc*. <https://doi.org/10.1016/j.matpr.2020.07.568>
- [81] Holzschuh G. incorporation of rice husk ash and magnesium Metal matrix production: Casting of recycled aluminium cans and incorporation of rice husk ash and magnesium. *J Compos Mater* 2020:1–13. <https://doi.org/10.1177/0021998320911964>.
- [82] Gupta MK (2020) Effects of tool pin profile and feed rate on wear performance of pine leaf ash / Al composite prepared by friction stir processing. *J Adhes Sci Technol*. <https://doi.org/10.1080/01694243.2020.1800290>
- [83] Sangale AS, Rice K, Ash H, Treatment H (2019) Effect of heat treatment on hardness of aluminium alloy reinforced with Rice Husk Ash. *Int J Eng Res Technol* 8:754–756
- [84] Kumar NS, Harshavardhan KP, Murugan RA (2020) Characterization of aluminium hybrid composite reinforced with baggase ash and graphite processed through squeeze casting. *J Crit Rev* 7:176–178
- [85] Arulraj M, Palani PK, Sowrirajan M (2019) Enhancing wear resistance of squeeze cast hybrid aluminium matrix (LM24-SiCp-coconut shell ash) composite. *Int J Comput Mater Sci Surf Eng* 8:145–166. <https://doi.org/10.1504/IJCMSSE.2019.102302>
- [86] Vinod SRB, Anandajothi PNM. Dry Sliding Wear Mechanism Maps of Al – 7Si – 0.3Mg Hybrid Composite: Novel Approach of Agro-Industrial Waste Particles to Reduce Cost of Material. *J Bio- Tribo-Corrosion* 2019;0:0. <https://doi.org/10.1007/s40735-019-0227-7>.
- [87] Harish TM, Mathai S, Cherian J, Mathew KM, Thomas T, Prasad KVV, et al. Development of aluminium 5056 / SiC / bagasse ash hybrid composites using stir casting method. *Mater Today Proc* 2019:2–6. <https://doi.org/10.1016/j.matpr.2019.11.081>.
- [88] Patil NA, Safwan A, Pedapati SR, Ash RH (2020) Effect of deposition methods on microstructure and mechanical properties of Al 7075 alloy-rice husk ash surface composites using friction stir processing. *Mater Today Proc*. <https://doi.org/10.1016/j.matpr.2020.05.639>
- [89] Oghenevweta JE, Aigbodion VS (2016) Mechanical properties and microstructural analysis of Al – Si – Mg / carbonized maize stalk waste particulate composites. *J King Saud Univ - Eng Sci* 28:222–229. <https://doi.org/10.1016/j.jksues.2014.03.009>
- [90] Atuanya CU, Ibadode AOA, Dagwa IM (2012) Effects of breadfruit seed hull ash on the microstructures and properties of Al – Si – Fe alloy / breadfruit seed hull ash particulate composites. *Results Phys* 2:142–149. <https://doi.org/10.1016/j.rinp.2012.09.003>
- [91] Saravanan SD, Kumar MS (2013) Effect of mechanical properties on rice husk ash reinforced aluminum alloy (AlSi10Mg) matrix composites. *Procedia Eng* 64:1505–1513. <https://doi.org/10.1016/j.proeng.2013.09.232>
- [92] Gladston JAK, Sheriff NM, Dinaharan I, Selvam JDR (2015) Production and characterization of rich husk ash particulate reinforced AA6061 aluminum alloy composites by compocasting. *Trans Nonferrous Met Soc China*

- 25:683–691. [https://doi.org/10.1016/S1003-6326\(15\)63653-6](https://doi.org/10.1016/S1003-6326(15)63653-6)
- [93] Jose J, Christy TV, Peter PE, Feby JA, George AJ, Joseph J, Chandra RG, Benjie NM (2018) Manufacture and characterization of a novel agro-waste based low cost metal matrix composite (MMC) by compocasting. *Mater Res Express* 5:1–32
- [94] Kumar BP, Birru AK. Microstructure and mechanical properties of aluminium metal matrix composites with addition of bamboo leaf ash by stir casting method. *Trans Nonferrous Met Soc China (English Ed)* 2017;27:2555–72. [https://doi.org/10.1016/S1003-6326\(17\)60284-X](https://doi.org/10.1016/S1003-6326(17)60284-X).
- [95] Venkatesh L, Arjunan TV, Ravikumar K (2019) Microstructural characteristics and mechanical behaviour of aluminium hybrid composites reinforced with groundnut shell ash and B4C. *J Brazilian Soc Mech Sci Eng* 41:1–13. <https://doi.org/10.1007/s40430-019-1800-1>
- [96] Ahamed AA, Ahmed R, Hossain MB, Billah M (2016) Fabrication and characterization of aluminium-rice husk ash composite prepared by stir casting method. *Rajshahi Univ J Sci Eng* 44:9–18
- [97] Varalakshmi K, Ch Kishore Kumar K, Ravindra Babu P, Ch Sastry MR. Characterization of Al 6061-coconut Shell ash metal matrix composites using stir casting. *Int J Latest Eng Sci* 2019;2:41–9.
- [98] Prasad DS, Shoba C, Ramanaiah N (2014) Investigations on mechanical properties of aluminum hybrid composites. *J Mater Res Technol* 3:79–85. <https://doi.org/10.1016/j.jmrt.2013.11.002>
- [99] Gireesh CH, Prasad KGD, Ramji K, Vinay PV (2018) Mechanical characterization of aluminium metal matrix composite reinforced with aloe vera powder. *Mater Today Proc* 5:3289–3297. <https://doi.org/10.1016/j.matpr.2017.11.571>
- [100] Devanathan R, Ravikumar J, Boopathi S, Selvam DC, Anicia SA (2020) Influence in mechanical properties of stir cast aluminium ( AA6061) Hybrid Metal matrix Composite ( HMMC ) with Silicon Carbide, Fly Ash and Coconut coir Ash Reinforcement. *Mater Today Proc* 22:3136–3144. <https://doi.org/10.1016/j.matpr.2020.03.450>
- [101] Gupta V, Takhi S (2015) Effects of Rice Husk Ash particulates on the mechanical and tribological properties of the aluminum metal composite reinforced with aluminum oxide. *Int J Sci Res Dev* 3:1995–1998
- [102] Shankar S, Balaji A, Kawin N (2018) Investigations on mechanical and tribological properties of Al-Si10-Mg alloy/sugarcane bagasse ash particulate composites. *Part Sci Technol* 36:762–770. <https://doi.org/10.1080/02726351.2017.1301609>
- [103] Haque H, Ahmed R, Khan M, Shahriar S. Fabrication, Reinforcement and Characterization of Metal Matrix Composites (MMCs) using Rice Husk Ash and Aluminium Alloy (A-356.2). *Int J Sci Eng Res* 2016;7:28–35.
- [104] Singh J, Suri NM, Verma A (2015) Affect of mechanical properties on groundnut shell ash reinforced AL6063. *Int J Technol Res Eng* 2:2619–2623
- [105] Fatile OB, Akinruli JI, Amori AA (2014) Microstructure and mechanical behaviour of stir-cast Al-Mg-Si alloy matrix hybrid composite reinforced with corn cob ash and silicon carbide. *Int J Eng Technol Innov* 4:251–259
- [106] Poornesh M, Saldanha JX, Singh J, Pinto GM (2017) Effect of coconut shell ash and SiC particles on mechanical properties of aluminium based composites. *Am J Mater Sci* 7:112–115. <https://doi.org/10.5923/j.materials.20170704.09>
- [107] Natrayan L, Sivaprakash V, Santhosh MS (2018) Mechanical, Microstructure and wear behavior of the material AA6061 reinforced SiC with different leaf ashes using advanced stir casting method. *Int J Eng Technol* 8:366–371
- [108] Subramaniam B, Natarajan B, Kaliyaperumal B, Cheladurai SJS (2018) Investigation on mechanical properties of aluminium 7075 - boron carbide - coconut shell fly ash reinforced hybrid metal matrix composites. *China Foundry* 15:449–456. <https://doi.org/10.1007/s41230-018-8105-3>
- [109] Daramola OO, Ogunsanya A, Akintayo O, Oladele IO (2018) Mechanical properties of Al 6063 metal matrix composites reinforced with agro-wastes silica particles. *Leonardo Electron J Pract Technol* 106:89–104
- [110] Udoye NE, Fayomi OSI, Inegbenebor AO. Fractography and tensile properties of AA6061 aluminium alloy/rice husk ash silicon nanocomposite. *Int J Chem Eng* 2020;2020. <https://doi.org/10.1155/2020/8818224>.
- [111] Yekinni AA, Durowoju MO, Agunsoye JO, Mudashiru LO. Effect of particle size of rice husk ash on aluminium/graphene composites. *IOP Conf Ser Mater Sci Eng* 2020;805. <https://doi.org/10.1088/1757-899X/805/1/012012>.
- [112] Bilal M, Shaikh N, Arif S, Aziz T, Waseem A, Ahmed M et al (2019) Microstructural, mechanical and tribological behaviour of powder metallurgy processed SiC and RHA reinforced Al-based composites. *Surfaces and Interfaces* 15:166–179. <https://doi.org/10.1016/j.surfin.2019.03.002>
- [113] Kanayo Alaneme K, Apata OP (2013) Corrosion and wear behaviour of rice husk ash - Alumina reinforced Al-Mg-Si alloy matrix hybrid composites. *J Mater Res Technol* 2:188–194. <https://doi.org/10.1016/j.jmrt.2013.02.005>
- [114] Bodunrin M.O, Oladijo O. P, Daramola O.O, Alaneme K. K MNB. Porosity measurement and wear performance of



- aluminium hybrid composites reinforced. *Ann Fac Eng Hunedoara – Int J Eng Tome* 2016;14:231–8.
- [115] Alaneme KK, Adewale TM, Olubambi PA (2014) Corrosion and wear behaviour of Al-Mg-Si alloy matrix hybrid composites reinforced with rice husk ash and silicon carbide. *J Mater Res Technol* 3:9–16. <https://doi.org/10.1016/j.jmrt.2013.10.008>
- [116] Siva Prasad D, Shoba C (2014) Hybrid composites - a better choice for high wear resistant materials. *J Mater Res Technol* 3:172–178. <https://doi.org/10.1016/j.jmrt.2014.03.004>
- [117] Pallavi Deshmukh • Shailkumar Pathak. Influence of varying SiO<sub>2</sub> % on the mechanical properties of Al based MMC. *Trans Indian Inst Met* (December 2012;65:741–5. <https://doi.org/10.1007/s12666-012-0196-8>.
- [118] Bannaravuri, P.K. and Birru AK. Strengthening of mechanical and tribological properties of Al-4.5%Cu matrix alloy with the addition of bamboo leaf ash. *Results Phys* 2018;10:360–73. <https://doi.org/10.1016/j.rinp.2018.06.004>.
- [119] Bodunrin, M.O., Oladipo O. P., Daramola, O.O., Alaneme, K. K., Maled NB. Porosity measurement and wear performance of aluminium hybrid composites reinforced with silica sand and bamboo leaf ash. *Ann Fac Eng Hunedoara-International J Eng* 2016:231–8.
- [120] Lakshmikanthan P, Prabu B (2016) Mechanical and tribological behaviour of aluminium Al6061-coconut shell ash composite using stir casting pellet method. *J Balk Tribol Assoc* 22:4008–4018
- [121] Prasad DS, Krishna AR. Tribological Properties of A356.2/RHA Composites. *J Mater Sci Technol* 2012;28:367–72. [https://doi.org/10.1016/S1005-0302\(12\)60069-3](https://doi.org/10.1016/S1005-0302(12)60069-3).
- [122] Panda B, Mahato AK, Varun C, R SSR. Wear Behavior of Aluminum Based Composite Reinforced With Coconut Shell Ash. *Imp J Interdiscip Res* 2016;2:890–5.
- [123] Virkunwar AK, Ghosh S, Basak R (2019) Wear characteristics optimization of Al6061-Rice husk ash metal matrix composite using Taguchi method. *Mater Today Proc* 19:546–550. <https://doi.org/10.1016/j.matpr.2019.07.731>
- [124] Sankara Raju RS, Panigrahi MK, Ganguly RI, Srinivasa RG (2019) Tribological behaviour of al-1100-coconut shell ash (CSA) composite at elevated temperature. *Tribol Int* 129:55–66. <https://doi.org/10.1016/j.triboint.2018.08.011>
- [125] Coyal A, Yuvaraj N, Butola R, Tyagi L. An experimental analysis of tensile, hardness and wear properties of aluminium metal matrix composite through stir casting process. *SN Appl Sci* 2020;2. <https://doi.org/10.1007/s42452-020-2657-8>.
- [126] Kasagani S, Bellamkonda PN, Sudabathula S. Wear and Friction Behaviour of Coconut Shell Ash Reinforced Aa-7075 Metal. *Int J Res* 2020;VIII:477–85.
- [127] Kumar A, Kumar M (2019) Mechanical and dry sliding wear behaviour of B4C and rice husk ash reinforced Al 7075 alloy hybrid composite for armors application by using taguchi techniques. *Mater Today Proc* 27:2617–2625. <https://doi.org/10.1016/j.matpr.2019.11.075>
- [128] Usman Y, Dauda ET, Abdulwahab M, Dodo RM (2020) Effect of mechanical properties and wear behaviour on locust bean waste ash (LBWA) particle reinforced aluminium alloy (A356 alloy) composites. *FUDMA J Sci* 4:7–9
- [129] Ikumapayi OM, Akinlabi ET, Majumdar JD, Oladipo OP, Akinlabi SA. Influence of wood fly ash reinforcement on the wear behaviour of friction stir processed aluminium-based surface matrix composite. *Proc Int Conf Ind Eng Oper Manag* 2019;1:966–77.
- [130] Ikumapayi OM, Akinlabi ET, Majumdar JD, Akinlabi SA. Characterization of high strength aluminium-based surface matrix composite reinforced with low-cost PKSA fabricated by friction stir processing. *Mater Res Express* 2019;6. <https://doi.org/10.1088/2053-1591/ab395b>.
- [131] Krushna MG, Shekhar PS, Kumar SA. Effect of hot forging on high temperature tribological properties of aluminium composite reinforced with agro and industrial waste. *Int J Eng Adv Technol* 2019;8:1607–12. <https://doi.org/10.35940/ijeat.F8204.088619>.
- [132] Arora G, Sharma S (2020) Effects of rice husk ash and silicon carbide addition on AA6351 hybrid green composites. *Emerg Mater Res* 9:1–7. <https://doi.org/10.1680/jemmr.18.00007>
- [133] Alaneme KK, Ademilua BO, Bodunrin MO (2013) Mechanical properties and corrosion behaviour of aluminium hybrid composites reinforced with silicon carbide and bamboo leaf ash. *Tribol Ind* 35:25–35
- [134] Hossain MR, Ali MH, Amin M Al, Kibria MG, Ferdous MS. Fabrication and Performance Test of Aluminium Alloy-Rice Husk Ash Hybrid Metal Matrix Composite as Industrial and Construction Material. *Int J Eng Mater Manuf* 2017;2:94–102. <https://doi.org/10.26776/ijemm.02.04.2017.03>.
- [135] Sarkar S, Bhirangi A, Mathew J, Oyyaravelu R, Kuppan P, Balan ASS (2018) Fabrication characteristics and mechanical behavior of Rice Husk Ash-Silicon Carbide reinforced Al-6061 alloy matrix hybrid composite. *Mater Today Proc* 5:12706–12718. <https://doi.org/10.1016/j.matpr.2018.02.254>
- [136] Rohatgi P (1991) Cast aluminum-matrix composites for automotive applications. *Jom* 43:10–15

- [137] Ravi KR, Sreekumar VM, Pillai RM, Mahato C, Amaranathan KR, Arul R et al (2007) Materials & design optimization of mixing parameters through a water model for metal matrix composites synthesis. *Mater Des* 28:871–881. <https://doi.org/10.1016/j.matdes.2005.10.007>
- [138] Singla M, Dwivedi DD, Singh L, Chawla V (2009) Development of aluminium based silicon carbide particulate metal matrix composite. *J Miner Mater Charact Eng* 8:455–467
- [139] Durowoju MO, Agunsoye JO, Mudashiru LO, Yekinni AA, Bello SK, Rabi TO. Optimization of Stir Casting Process Parameters to Improve the Hardness Property of Al/RHA Matrix Composites. *Eur J Eng Res Sci* 2017;2:5. <https://doi.org/10.24018/ejers.2017.2.11.498>.
- [140] Hashim J, Looney L, Hashmi MSJ (1999) Metal matrix composites: production by the stir casting method. *J Mater Process Technol* 92:1–7. [https://doi.org/10.1016/S0924-0136\(99\)00118-1](https://doi.org/10.1016/S0924-0136(99)00118-1)
- [141] Hashim J (2007) The production of cast metal matrix composite by a modified stir casting method. *J Teknol* 35:9–20
- [142] Alaneme KK, Akintunde IB, Olubambi PA, Adewale TM (2013) Fabrication characteristics and mechanical behaviour of rice husk ash - Alumina reinforced Al-Mg-Si alloy matrix hybrid composites. *J Mater Res Technol* 2:60–67. <https://doi.org/10.1016/j.jmrt.2013.03.012>
- [143] Rajan TPD, Pillai RMPBC (1998) Reinforcement coatings and interfaces in aluminium metal matrix composites. *J Mater Sci* 33:3491–3503
- [144] Pai BC, Ramani G, Pillai RMSKG (1995) Role of magnesium in cast aluminium alloy matrix composites. *J Mater Sci* 30:1903–1911
- [145] Verma S. Study on mechanical behavior of boron carbide and rice husk ash based aluminium alloy 6061 hybrid composite. *Int J Tech Innov Mod Eng Sci (IJTIMES)* 2018.
- [146] Ghosh S, Basak R, Rao AS. Study of Mechanical and Tribological Characteristics of Aluminium Alloy Reinforced with Rice Husk Ash. *An Int Conf Tribol* 2018:6–10.
- [147] Arora G, Sharma S (2018) A comparative study of AA6351 mono-composites reinforced with synthetic and agro waste reinforcement. *Int J Precis Eng Manuf* 19:631–638. <https://doi.org/10.1007/s12541-018-0076-1>
- [148] Dwivedi SP, Srivastava A, Kumar A, Nandan B (2017) Microstructure and mechanical behaviour of RHA and B<sub>4</sub>C reinforced aluminium alloy hybrid metal matrix composite. *Indian J Eng Mater Sci* 24:133–140
- [149] Laad M, Jatti VS, Yadav S (2015) Comparative study between SiC reinforced Al 64430 metal matrix composites and RHA reinforced Al 64430 metal matrix composites. *Adv Mater Res* 1119:234–238.
- [150] ChinnamahammadBhasha A, Balamurugan K (2020) Studies on Al6061nanohybrid composites reinforced with SiO<sub>2</sub>/3x% of TiC -a Agro-waste. *SILICON*. <https://doi.org/10.1007/s12633-020-00758-x>
- [151] Apasi A, Yawas DS, Abdulkareem S, Kolawole MY (2016) Improving mechanical properties of aluminium alloy through addition of coconut shell-ash. *J Sci Technol* 36:34–43
- [152] Aku SY, Yawas DS, Apasi A (2013) Evaluation of cast Al-Si-Fe alloy/coconut shell ash particulate composites. *Gazi Univ J Sci* 26:449–457
- [153] Mangalore P, Akash, Ulvekar A, Abhiram, Sanjay J, Advait. Mechanical properties of coconut shell ash reinforced aluminium metal matrix composites. *AIP Conf Proc* 2019;2080. <https://doi.org/10.1063/1.5092897>.
- [154] Chethan KN, Pai A, Padmaraj NH, Singhal A, Sinha S. Effect of bamboo char and boron carbide particles on mechanical characteristics of Aluminum 6061 hybrid composites. *IOP Conf Ser Mater Sci Eng* 2018;377. <https://doi.org/10.1088/1757-899X/377/1/012038>.
- [155] Jadhav S, Aradhya A, Kulkarni S, Shinde Y, Vaishampayan V. Effect of hybrid ash reinforcement on microstructure of A356 alloy matrix composite. *AIP Conf Proc* 2019;2105. <https://doi.org/10.1063/1.5100695>.
- [156] Kawin N, Jagadeesh D, Saravanan G, Periasamy K (2020) Optimization of turning parameters in sugarcane bagasse ash reinforced with Al-Si10-Mg alloy composites by Taguchi method. *Mater Today Proc* 21:474–476. <https://doi.org/10.1016/j.matpr.2019.06.634>
- [157] Usman AM, Raji A, Waziri NH, Hassan MA (2014) Production and characterisation of aluminium alloy - bagasse ash composites. *IOSR J Mech Civ Eng* 11:38–44. <https://doi.org/10.9790/1684-11433844>
- [158] Imran M, Khan ARA, Megeri S, Sadik S (2016) Study of hardness and tensile strength of Aluminium-7075 percentage varying reinforced with graphite and bagasse-ash composites. *Resour Technol* 2:81–88. <https://doi.org/10.1016/j.reffit.2016.06.007>
- [159] Suleiman IY, Salihu SA, Mohammed TA (2018) Investigation of mechanical, microstructure, and wear behaviors of Al-12%Si/reinforced with melon shell ash particulates. *Int J Adv Manuf Technol* 97:4137–4144. <https://doi.org/10.1007/s00170-018-2157-9>
- [160] Aigbodion VS (2019) Bean pod ash nanoparticles a promising reinforcement for aluminium matrix biocomposites. *J Mater Res Technol* 8:6011–6020. <https://doi.org/10.1016/j.jmrt.2019.09.075>

- [161] Edoziuno FO, Adediran AA, Odoni BU, Utu OG, Olayanju A (2021) Physico-chemical and morphological evaluation of palm kernel shell particulate reinforced aluminium matrix composites. *Mater Today Proc* 38:652–657. <https://doi.org/10.1016/j.matpr.2020.03.641>
- [162] Kumar PV, Paranthaman P. Friction stir welding process parametric optimization of hybrid aluminium-bagasse ash-graphite composite by Taguchi approach. *Mater. Today Proc.*, vol. 37, Elsevier Ltd; 2020, p. 764–8. <https://doi.org/10.1016/j.matpr.2020.05.789>.
- [163] Narenthiran, B. and Paranthaman P. Investigations on effect of FSW process parameter on hybrid Al MMC using Taguchi. *Mater. Today Proc.*, vol. 37, Elsevier Ltd; 2020, p. 759–63. <https://doi.org/10.1016/j.matpr.2020.05.787>.
- [164] Kalaiselvan K, Murugan N, Parameswaran S (2011) Production and characterization of AA6061 – B 4 C stir cast composite. *Mater Des* 32:4004–4009. <https://doi.org/10.1016/j.matdes.2011.03.018>
- [165] Adediran AA, Alaneme KK, Oladele IO, Akinlabi ET. Wear characteristics of aluminium matrix composites reinforced with Si-based refractory compounds derived from rice husks. *Cogent Eng* 2020;7. <https://doi.org/10.1080/23311916.2020.1826634>.
- [166] Sahin Y (2003) Preparation and some properties of SiC particle reinforced aluminium alloy composites. *Mater Des* 24:671–679. <https://doi.org/10.1016/S0261-3069>
- [167] Mart EE, Rodrigo P, Gil L (2004) Oxidation treatments for SiC particles used as reinforcement in aluminium matrix composites. *Compos Sci Technol* 64(64):1843–1854. <https://doi.org/10.1016/j.compscitech.2004.01.010>
- [168] Ramesh CS, Keshavamurthy R, Channabasappa BH, Ahmed A (2009) Microstructure and mechanical properties of Ni – P coated Si<sub>3</sub>N<sub>4</sub> reinforced Al6061 composites. *Mater Sci Eng A* 502:99–106. <https://doi.org/10.1016/j.msea.2008.10.012>
- [169] Ceschini L, Minak G, Morri A (2006) Tensile and fatigue properties of the AA6061/20 vol% Al<sub>2</sub>O<sub>3</sub>p and AA7005/10 vol% Al<sub>2</sub>O<sub>3</sub>p composites. *Compos Sci Technol* 66:333–342. <https://doi.org/10.1016/j.compscitech.2005.04.044>
- [170] Mohamed A Taha. Practicalization of cast metal matrix composites (MMCC's). *Mater Des* 2001;22:431–41.
- [171] Amir Khanlou S, Rezaei MR, Niroumand B, Toroghinejad MR (2011) High-strength and highly-uniform composites produced by compocasting and cold rolling processes. *Mater Des* 32:2085–2090. <https://doi.org/10.1016/j.matdes.2010.11.046>
- [172] Luangvaranunt T, Dhadsanadhep C, Umeda J, Nisaratanaporn E, Kondoh K (2010) Aluminum-4 mass % Copper/Alumina composites produced from Aluminum Copper and rice husk ash silica powders by powder forging. *Mater Trans* 51:756–761. <https://doi.org/10.2320/matertrans.M2009429>
- [173] Dhadsanadhep C, Luangvaranunt T, Umeda J, Kondoh K (2008) Fabrication of Al / Al<sub>2</sub>O<sub>3</sub> composite by powder metallurgy method from aluminum and Rice Husk Ash. *J Met Mater Miner* 18:99–102
- [174] Shaikh MBN, Arif S, Aziz T, Waseem A, Shaikh MAN, Ali M (2019) Microstructural, mechanical and tribological behaviour of powder metallurgy processed SiC and RHA reinforced Al-based composites. *Surfaces and Interfaces* 15:166–179. <https://doi.org/10.1016/j.surfin.2019.03.002>
- [175] Yusoff Z, Baharin S, Amin M, Hidayah N (2010) Sliding wear properties of hybrid aluminium composite reinforced by particles of palm shell activated carbon and slag. *J Sci Technol Sliding* 2:79–96
- [176] Guo N, Leu MC (2013) Additive manufacturing: technology, applications and research needs. *Front Mech Eng* 8:215–243. <https://doi.org/10.1007/s11465-013-0248-8>
- [177] Harris ID. Development and implementation of metals additive manufacturing. *Addit Manuf Handb Prod Dev Def Ind* 2017:215–24. <https://doi.org/10.1201/9781315119106>.
- [178] Rashid A. Additive Manufacturing Technologies. 2019. [https://doi.org/10.1007/978-3-642-35950-7\\_16866-1](https://doi.org/10.1007/978-3-642-35950-7_16866-1)
- [179] Kempen K, Thijs L, Yasa E, Badrossamay M, Verheecke W, Kruth JP. Process optimization and microstructural analysis for selective laser melting of AlSi10Mg. *22nd Annu Int Solid Free Fabr Symp - An Addit Manuf Conf SFF* 2011 2011:484–95.
- [180] Krishnan M, Atzeni E, Canali R, Calignano F, Manfredi D, Ambrosio EP et al (2014) On the effect of process parameters on properties of AlSi10Mg parts produced by DMLS. *Rapid Prototyp J* 20:449–458. <https://doi.org/10.1108/RPJ-03-2013-0028>
- [181] Ghosh S, Saha P, Kishore S. Influence of size and volume fraction of SiC particulates on properties of ex situ reinforced Al-4.5Cu-3Mg metal matrix composite prepared by direct metal laser sintering process. *Mater Sci Eng A* 2010;527:4694–701. <https://doi.org/10.1016/j.msea.2010.03.108>.
- [182] Ghosh SK, Saha P (2011) Crack and wear behavior of SiC particulate reinforced aluminium based metal matrix composite fabricated by direct metal laser sintering process. *Mater Des* 32:139–145. <https://doi.org/10.1016/j.matdes.2010.06.020>
- [183] Manfredi D, Calignano F, Krishnan M, Canali R, Paola E, Biamino S et al (2014) Additive manufacturing of Al alloys and Aluminium Matrix Composites (AMCs). *Light Met Alloy Appl*. <https://doi.org/10.5772/58534>

- [184] Deepak D, Sidhu RS, Gupta VK (2013) Preparation of 5083 Al-SiC surface composite by friction stir processing and its mechanical characterization. *Int J Mech Eng* 3:1–11
- [185] Akinlabi ET, Mahamood RM, Akinlabi SA, Ogunmuyiwa E. Processing parameters influence on wear resistance behaviour of friction stir processed Al-TiC composites. *Adv Mater Sci Eng* 2014:1–13.
- [186] Prakrathi S, Ravikumar M, Udupa KR, Bhat KU. Fabrication of hybrid surface composite through friction stir processing and its impression creep behaviour. *ISRN Mater Sci* 2013:1–6.
- [187] Izadi H, Nolting A, Munro C, Bishop DP, Plucknett KP, Gerlich AP (2013) Friction stir processing of Al / SiC composites fabricated by powder metallurgy. *J Mater Process Tech* 213:1900–1907. <https://doi.org/10.1016/j.jmatprotec.2013.05.012>
- [188] Zahmatkesh B, Enayati MH (2010) A novel approach for development of surface nanocomposite by friction stir processing. *Mater Sci Eng A* 527:6734–6740. <https://doi.org/10.1016/j.msea.2010.07.024>
- [189] Sahraeinejad S, Izadi H, Haghshenas M, Gerlich AP (2015) Fabrication of metal matrix composites by friction stir processing with different particles and processing parameters. *Mater Sci Eng A* 626:501–513. <https://doi.org/10.1016/j.msea.2014.12.077>
- [190] Wang W, Shi Q, Liu P, Li H, Li T (2009) A novel way to produce bulk SiCp reinforced aluminum metal matrix composites by friction stir processing. *J Mater Process Technol* 209:2099–2103. <https://doi.org/10.1016/j.jmatprotec.2008.05.001>
- [191] Dinaharan I, Kalaiselvan K, Akinlabi ET, Davim JP (2017) Microstructure and wear characterization of rice husk ash reinforced copper matrix composites prepared using friction stir processing. *J Alloys Compd* 718:150–160. <https://doi.org/10.1016/j.jallcom.2017.05.117>
- [192] Fatchurrohman N, Farhana N, Marini CD (2018) Investigation on the effect of friction stir processing parameters on micro-structure and micro-hardness of Rice Husk Ash reinforced Al6061 metal matrix composites. *IOP Conf Ser Mater Sci Eng* 319:1–6. <https://doi.org/10.1088/1757-899X/319/1/012032>
- [193] Abdulmalik SS, Ahmad R (2014) Fabrication of AA6061-0/RHA surface composite via friction stir processing. *Appl Mech Mater* 660:214–218.
- [194] English CL, Tewari SK, Abbott DH. An overview of ni base additive fabrication technologies for aerospace applications. *7th Int Symp Superalloy* 718 *Deriv* 2010 2010;1:399–412. <https://doi.org/10.1002/9781118495223.ch31>.
- [195] Horn TJ, Harrysson OLA (2012) Overview of current additive manufacturing technologies and selected applications. *Sci Prog* 95:255–282. <https://doi.org/10.3184/003685012X13420984463047>
- [196] Luisa S, Contuzzi N, Angelastro A, Domenico A. Capabilities and Performances of the Selective Laser Melting Process. *New Trends Technol Devices, Comput Commun Ind Syst* 2010. <https://doi.org/10.5772/10432>.

**Publisher's Note** Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.