



Synthesis and Characterization of PVA/Starch Hydrogel Membranes Incorporating Essential Oils Aimed to be Used in Wound Dressing Applications

Farrukh Altaf¹ · Muhammad Bilal Khan Niazi¹ · Zaib Jahan¹ · Tahir Ahmad² · Muhammad Aftab Akram¹ · Amna safdar¹ · Muhammad Shoaib Butt¹ · Tayyaba Noor¹ · Farooq Sher³

Published online: 25 August 2020

© Springer Science+Business Media, LLC, part of Springer Nature 2020

Abstract

Wound care has come through various trials and errors with primitive cultures applying old age techniques and knowledge. Recent research has shown that the moist environment promotes wound healing than the dry. In the present research, hydrogel membranes were fabricated by esterification of polyvinyl alcohol (PVA) with starch and glutaraldehyde as a cross-linker. The essential oils (clove oil, Oregano oil and tea tree oil) have been incorporated in PVA/Starch based hydrogel membranes. The aim was to achieve optimized anti-bacterial activity and mechanical strength. The anti-bacterial testing was performed using the disc diffusion method. The maximum antibacterial activity for fabricated hydrogels was attained by addition of 0.1 mL clove oil in PVA/Starch hydrogel was 39 ± 0.57 mm and 37 ± 0.29 mm for MRSA and *E. coli*, respectively. The FTIR results presented the occurrence of –OH group in hydrogel membrane. The SEM results showed around dense nature of membranes with having an antibacterial agent in it or not. Mechanical examination of hydrogel membranes presented suitable tensile strength of 19.36 MPa for 0.1 mL Clove oil. Furthermore, water vapour transmission rate (WVTR) and moisture retention capability (MRC) for 0.1 mL clove oil was $36.22 \text{ g/m}^2\text{h}$ and 95.50%, respectively. The experimental conclusion nominated that fabricated hydrogel articulates good antibacterial, mechanical and physical properties that it could be used in wound dressing applications. The best results were obtained for clove oil using 0.1 mL as an antibacterial agent.

Electronic supplementary material The online version of this article (doi:[10.1007/s10924-020-01866-w](https://doi.org/10.1007/s10924-020-01866-w)) contains supplementary material, which is available to authorized users.


✉ Muhammad Bilal Khan Niazi
m.b.k.niazi@scme.nust.edu.pk

¹ Department of Chemical Engineering, School of Chemical and Materials Engineering, National University of Sciences and Technology, Islamabad, Pakistan

² Atta Ur Rehman School of Applied Bio-Sciences, National University of Science and Technology, Islamabad, Pakistan

³ School of Mechanical, Aerospace and Automotive Engineering, Faculty of Engineering, Environment and Computing, Coventry University Coventry, Coventry, UK

Graphic Abstract

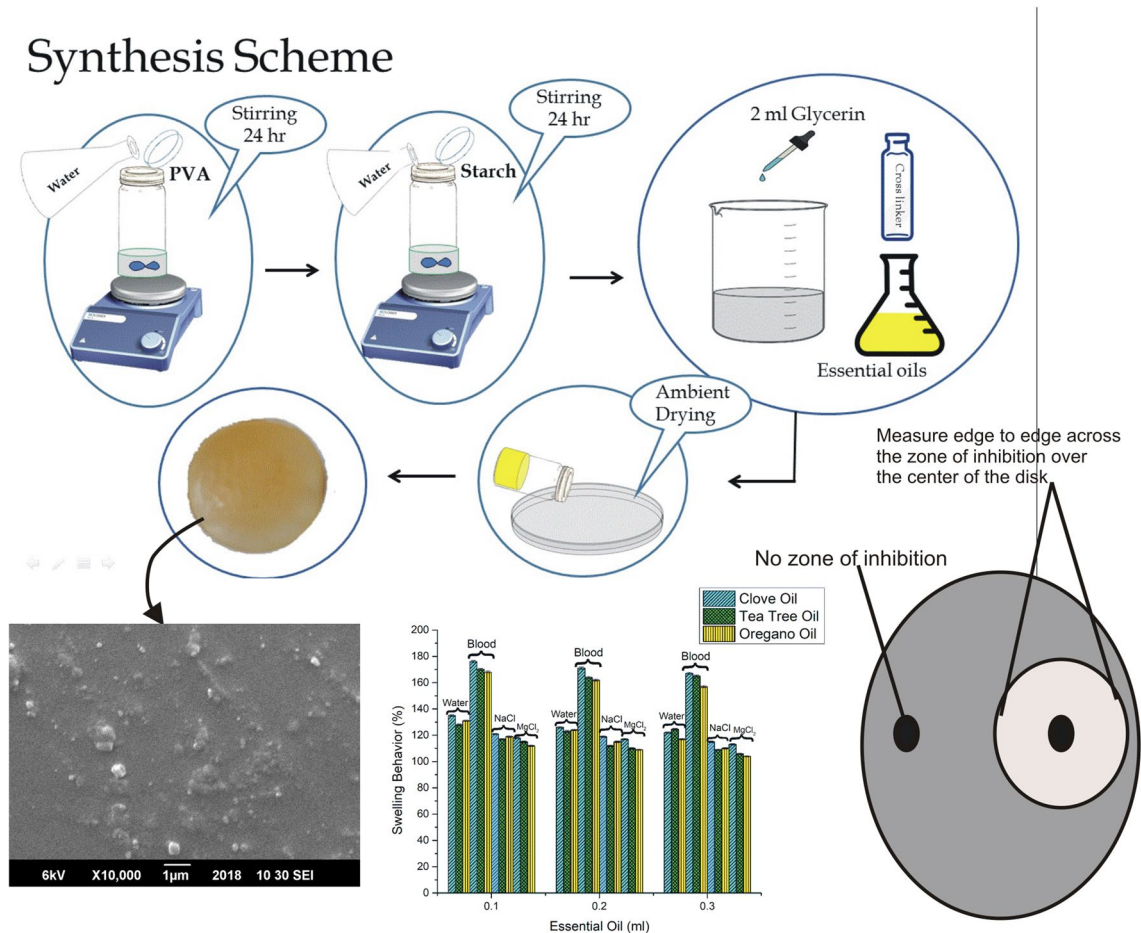

Keywords Hydrogel · Polyvinyl alcohol (PVA) · Starch · Clove oil · Tea tree oil · Oregano oil · Antibacterial activity

Introduction

Over the past few decades, membrane technology has gained the significant importance in finding its applications in desalination, food processing and medical fields. But since last few years, the hydrogel membranes have gained importance due to their feasibility in healing the burn wounds [1]. Though, in scenario of wound dressing application, the life span of membrane is not an issue because it is used for a limited period of time [2].

Despite the largest human body organ, the skin is the least well-known organ. The reason is that its function is easily defined and measured rather than the circulatory or renal systems.

According to the World Health Organization (WHO), approximately 180,000 deaths occur due to burns annually. Most of these casualties occur in underdeveloped regions and two-third in African and Asian countries. Burning is

the foremost reason of disabilities [3]. The scald injuries are incontrovertibly amongst the maximum problematic ones to handle with, where extensive liquid loss and tissue damages weaken numerous momentous functions [4]. Each year, millions of people are exposed to burns caused by flames, hot water, boiling oil and accidents and these end in major disabilities or even death [4]. The wound healing process is defined through four steps; Homeostasis, inflammatory response, proliferation and remodeling [5].

In the past, dry wound was considered optimal for the wound dressings. This was the major drawback of these types of dressings. Because the recent research has shown that wounds needs the moist environment. It helps in mimicking the skin functioning. That's why hydrogels are introduced for heal wounding.

Hydrogels are polymeric 3-D cross-linked arrangements that have high moisture retaining capabilities. This moisture absorption is caused by the presence of carboxyl, hydroxyl

and hydrophilic compounds present in them [6]. They tend to swell when exposed to various fluids. The moisture absorbing ability makes them a potential candidate for wound dressing applications. Exudates from the wound are collected inside the hydrogel membrane as a gel, providing suppressing and conserving effect to the wound and hinders bacterial infections [7]. This effect also helps in reducing the unpleasant odor caused by the exudates present at the wound site. Hydrogel membranes can be easily removed from the wound surface without rupturing, due to hydrophilic groups present in them [8]. Hydrogel membranes strength must be greater than the strength of human skin (11.5 MPa) which makes them further a suitable candidate [9]. The strength of the hydrogel membrane depends primarily on the polymer used. Since they are hydrophilic, it can help in hydrating dried wounds and does not leave any debris behind [10].

Hydrogels from natural polymers such as polysaccharides are getting some prominence over the last few years [11]. But the polysaccharides cannot be used alone because of low mechanical and physical properties such as moisture retention, gel fraction, water vapour transition rate, etc. Hence, polysaccharides are blended with some synthetic polymers (poly (vinyl alcohol), poly (methyl methacrylate), polyurethane etc.). The natural polymers have many advantages over synthetic i.e., ecofriendly, non-toxic, biodegradable and absorbent. Starch is a glucose-based natural polymer, which is considered as the best option due to common availability, biodegradability, biocompatibility and low cost. It partially dissolves in water and can be easily modified i.e. physically or chemically. However, starch cannot be used as a base polymer alone because it cannot form a stable hydrogel. Mechanical strength has a good impact on the hydrogels but using starch alone it loses the strength. Hence, it is mixed with other polymers to overcome this issue. Polyvinyl alcohol (PVA) is one of the most widely applied and important polymers used in hydrogels [12]. This is attributed to its solubility in water, biocompatibility, non-toxicity, biodegradability, low cost, ease of formulation as a hydrogel and non-carcinogenic properties. Glutaraldehyde acts as a cross linker to chemically link PVA Starch. Secondly, glycerine is used as a plasticizers to enhance its strength.

The antibacterial characteristics of essential oils extracted from herbs have been implied heuristically for centuries. The innovative potential of essential oils towards anti-microbial composites is highly appreciated, particularly while resisting against bacterial strains [13]. Medicinal and edible herbs like turmeric, oregano, rosemary, ginger, basil, clove, garlic and nutmeg have been effectively utilized either individually or in conjunction with other conservational procedures [14]. From food packaging to preservation and dentistry to medicine, more research data is being collected on the antibacterial properties of numerous essential oils. These all perplexes

makes them the best candidate in advancing their research in wound dressing applications [15]. Three different essential oils have been used in this research work.

Clove oil has been widely studied for its biological characteristics including antioxidant, antifungal, antibacterial and insecticidal properties [16]. Chami et al. used clove oil on the yeast model due to its anti-bacterial properties [17]. It has also been found operative against listeriosis and salmonellosis causing bacteria [18]. Strong antimicrobial and biological characteristics of clove oil are due to the presence of large amounts of eugenol in it [19].

Tea tree oil can be utilized in the number of medicinal ways together with keeping skin healthy and hair strong [20]. The presence of terpinen-4-ol in tea tree oil makes it a better candidate for fighting bacteria and fungi [21]. These antibacterial properties make this essential oil an esteemed natural cure in handling skin conditions and to stimulate wound healing [22]. Besides averting septicity in wounds, tea tree oil also boosts wound healing. Nano emulsions of tea tree oil were used. It showed good anti-bacterial and anti-fungal phenomena with no adverse effects [23].

Oregano oil is a herbal oil that is extracted from the oregano plant and is extensively reported to have therapeutic characteristics [22]. P.E. Simitzis et al. studied the effect of dietary oregano essential oil supplementation on lamb meat characteristics was investigated. No difference in weight was observed after supplementation of oil while its strong anti-oxidant effects enhances its long term frozen storage [24].

These three essential oils have been selected because of their anti-bacterial properties. Moreover, they have also been used in the packaging and in pharmaceutical industry but have never been incorporated in PVA/starch based hydrogel membranes. Dilutions of oils or in the form of gel for skin treatment had already been used and available in the market but incorporation in hydrogel membranes were done for the first time.

In this scenario, hydrogel membranes for wound dressing were fabricated through solution casting technique. The key interest is to promote the moist wound environment through enhanced anti-bacterial activity. Hydrogel membranes containing polyvinyl alcohol (PVA) and starch incorporated with essential oils were prepared. Morphology and molecular interaction among various polymers used in the hydrogel membranes were investigated by using scanning electron microscopy (SEM) and fourier transform infrared spectroscopy (FTIR). Atomic force microscopy (AFM) was used to find the roughness. Antibacterial testing was performed using the disc diffusion method. The physical and mechanical characteristics of the membrane were also considered to check their usefulness in practical application.

Experimental

Materials

Poly vinyl alcohol (Degree of Polymerization = 1500), glycerin and starch were supplied from Dae-Jung, Korea. Clove oil, tree tea oil and oregano oil of 100% purity was provided by plant therapy, Inc. Glutaraldehyde (50% aqueous solution) was purchased from Sigma Aldrich whereas ethanol of 99.7% purity from BDH Laboratory Supplies. Analytical grade Hydrochloric Acid (HCL) (37% purity) was purchased from Lab scan Asia Co. Distill water was used in the overall research.

Preparation of Hydrogel Membrane

The hydrogel membranes are prepared by solution casting method. 10% (w/v) of the PVA solution was prepared in water. The blend was heated at 70 °C for 2 h with continuous stirring until the solution became transparent. After that, 7% (w/v) of the starch solution was prepared, and heating was carried out for 15 min at 100 °C with continuous stirring to get a homogenized solution. Essential oils were added in varying concentrations to the starch solution and then it was cooled after the addition of essential oils. These starch/clove oil, starch/tea tree oil and starch/oregano oil solutions were then added to the PVA solution along with the cross-linking agent. The cross-linking agent was prepared by using 10 mL ethanol, 0.5 mL glutaraldehyde and 0.05 mL diluted HCl. Furthermore, PVA/Starch/Essential oil solution and crosslinking agents were mixed; 2 mL glycerin was added to the polymer/cross-linker mixture as a plasticizer. All the solutions were introduced to sonication for the preparation of homogenization solutions. Coldwater was used during the sonication process to control the temperature. The solution casting method was applied for the fabrication of membranes. After overnight drying, the hydrogel membranes

were extracted from the petri dish. Hydrogels were then stored in cool, dry and air free bags to avoid contamination. Table 1 shows the composition of hydrogels prepared.

Membrane Characterization

Scanning Electron Microscopy

SEM (JSM-64900) was employed to investigate the surface morphology of the hydrogel membrane. It also gives information about structure i.e., porous or dense membrane. The acceleration voltage of 10 kV was utilized and membranes were coating with a thin conductive layer of platinum/palladium.

Fourier Transform Infrared Spectroscopy

The dry and impurity-free samples of hydrogel membranes were directly exposed to FTIR. The spectra were noted in the array of 450 cm^{-1} to 4000 cm^{-1} . In the case of the hydrogel membrane, the samples were placed right in the FTIR machine for processing. But pellets are made for the powdered samples.

X-ray Diffraction

XRD analysis was conducted to determine phase identification and crystalline nature of prepared hydrogel membranes. The XRD was performed using XR D8 advanced (Bruker Germany). The membranes were used directly for the XRD analysis. The current and voltage of X-ray basis were 40 mA and 40 kV mA, respectively. The scanning of sample was done at step size of 0.04 while the step time is 0.5 s/step and 2θ ranges from 10° to 70°. The wavelength of $\text{CuK}\alpha$ radioactivity was 1.540 Å.

Table 1 Composition of hydrogel membranes

Sample no.	PVA:Starch (gm)	Cross-Linker	Oregano Oil (mL)	Tea Tree Oil (mL)	Clove Oil (mL)	Glycerin (mL)
1	5:3.5	Ethanol/GA/HCL	0.1	–	–	2
2	5:3.5	Ethanol/GA/HCL	0.2	–	–	2
3	5:3.5	Ethanol/GA/HCL	0.3	–	–	2
4	5:3.5	Ethanol/GA/HCL	–	0.1	–	2
5	5:3.5	Ethanol/GA/HCL	–	0.2	–	2
6	5:3.5	Ethanol/GA/HCL	–	0.3	–	2
7	5:3.5	Ethanol/GA/HCL	–	–	0.1	2
8	5:3.5	Ethanol/GA/HCL	–	–	0.2	2
9	5:3.5	Ethanol/GA/HCL	–	–	0.3	2

Atomic Force Microscopy

Surface roughness of the membrane is an important parameter to check the functioning in respect to biocompatibility. Atomic Force Microscopy, JOEL (JSPM-5200) was used to investigate topography; porosity and roughness. The 3-D micrographs images were taken. The AFM tip or cantilever in a raster scanning motion contacts sample surface. In this contact mode the repulsive forces between the tip and sample were converted into spatial variation of an image. The scanning area was approximately in $10\ \mu\text{m} \times 10\ \mu\text{m}$ and all the roughness parameter was determined by using AFM software. In the data “Ra”, “R_t” and “RMS” shows mean roughness and root mean square roughness, respectively.

Hydrophilicity

Tantec Contact Angle meter was used to study hydrophobicity and hydrophilicity of membrane. Single water droplet was allowed at dosing rate of $0.1\ \mu\text{L/s}$, with a constant dosing rate of $0.2\ \mu\text{L/s}$ using a micro syringe. The membranes were cut into thin strips and the sessile drop method was used for static angle. On an average thrice times the angle was measured. During the experiment the relative humidity and temperature were at ambient conditions.

Water Vapor Transmission Rate Measurement

To determine WVTR, 10 mL distilled water was poured into media glass bottles of 29.5 mm mouth diameter. These bottles were covered with hydrogel membranes, wrapped through Teflon tape and then were weighed. These bottles were located at $40\ ^\circ\text{C}$ inside an oven for 1 day [9]. After 1 day, they were weighed again and WVTR ($\text{g/m}^2\text{h}$) was evaluated using Eq. (1) [25]:

$$\text{WVTR} = (W_i - W_t) / (A \times 24) \times 10^6 \quad (1)$$

where, A is the area of the round opening of the bottle, W_i is the mass of bottle before heating and W_t is the weight of bottle after heating.

As the temperature of human body is $37.2\ ^\circ\text{C}$ so the testing was done at $40\ ^\circ\text{C}$ because the practical application of our research work is human skin. That's why the temperature was kept near to it in both of the cases i.e. water vapor transmission rate and moisture retention capability [26].

Moisture Retention Capability

Prepared hydrogel membranes were cut into equal pieces and weighed. These samples were then placed inside an oven

for 6 h at $40\ ^\circ\text{C}$. Later, they were removed from the oven and weighed again. Equation (2) was used to determine the moisture retention capability [9]:

$$\text{Moisture retention capability (\%)} : (W_{6\text{hrs}} / W_i) \times 100 \quad (2)$$

where, W_i is the initial weight and $W_{6\text{hrs}}$ is the weight in g after 6 h of heating at $40\ ^\circ\text{C}$.

Gel Fraction

The fabricated hydrogel membranes were cut into identical pieces and dried in the oven to get their weight constant. After attaining constant weight, they were assessed and put in de-ionized water aimed at 96 h. Afterwards, the hydrogel membrane samples were again dried in a vacuum oven until a constant weight is reached. Gel fraction was determined using Eq. (3) [27]:

$$\text{Gel fraction (\%)} = (W_t / W_i) \times 100 \quad (3)$$

where, W_i is the initial weight before immersing in distilled water and W_t was the final weight after drying.

Hydrogel Membrane Porosity

The hydrogel membranes were immersed into ethanol until they got saturated. Ethanol is used to wet the sample and immerse into it. Hydrogel membranes were assessed earlier and later having absorption in ethanol. Equation (4) was used for calculation of porosity [28]:

$$\phi = (W_2 - W_1) / (\rho V_2 - \rho V_1) \times 100 \quad (4)$$

where, W_1 and W_2 specify the weight of samples earlier and later having absorption in ethanol, respectively. V_1 is the volume of ethanol before absorption, V_2 is the volume of ethanol after absorption and ρ is density is the density of alcohol at room temperature.

Swelling Behavior Measurement

The capacity of the hydrogel membrane to absorb fluids that are surfaced by the wound is called its swelling behavior. The swelling behavior of prepared hydrogel membrane was examined contrary to H_2O (water), 0.9% MgCl_2 (Magnesium Chloride), 0.9% NaCl (Sodium Chloride) and blood. A 0.9% MgCl_2 and 0.9% NaCl solution is said to be isotonic: when blood cells reside in such a medium, the intracellular and extracellular fluids are in osmotic equilibrium across the cell membrane, and there is no net influx or efflux of water. To determine the swelling behavior of prepared hydrogel membranes, they were identically cut and balanced to be equal in size and weight. These samples were then immersed

into water, $MgCl_2$, NaCl, and blood solutions for 1 day and cleaned through filter papers and weighed again. The swelling percentage was determined using the Eq. (5) [29]:

$$\text{Swelling (\%)} = [(W_s - W_d)/W_d] \times 100 \quad (5)$$

where, W_s is weight of the swelled sample and W_d is weight of dry sample.

Tensile Testing

The prepared hydrogel membrane was primed for tensile testing by following the standing operating procedures as described in “SOP—Tensile testing of electrospun nanofiber membrane” [30]. Samples that were equal in thickness and had no surface defects were selected and were attached to the holding clamps of the universal testing machine. With a constant strain rate of 10 N/mm², the clamps were allowed to move in opposite directions and the stress over hydrogel membrane samples was recorded.

Anti-Bacterial Activity Measurement Disc diffusion method was used to measure the anti-bacterial activity of fabricated hydrogel membranes. Two bacterial strains have been used for this purpose i.e. Gram Negative *Escherichia coli* and Gram-Positive *Staphylococcus aureus*. The bacteria were cultivated in a test tube having broth in it, then it was sited in a shaky water bath at a temperature of 37 °C. The agar media was arranged by dissolving 11.5 g nutrient agar in 500 mL distilled water. This agar solution was then consistently decanted into the petri dishes and was left for few minutes to freeze it. The bacteria was spread on these petri dishes with the help of spreader. The fabricated hydrogel membranes were cut into 6 mm disks and were positioned over the agar plates. Later, they were sited into an incubator for 24 h at 37 °C. Then, the plates were taken out and region of inhibition were measured by Vernier calipers. The negative control was a PVA/St membrane without essential oil while the positive control was gentamicin. All the apparatus was autoclaved which includes petri dishes, forceps, pipette, spreader, LB broth and agar media. The purpose of doing autoclave was to avoid contamination.

Statistical Analysis

ANOVA two factor without replication was performed on all analysis to calculate the statistical significant and non-significant. In table “ss”, “df” and “ms” represent sum of squares, degree of freedom and mean square, respectively. The ANOVA table of gravimetric has provided as significant value of less than 0.05 ($p=0.05$). Anti-bacterial test has provided us higher value in the case of oregano oil. Hence, they have no effect on the *E. coli* and MRSA. Hence, this proves

the effect of essential oils as anti-bacterial agent when incorporated in hydrogels. Moreover, it also depending on their concentration levels.

Results and Discussion

Morphological Analysis

The results of SEM show that the morphology of the hydrogel membrane was dense, and there were no pores even at advanced magnifications. The dense surface of the hydrogel membrane restricts any bacteria passage and approach to the wound. As oils are hydrophobic in nature and immiscible in water, their particles are seen on the surface through SEM images. Figure 1 shows the SEM of a pristine hydrogel membrane. Smooth and homogeneous surface of hydrogel films are obtained because of the absence of essential oils. On the other hand, Fig. 2a–c shows the SEM images of oregano oil with concentrations of 0.1, 0.2 and 0.3 mL, respectively. The following similar observations were obtained from the results as in literature [31]. The surface becomes rough with an increase in essential oil concentration. The essential oil becomes immiscible in water above 0.3 mL concentration due to its hydrophobic nature. The micro porosities range from few microns to macro voids were distributed evenly on the surface. The roughness causes issue in the biocompatibility of the membrane as more wound healing cells such as fibroblasts and keratinocytes will adhere to the surface. When we go into the chemistry of oregano oil, it has carvacrol component present in it. The structure of carvacrol shows that it has the phenolic group, while three methyl groups and one hydroxyl group is attached to it. When the concentration of oil in hydrogel membranes increases from 0.1 to 0.3 mL, agglomeration starts to take place. This

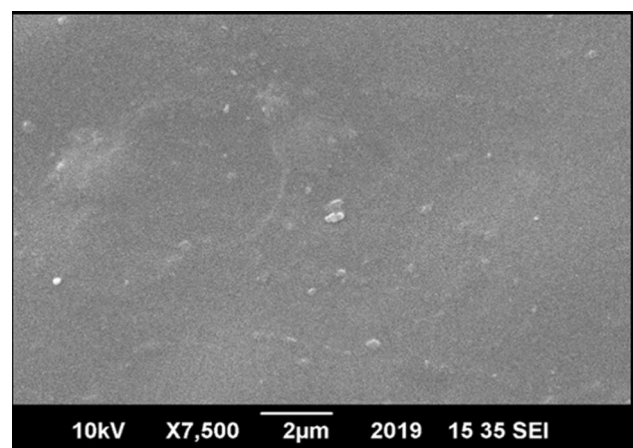


Fig. 1 Surface morphology of pristine hydrogel membrane

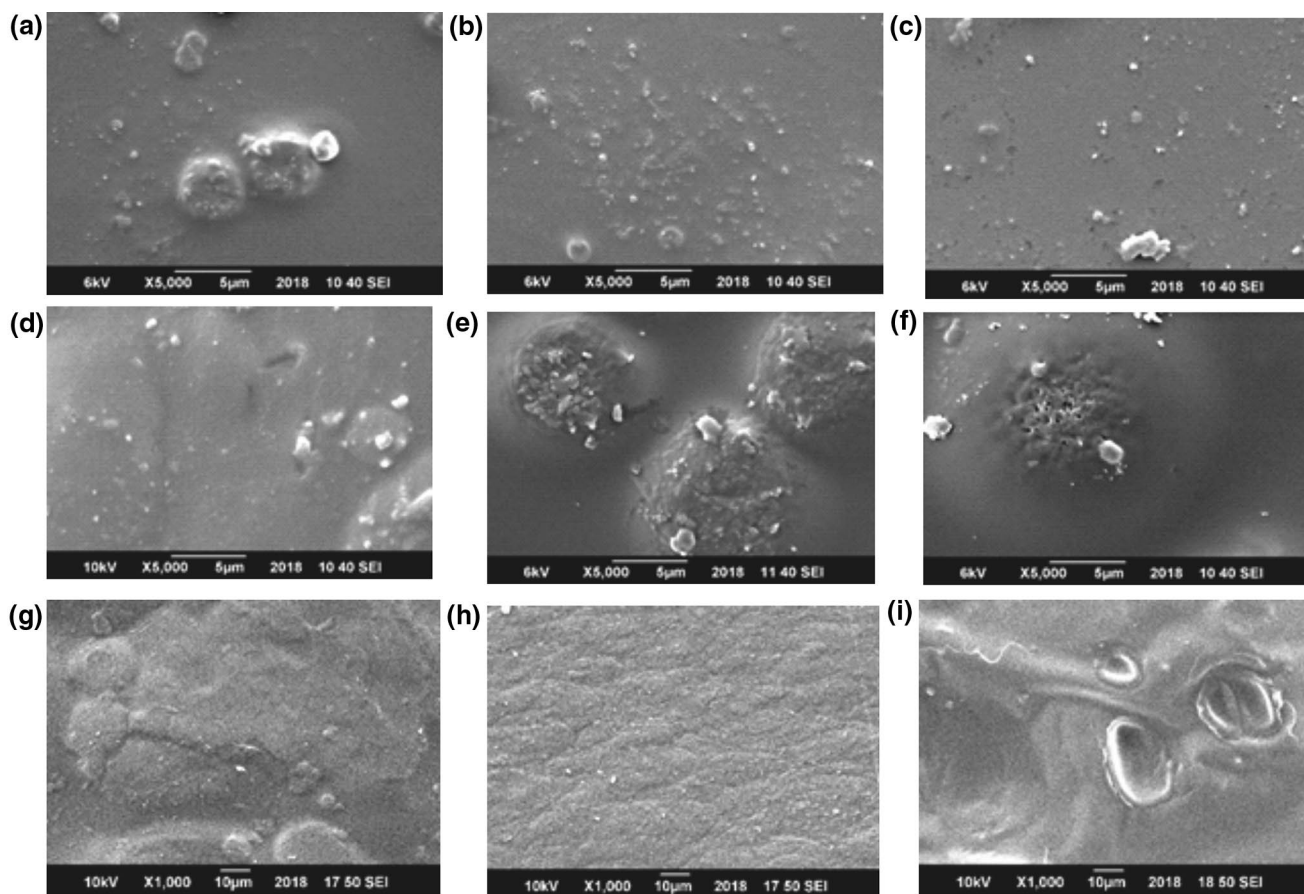


Fig. 2 SEM Images of hydrogel membranes using essentials oils; **a** 0.1 mL tea tree oil, **b** 0.2 mL tea tree oil, **c** 0.3 mL tea tree oil, **d** 0.1 mL clove oil, **e** 0.2 mL clove oil, **f** 0.3 mL clove oil, **g** 0.1 mL oregano oil, **h** 0.2 mL oregano oil, **i** 0.3 mL oregano oil

is due to the presence of three methyl groups. They are not soluble in polar solvents [32]. Figure 2d–f shows the hydrogel membrane with concentration of clove oil 0.1, 0.2, and 0.3 mL respectively. 0.1 mL clove oil has shown best results as no pore formation takes place and all the oil particles are trapped within the 3-D structure of the membrane. Whereas, the formation of macro voids represents the rapid evaporation of the oil. These results are also validated by anti-bacterial testing. It is also observed from the SEM that the insoluble particles of oil become visible with the increase in essential oil concentrations. But as the concentration of clove oil is increased above 0.3 mL, pores start to generate because of their immiscibility in water. This is because at higher concentrations hydroxyl group becomes less efficient and phenolic group becomes dominant which is not suitable for polar solvents [33].

Figure 2g–i shows the result for tea tree oil concentrations. Similar, results are obtained within oil as well. Pores started to generate above 0.3 mL as the concentration of oil is increased in the hydrogel membrane. This is because of the presence of phenolic group present in it because it is not soluble [34].

From the SEM images of all hydrogel membranes, it has been observed that the clove oil and tea tree oil has more smooth surfaces than the oregano oil. This is because of the presence of hydroxyl group attached to them while oregano oil has three methyl groups which are not soluble resulting in rough surface. But when the concentration of oil is increased in tea tree and oregano oil, the phenolic group becomes more dominant that's why pores started to appear.

Fourier Transform Infrared Spectroscopy

The FTIR results designate the occurrence of hydroxyl groups which are accountable for water holding capacity in hydrogel membranes. Figure 3a shows the FTIR of the hydrogel membrane have a similar peak around 3300 cm^{-1} which represent the hydroxyl group present in PVA, Glycerin and Starch. This peak is present in all formulations. Clove oil consists of eugenol, eugenyl acetate and caryophyllene. There is no change observed in the spectra with increase in concentration of clove oil. First of all, the broad peak at $3000\text{--}3500\text{ cm}^{-1}$ is observed. This can be ascribed to the presence of OH group. It broadens due to the presence

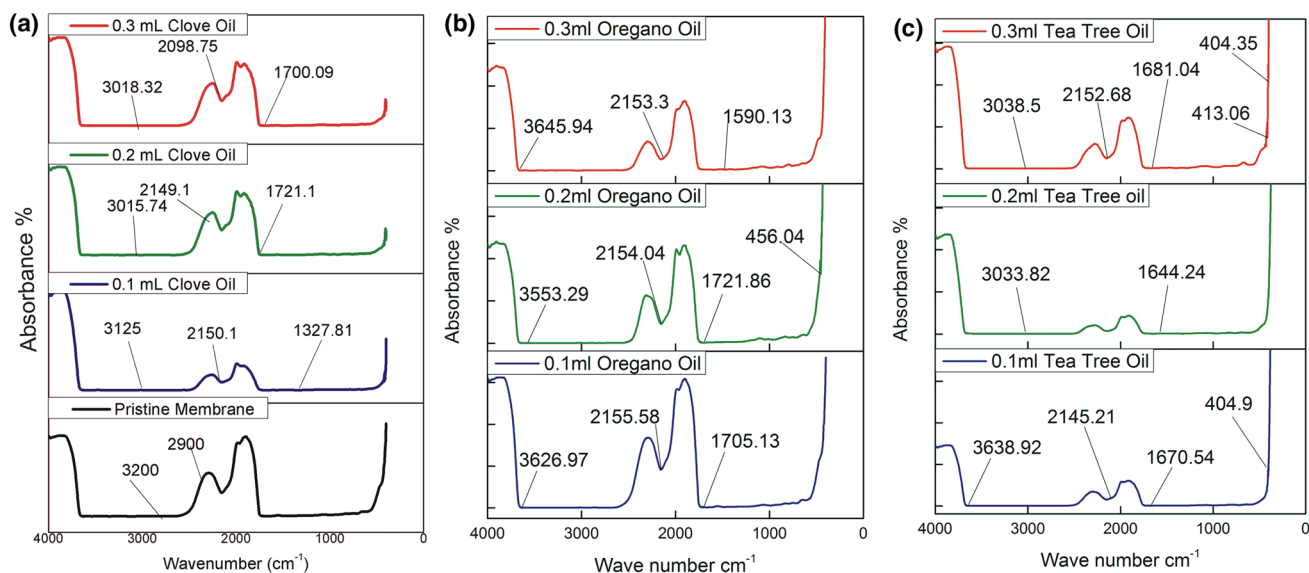


Fig. 3 FTIR spectra of hydrogels with essential oils at different concentrations

of the carboxyl group due to acetate group [35]. Moreover, the peaks between 1600–1800 cm^{-1} is due to the presence of C=O and C=C double bonds found in all the three major components of clove oil [36]. Also, the Csp²-H bond is signified in the wavenumber range greater than 3000 cm^{-1} as seen in all spectra [37]. The presence of hydroxyl group handles its water holding capacity. The stronger the peak of the hydrogel membrane, the higher will be the tendency to absorb water and exudates coming from the wound. The main difference occurring in the functional group peaks is due to the transmittance difference in the various concentrations. The intensity of the essential oil in hydrogel membranes dependent directly on the concentration, because of presence of anti-oxidants.

Figure 3b shows the FTIR spectra of tea tree oil. The main components of tea tree oil are alpha and gamma Terpinene along with Cymene and Cineole. In these spectra, the broad peak between 2000 to 3000 cm^{-1} can be attributed to the presence of the abundant and interconnected Csp²-H bonds as well as the Csp³-H bonds [38]. Other than that, the only peak to be mentioned are the prominent peaks between 1600–1800 cm^{-1} , which is due to the presence of C=C double bonds [39]. These are the only bonds found in the components making up tea tree oil.

Figure 3c shows the FTIR spectra of oregano oil. In the case of oregano essential oil, the major components are carvacrol, beta-fenchyl alcohol, thymol and gamma-terpinene [40]. The main component functional groups are O–H, C=O and C=C as well as Csp²-H and Csp³-H. O–H as well as the presence of C=O bond is proven by the excessively broad peak at 2500–3500 cm^{-1} . This same region also contains the peak for Csp³-H at less than 3000 cm^{-1} , and Csp²-H at

a value slightly greater than 3000 cm^{-1} . The peaks between 1600 and 1800 cm^{-1} signify the presence of both C=O and C=C bonds [41]. The sharp and broad peak further validates the presence of a wide array of both C=O and C=C double bonds.

X-ray Diffraction

XRD spectrum tells us about the nature of material crystallinity. Figure 4 shows the XRD spectrum of PVA/Starch hydrogel membrane with essential oils. For PVA/Starch hydrogel membrane with essential oils, single peak was detected at 19.8°, (101) plane of PVA and no other sharp peak can be seen in the pattern. The amorphous nature of PVA/St membrane was hence proved by XRD analysis. This typical diffraction peak confirms the presence of hydrogen bonds between hydroxyl groups present in PVA [42]. From the XRD spectrum, it has been observed that essential oils do not show any peaks. This is due to the absence of crystallinity in them [12]. Varying the essential oil concentration does not affect the lamellar structure [43].

Atomic Force Microscopy

The PVA/Starch formulated membranes were studied under “tapping mode” and results are presented in Fig. 5. The dark regions represent depression whereas the lighter region represents height in 3-D images of membranes topography [44].

The results of pristine membranes showed smoothest surface among all the formulated membranes. However, the smoothness started to decrease after the incorporation of essential oils. It can be ascribed to the immiscibility

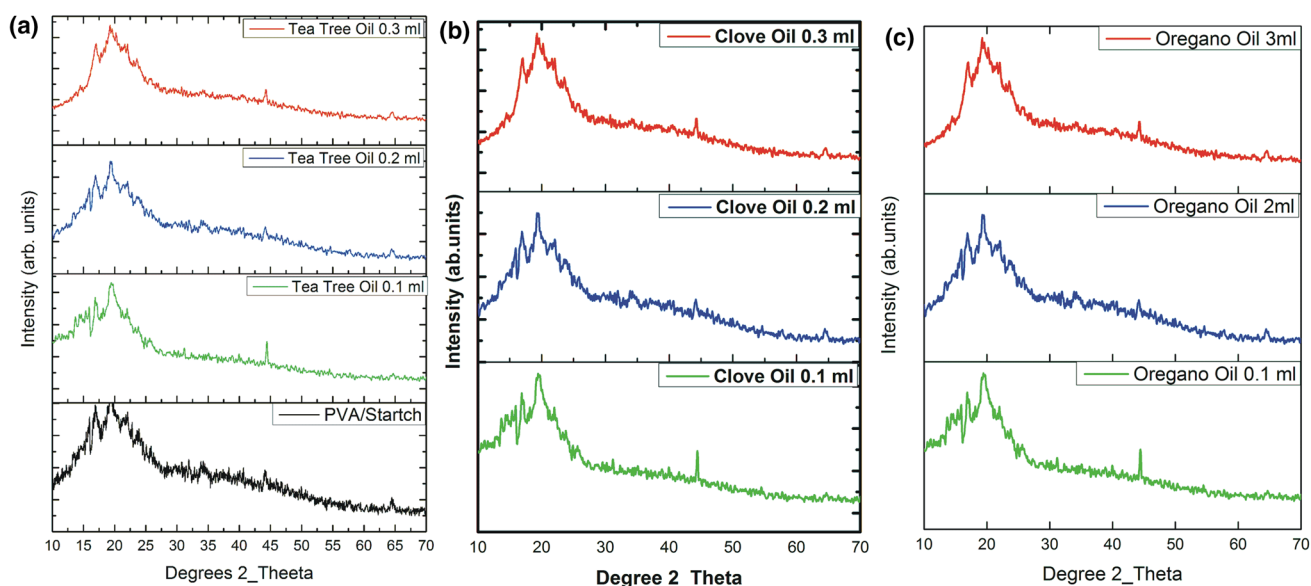


Fig. 4 XRD spectrum of hydrogels with essential oils at different concentrations

of essential oils at higher concentrations in membranes thus forming pores at micro and Nano level, which formed heightened structures [45]. The tea tree oil has the lowest roughness as compared to clove oil and oregano oil due to high hydroxyl group which forms a uniform structure as compared to other two oils.

Hydrophilicity

For material contacting the human skin, a balance between the hydrophobic and hydrophilic is important [46]. All formulated membranes have contact angle less than 90 as shown in Table 2 and Fig. 6, thus making them hydrophilic in nature. The presence of hydroxyl group, carboxyl group and phenolic groups form hydrogen bonding and Van der Waals's forces creates physical bonding with water which lowers the contact angle [47].

Table 2 represents the behavior of essential oils incorporated in hydrogel membranes. At lower concentration, hydrogen bonding is produced. However, as the concentration increases the phenolic group overshadows the hydroxyl group of PVA. This results in higher contact angle. The essential oils showed hydrophilic behavior at lower concentrations. However, membranes become hydrophobic at higher concentrations of essential oils. For hydrogels, hydrophilicity is an important factor because it produces a crosslinking between the membranes and anti-bacterial agent.

Water Vapor Transmission Rate (WVTR)

Hydrogel membranes sustain the humid environment underneath the wound, thus curtailing the fluid loss. Water loss without any dressing film as reported in the literature for second degree burn skin wound is $178.55 \pm 4.5 \text{ g/m}^2\text{h}$ and that of third degree is reported as $143.2 \pm 4.5 \text{ g/m}^2\text{h}$ [48, 49]. Water loss in the body occurs through two processes: sweat glands and diffusion take place through the body at low relative humidity regions. 70% of the inner milieu of the body is water and 20% of it is retained in the skin. The epidermis and dermis of the layer have sweat glands in which there is 70% of moisture. The second degree burns mostly affect the dermis of the skin whereas in the case of third-degree muscles loss takes place. Without any dressing, major water loss happens in a second degree [50]. The higher WVTR indicates that the wound will dry up quickly while if the WVTR is low it will slow the process of healing and will increase the bacterial infections [51].

Figure 7a shows the graph for WVTR of hydrogel membranes using essential oils. The hydrogels prepared without essential oil has the WVTR of $61.25 \pm 3.06 \text{ g/m}^2\text{h}$. By adding essential oils, it was observed that the clove essential oil provides the best WVTR results of $36.22 \pm 1.81 \text{ g/m}^2\text{h}$ with only 0.1 mL. The WVTR decreases due to the increment of clove oil. This is because of the presence of hydroxyl group in clove oil. Therefore, it is evident that clove oil induced hydrogel membranes can preserve the wound environment and consequently results

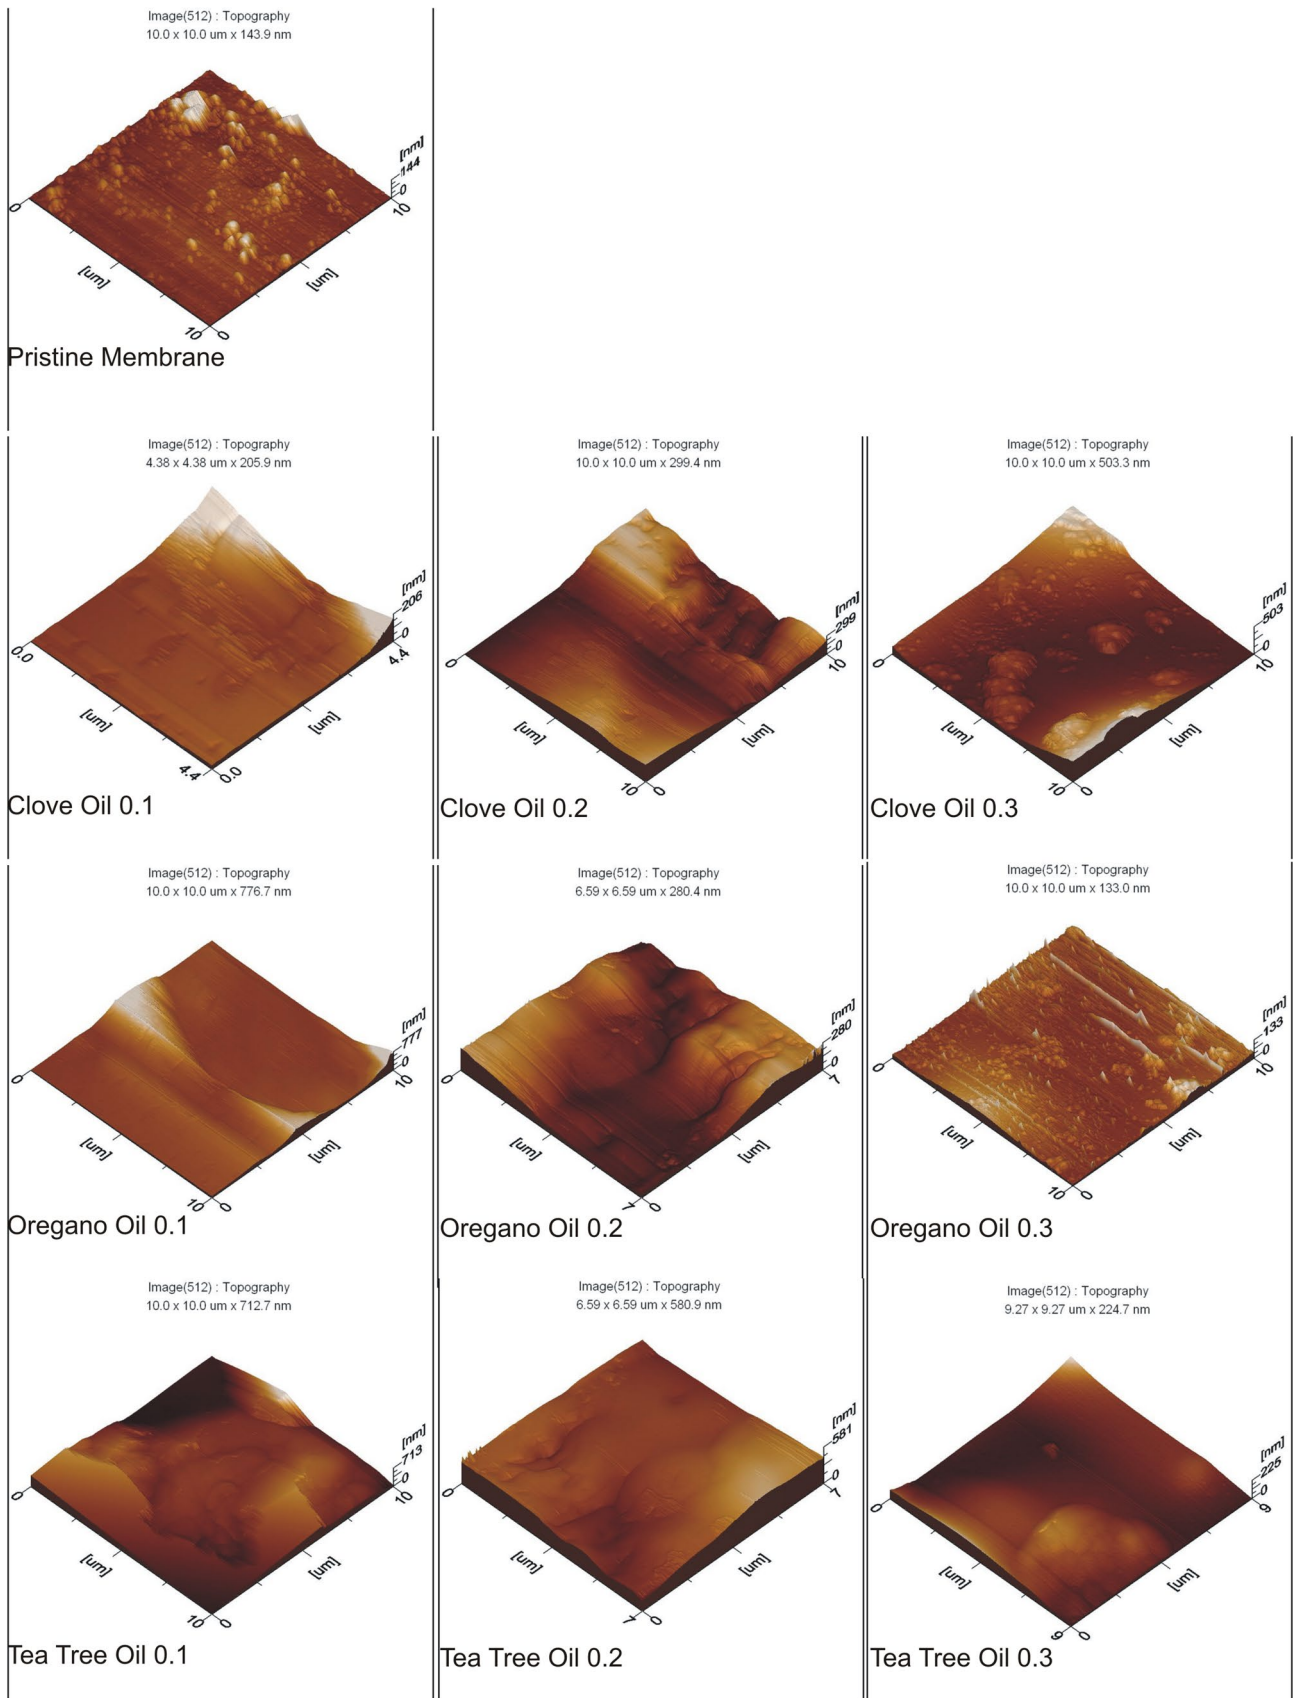
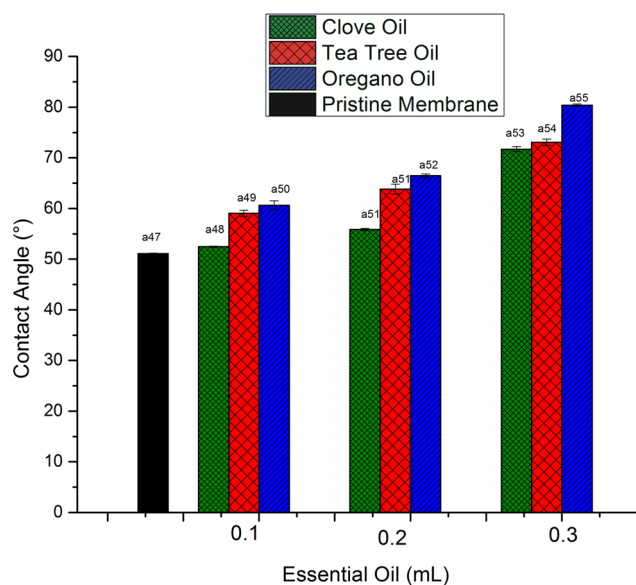


Fig. 5 AFM analysis of hydrogel membranes with essential oils at different concentrations

Table 2 Contact angle measurement of hydrogel membranes with essential oils at different concentrations

Sr. no.	Classification	Essential oil (mL)	Contact angle	Standard deviation
1	PVA/starch	–	51.1	0.11
2	PVA/starch/clove oil	0.1	52.45	0.11
3	PVA/starch/clove oil	0.2	55.85	0.23
4	PVA/starch/clove oil	0.3	71.7	0.522
5	PVA/starch/tea tree oil	0.1	59.05	0.6
6	PVA/starch/tea tree oil	0.2	63.8	0.98
7	PVA/starch/tea tree oil	0.3	73.05	0.65
8	PVA/starch/oregano oil	0.1	60.65	0.87
9	PVA/starch/oregano oil	0.2	66.45	0.355
10	PVA/starch/oregano oil	0.3	80.4	0.22

**Fig. 6** Contact angle measurement of hydrogel membranes with essential oils at different concentrations


in minimal loss of fluid from the wound. However, a tea tree showed WVTR of 45.63 ± 2.28 g/m²h and oregano oil of 51.15 ± 2.55 g/m²h has shown the best results in their respective composition. This can be attributed to the fewer pore formation on the membrane surface morphology which causes more water retention. The essential oils are immiscible in water and leached out of the membrane through the drying process which resulted in the generation of pores and macro-voids. Hence, clove oil shows the best result then the tea tree and oregano oil. Clove oil has hydroxyl group present with the phenolic group. However, oregano and tea tree oil has methyl and phenolic

groups present which are not soluble in polar solvents. Therefore, their WVTR value is less than the clove oil. However, with the increasing concentration of clove oil the phenolic group becomes more dominant which also becomes insoluble. The water content plays a characteristic role in polymeric network formation. In gel system, water is present in three different structures: bulk water in which polymers are dissolved and present within the matrix, interfacial water has a certain cage like geometry and hydrated water. The presence of water introduces the biocompatibility in the hydrogel as mimicking the function of water in the human cells [52].

Moisture Retention Capability (MRC)

The measure of moisture that is preserved inside the hydrogel membrane is termed as its moisture retention capability. The WVTR of any hydrogel membrane is inversely proportional to MRC i.e. higher the amount of vapour loss, lower will be the tendency of the membrane to hold moisture, which makes it difficult for the wound to get a healing environment. It is reported in the literature that lack of moisture at the wound's surface will halt cellular migration, decrease oxygenation of the blood and vastly delay the wound treatment process [53]. Furthermore, many advantages of moist wound treatment over dry wound treatment have been reported. The moist environment helps in mimicking of skin functioning and tissue regeneration. Therefore, it can be inferred that hydrogels that have a large tendency to retain moisture content hold a better chance to be used as wound dressings.

It can be seen in Fig. 7b, the highest MRC value was obtained at 0.1 mL of clove oil with $95.50 \pm 0.48\%$, while that of neat hydrogel was 90%. The MRC values of tea tree and oregano oil was 93 and 92%, respectively. As discussed in the WVTR, the decrease in the values of other than clove oil owes the occurrence of methyl and phenolic groups present in them. These results are in line with the WVTR results and confirm that lower the WVTR, higher will be the corresponding MRC. The results showed that essential oils especially clove oil is the best candidate for wound dressing applications. But with the increase in concentration of clove oil, the value of MRC decreased. This is ascribed to the dominance of phenolic group present in it. It provides more than 90% moisture prevention within the wound when use in small concentrations. Due to hydrophobicity of the oils as the concentration increases the retention decreases or vice versa. Thus, it can maintain the healing environment under the dressing and prompts the healing procedure [54]. Consequently, the MRC is reduced which entails the non-suitability of higher concentrations of essential oils.

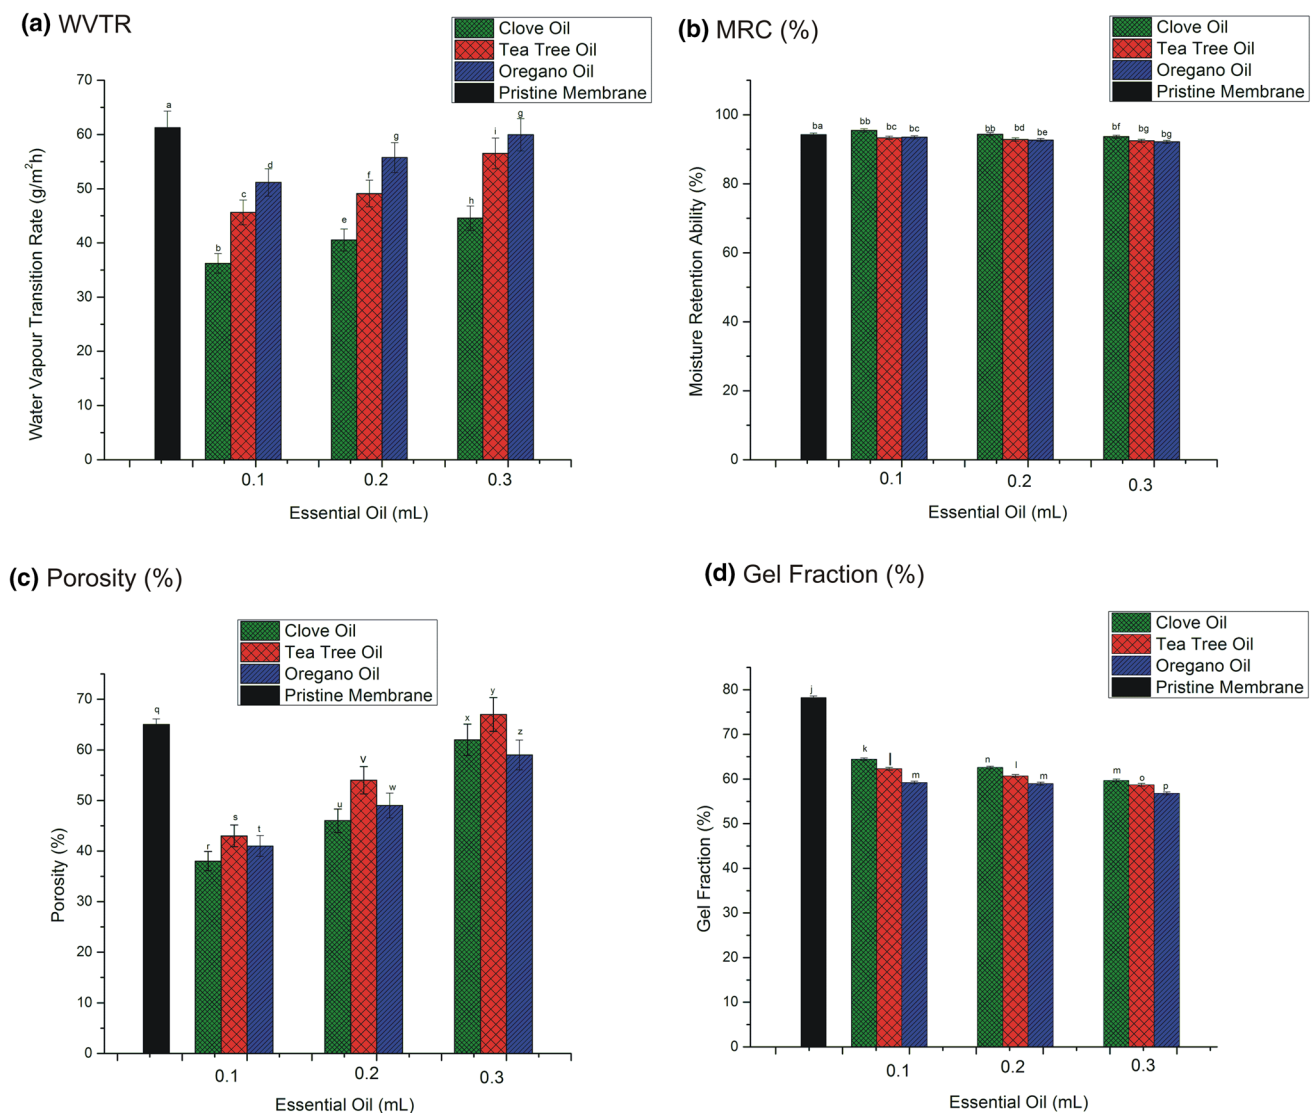

Bars with same alphabets are not significantly different ($p > 0.05$) from each other

Fig. 7 Physical testing of hydrogels **a** WVTR of PVA/starch/essential oil hydrogel membranes. **b** MRC of PVA/starch/essential oil hydrogel membranes. **c** Porosity of PVA/starch/essential oil Hydrogel Membranes **d** Gel Fraction of PVA/starch/essential oil hydrogel membranes

Hydrogel Membrane Porosity

Porosity is more likely to depend on the fabrication process of membrane, relatively than the compositions [55]. Porosity of hydrogel membranes have been calibrated by using the alcohol displacement method [56]. The porosity of neat hydrogel membranes is 54%. Porosities of hydrogels using essential oils has been observed in Fig. 7c. It has been observed that the porosity is enhanced as the concentration of the oil is increased in the hydrogel membrane. Hydrogels used as wound dressing allow the permeation of gases such as oxygen, water vapors to maintain the moisture in the dressing and small protein molecules while retaining the microorganisms [57]. The percentage of porosity for 0.1 mL

clove oil is 38%. However, as the concentration is increased it goes up to 62%. The porosity of tea tree oil was observed 43% for 0.1 mL concentration and 67% for 0.3 mL. Furthermore, porosity of oregano oil is 41% at 0.1 mL concentration and 59% for 0.3 mL concentration. The porosity in the range of (30–40)% is considered good for heal wounding [58]. The size and the surface of membranes containing pores tells us how much it uptakes water. The proportion of the water must be less than 40–60% to get transparent hydrogels. Whereas, if the content increased to 80%, phase separation occurs and the macroporous network is obtained [59]. The porosity of the membrane is highly dependent on the water content presented during the synthesis of a membrane in the polymer solution. It can also be observed from SEM images

that increasing the concentration of essential oils enhances porosity as the profile pattern represents. Moreover, when the concentration of oil was increased more than 0.3 mL these pores become macro voids.

Gel Fraction

Polar, naturally hydrophilic and synthetic polymers are crosslinked through physical or chemical processes forming a 3-D network and bonding a large number of water molecules (up to 100 g/g or higher) [60]. The gelation percentage is done to evaluate how water is affected by temperature parameters. Gel fraction (GF) test is performed to check how much the cross linker is effective. The crystallinity of network and extent of crosslinking determines the gel fraction values. Also, it influences the flexibility and strength of the films. Secondly, the burn patients are treated in cold environments so that there wound does not disintegrate and deteriorate more. The gelation percentage of neat PVA/Starch hydrogel membrane was found to be $78.24 \pm 0.39\%$. this was the maximum value attained. This high value can be attributed which indicates the PVA and starch cross-linking has taken place to form a 3-D network [43].

Figure 7d shows the graph of gel fraction with essential oils. With the increment of essential oils, the gel fraction starts to decrease. This is because with the increasing concentration the cross linking becomes poor [27]. The gel fraction of 0.1 mL clove oil is 64%. However, 0.3 mL clove oil is 59%. Tea tree oil and oregano oil has gel fraction concentrations in the range of 61–56% and 58–53%, respectively [61]. Higher gel fraction is suitable for hydrogel membranes. It tells the extent of cross linking taken place between materials used for the fabrication of hydrogel. It has been observed 0.1 mL clove oil gives the best results. As discussed earlier, this is attributed to the presence of hydroxyl group [62]. While, the oregano and tea tree oil has methyl and phenolic group present. This is not soluble in polar solvents.

Swelling Behavior

A hydrogel to be used as a wound dressing should absorb fluids that surfaced over the wound [37]. Swelling is considered a chief and significant criterion for evaluating how a membrane will behave with the wound. Wound exudates are absorbed by the membrane; it prevents wound maceration and the healing process is achieved. The degree of swelling can be affected by pH, temperature, nature of the chemicals, wound environment and degree of crosslinking [51]. Swelling is controlled by hydrogen bonding in the water molecules [63]. Starch and PVA have the affinity to absorb moisture from the environment and hold it together, owing to the existence of –OH radicals within their polymeric chains [64]. Starch maintains equilibrium by absorbing and

desorbing water molecules from the atmosphere. On the other hand, the ability of cross-linked polymer to absorb moisture decreases since cross-linking causes the formation of compact 3D structures and consequently the amount of –OH radicals decreases [65].

The swelling behaviors of prepared hydrogel, membranes were tested against water, blood, $MgCl_2$ solutions, and NaCl solutions as shown in Fig. 8. These solutions are used for testing because of the presence of their excess amount in human body. It could be seen that the swelling behavior of hydrogels is highest at 0.1 mL concentration of essential oils. The 0.1 mL clove oil within the polymer matrix has given the 135, 176, 121 and 118% swelling in all the fluids with respect to other essential oils. The swelling capacity is moderately good for tea tree and oregano oil. Their swelling behavior is also higher than 100%. Thus, implying their use in wound dressing. As the concentration of essential oil is increased the swelling behavior decreases. This is due to the interaction of oil with the cross-linking sites of PVA/Starch co-polymer [66]. Secondly, as the crosslinking density decreases due to the presence of oils swelling percentage reduced due to decrease in the entanglement of polymeric chains. This interaction causes an increase in the amount of free –OH radicals, thus promoting moisture absorbing capacity and increasing the swelling ability [67]. The propensity of PVA/Starch hydrogel films to swell decreased with the increase in essential oil concentration. This can be accredited to the precipitation of essential oils over the hydrogels at higher concentrations and eventually, voids are created within the membrane [68]. The decrease in swelling behavior percentage can also be explained by the analogous increase in the gel fraction percentage which implies the increase in the rigidity of cross-link due to the addition of essential oils.

The swelling behavior is highest against blood which makes them suitable for wound dressing applications. The maximum value of welling is achieved with blood. This may be attributed to the circumstance that crosslinking strengthen the molecular spacing between the chains and weaken the hydrogen bonding [69]. Furthermore, a supplementary osmotic pressure is formed owed to the ionic nature of blood that increases the electro-neutrality effect and origins swelling. Moreover, blood has the property to form clots [70]. Because of development of clots, extra capacity is formed inside the system, that allows more fluid to penetrate inside. With the increase in amount of essential oils, the structure was disrupted, and the macromolecular chains were extended straightforwardly [71].

The second highest swelling behavior is seen against water and then the salt solutions. The hydrophilic groups have a greater influence in swelling. It is started when water is exposed to the membrane and due to the concentration gradient, it starts moving into the polymer matrix. The

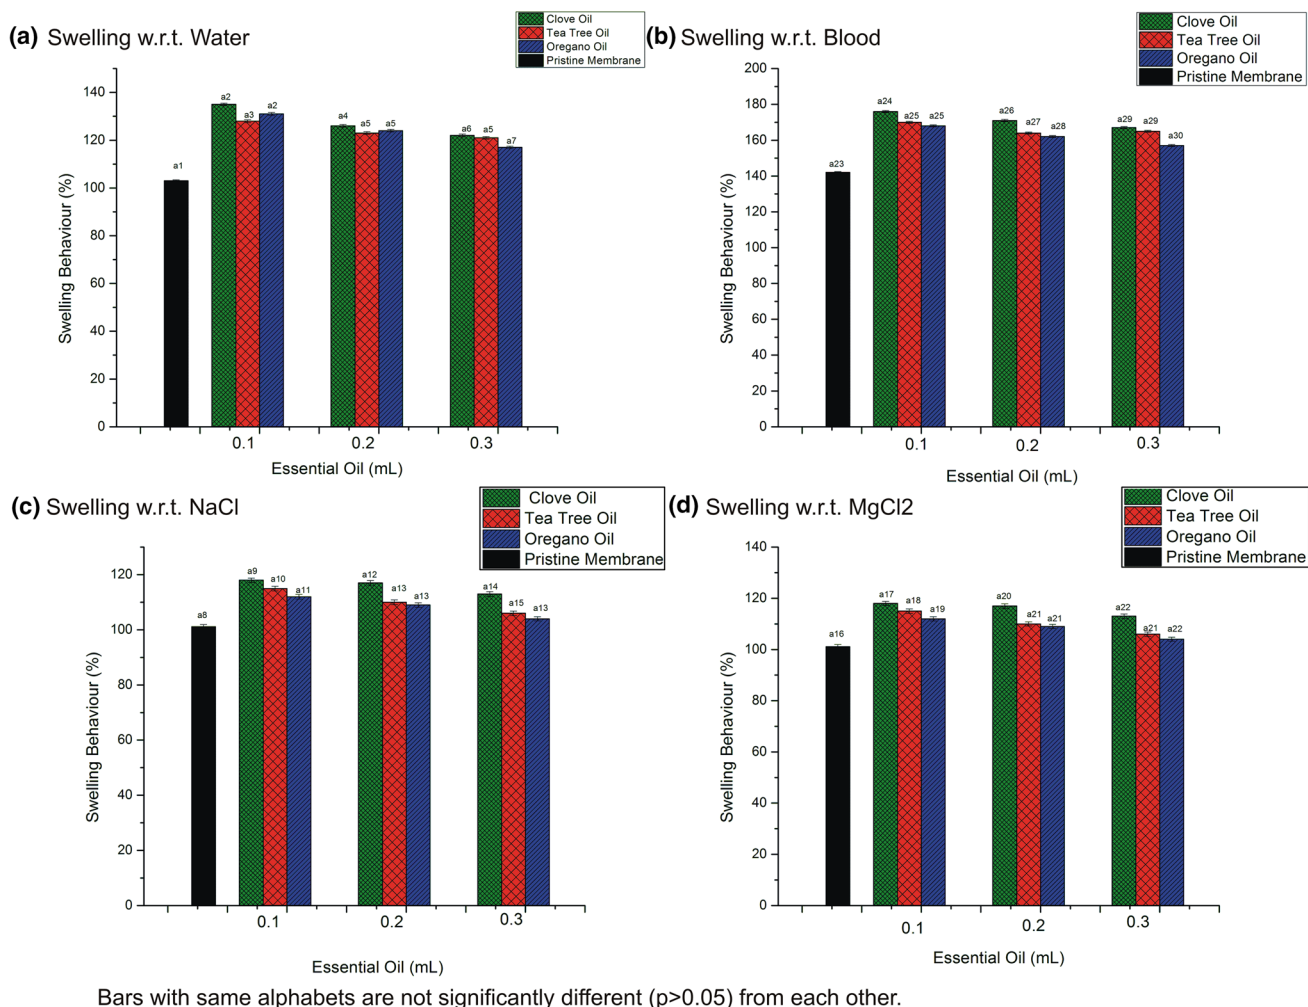


Fig. 8 Swelling behavior of PVA/starch/essential oil hydrogel membranes against water, blood NaCl and MgCl₂

–OH group present on the essential oils attract the water and forms weak Van der Waals bonding. This mechanism is taking place at the macro-molecule level. The reduction in the crystallinity of PVA is also attributed to high swelling as already seen in XRD graphs. For the case of a salt solution, it is of the minimum value. The electrostatic repulsion due to the presence of the ionic charge on the salts induced the swelling, the stops the accumulation of polymeric chains and tend to increase the matrix [72]. As the ionic strength is improved, the osmotic pressure change arises between the polymer matrix and solution. This deferred the water penetration into the matrix triggering swelling volume transition [73].

pH is another vital factor that rules the swelling behavior of hydrogel membranes. The pH of 0.9% MgCl₂ (Magnesium Chloride), 0.9% NaCl (Sodium Chloride), H₂O (distilled water) and blood is 6, 7, 7 and 7.45 respectively. While for native skin the pH is in the range of 4.7–5.45 and that for injured skin is 7.15–8.93. Therefore, it is quite evident from

the results that increase in pH enhances the degree of swelling. Consequently, swelling ability also upsurges.

Tensile Testing

Many natural and synthetic polymers have been developed for the treatment of wounds, but low mechanical properties and weak water absorption capacity limited their application in tensile testing. The mechanical properties of all formulated hydrogel are investigated by measuring tensile behaviour. Mechanical strength defines the integrity of the hydrogel membrane during the handling and dressing on the patient's body. The mechanical properties such as breaking stress (MPa) and percentage elongation (%) at the break of all formulated membranes were investigated by using a Universal tensile machine (UTM). The hydrogel membranes should have sufficient strength to engage these frictional stresses without breakage.

Neat hydrogel membrane showed good tensile strength i.e. 26.5 MPa. During the wound healing process, the hydrogels withstand the frictional stresses while attachment on the skin and absorb the moisture without any rupture. The tensile strength of the human skin is up to 11.5 MPa. The strength of the hydrogel should be higher than the skin as mentioned above [9]. The 0.1 mL clove has shown better result in all the specimens. With the incorporation of essential oils, the tensile strength undergoes deterioration. As observed from porosity and gel fraction, the cross linking reduces with the increase in essential oils. Hence, tensile strength starts to decrease. Their reduction in values was due to a decrease in chain length and mobility of the polymer chain due to the incorporation of essential oils [74]. Incorporation of oil decreases the breaking stress. The reduction in value was due to a reduction in polymer content [75]. The essential oils are not been entirely soluble in water so it gives the weak point for breakage [68]. Clove oil 0.1 mL gives the maximum breaking stress i.e. 19.55 MPa. However, tea tree and oregano oil has maximum breaking strength stress of 18.7 and 14.5 MPa, respectively as shown in Fig. 9. This can be qualified to presence of essential oils as mentioned above in water vapor transmission rate. Similar trend is observed in the percentage elongation results. As the concentration of oils was increased, its pore size decreased. Therefore, the membrane becomes more brittle.


Anti-Bacterial Activity

Anti-bacterial activity is of key importance in the hydrogel membrane essential for the healing of wounds. Almost all anti-bacterial agents (essential oils) showed good results

when incorporated with hydrogels. However, the best result was obtained from clove oil with 0.1 mL concentration in PVA/Starch hydrogel membrane. The neat hydrogel membrane in which there was no anti-bacterial agent present did not show any anti-bacterial activity.

Clove oil incorporated in polymer hydrogel give excellent antibacterial activity. Clove oil showed good resistance against gram positive bacteria (MRSA) and gram negative bacteria (*E. coli*) i.e., *Staphylococcus aureus* and *DH5-ALPHA*, respectively. For MRSA, 0.1 mL clove oil shows the best results and its antibacterial activity was in 39 ± 0.57 mm while that of 0.3 mL is 34 ± 0.42 mm while that for *E. coli* is in the range of (37–31 mm) from lower to higher concentration. It has been observed from results with increasing concentration the inhibition zone decreases, and it gives the less anti-bacterial activity. The larger zones of inhibition were achieved for gram negative bacteria than that of gram positive and this is due to their thick cell walls as shown in Fig. 10. The key component in the clove oil is eugenol which is around 80–90% [76]. This is insoluble in water [77]. Hence, with an increase in the concentration of clove oil, its solubility decreases. Therefore, it becomes less homogeneous and the anti-bacterial activity decreases [78]. Figure 11a shows the anti-bacterial activity against clove oil with all concentrations in which 0.1 mL showed the best results.

The use of tea tree oil with hydrogel membranes shows good anti-bacterial activity. But the tea tree oil shows less inhibition zones than clove oil. The main constituent of the tea tree oil is terpinen-4-ol which show resistance against both gram positive (MRSA) and gram-negative bacteria (*E. coli*). The inhibition zones in MRSA are in the range

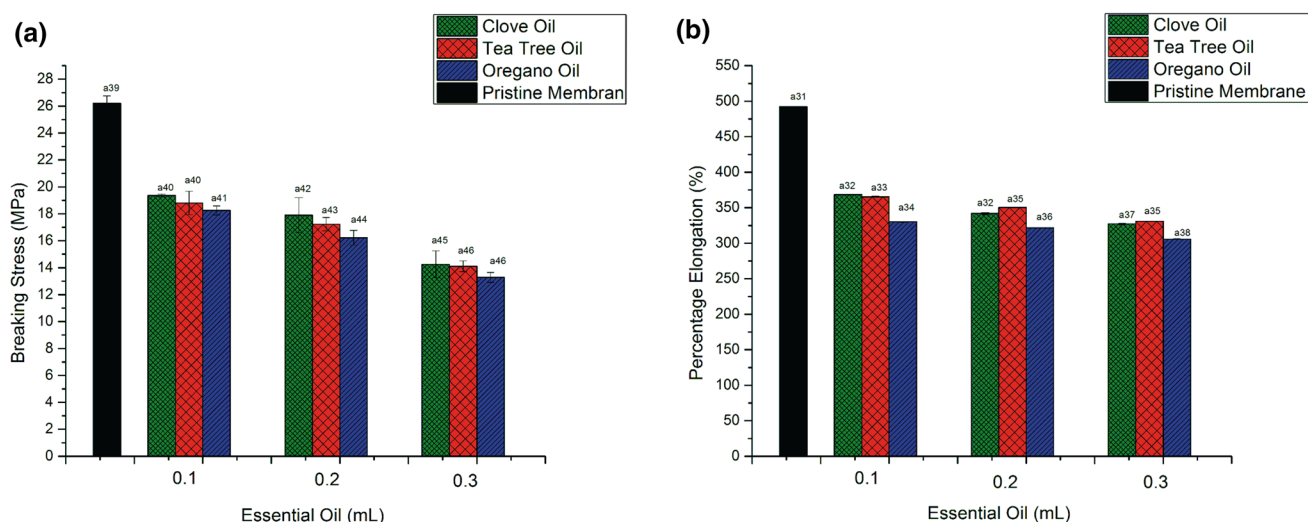

Bars with same alphabets are not significantly different ($p > 0.05$) from each other.

Fig. 9 Breaking stress and percentage elongation of hydrogels with essential oils

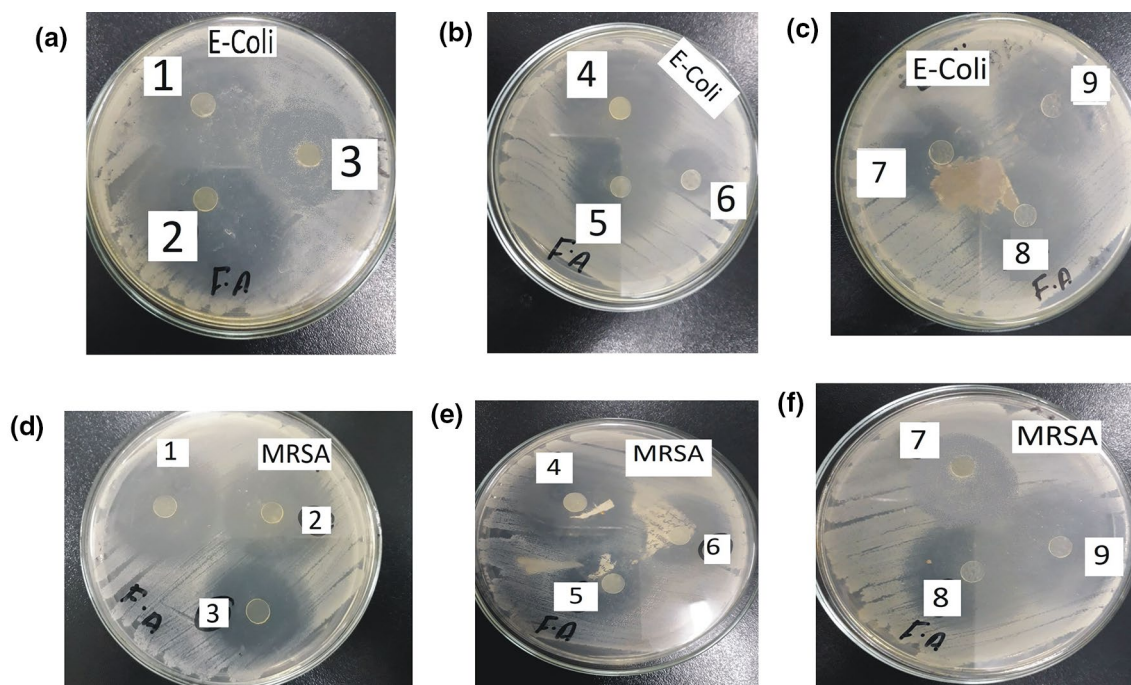


Fig. 10 Inhibition zones of hydrogels **a** *E. coli* with clove oil, **b** *E. coli* with tea tree oil, **c** *E. coli* with oregano oil, **d** MRSA with clove oil, **e** MRSA with tea tree oil, **f** MRSA with oregano oil

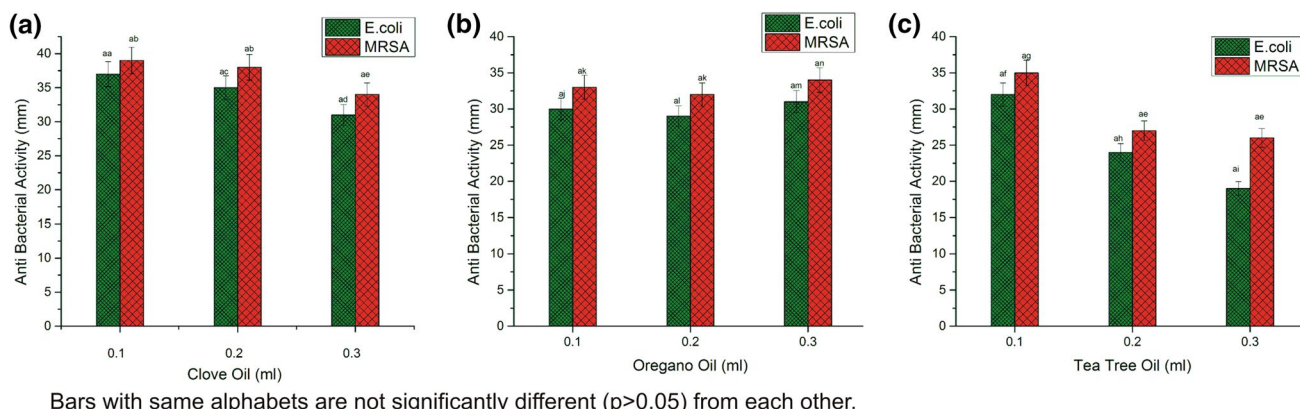


Fig. 11 Anti-bacterial activity with essential oils **a** clove oil, **b** tea tree oil **c** oregano oil

of (35–26 mm) while that for *E. coli* is (32–19 mm). The 0.1 mL Tea Tree oil showed good resistance against both Gram positive (MRSA) and Gram-negative bacteria (*E. coli*). The inhibition zone is 35 ± 0.36 and 32 ± 0.42 mm, respectively. But as the concentration increases the inhibition zones started to deplete. This is because of the poor dispersion of oil with increasing concentration. Figure 11b shows the result for both gram positive (MRSA) and gram negative bacteria (*E. coli*) [79]. Oregano oil showed less resistance against both gram positive (MRSA) and Gram-negative bacteria (*E. coli*) than the other essential oils. The major constituents of oregano oil is carvacrol which has the

highest phenolic content and it shows resistance against the bacteria [80].

The inhibition zones for gram positive (MRSA) and gram-negative bacteria (*E. coli*) are in the range of (33–34 mm) and (30–31 mm), respectively. All the essential oils show almost similar result which means that they are miscible. Figure 11c shows the inhibition zones for both bacteria [81]. The formulated hydrogels are hydrophilic and have a cross-linking property that imparts excellent biocompatibility. They exhibit soft material nature, which encourages the uptake of water. Therefore, it forms hydrated solid materials, like cells in the body. Due to the composition and presence

of functional groups in active compounds and synergistic interactions of the hydrogel, they give more anti-bacterial activity as compared to original essential oils. Clove oil shows the best result at 0.1 mL which is due to its composition. It comprises 90% of eugenol which is very much resistant against bacteria. The antiseptic compound in tea tree oil is triphenin-4-ol and in oregano oil is carvacrol but they comprise 60% and 30% of the compound, respectively [82].

Conclusions

The existing investigation designates the effective fabrication of PVA and Starch membranes crosslinked with glutaraldehyde. The investigation stayed focused on the development and characterization of antibacterial polymeric wound dressings. PVA and Starch entailed the polymeric matrix, and essential oils (clove oil, tea tree oil, oregano oil) as antibacterial agent. Nine samples with three different combinations were tested. The antibacterial efficacy was inspected against *Escherichia Coli* and *Staphylococcus aureus*. The diameter of inhibition zone was less against E-coli, which disclosed their greater contest to anti-biotic effects in 0.1 ml clove oil. The inhibition zone measured was 39 ± 0.57 mm for *Staphylococcus aureus* and for *Escherichia coli* is 37 ± 0.29 mm. The hydrogels have exposed exceptional swelling capabilities against water, blood, $MgCl_2$ solutions and NaCl solutions. The results evidenced the ability of the prepared hydrogels to provide moist environment by meaningfully reducing the transmission of moisture from wound bed. FTIR, SEM and XRD characterization techniques were applied to check the morphology as well as the 3-D crosslinking taking place in the membrane. Increasing the oil concentration starts to generate pores and became immiscible. XRD proves the semi crystalline nature of membranes, while FT-IR spectra showed that PVA and Starch are properly cross-linked with essential oils providing amine, hydroxyl and ether groups. The mechanical strength was decreased by the addition of essential oils but it was greater than the human skin. The 0.1 mL clove oil has shown best result from oregano oil and tree tea oil.

Proceeding the basis of above outcomes, it can be claimed that the hydrogels with 0.1 mL clove oil have the outstanding results to be used as wound dressings operative for burn wounds.

References

- Clark WR, Gao D (2002) Properties of membranes used for hemodialysis therapy. *Semin Dial* 15(3):191–195
- Kamoun EA, Kenawy ES, Chen X (2017) REVIEW A review on polymeric hydrogel membranes for wound dressing applications: PVA-based hydrogel dressings. *J Adv Res* 8(3):217–233
- Madaghiele M, Demitri C, Sannino A, Ambrosio L (2014) Polymeric hydrogels for burn wound care: advanced skin wound dressings and regenerative templates. *Burns Trauma* 2(4):153–161
- Arca HÇ, Şenel S (2008) Chitosan based systems for tissue engineering part II: soft tissues. *ABAD J Pharm Sci* 2:211–216
- Daunton C, Kothari S, Smith L, Steele D (2014) A history of materials and practices for wound management. *Wound Pract Res* 20:174
- Pal K, Banthia AK, Majumdar DK (2009) Polymeric hydrogels: characterization and biomedical applications. *Des Monomers Polym* 12(3):197–220
- Yahia Lh (2017) History and applications of hydrogels. *J Biomed Sci* 04:02
- Devices D, Lafayette W (2000) Structural design of hydrogels. pp 9–29
- Hassan A, Niazi MBK, Hussain A, Farrukh S, Ahmad T (2018) Development of anti-bacterial PVA/starch based hydrogel membrane for wound dressing. *J Polym Environ* 26(1):235–243
- Ratner BD, Hoffman AS (1976) Synthetic hydrogels for biomedical applications. ACS Publications, Washington
- Hoffman AS (2012) Hydrogels for biomedical applications. *Adv Drug Deliv Rev* 64:18–23
- Bursali EA, Coskun S, Kizil M, Yurdakoc M (2011) Synthesis, characterization and in vitro antimicrobial activities of boron/starch/polyvinyl alcohol hydrogels. *Carbohydr Polym* 83(3):1377–1383
- Baratta MT, Dorman HJD, Deans SG, Figueiredo AC, Barroso JG, Ruberto G (1998) Antimicrobial and antioxidant properties of some commercial essential oils. *Flavour Fragr J* 13(4):235–244
- Lai P, Roy J (2012) Antimicrobial and chemopreventive properties of herbs and spices. *Curr Med Chem* 11(11):1451–1460
- Kalemba D, Kunicka A (2003) Kalemba-2003-antibacterial-properties-of-EO.pdf. pp 813–829
- Devi KP, Nisha SA, Sakthivel R, Pandian SK (2010) Eugenol (an essential oil of clove) acts as an antibacterial agent against *Salmonella typhi* by disrupting the cellular membrane. *J Ethnopharmacol* 130(1):107–115
- Chami F, Chami N, Bennis S, Bouchikhi T, Remmal A (2005) Oregano and clove essential oils induce surface alteration of *Saccharomyces cerevisiae*. *Phyther Res* 19(5):405–408
- Nishigaki I, Peramaiyan R, Ramachandran V, Gnpathy E, Dhana-pal S, Yutaka N (2010) Cytoprotective role of astaxanthin against glycated protein/iron chelate-induced toxicity in human umbilical vein endothelial cells. *Phyther Res* 24(June):54–59
- Burt S (2004) Essential oils: their antibacterial properties and potential applications in foods - a review. *Int J Food Microbiol* 94(3):223–253
- Myers SL, Yang CZ, Bittner GD, Witt KL, Tice RR, Baird DD (2015) Estrogenic and anti-estrogenic activity of off-the-shelf hair and skin care products. *J Expo Sci Environ Epidemiol* 25(3):271–277
- Sánchez-González L, González-Martínez C, Chiralt A, Cháfer M (2010) Physical and antimicrobial properties of chitosan-tea tree essential oil composite films. *J Food Eng* 98(4):443–452
- Jopke K, Sanders H, White-Traut R (2017) Use of essential oils following traumatic burn injury: a case study. *J Pediatr Nurs* 34:72–77
- Li M et al (2016) Tea tree oil nanoemulsions for inhalation therapies of bacterial and fungal pneumonia. *Colloids Surf B* 141:408–416
- Simitzis PE, Deligeorgis SG, Bizelis JA, Dardamani A, Theodosiou I, Fegeros K (2008) Effect of dietary oregano oil supplementation on lamb meat characteristics. *Meat Sci* 79(2):217–223
- Khorasani MT, Joorabloo A, Moghaddam A, Shamsi H, MansooriMoghaddam Z (2018) Incorporation of ZnO nanoparticles

- into heparinised polyvinyl alcohol/chitosan hydrogels for wound dressing application. *Int J Biol Macromol* 114:1203–1215
26. Roy N, Saha N, Kitano T, Vitkova E, Saha P (2011) Trends Colloid Interface Sci 14:127–130
 27. Kenawy ER, Kamoun EA, MohyEldin MS, El-Meligy MA (2014) Physically crosslinked poly(vinyl alcohol)-hydroxyethyl starch blend hydrogel membranes: synthesis and characterization for biomedical applications. *Arab J Chem* 7(3):372–380
 28. Yang J et al (2002) Fabrication and surface modification of macroporous poly(L-lactic acid) and poly(L-lactic-co-glycolic acid) (70/30) cell scaffolds for human skin fibroblast cell culture. *J Biomed Mater Res* 62(3):438–446
 29. Thangavel P, Ramachandran B, Kannan R, Muthuvijayan V (2017) Biomimetic hydrogel loaded with silk and l-proline for tissue engineering and wound healing applications. *J Biomed Mater Res Part B* 105(6):1401–1408
 30. Mikos AG, Athanasiou KA, Temenoff JS, Lebaron RG (2002) Effect of poly(ethylene glycol) molecular weight on tensile and swelling properties of oligo(poly(ethylene glycol) fumarate) hydrogels for cartilage tissue engineering. *J Biomed Mater Res* 59(3):429–437
 31. Koosehbol S, Ebrahimian-Hosseiniabadi M, Alizadeh M, Zamanian A (2017) Preparation and characterization of in situ chitosan/polyethylene glycol fumarate/thymol hydrogel as an effective wound dressing. *Mater Sci Eng C* 79:66–75
 32. Fakhreddin S, Zandi M, Rezaei M, Farahmandghavi F (2013) Two-step method for encapsulation of oregano essential oil in chitosan nanoparticles: preparation, characterization and in vitro release study. *Carbohydr Polym* 95(1):50–56
 33. Cui H, Zhang C, Li C, Lin L (2018) Antimicrobial mechanism of clove oil on *Listeria monocytogenes*. *Food Control* 94(June):140–146
 34. Eick S (2009) Effects of tea tree (*Melaleuca alternifolia*) oil on *Staphylococcus aureus* in biofilms and stationary growth phase. *Int J Antimicrob Agents* 33:343–347
 35. Abdelfadel M (2015) Effect of extraction methods on antioxidant and antimicrobial activities of some spices and herbs extracts. *Int J Adv Res* 3:12
 36. Abou El Nour M (2018) Potential of diethyl ether clove (*Syzygium aromaticum*) extract against different pathogens and in combination with antibiotic against Mdr-resistant *Staphylococcus aureus*. *Egypt J Microbiol*
 37. Jin X, Lo Hsieh Y (2005) PH-responsive swelling behavior of poly(vinyl alcohol)/poly(acrylic acid) bi-component fibrous hydrogel membranes. *Polymer (Guildf)* 46(14):5149–5160
 38. Chen M et al (2016) Facile fabrication of tea tree oil-loaded antibacterial microcapsules by complex coacervation of sodium alginate/quaternary ammonium salt of chitosan. *RSC Adv* 6(16):13032–13039
 39. Riley TV, Carson CF, Hammer KA (2006) *Melaleuca alternifolia* (tea tree) oil: a review of antimicrobial and other medicinal properties. *Clin Microbiol Rev* 19(1):50–62
 40. Orhan D, Hartevioglu A (2013) Chemical composition and biological activities of rosehip. *Spat DD* 3(1):23
 41. Ferrándiz M, Capablanca L, García D, Bonet MÁ (2017) Application of antimicrobial microcapsules on agrotexiles. *J Agric Chem Environ* 06(01):62–82
 42. Sun X, Lu C, Liu Y, Zhang W, Zhang X (2014) Melt-processed poly(vinyl alcohol) composites filled with microcrystalline cellulose from waste cotton fabrics. *Carbohydr Polym* 101:642–649
 43. Gottschalk P, Brodesser B, Poncelet D, Jaeger H, Cole S (2018) Vegetable oil matrix and characterisation thereof accept us crt. *J Microencapsul*
 44. Lee JS et al (2016) Multifunctional hydrogel nano-probes for atomic force microscopy. *Nat Commun* 7(May):1–14
 45. Tronci G, Grant CA, Thomson NH, Russell SJ, Wood DJ (2015) Multi-scale mechanical characterization of highly swollen photo-activated collagen hydrogels. *J R SocInterface* 12:102
 46. Boulogne F, Ingremeau F, Limat L, Stone HA (2016) Tuning the receding contact angle on hydrogels by addition of particles. *Langmuir* 32(22):5573–5579
 47. Eftimov P, Yokoi N, Peev N, Georgiev GA (2019) Impact of air exposure time on the water contact angles of daily disposable silicone hydrogels. *Int J Mol Sci* 20:6
 48. Matanović MR, Kristl J, Grabnar PA (2014) Thermoresponsive polymers: Insights into decisive hydrogel characteristics, mechanisms of gelation, and promising biomedical applications. *Int J Pharm* 472(1–2):262–275
 49. Oliver GJA, Dugard PH (1982) *Deermatological*. pp 57–64
 50. Guzmán-alonso M, Cortazar TM (2016) Water content at different skin depths and the influence of moisturizing formulations. *Househ Pers Care Today* 11(February):35–40
 51. Baghaie S, Khorasani MT, Zarrabi A, Moshtaghian J (2017) Wound healing properties of PVA/starch/chitosan hydrogel membranes with nano zinc oxide as antibacterial wound dressing material. *J Biomater Sci Polym Ed* 28(18):2220–2241
 52. Jhon MUS, Andrade JD, Materials D (1973) Water Hydrogel 7:509–522
 53. Sood A, Granick MS, Tomaselli NL (2014) Wound dressings and comparative effectiveness data. *Adv Wound Care* 3(8):511–529
 54. Kannon GA, Garrett AB (1995) Moist wound healing with occlusive dressings. *Dermatol Surg* 21(7):583–590
 55. Ghanbari M, Karimian R, Mehramouz B (2018) Preparation of biocompatible and biodegradable silk fibroin/chitin/silver nanoparticles 3D scaffolds as a bandage for antimicrobial wound dressing. *Int J Biol Macromol* 114:961–971
 56. Yañez F, Gomez-Amoza JL, Magariños B, Concheiro A, Alvarez-Lorenzo C (2010) Hydrogels porosity and bacteria penetration: where is the pore size threshold? *J Memb Sci* 365(1–2):248–255
 57. Chen YC, Chirila TV, Russo AV (1993) Hydrophilic sponges based on 2-hydroxyethyl methacrylate. II. Effect of monomer mixture composition on the equilibrium water content and swelling behaviour. *Mater Forum* 17(1):57–65
 58. El GF, Abu-serie MM, Hassan MA, Elnouby MS (2018) Hydroxyethyl cellulose hydrogel for wound dressing: fabrication, characterization and in vitro evaluation. *Int J Biol Macromol* 111:649–659
 59. Weller C, Sussman G (2006) Wound dressings update. *J Pharm Pract Res* 36(4):318–324
 60. Gun VM, Savina IN, Mikhailovsky SV (2017) Properties of water bound in hydrogels
 61. Paralikar SA, Simonsen J, Lombardi J (2008) Poly(vinyl alcohol)/cellulose nanocrystal barrier membranes. *J Memb Sci* 320(1–2):248–258
 62. Hassan CM, Peppas NA (2000) Structure and morphology of freeze/thawed PVA hydrogels. *Macromolecules* 33(7):2472–2479
 63. Vrana NE, Grady AO, Kay E, Cahill PA, Mcguinness GB (2009) Cell encapsulation within PVA-based hydrogels via freeze-thawing: a one-step scaffold formation and cell storage technique. pp 567–572
 64. Zhai M, Yoshii F, Kume T, Hashim K (2002) Syntheses of PVA/starch grafted hydrogels by irradiation. *Carbohydr Polym* 50(3):295–303
 65. Xiao C, Yang M (2006) Controlled preparation of physical cross-linked starch-g-PVA hydrogel. *Carbohydr Polym* 64(1):37–40
 66. Atarés L, Chiralt A (2016) Essential oils as additives in biodegradable films and coatings for active food packaging. *Trends Food Sci Technol* 48:51–62
 67. Glenn GM, Klamczynski AP, Woods DF, Chiou B, Orts WJ, Imam SH (2010) Encapsulation of plant oils in porous starch microspheres. *J Agric Food Chem* 58(7):4180–4184

68. Ashori A, Sheshmani S (2010) Hybrid composites made from recycled materials: moisture absorption and thickness swelling behavior. *Bioresour Technol* 101(12):4717–4720
69. Zhang D et al (2015) Carboxyl-modified poly (vinyl alcohol) -crosslinked chitosan hydrogel films for potential wound dressing. *Carbohydr Polym* 125:189–199
70. Biranje SS, Madiwale PV, Patankar KC, Chhabra R, Dandekar-jain P, Adivarekar RV (2019) Macromolecules Hemostasis and anti-necrotic activity of wound-healing dressing containing chitosan nanoparticles. *Int J Biol Macromol* 121:936–946
71. Hansson C (1997) A practical guide to their use in older patients. *11(4):271–284*
72. Yiamsawas D, Kangwansupamonkon W, Chailapakul O (2007) Synthesis and swelling properties of poly[acrylamide-co-(crotonic acid)] superabsorbents. *67:865–882*
73. Qi X et al (2015) Investigation of Salecan/poly(vinyl alcohol) hydrogels prepared by freeze/thaw method. *Carbohydr Polym* 118:60–69
74. Yang Z, Peng H, Wang W, Liu T (2010) Crystallization behavior of poly(ϵ -caprolactone)/layered double hydroxide nanocomposites. *J Appl Polym Sci* 116(5):2658–2667
75. Bolto B, Tran T, Hoang M, Xie Z (2009) Crosslinked poly(vinyl alcohol) membranes. *Prog Polym Sci* 34(9):969–981
76. Ntamila MS, Hassanali A (2009) Isolation of oil of clove and separation of eugenol and acetyl eugenol. An instructive experiment for beginning chemistry undergraduates. *J Chem Educ* 53(4):263
77. Bassolé IHN, Juliani HR (2012) Essential oils in combination and their antimicrobial properties. *Molecules* 17(4):3989–4006
78. Chouhan S, Sharma K, Guleria S (2017) Antimicrobial activity of some essential oils—present status and future perspectives. *Medicines* 4(4):58
79. Article R (2004) Methods to study the phytochemistry and bioactivity of essential oils. *Phyther Res* 448:435–448
80. Zhang Y, Lashgari HR, Di Y, Sepehrnoori K (2017) Capillary pressure effect on phase behavior of CO₂/hydrocarbons in unconventional reservoirs. *Fuel* 197:575–582
81. Benavides S, Villalobos-Carvajal R, Reyes JE (2012) Physical, mechanical and antibacterial properties of alginate film: effect of the crosslinking degree and oregano essential oil concentration. *J Food Eng* 110(2):232–239
82. Arweiler NB, Donos N, Netuschil L, Reich E, Sculean A (2000) Clinical and antibacterial effect of tea tree oil—a pilot study. *Clin Oral Investig* 4(2):70–73

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.