

A Study on the Charpy Impact Response of the Cracked Aluminum Plates Repaired with FML Composite Patches

Faramarz Ashenai Ghasemi · Lotfali Mozafari Vanani · Ali Pourkamali Anaraki

Submitted: 21 January 2016/in revised form: 29 March 2016/Published online: 3 June 2016
© ASM International 2016

Abstract Fiber metal laminates (FMLs) are widely used in aerospace industries nowadays. Reparation of the cracks in these advanced materials was first done by some aeronautical laboratories in the early 1970s. In this study, experimental investigations were done on the effects of repairing the edge-cracked aluminum plates using the FML patches. The repairing processes were conducted to characterize the response of the repaired structures to the Charpy impact tests. The composite patches were made of one aluminum layer and two woven glass–epoxy composite layers. Three different crack lengths, crack angles, and patch lay-ups were examined. It was indicated that for the lengthen cracks, the effect of increasing the crack angle on energy absorption in the structure was more. When the ratio of crack length to the specimen width, i.e., a/w , is 0.5, the energy absorption per unit area of the specimens having different crack angles but the same patch lay-ups was so different. It was also observed that the percentage of the absorbed energy of 45° cracked angle specimens was about 25% higher than the 0° ones. Also it was observed that the lay-up of the patches and the place where the metal layer was embedded in the FML patches had an important effect on the impact response of the tested specimens. The more the metal layer of the patches is far from the interfacial surface of the aluminum plate and the FML patches, the less the energy absorbs in the structure.

Keywords Crack · Repair · Composite materials · FML · Aluminum · Plate

Introduction

Composite patches are used most commonly to repair cracked components [1]. There are lots of advantages to use adhesively bonded composite patches, such as high corrosion properties, good specific strength and stiffness, facility of fabrication, and lightweight. These structures also show different properties in different directions by changing the lay-up sequence of their plies and amount of their reinforcement. Crack growth behavior of engineering components has been studied by many researchers. The positive effect of using composite patches to improve the mechanical behavior of cracked components was first studied by the Aeronautical and Maritime Research Laboratory [2]. Chue et al. [3] discussed the effect of laminated composite patch with different stacking sequences on repairing an inclined central cracked plate under biaxial loads. They showed that the use of different stacking sequences for the patch does not affect the energy distribution near the crack tip significantly. Naboulsi et al. [4] involved nonlinear analysis of the adhesively bonded composite patch to investigate its effects on the damage tolerance of the repaired structure. They showed that the crack-opening displacement of the crack in the repaired plate is smaller for the geometrically nonlinear analysis than its counterpart from linear analysis. Hence, the stress intensity factor of the repaired structure computed from geometrically nonlinear analysis is less than its counterpart from geometrically linear analysis.

Chung et al. [5] performed experimental investigations on the effect of composite material patch repairing to characterize the fatigue crack growth behavior in a thick Al6061-T6 (6 mm) panels with a single-sided fiber-reinforced composite patch. They showed that the fatigue life

F. Ashenai Ghasemi (✉) · L. Mozafari Vanani ·
A. Pourkamali Anaraki
Shahid Rajaei Teacher Training University (SRTTU), Lavizan,
Tehran 16788-15811, Iran
e-mail: faramarz_ashenai_ghasemi@yahoo.com

of patched plate increases about 4–6 times compared to the un-patched plate. They also demonstrated that the stress intensity factor value decreases rapidly at the end of patch. Okafor et al. [6] studied on the design, analysis, and durability of adhesively bonded composite patch repairs of cracked aircraft aluminum panels. They found that the maximum skin stress decreases significantly after the application of the patch and the region of maximum skin stress shifts from the crack front for an un-patched panel to the patch edges for a patched one. They also showed that the maximum skin stress for the patched specimen was reduced by 83–85% from that of the un-patched specimen. Sabelkin et al. [7] studied several parameters/factors related to mechanical and fatigue behaviors of a cracked 7075-T6 aluminum panel repaired with one-sided adhesively bonded composite patch by a combined experimental–analytical approach. They showed that the disbond does not affect the out-of-plane deformation and in-plane strain except in their vicinity. They also investigated that the crack length has a small effect upon the in-plane strain and out-of-plane deformation. They observed that the bonded patch repair of a cracked panel provides a considerable increase in the residual strength as well as fatigue life. Cheng et al. [8] demonstrated that applying the adaptive control of the electric field to the surface bonded piezoelectric patch could significantly decrease the lateral deflection of laminated composite beam and, in turn, increase its dynamic buckling capacity. They observed that the application of the externally applied electric field to the surface bonded piezoelectric patch could effectively enhance the dynamic buckling capacity of the laminated beams. They also demonstrated that a nonalternating electric field applied to the patch could more effectively enhance the dynamic (pulse buckling) response of the beam. Khalili et al. [9] investigated edge-cracked aluminum plates repaired with one-sided composite patches experimentally for their response to Charpy impact test. They observed that carbon patches are more effective in reinforcing the cracked plates than glass patches. They showed that when the ratio of crack length to specimen width is constant, carbon fiber patches show better characteristic than glass ones.

In this paper, experimental investigations were done on the effect of repairing the single-sided cracked aluminum plates using the single side three layers of FML patches. The repairing processes were conducted to characterize the response of the repaired structures to Charpy impact tests. The composite patch was made of one metal layer and two woven fiber-reinforced composite layers. Three different crack lengths, angles, and patch lay-ups were examined. Some experiments were done to study the energy absorption mechanism of repaired and un-repaired cracked specimens and to see the effects of patch lay-up,

crack angle, and length in reinforcing the cracked structures too.

Specimens and Patches Preparation

Specimens Preparations

The specimens were made of aluminum AA1035 [10] having dimensions of 70 mm × 15.3 mm × 3 mm as shown in Fig. 1. The mechanical properties of aluminum plates are determined by tensile tests (Fig. 2; Table 1). The specimens were cut with a water jet machine in principle dimensions, and thereafter, using a wire cut machine, the notches were created. Three different crack length-to-specimen width ratios, i.e., $a/w = 0.1, 0.3,$ and $0.5,$ were created on one edge of the specimens (Fig. 1). The value of the crack angles with respect to the width axis of the specimens were chosen as $0^\circ, 30^\circ,$ and 45° (Fig. 3). The

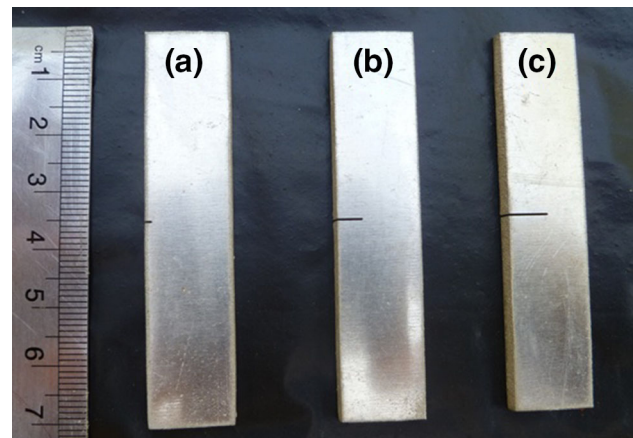


Fig. 1 Cracked specimens with different crack length-to-specimen width ratios: (a) $a/w = 0.1,$ (b) $a/w = 0.3,$ and (c) $a/w = 0.5$

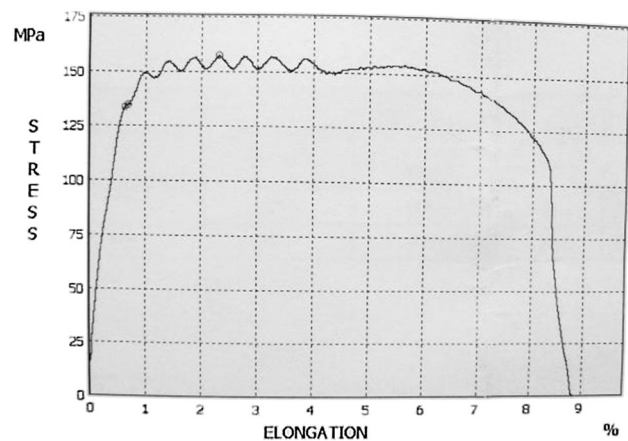


Fig. 2 Stress–elongation curve of aluminum plates

Table 1 Material properties of the aluminum plate, the patches, and the adhesive

	Stiffness $E_x = E_y$ (GPa)	Shear modulus G_{xy} (GPa or MPa)	Ultimate tensile strength $S_x = S_y$ (MPa)	Density P (g/cm ³)	Poisson's ratio ν_{xy}
Aluminum-AA1035	69	26 GPa	157	2.7	0.3
Epoxy-LY5052	3.5	***	60	1.16	0.35
GFRP layer	16	***	230	1.6	0.25
Araldite-2015	2	10–20 MPa	30	1.4	***


Fig. 3 Specimens with three different crack angles: (a) $\theta = 0^\circ$, (b) $\theta = 45^\circ$, and (c) $\theta = 30^\circ$ 

specimens with same crack configuration in length and angle were kept together and then wire cut.

In order to have a complete bonding between the specimens and FML patches, the surface preparation procedure according to the P2 etching process [11] was conducted on the bonding surface of the aluminum specimens. In this method, the bonding surface of the aluminum plates was first degreased with acetone and then abraded with emery cloth. Finally, alkaline cleaning was applied. Thereafter, the specimens were immersed for 12 min at 65–70 °C P2 etch mixture of 15 wt.% FeSO₄, 37% H₂SO₄, and 48% water. They were washed with the clean cold running water, followed by clean hot water, and then were dried with hot air. The temperature of the hot water and air must not be greater than 65 °C [12].

Patches Preparation

The FML composite patches were fabricated with two woven glass fabric ($T(90^\circ)/M200-E10$) layers as the fiber (F, hereinafter) layers and one thin aluminum (A, hereinafter) sheet (AA1035, 0.3 mm) as the metal layer. The lay-up of the FML patches varied in different make-ups so that the A layer could be near or far from the cracked surface. Different codes were chosen to simplify presenting the results. For the un-repaired cracked specimens, code B was supposed. Three different repair types of patch lay-ups were conducted on the cracked specimens. The code C1 means that the lay-up of the patch is F–F–A, from bottom to up direction. The code C2 demonstrates that the lay-up is A–F–F, and finally, the code C3 shows that the lay-up is F–A–F. This means that in C1 patches, the A layer of the patch is far from repaired surface; in C2 ones, the A layer is exactly bonded to the cracked specimen; and in C3 ones, the A layer was in the middle of the patches. The direction of fibers in the patches lay-ups are equally along 0° and 90°. To bond the F and the A layers strongly, the surface

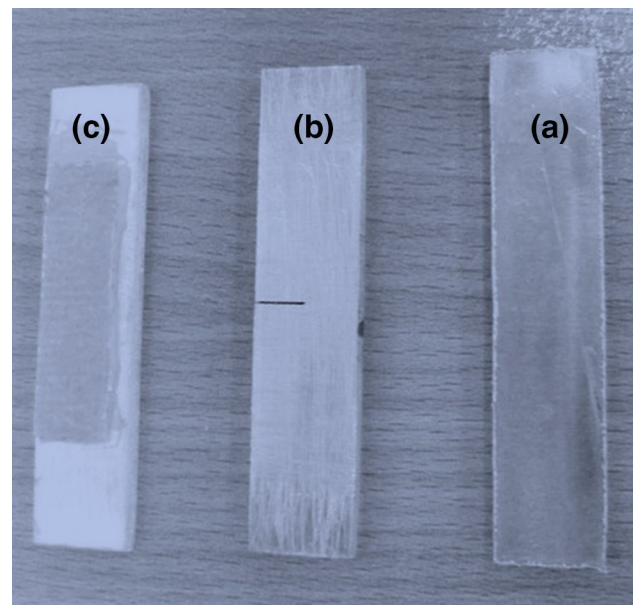**Fig. 4** Specimens (a) without a crack, (b) with a crack but not repaired, and (c) with a crack and repaired with a composite patch

preparation procedure for bonding the surfaces of A layer was done according to ASTM E 23-02a [13]. The epoxy (LY5052) was used as the matrix because of its efficiency for the aerospace applications [14].

The content of fiber was about 55 wt.% in glass–epoxy layers. The composite was made by hand, and then the curing procedure according to the recommended cure schedule in two stages was done [14]. The patches dimensions were 40 mm × 10 mm, and after curing, their thickness was 0.8 mm. Figure 4 shows the specimen that is not cracked (a), is cracked but not repaired (b), and finally is cracked and repaired with a patch (c). Araldite 2015 was used for bonding the FML patches to the cracked plates [15]. The thickness of the adhesive layer was about 0.2 mm. Before bonding the patches to the cracked plates,

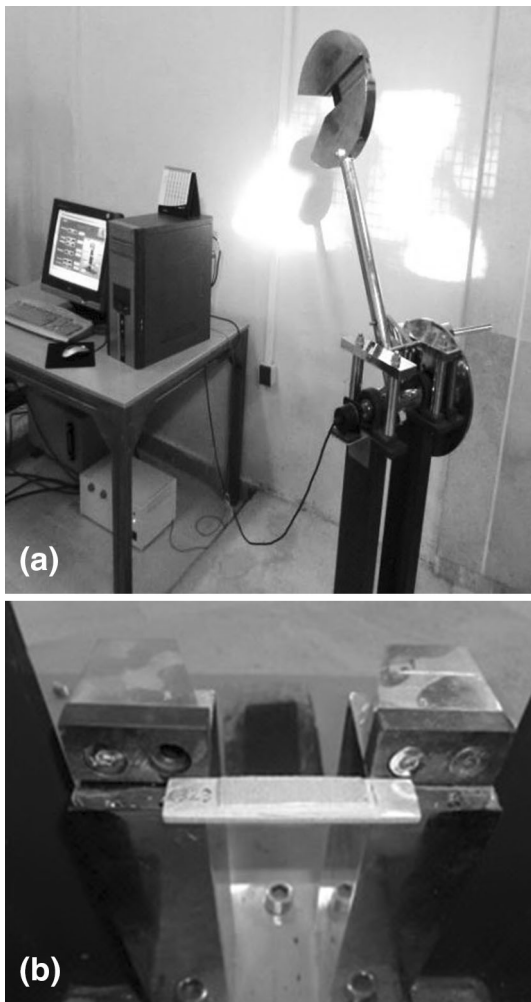


Fig. 5 The Charpy test device and the specimen setup for testing (a) the Charpy test device, (b) specimen setup before testing

surface preparation procedure of A layer of patch was applied according to the P2 etching process (as mentioned before). For bonding F layer, the surface preparation was done according to the procedure recommended for thermoset materials [16]. Table 1 shows the mechanical properties of the aluminum plate, the patches, and the bonding material.

Impact Test

Charpy is a dynamic three-point bending experiment of a beam. The experimental setup consists of the specimen, the fixture where the specimen is freely supported, and a pendulum with a defined mass attached to a rotating arm. The pendulum falls following a circular trajectory and hits to the test specimen at the middle span length and transfers its kinetic energy to it [17]. In this research, a Charpy test device (Fig. 5a) was used for impact testing of all

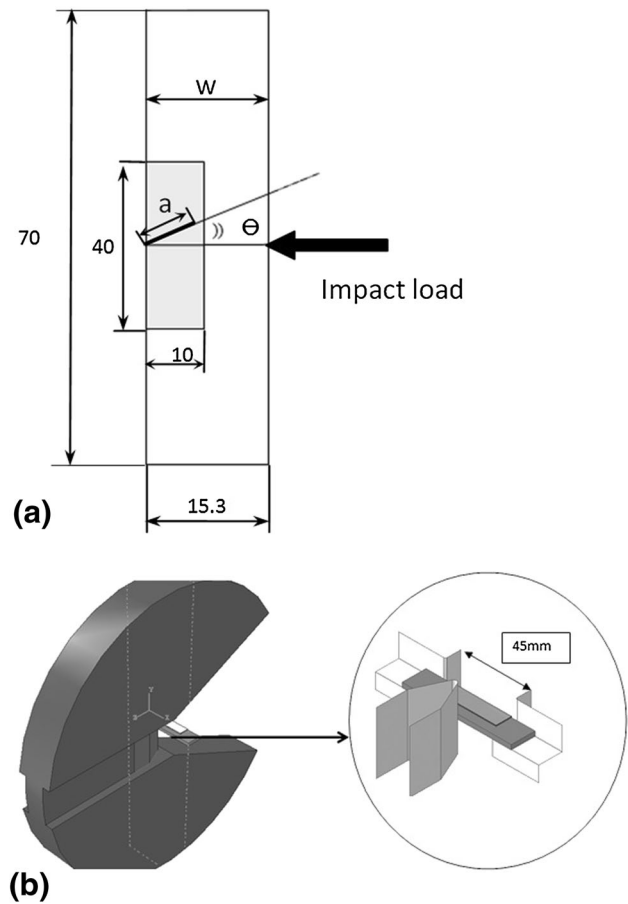


Fig. 6 Schematic view of geometry and test configuration of specimens (a) schematic view of geometry of stiffened cracked panel repaired with a FML patch, (b) schematic view of impact time

specimens according to ASTM E 23-02a [13]. Each sample was tested three times to verify the repeatability. The pendulum hammer had a mass of 15.200 kg and a disk radius of 150 mm. The swing arm length and mass were 520 mm and 5.270 kg, respectively, leading to a speed at impact point of around 5.033 m/s and a stored energy of 218.5 J. The friction energy loss was about 1.9 J, and the energy loss due to air resistance was neglected. The span distance in the test setup was 45 mm. The final energy absorption of each specimen was the average value of the three same tested samples. Figure 5b shows a typical impact test specimen that is prepared to test. Figure 6 shows the schematic view of geometry and loading of repaired specimens.

Results and Discussion

At first, the un-cracked specimen was tested, and the energy absorption was acquired 53.00 J for it. Then the un-repaired cracked specimens were tested. The results of

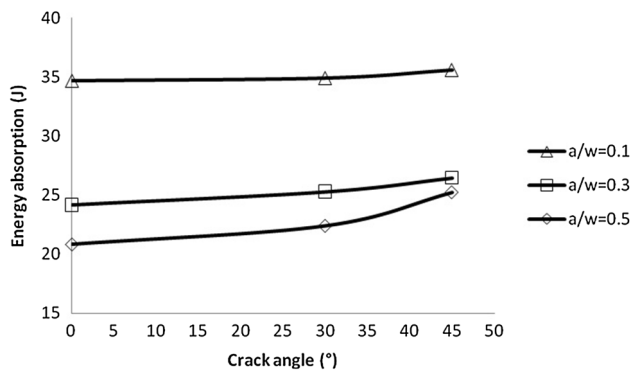


Fig. 7 Energy absorption of the un-repaired cracked specimens

Table 2 Energy absorption of the un-repaired cracked specimens

Crack angle (°)	<i>a/w</i> ratio		
	0.1	0.3	0.5
0	34.7	24.19	20.83
30	34.93	25.3	22.4
45	35.61	26.47	25.24

these tests are depicted in Fig. 7 and Table 2. Figure 7 shows that the more the increase in crack angle, the more the increase in absorbed energy no matter what the crack length is. One also sees that in specimens with 45° crack angle, the most energy is absorbed in the structure. This is due to the change of the crack growth path that forces the crack to go in mode I of the fracture. This change in direction leads to a more energy absorption (Fig. 7).

Also it is shown that by increasing the crack length, the energy absorption increases (when the crack angle changes from 0° to 45°). For instance, according to Table 2, the percentage of increasing energy absorption of un-repaired specimens with a crack length ratio of $a/w = 0.5$ is about 21% when the crack angle changes from 0° to 45°. Similarly, the differences for the ratios of $a/w = 0.3$ and $a/w = 0.1$ are equal to 9 and 2%, respectively. The reason for this behavior is that by increasing the crack length, the distance that the crack must go to reach to the mode I of fracture becomes longer. Therefore, the amount of energy absorption increases too.

In next step, selected patches were adhered to the specimens having different crack angles and lengths that mentioned earlier. They were tested to see how the effects of patch lay-up and crack characteristics are in the strength of the repaired structures. Table 3 shows the results of the repaired specimens having a crack length ratio of $a/w = 0.1$ with some selected patch configurations. The amount of the energy absorption of the specimens having ratios of $a/w = 0.3$ and $a/w = 0.5$ are presented in Tables 4 and 5 too, respectively.

Table 3 Energy absorption (J) of specimens with a crack length ratio of $a/w = 0.1$

Crack angle (°)	Repair type		
	C1	C2	C3
0	***	36.5	***
30	35.34	***	36.91
45	***	40.61	***

C1 A patch with the F–F–A lay-up, C2 A patch with the A–F–F lay-up, C3 A patch with the F–A–F lay-up

Table 4 Energy absorption (J) of specimens with a crack length ratio of $a/w = 0.3$

Crack angle (°)	Repair type		
	C1	C2	C3
0	26.61	***	27.63
30	***	31.69	***
45	31.46	***	34.56

Table 5 Energy absorption (J) of specimens with a crack length ratio of $a/w = 0.5$

Crack angle (°)	Repair type		
	C1	C2	C3
0	***	23.48	***
30	24.09	***	26.15
45	***	29.5	***

As can be seen in Tables 3, 4, and 5, there is a meaningful correlation between length and the angle of crack with the amount of specimens' energy absorption. By increasing crack length, the fracture energy of the structure decreases. But, by increasing crack angle, the strength of the specimens increases.

In this section, the important point to be taken into account is the difference of energy absorption of various repairs. The reason for this behavior is that by changing the patch lay-up, the amount of energy absorption of the structure changes too. By looking at the obtained results, it can be concluded that the location of the A layer in the patch lay-up has a significant role upon the efficiency of the repair. The more the location of the A layer (aluminum layer) is near the base structure (repair type C2), the more the energy will be absorbed in the structure and vice versa. The more the A layer is far from the repaired surface (repair type C1), the less the energy will be absorbed in the structure (Table 6).

Table 6 Energy absorption (%) of cracked specimens compared to an un-cracked one

Crack length	Repair type	Energy absorption (%) for different crack angles		
		0°	30°	45°
$a/w = 0.1$	B	65.47	65.91	67.19
	C1	***	66.68	***
	C2	68.87	***	76.62
	C3	***	69.64	***
$a/w = 0.3$	B	45.64	47.74	49.94
	C1	50.21	***	59.36
	C2	***	59.79	***
	C3	52.13	***	65.21
$a/w = 0.5$	B	39.3	42.26	47.62
	C1	***	45.45	***
	C2	44.3	***	55.66
	C3	***	49.34	***

B un-repaired cracked specimen

The reason of this behavior is changing the fracture mechanism of the patch. Whenever the A layer is near the repaired surface, the ductility of the whole structure becomes more. Therefore, the structure can absorb the more energy by the plasticity behavior of the A layer. When the A layer is placed in the middle of patch lay-up or even more far from the repaired surface, nearly the brittle fracture occurs. The reason of this behavior is that the F layer is less ductile, i.e., if the F layer fails, the A layer fails suddenly too. One should be noted that the amount of the loading and the required time of A layer plasticity is too low. Therefore, the more the A layer is far from the repaired surface, the more the structure shows a brittle behavior and vice versa. It can be concluded that if the structure is repaired with the C2 type patches, no matter what the crack angle or length is, its strength becomes extreme.

It is important to study the difference of energy absorption of different repaired or un-repaired cracked specimens respect to un-cracked ones. One sees that the amount of energy absorption (%) shows that every cracked specimen without a patch (B) or each of the repaired specimens with different types of patches (types C1, C2, or C3) are able to absorb the more energy compared to the un-repaired cracked specimens. The results also shows that in the un-repaired cracked specimens, the maximum energy absorption belongs to the specimen having the minimum crack length ratio (i.e., $a/w = 0.1$) and the maximum crack angle (i.e., $\theta = 45^\circ$), and is equal to 67.19%. By increasing the crack length, the energy absorption decreases, and finally, in the specimens having the maximum crack length ratio (i.e., $a/w = 0.5$) and the minimum crack angle (i.e.,

$\theta = 0^\circ$), the percentage of the energy absorption value becomes the minimum (i.e., 39.3%). The effect of crack length ratio and crack angle of the repaired specimens is similar to the un-repaired ones.

Conclusions

In this paper, the effects of using the FML patches on strengthening of cracked aluminum plates were studied. The specimens were repaired with single-sided FML patches, and then they were subjected to Charpy impact test. The following conclusions can be drawn:

- (1) When the crack length ratio is constant, the more the crack angle is, the more the energy absorbs in the structure.
- (2) By increasing the crack length ratio, the strength of specimens decreases, no matter they are repaired or not.
- (3) No matter what the type of the crack is, the strength of the repaired structures depends on the type of patch lay-up. The more the metal layer of the patch structure is close to the repaired surface, the more the energy absorbs in the structure.

References

1. A.A. Baker, L.R.F. Rose, R. Jones, *Advances in the Bonded Composite Repair of Metallic Aircraft Structure* (Elsevier, Amsterdam, 2002)
2. A.A. Baker, Repair efficiency in fatigue-cracked aluminum components reinforced with boron/epoxy patches. *Fatigue Fract. Eng. Mater. Struct.* **16**, 753–765 (1993)
3. C.H. Chue, T.J.C. Liu, The effects of laminated composite patch with different stacking sequences on bonded repair. *Compos. Eng.* **5**(2), 223–230 (1995)
4. S. Nabousli, S. Mall, Nonlinear analysis of bonded composite patch repair of cracked aluminum panels. *Compos. Struct.* **41**, 303–313 (1998)
5. K.H. Chung, W.H. Yang, A study on the fatigue crack growth behavior of thick aluminum panels repaired with a composite patch. *Compos. Struct.* **60**, 1–7 (2003)
6. A.C. Okafor, N. Singh, U.E. Enmuoh, S.V. Rao, Design, analysis and performance of adhesively bonded composite patch repair of cracked aluminum aircraft panels. *Compos. Struct.* **71**, 258–270 (2005)
7. V. Sabelkin, S. Mall, M.A. Hansen, R.M. Vandawaker, M. Der-riso, Investigation into cracked aluminum plate repaired with bonded composite patch. *Compos. Struct.* **79**, 55–66 (2007)
8. J. Cheng, H. Han, F. Taheri, An adaptive enhancement of dynamic buckling of a laminated composite beam under axial impact by surface bonded piezoelectric patches. *Comput. Methods Appl. Mech. Eng.* **197**, 2680–2691 (2008)
9. S.M.R. Khalili, R. Ghadjar, M. Sadeghinia, R.K. Mittal, An experimental study on the Charpy impact response of cracked

- aluminum plates repaired with GFRP or CFRP composite patches. *Compos. Struct.* **89**, 270–274 (2010)
10. R. Steiner, *Handbook, Properties and Selection: Nonferrous Alloys and Special-Purpose Materials*, vol. 2 (American Society for Metals (ASM) International, Cleveland, 1990)
 11. H.M. Clearfield, D.K. McNamara, G.D. Davis, in *Engineered Materials Handbook. Adhesives and Sealants*, vol. 3, ed. by H.F. Brinson, H.F. Brinson (ASM International, Cleveland, 1990), p. 260
 12. H. Hosseini-Toudeshky, B. Mohammadi, S. Bakhshandeh, Crack trajectory analysis of single-side repaired thin panels in mixed-mode conditions using glass/epoxy patches. *Comput. Struct.* **86**, 997–1005 (2008)
 13. ASTM E 23-02A, *Standard Test Methods for Notched Bar Impact Testing of Metallic Materials* (American Society for Testing and Materials (ASTM), West Conshohocken, 2010)
 14. Huntsman, Advanced materials data sheet for Araldite LY5052-1/ Aradure 5052-1 (2007), www.huntsman.com/advanced_materials
 15. Huntsman, Advanced materials data sheet for Araldite 2015 (2007), www.huntsman.com/advanced_materials
 16. R.F. Wegman, *Surface preparation techniques for adhesive bonding* (William Andrew Inc, Norwich, 1989)
 17. W. Hufenbach, F. Marques Ibrahim, A. Langkamp, R. Böhm, A. Hornig, Charpy impact tests on composite structures—an experimental and numerical investigation. *Compos. Sci. Technol.* **68**, 2391–2400 (2008)