

Removal of humic acid from peat water using untreated powdered eggshell as a low cost adsorbent

M. A. Zulfikar · E. Novita ·
R. Hertadi · S. D. Djajanti

Received: 1 January 2012/Revised: 3 January 2013/Accepted: 2 February 2013/Published online: 22 February 2013
© Islamic Azad University (IAU) 2013

Abstract The main objective of this study is to investigate the possibility of powdered eggshell used as an adsorbent material for removal of humic acid from peat water. The influences of contact time, dose of eggshells, pH, and temperature were the factors considered in the removal processes of humic acid from peat water. In addition, adsorption isotherms of humic acid onto the powdered eggshell were also evaluated with the Langmuir and Freundlich approximations. Our results showed that the equilibrium of the process was eventually established after 60 min of the contact time, and also found that using 5 g of the powdered eggshell nearly 95 % of humic acid has been successfully removed from the peat water. The removal of humic acid gave better result when it was conducted at low pH, and it was almost unaffected the temperatures variation. The data was well fitted to Freundlich isotherm with the correlation coefficient of not <0.999, and could uptake the humic acid about 126.58 mg/g at pH 4.01, estimated from the Langmuir model. The kinetic experimental data proportionally correlated with the pseudo-second-order kinetic model with a rate constant in the range of 0.016–0.112 g mg⁻¹ min⁻¹, while intra-particle-diffusion were the main rate determining step in the

humic acid removal process. The powdered eggshell investigated in this study, thus, exhibited as a high potential adsorbent for the removal of humic acid from peat water.

Keywords Adsorption · Calcium carbonate · Isotherm · Kinetics

Introduction

One of problems that are faced by people who live in lowland and marshy area is the scarcity of available clean water. This is due to the fact that the abundant source of water in that area is peat water. Such problem is also readily found in several remote villages in Riau Province, Indonesia. Almost 45 % of Riau Province area is peat land; thereby, the major source of water is peat water. Peat water is water having more than 75 % organic content with red brown color and has the character of acid.

Humic acid is one of the main components of peat water that consisted of large molecules with molecular weights ranging from thousands to hundreds of thousands (Gezici et al. 2005) and have a backbone of aromatic and aliphatic residues with numerous substituents such as OH groups, ketones, carboxylic acid groups, amino acids/peptides, saccharides, and amino saccharides (Albers et al. 2008). Humic acid imparts a brown or yellow color in peat water and pose a serious environmental problem, particularly in drinking water treatment because of their taste and odor. They also tend to react with a variety of oxidants and disinfectants used for the purification of drinking water forming carcinogenic disinfection byproducts (DBPs) such as trihalomethanes and haloacetic acids (Daifullah et al. 2004; Kamari et al. 2009; Ngah et al. 2011; Uygunera et al. 2007; Sonea et al. 2010; Tao et al. 2010; Wang et al. 2008a; Wang et al. 2011).

M. A. Zulfikar (✉) · S. D. Djajanti
Analytical Chemistry Research Group, Institut Teknologi
Bandung, Jl. Ganesha 10, Bandung 40132, Indonesia
e-mail: zulfikar@chem.itb.ac.id

E. Novita
Madrasah Aliyah Negeri 2 Pekanbaru, Jl. Pangoran
Diponegoro 55, Pekanbaru 28131, Indonesia

R. Hertadi
Biochemistry Research Group, Institut Teknologi
Bandung, Jl. Ganesha 10, Bandung 40132, Indonesia

In order to acquire clean water from peat water, it is necessary to do pretreatment process to this water. At present, there are several methods used to remove humic substance, especially humic acid as main component from peat water, such as coagulation–flocculation (Uygunera et al. 2007), electro coagulation processes (Ghernaout et al. 2009), oxidation (Uygunera et al. 2007), photocatalysis (Sonea et al. 2010), and membrane technology (Katsoufidou et al. 2010). All of these alternative processes, however, are high operational cost, especially when applying membrane technology, because humic acid component tends to severely foul the membrane (Katsoufidou et al. 2010) and hence, limiting the membrane application in this field. None of them, therefore, is considered by industries to be commercially viable because economically unrealistic.

Being easy to operate and being the most effective, adsorption has been considered as one of the most economically promising techniques for the water and wastewater treatments (Gupta et al. 2009). Activated carbon is the most widely studied and used adsorbents for water and wastewater treatments (Gupta et al. 2009). However, the main disadvantage of activated carbon is its high cost in manufacturing and treatment and difficult to regenerate. Therefore, there is a need to continue the search and developing alternative adsorbents with high adsorptive capacity and low cost for humic acid removal. As a consequence, numerous low cost materials such as rice husk activated carbon (Daifullah et al. 2004), *Shorea dasyphylla* sawdust (Kamari et al. 2009), chitosan (Wang et al. 2008a), fly ash (Wang et al. 2008b), and other adsorbents (Nghah et al. 2011; Sonea et al. 2010; Tao et al. 2010; Wang et al. 2011; García et al. 1998; Zhang and Bai 2003; Nghah et al. 2008) were used for removal of humic acid. In the present work, the possibility of powdered eggshell to be used as an adsorbent material for removal of humic acid from peat water has been investigated. The choice of eggshell as the adsorbent is due to its reasonable cost and ease of regeneration. In addition, there is no study reported in the literature related to the use of powdered eggshell as an adsorbent to removal of humic acid from peat water to produce clean water. In this study, the effect of contact time, adsorbent dosage, pH, and temperature on the adsorption were investigated. Adsorption isotherm model and kinetic models were also investigated. This work was done in 2010, at Chemistry Department of Bandung Institute of Technology, Indonesia.

Materials and methods

Adsorbent preparation

Chicken eggshells collected from Balubur traditional market Bandung was initially washed with detergent and

the membrane layer was manually separated from the shells. The membrane free eggshell was further washed with distilled water, and then air-dried for 2 days before it was finally grounded to 75 μm in particle size.

Peatwater solution preparation

The peat water sample was obtained from Bukit Timah, a sub district of Dumai city in Riau Province, Indonesia. Before mixing the peat water sample with adsorbent, its pH value was adjusted using NaOH and HCl (Merck, Germany) with 0.1 M in concentration. The pH value was measured using 300 Hanna Instrument (USA) pH meter. The characteristic of peat water sample can be seen at Table 1.

Characterization of powdered eggshells

In order to examine the crystallinity of the powdered eggshells, X-ray diffraction of sample were recorded using RINT 2000 (Rigaku Instrument Corp., Japan) with Cu K α radiation. A scanning electron microscope (JEM-2010, JEOL, Japan) was used for the investigation of particle morphology of powdered eggshells. Fourier transform infra red spectroscopic model 8300 IR-TF (Shimadzu, Japan) analysis was performed within the range 400–4,000 cm^{-1} to identify the presence of functional groups in the samples. The zeta potential of eggshells as a function of pH in 0.01 mol/L sodium chloride was measured using a Zeta-Plus 4 Instrument (Brookhaven Instruments Corp., USA). The surface area of powdered eggshells was analyzed through nitrogen adsorption measurements at 77 K using Micromeritics Gemini 2370 (USA) equipment.

Batch adsorption studies

Adsorption experiments were carried out by mixing of 1, 3 and 5 g chicken eggshell with 50 mL peat water pH of 4.01 at 25 °C in thermostatic shaker bath (Innova 3000, 3000)

Table 1 The peat water sample characteristics

Parameters	Unit	Result
Color	Pt–Co	475
Organic compounds	mg/L KMnO_4	238
pH	–	4.01
Conductivity	$\mu\text{S}/\text{cm}$	62
Turbidity	mg/L SiO_2	7.5
Iron	mg/L	0
Manganese	mg/L	0
Calcium	mg/L	0
Magnesium	mg/L	6.2

with shaking speed at 100 rpm for 2, 5, 10, 15, 20, 25, 30, 45, 60, 75, 120, 180, 240 and 300 min. At the end of the predetermined time interval, the suspension was taken out and the supernatant was centrifugated. The concentration of humic acid solution was measured by an ultraviolet–visible spectrophotometer model UV–vis 1601 (Shimadzu, Japan) at the λ 400 nm (Zhang and Bai 2003). As the absorbance was pH-dependent, calibration lines were made for each required pH in the study. The percent of humic acid removal from peat water was calculated using the following equation:

$$\text{Removal (\%)} = \frac{C_i - C_e}{C_i} \times 100 \quad (1)$$

where C_i and C_e are initial and final concentration of humic acid (mg/L) in solution, respectively. The adsorption capacity of an adsorbent at equilibrium with solution volume V was calculated using the following equation:

$$q_e(\text{mg/g}) = \frac{C_i - C_e}{m} \times V \quad (2)$$

where C_i and C_e are the initial and final concentration of humic acid (mg/L) in solution, respectively. V is the volume of solution (L) and m is mass of adsorbent (g) used.

The effect of pH on the humic acid removal from peat water was studied in the suspension with pH range from 2.0 to 10.0 by adjusting the pH using 0.1 M HCl and 0.1 M NaOH solution and using 3 g of powdered eggshell for 15, 30, 45, 60, 75, and 90 min at 25 °C and shaking speed at 100 rpm.

The effect of dosage of powdered eggshell on the humic acid removal was investigated by mixing 50 mL peat water with different dosages (1, 3, 5, 7, 10, 15 and 20 g) for 60 min and at pH of 4.01, 25 °C and shaking speed at 100 rpm. To analyze the effect of temperature on humic acid removal, the experiments were carried out at different temperatures: 25, 45, 55 and 65 °C. The amount of powdered eggshells used was 3 g in 50 mL of peat water sample at pH 4.01 with shaking speed at 100 rpm.

For desorption studies, 5 g of powdered eggshell were loaded with 50 mL peat water at pH 7 and 25 °C for 30 min. The loaded powdered eggshell collected was gently washed with distilled water to remove any unadsorbed humic acid. The powdered eggshell was then loaded with 50 mL of HCl at concentration 0.1–0.001 M for 120 min. The desorption percentage (DP) of humic acid is defined as (Nghah et al. 2008):

$$DP = \frac{C_{e(\text{des})}}{C_{e(\text{ads})}} \times 100\% \quad (3)$$

Study of adsorption isotherm

Adsorption experiments were carried out by mixing various dosage of powdered eggshell (1, 3, 5, 7, 10, 15 and 20 g)

with 50 ml of peat water sample, which other conditions were held constant at pH of 4.01, particle size of 75 μm , and temperature of 25 °C. The experimental data were calculated to determine the adsorption isotherm using the Langmuir and Freundlich models.

Results and discussion

Characterization of powdered eggshells

From the XRD patterns (Figure not shown), it was found that the eggshell structure is similar to the calcite structure containing calcium carbonate mineral (Murakami and Rodrigues 2007). The surface morphology of the eggshell sample, which analyzed with SEM, showed that it has many pores with different sizes and shapes (Fig. 1). SEM image was also revealed that the eggshells have crystalline structure, exhibited an angular pattern (Tsai et al. 2006), non-adhesive appearance, and formation of agglomerates. This observation was similar to other researches reported (Bhaumik et al. 2012).

The zeta potential of eggshells as a function of the pH solution values are shown in Fig. 2. The zeta potentials are positive in an acidic condition but negative in a basic condition. The point of zero zeta potential was obtained at about pH 8.8 which is similar to the zero zeta potential of calcite reported by other (Labidi and Djebaili 2008). Below pH 8.8, the zeta potential of eggshells increases with the decrease of solution pH value. This may be attributed to the Ca^{2+} and CaOH_2^+ species adsorbed at eggshell surface. Above pH 8.8, the zeta potential of eggshell was negative, because of excess HCO_3^- and CO_3^{2-} species adsorbed at its surface (Bhaumik et al. 2012).

IR spectra of the powdered eggshells before adsorption showed that the most significant peak of intensity of powdered eggshells is at 1425.40 cm^{-1} (Fig. 3); thereby, strongly associated with the presence of carbonate minerals

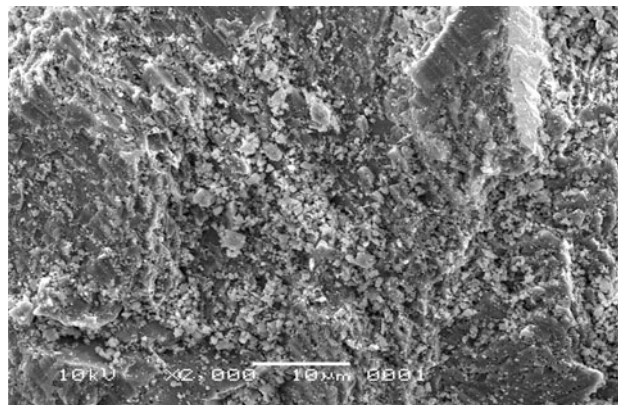


Fig. 1 SEM micrographs of powdered eggshell

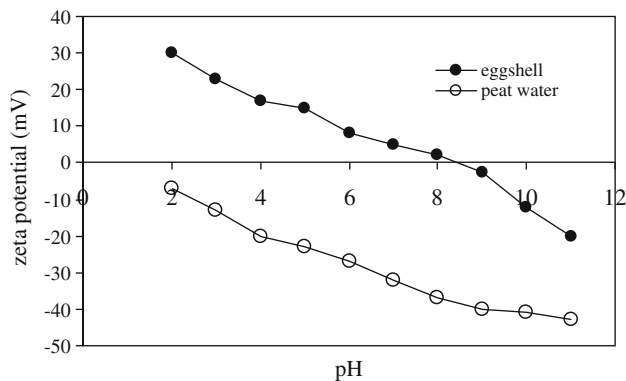


Fig. 2 Zeta potential of powdered eggshell

within the eggshells matrix (Tsai et al. 2006; Carvalho et al. 2011). There are also two observable peaks at about 711.73 and 875.68 cm^{-1} which should be associated with the in-plane deformation and out-plane deformation modes, respectively, in the presence of calcium carbonate (Tsai et al. 2006; Carvalho et al. 2011).

The surface area of powdered eggshells obtained from nitrogen adsorption measurement is 3.23 m^2/g . This value is greater than that obtained by Tsai et al. (2006), but smaller than that obtained by Kose and Kivanc (2011).

Effect of contact time

Figure 4 shows the effect of contact time on humic acid removal from peat water on powdered eggshell for different dosages. Based on the plot, humic acid removal was relatively fast with more than 50 % of peat water removed in <15 min. This was due to the increased availability of adsorption site for the uptake of humic acid. Meanwhile, the second slower phase was due to the quick exhaustion of

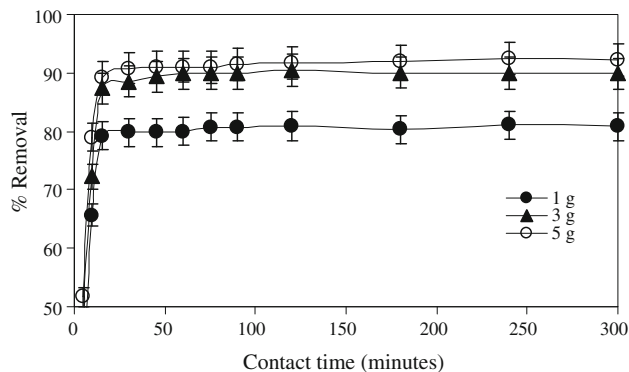



Fig. 4 Effect of contact time on humic acid removal from peat water onto powdered eggshell (volume 50 mL, pH 4.01, particle size 75 μm , shaking speed 100 rpm, and 25 $^{\circ}\text{C}$)

the adsorption sites (Nghah et al. 2011). The adsorption rapidly occurs and normally controlled by the diffusion process from the bulk to the adsorbent surface (Bhaumik et al. 2012). After 60 min, it can be observed that the humic acid removal remained constant, indicating the establishment of equilibrium

Effect of powdered eggshells dosage

The effect of powdered eggshell dosages on humic acid removal was shown in Fig. 5. The maximum humic acid removal of about 94.56 % was observed at the dosage of 5 g. The percentage removal decreased slightly at higher dosage (up to 5 g) of the adsorbent. This trend could be explained as a consequence of partial aggregation, agglomeration, overlapping, and overcrowding of adsorbent at higher dosage; thereby, reducing the availability of surface area for adsorption (Bhaumik et al. 2012;

Fig. 3 Infra red spectrum of powdered eggshell

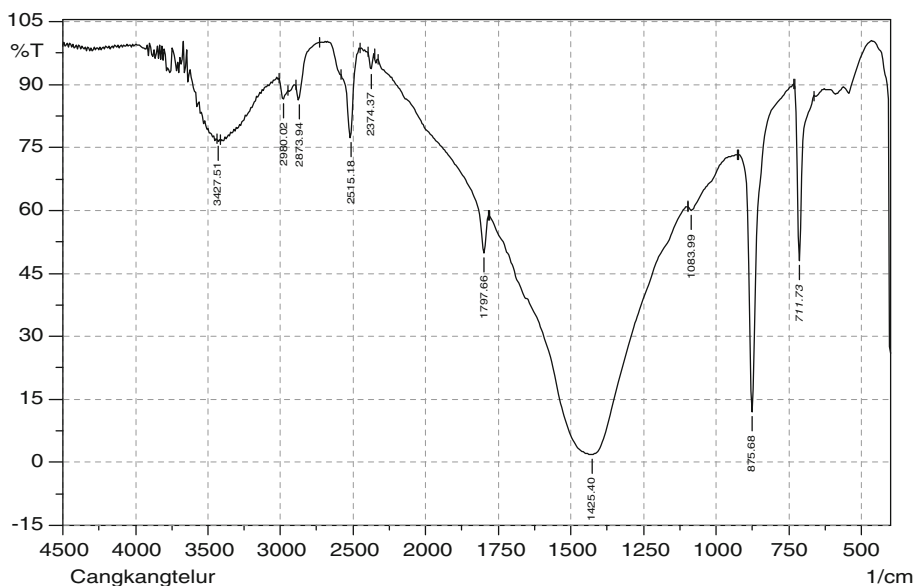

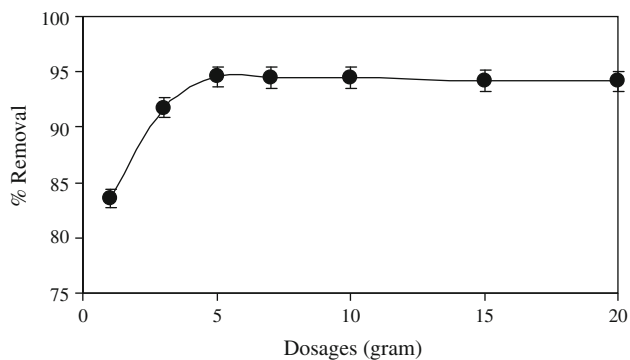


Fig. 5 Effect of dosages on humic acid removal from peat water onto powdered eggshell (contact time 60 min, volume 50 mL, pH 4.01, particle size 75 μm , shaking speed 100 rpm, and 25 $^{\circ}\text{C}$)

Elwakeel and Yousif 2010; Gupta and Rastogi 2008; Ehrampoush et al. 2011).

Effect of pH

The effect of pH on humic acid removal from peat water by powdered eggshells (Fig. 6) demonstrated that the optimum humic acid removal from peat water occurred at pH 2, and it would decrease when increasing the pH value of the initial solution.

To explain the adsorption behavior of this humic acid, a model of modified double-electric layer has been used (Zulfikar et al. 2012). According to this model, the Stern layer consists of two layers: an inner layer (IL) in which adsorbed molecules or ions connect with surface of eggshell directly and an outer layer (OL) in which adsorbed molecules or ions have a looser arrangement. At low pH, hydrogen, Ca^{2+} , and CaOH_2^+ ions are present in the solution and may be adsorbed onto the surfaces of eggshell particles forming an electrical double layer, with the

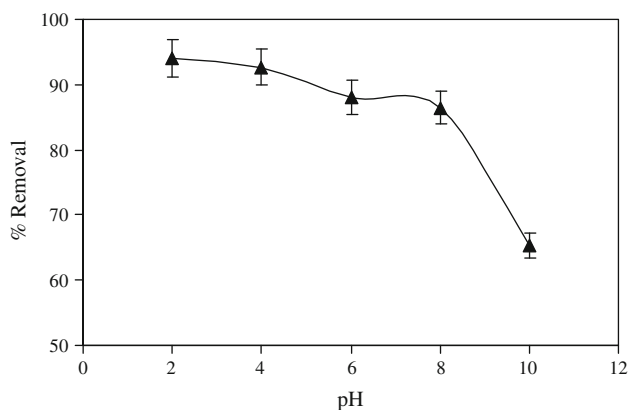


Fig. 6 Effect of pH on humic acid removal from peat water onto powdered eggshell (contact time 60 min, volume 50 mL, dosage 3 g, particle size 75 μm , shaking speed 100 rpm, and 25 $^{\circ}\text{C}$)

surface of the eggshell particle acquiring a positive charge, as confirmed by zeta potential measurement (Fig. 2).

As previously explained, humic acid is the main components of peat water, which consist of many phenolic and carbonyl functional groups. As known, the phenolic and carbonyl functional group can be ionized in aqueous medium and may acquire a negative charge in aqueous medium, as confirmed by zeta potential measurement (Fig. 2). When humic acid is present in solution, humic acid ion will be attracted to the surface of the adsorbent by electrostatic interaction, forming a Stern OL and thus, increasing the adsorption rate of humic acid.

Meanwhile at high pH, more hydroxyl, HCO_3^- , and CO_3^{2-} ions are present in the bulk solution and are adsorbed onto eggshell surface, so the surface charge is negative (Fig. 2). These will reduce the electrostatic attraction between the eggshell particle surface and humic acid compound because of the less positive or more negative surface charges. This decreases the adsorption rate or removal of humic acid.

Effect of temperature

Effect of temperature variations to the humic acid removal by the powdered eggshell has been examined by conducting the experiments in four different temperatures: 25, 45, 55 and 65 $^{\circ}\text{C}$. The results clearly demonstrated that variation in temperatures statistically has no significant effect on the humic acid removal from peat water (Fig. 7). These results show that although the enhancing effects of temperature on humic acid adsorption are not significant, the inhibition effects of the higher temperatures are significant and should be considered as an operational parameter in economical aspect. This observation was similar to other researches reported (Kose and Kivanc 2011). The similarity of these results may be related to adsorbent

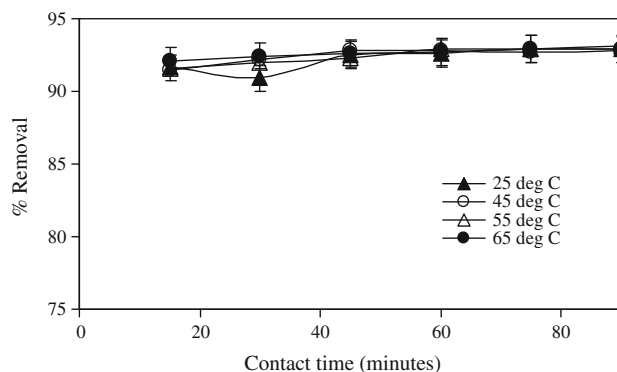


Fig. 7 Effect of temperature on humic acid removal from peat water onto powdered eggshell (volume 50 mL, dosage 3 g, pH 4.01, particle size 75 μm , shaking speed 100 rpm)

characteristics especially in term of chemical constituents (Ehrampoush et al. 2011).

Adsorption isotherms

Adsorption isotherms describe how adsorbates interact with adsorbents at constant temperature. Sorption equilibrium data provide fundamental physicochemical information for evaluating the applicability of sorption process as a unit operation. In the present investigation, the equilibrium data were analyzed with Langmuir and Freundlich isotherms.

The Langmuir isotherm theory assumes monolayer coverage of adsorbate over a homogeneous adsorbent surface. Adsorption is assumed to take place at specific homogeneous sites with the adsorbent and once an organic molecule occupies a site, no further adsorption can take place at the site. The isotherm experimental data were fitted with Langmuir model by using the following equation:

$$q_e = \frac{q_m \cdot b \cdot C_e}{1 + b \cdot C_e} \quad (4)$$

where C_e is the equilibrium concentration (mg/L), q_e is amount of adsorbate adsorbed per unit weight of adsorbent (mg/g), q_m and K_L are Langmuir constants related to maximum adsorption capacity (mg/g) and energy of adsorption (L/mg), respectively.

In Freundlich adsorption isotherm, the model assumes a heterogeneous surface with a non-uniform distribution of heat of adsorption over the surface. The isotherm experimental data were fit to the Freundlich model by using equation below:

$$q_e = K_f C_e^{1/n} \quad (5)$$

where C_e is the equilibrium concentration (mg/L), q_e is amount of adsorbate adsorbed per unit weight of adsorbent (mg/g), and K_f and n are Freundlich constants related to adsorption capacity and adsorption intensity, respectively. The value of K_f itself can be used to comparable parameter for sorption capacity of an adsorbent (Daifullah et al. 2004).

The results showed that the Freundlich isotherm model fitted well to the experimental results (Fig. 8). The isotherm parameters from the models indicated that the Freundlich isotherm produces a better fitting result in terms of regression coefficient than Langmuir isotherms (Table 2). This may mean that powdered egg shell have more heterogenous types of adsorption sites (Oke et al. 2008). This result was similar to other researches reported using eggshell as adsorbent for various adsorbate (Tsai et al. 2006; Kose and Kivanc 2011; Ehrampoush et al. 2011; Oke et al. 2008). High value of n indicates a strong bond between the adsorbent and the adsorbate. In our

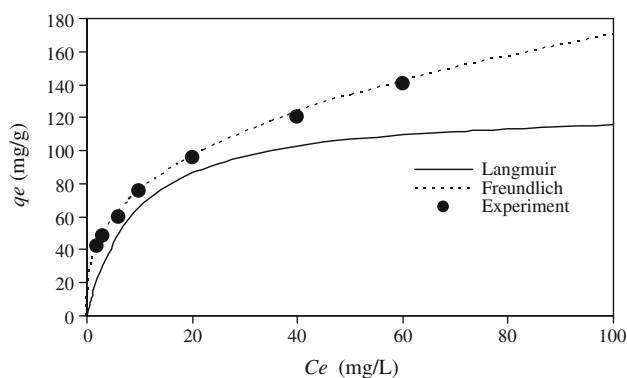


Fig. 8 Isotherm curve for humic acid removal from peat water at different powdered egg shell dosage (contact time 60 min, volume 50 mL, pH 4.01, particle size 75 μm , shaking speed 100 rpm, and 25 $^{\circ}\text{C}$)

experiment, the value of n was greater than unity (Table 2), an indication of a favorable adsorption process at high concentration of adsorbate (Nghah et al. 2008, 2011). Estimated from the Langmuir model, the maximum adsorption of humic acid from peat water on powdered egg shell is about 126.58 mg/g (Table 2).

Adsorption kinetic

In order to examine the controlling mechanism of humic acid removal process, the pseudo-first-order adsorption, the pseudo-second-order adsorption, the intra-particle diffusion, and Elovich and Boyd models were used to test the experimental data. The pseudo-first-order rate expression was evaluated with the following equation (Kamari et al. 2009; Nghah et al. 2011; Tao et al. 2010; Wang et al. 2011; Zhang and Bai 2003; Bhaumik et al. 2012; Elwakeel and Yousif 2010; Gupta and Rastogi 2008, Gupta et al. 2010; Kose and Kivanc 2011; Ehrampoush et al. 2011; Chen et al. 2010; Ugurlu et al. 2005; Okoye et al. 2010; Wang et al. 2008b; Elkady et al. 2011):

$$\log(q_e - q_t) = \log q_e - k/2.303 \cdot t \quad (6)$$

where q_e and q_t are the amounts of humic acid (mg/g), adsorbed on adsorbents at equilibrium and at time t , respectively, and k is the rate constant (min^{-1}). The value of k was obtained from a slope of the linear plots of $\log(q_e - q_t)$ against t .

The result of fitting of kinetic data for pseudo-first-order model under different adsorbent dosage is presented in Table 3. From this table, it was observed that the values of the correlation coefficients are relatively low for the different adsorbent dosages. Furthermore, the estimated values of q_e calculated from the equation differ substantially from those measured experimentally. According to Febrianto et al. (2009), the q_e calculated values will be

Table 2 The Langmuir and Freundlich isotherms constants

Langmuir model			Freundlich model		
K_L (L/mg)	q_m (mg/g)	R^2	n	K_f [(mg/g)(L/mg) ^{1/n}]	R^2
0.108	126.58	0.895	2.86	33.95	0.9996

lower than the q_e experiment values due to the presence of boundary layers or external resistances controlling at the beginning of the adsorption process. That gives confirmation that humic acid removal using eggshell did not obey the pseudo-first-order model.

The pseudo-second-order model is based on the assumption that the rate-limiting step may be chemical sorption or chemisorption involving valence forces through sharing or exchange of electrons between sorbent and sorbate. It is assumed that the sorption capacity is proportional to the number of active sites occupied on the sorbent, then the kinetic rate law can be written as follows (Kamari et al. 2009; Ngah et al. 2011; Tao et al. 2010; Wang et al. 2011; Zhang and Bai 2003; Bhaumik et al. 2012; Elwakeel and Yousif 2010; Gupta and Rastogi 2008; Gupta et al. 2010; Kose and Kivanc 2011; Ehrampoush et al. 2011; Chen et al. 2010; Ugurlu et al. 2005; Okoye et al. 2010; Wang et al. 2008b; Elkady et al. 2011):

$$t/q_t = 1/k \cdot q_e^2 + t/q_e \tag{7}$$

where q_e and q_t are the amounts of organic compounds (mg/g) adsorbed on sorbents at equilibrium and at time t , respectively, and k is the rate constant (g/mg min⁻¹). If second-order kinetics is applicable, the plot of t/q_t against t of Eq. (7) should give a linear relationship from which the constants q_e and k can be determined.

Plot of t/q_t against t for pseudo-second-order model under different adsorbent dosage are shown in Fig. 9. The k_2 , q_e , and correlation coefficients R^2 were calculated from this plot and are given in Table 3. From this table, it was observed that the q_e determined from the model is very close to q_e experiment and correlation coefficient is also >0.97. This result suggests that the removal system could be well described by the pseudo-second-order model. Therefore, it can be said that more than one-step may be involved in the sorption processes (Ugurlu et al. 2005).

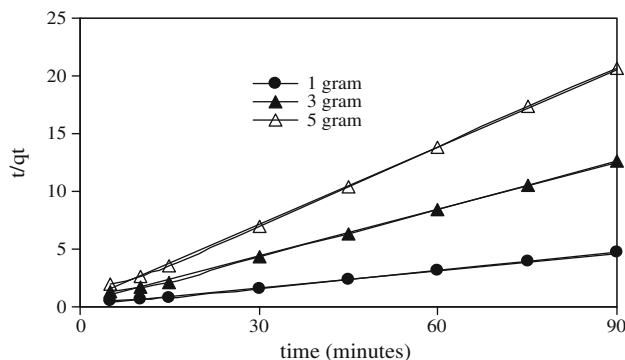


Fig. 9 Pseudo-second-order model plot for humic acid removal from peat water at different powdered egg shell dosages (volume 50 mL, pH 4.01, particle size 75 μm, shaking speed 100 rpm, and 25 °C)

The pseudo-second-order models could not identify the mechanism of removal process. Therefore, to analyze the mechanism of removal process, the intra-particle diffusion model can be used. The equation can be described as follow (Tao et al. 2010; Bhaumik et al. 2012; Elwakeel and Yousif 2010; Chen et al. 2010; Ugurlu et al. 2005; Okoye et al. 2010; Elkady et al. 2011):

$$q_t = k \cdot t^{0.5} + C \tag{8}$$

where k and c are an intra-particle diffusion rate constant (mg/g min^{0.5}) and a constant, respectively. The k is obtained from the slope of linier plot of q_t vs. $t^{0.5}$. From plot of q_t against $t^{0.5}$ (Figure not shown here), it can be seen that these plots generally have a dual nature, i.e., an initial curved portion and a final linear portion that may be explained by the fact that the initial curved portion represents boundary layer diffusion effects. The final linear portions are a result of intra-particle diffusion effects (Ugurlu et al. 2005; Jadhav and Vanjara 2004). Extrapolating the linear portion of the plot to the ordinate produces

Table 3 The pseudo-first-order and second-order kinetic parameters for humic acid removal from peat water using powdered egg shell

Adsorbent dosages (g)	Pseudo-first-order			Pseudo-second-order			
	k (min ⁻¹)	q_e , cal (mg/g)	R^2	k (min ⁻¹)	q_e , cal (mg/g)	R^2	q_e , exp (mg/g)
1	0.06	3.793	0.808	0.016	20.08	0.997	19.02
3	0.05	1.315	0.796	0.101	5.198	0.999	7.13
5	0.05	0.596	0.749	0.113	4.47	0.999	4.33

the intercept (C) which is proportional to the extent of boundary layer thickness (Jadhav and Vanjara 2004).

Referring to intra-particle diffusion plot at different adsorbent dosages, the first stage was completed within the first 15 min and the second stage of intra-particle diffusion control was then attained. The plot also showed that the linear lines of the second stages did not pass through the origin and this deviation from the origin or near saturation might be due to the difference in the mass transfer rate in the initial and final stages of adsorption (Mohanty et al. 2005). It confirms that intra-particle diffusion was not the only rate-limiting mechanism in the removal process (Tan et al. 2009).

The values of k_{d1} and k_{d2} as obtained from the slopes of the two straight lines are listed in Table 4. The k_d values were found to be generally decreased with the increasing adsorbent dosage. In order to determine the thickness of the boundary layers due to both the film diffusion and the intra-particle diffusion, the values of C_1 and C_2 are tabulated in Table 4. The thickness of the boundary layer in the second portion that corresponds to the intra-particle diffusion (C_2) is larger than that of the first portion that concerned the film diffusion (C_1). Consequently, the values of the intra-particle diffusion rates k_{d2} are smaller than the film diffusion rates k_{d1} (Elkady et al. 2011). That gives prediction that the humic acid removal process may be controlled by the intra-particle diffusion (Elkady et al. 2011; Abd El-Latif and Ibrahim 2010).

The Elovich equation is one of the most useful models for describing chemisorption, which is given as (Okoye et al. 2010):

$$q_t = 1/\beta \cdot \ln(\alpha \cdot \beta) + 1/\beta \cdot \ln t \quad (9)$$

where α represents the initial sorption rate (mg/g min) and β is related to the extent of surface coverage and activation energy for chemisorption (g/mg). The parameters α and β can be computed from the slope and intercept of the linear plot of q_t versus $\ln t$. From the plot Elovich model at different adsorbent dosages, it was indicated that the R^2 values were obtained in the range of 0.605–0.872 for the different adsorbent dosage, as seen in Table 5.

In order to determine the actual slow step involved in the humic acid removal process, the kinetic data as obtained by the batch method were further analyzed using the Boyd model given by (Chen et al. 2010; Elkady et al. 2011):

Table 5 The Elovich and Boyd kinetic parameters for humic acid removal from peat water using powdered egg shell

Adsorbent dosage (g)	Elovich model			Boyd model R^2
	α (mg/g min)	β (g/mg)	R^2	
1	18.267	0.202	0.872	0.831
3	5.141	0.484	0.613	0.900
5	3.514	0.202	0.605	0.821

$$B_t = -0,4977 - \ln(1 - F) \quad (10)$$

F represents the fraction of solute adsorbed at any time, t (h), which is calculated as follows:

$$F = q_t/q_\infty \quad (11)$$

where, q_∞ represents the amount sorbed (mg/g) at infinite time. The calculated B_t values were plotted against time t (h). The linearity of the plots can be used to characterize the particle diffusion control mechanism (Chen et al. 2010). From plot B_t against t (Figure not shown here), the plots are linear but do not pass through the origin, signifying that external mass transfer is the main rate controlling step at the initial stages (Chen et al. 2010). The values of correlation coefficient (R^2) as obtained from these slopes are listed in Table 5.

Desorption study

One of the important characteristics of an adsorbent is its ability to be regenerated (Nghah et al. 2008). A desorption study will help to elucidate the nature of adsorption process and to reuse the adsorbent. The most common desorbing agents used to desorb the adsorbates are NaOH, HCl, HNO₃, EDTA, CaCl₂, and organic solvents such as methanol and ethanol (Nghah et al. 2008). In this study, only HCl was used to regenerate the adsorbent. The results of desorption experiments showed that 82 % of humic acid removed from eggshell by treating with 0.1 M HCl (Figure not shown here). As the concentration of HCl increased, more adsorbed humic acid would be protonated. The high desorption percentage of humic acid with increase of HCl concentration was attributed to the more repulsive electrostatic interaction between humic acid protonated and adsorbent.

Table 4 The intra-particle diffusion model parameters for the humic acid removal from peat water using powdered egg shell

Adsorbent dosage (g)	k_{d1} (mg/g min ^{0.5})	C_1	R_1^2	k_{d2} (mg/g min ^{0.5})	C_2	R_2^2
1	6.392	-5.441	0.983	0.0623	18.6	0.693
3	1.976	-0.650	0.995	0.0389	6.8125	0.928
5	1.110	0.057	0.9686	0.0024	4.3117	0.3014



Table 6 Comparison of adsorption capacity of various adsorbent for humic acid removal

Materials	Adsorbate	q_m (mg/g)	Concentration range (mg/L)	pH	Contact time	Reference
<i>Shorea dasyphylla</i> sawdust	Humic acid	68.4	10–80	2	30 min	Kamari et al. 2009
Chitosan-PET	Humic acid	0.407	10–60	6.5	60 h	Zhang and Bai 2003
Rice husk activated carbon	Humic acid	45.4	20–150	10	–	Daifullah et al. 2004
Fly ash	Humic acid	36.0	10–100	5	170 h	Wang et al. 2008b
Eggshell	Peat water	126.58	–	4.01	60 min	This study
Chitosan-H ₂ SO ₄ beads (at 300 K)	Humic acid	377.4	0–70	–	60 min	Ngah et al. 2011
Activated carbon	Humic acid	52.4	0–200	7	24 h	Tao et al. 2010
SBA-15	Humic acid	8.5	0–200	7	24 h	Tao et al. 2010
APTS-SBA-15–5 %	Humic acid	72.5	0–200	7	24 h	Tao et al. 2010
APTS-SBA-15–10 %	Humic acid	117.6	0–200	7	24 h	Tao et al. 2010
ATP-PANI (at 25 °C)	Humic acid	52.91	5–60	5	24 h	Wang et al. 2011

Comparison of humic acid removal with other adsorbents reported in literature

It is also important to compare the value of maximum adsorption capacity obtained from this study with values from other reported adsorbents, since this will suggest the effectiveness of eggshells as a potential low cost adsorbent for humic acid removal. Although the Freundlich adsorption constants are difficult to compare with Langmuir adsorption isotherm, the maximum capacity, q_m , is comparable with the value in literature. The values of adsorption capacity for humic acid removal using some adsorbents are shown in Table 6.

The experimental data of the present investigations are higher than other reported values. The adsorption capacity varies and it depends on the characteristics of the individual adsorbent, the extent of surface/surface modification, the initial concentration of the adsorbate (Mousavi and Seyedi 2011), range of molecular size fraction of adsorbate, and degree of ionization per unit weight of the adsorbate (García et al. 1998).

Conclusion

The main aim of this study was to investigate the possibility powdered eggshell used as an adsorbent material. The results from this work showed that the process apparently reach equilibrium in nearly 60 min of contact time. The pH plays an important role in the humic acid removal from peat water and showed that the maximum removal occurred at pH 2. In addition, the temperature has no significant effect on the humic acid removal. The optimum dosage of powdered eggshell was 5 g. The adsorption isotherm data tends to fit with the Freundlich model. The adsorption capacity was obtained around 126.58 mg/g at pH 4.01, estimated

from the Langmuir model. The kinetic experimental data were strongly correlated with the pseudo-second-order kinetic model with a rate constant in the range of 0.016–0.112 g mg⁻¹ min⁻¹, while both the intra-particle diffusion and Boyd kinetic model indicated that intra-particle diffusion was the main rate determining step in humic acid removal process. Comparative results revealed that eggshell provides a better adsorbent property in comparison with other adsorbents. The results of this study suggest that powdered eggshell, with low cost and abundant availability in environment, have a potential of being used as an adsorbent for humic acid removal from peat water and could be used in water treatment.

Acknowledgments The authors are very grateful to authorities of the Pasar Balubur, Bandung, Indonesia for kindly providing the eggshell samples for this research study.

References

- Abd El-Latif MM, Ibrahim AM (2010) Removal of reactive dye from aqueous solutions by adsorption onto activated carbons prepared from oak sawdust. *Des Water Treat* 20:102–113
- Albers CN, Banta GT, Hansen PE, Jacobsen OS (2008) Effect of different of humic substances on the fate of diuron and its main metabolite 3,4-dichloroaniline in soil. *Environ Sci Technol* 42:8687–8691
- Bhaumik R, Mondal NK, Das B, Roy P, Pal KC, Das C, Banerjee A, Datta JK (2012) Eggshell powder as an adsorbent for removal of fluoride from aqueous solution: equilibrium, kinetic and thermodynamic studies. *E-J Chem* 9(3):1457–1480
- Carvalho J, Araujo J, Castro F (2011) Alternative low-cost adsorbent for water and wastewater decontamination derived from eggshell waste: an overview. *Waste Biomass Valor* 2:157–167
- Chen DZ, Zhang JX, Chen JM (2010) Adsorption of methyl tert-butyl ether using granular activated carbon: equilibrium and kinetic analysis. *Int J Environ Sci Technol* 7(2):235–242
- Daifullah AAM, Girgis BS, Gad HMH (2004) A study of the factors affecting the removal of humic acid by activated carbon prepared from biomass material. *Colloids Surf A* 235:1–10



- Ehrampoush MH, Ghanizadeh G, Ghaneian MT (2011) Equilibrium and kinetics study of reactive Red 123 dye removal from aqueous solution by adsorption on eggshell. *Iran J Environ Health Sci Eng* 8(2):101–108
- Elkady MF, Ibrahim AM, Abd El-Latif MM (2011) Assessment of the adsorption kinetics, equilibrium and thermodynamic for the potential removal of reactive red dye using eggshell biocomposite beads. *Desalination* 278:412–423
- Elwakeel KZ, Yousif AM (2010) Adsorption of Malathion on thermally treated egg shell material. *Water Sci Technol* 61(4):1035–1041
- Febrianto J, Natasia AK, Sunarso J, Ju YH, Indraswati N, Ismadji S (2009) Equilibrium and kinetic studies in adsorption of heavy metals using biosorbents: a summary of recent studies. *J Hazard Mater* 162:616–645
- García MAF, Utrilla JR, Toledo IB, Castilla CM (1998) Adsorption of humic substances on activated carbon from aqueous solutions and their effect on the removal of Cr(III) ions. *Langmuir* 14:1880–1886
- Gezici O, Kara H, Ersoz M, Abali Y (2005) The sorption behaviour of nickel-insolubilized humic acid system in a column arrangement. *J Colloid Interface Sci* 292:381–391
- Gheraout D, Gheraout B, Saibaa A, Boucherita A, Kellil A (2009) Removal of humic acids by continuous electromagnetic treatment followed by electrocoagulation in batch using aluminium electrodes. *Desalination* 239:295–308
- Gupta VK, Rastogi A (2008) Equilibrium and kinetic modeling of cadmium (II) biosorption by nonliving algal biomass *Oedogonium* sp. from aqueous phase. *J Hazard Mater* 153:759–766
- Gupta VK, Carrott PJM, Carrott MMLR, Suhas (2009) Low-cost adsorbents: Growing approach to wastewater treatment—a review. *Critical Rev Environ Sci Technol* 39:783–842
- Gupta VK, Rastogi A, Nayak A (2010) Adsorption studies on the removal of hexavalent chromium from aqueous solution using a low cost fertilizer industry waste material. *J Colloid Interface Sci* 342:135–141
- Jadhav DN, Vanjara AK (2004) Adsorption kinetics study: removal of dyestuff effluent using sawdust, polymerized sawdust and sawdust carbon-II. *Indian J Chem Technol* 11:42–50
- Kamari A, Ngah WSW, Wong LW (2009) *Shorea dasyphylla* sawdust for humic acid adsorption. *Eur J Wood Prod* 67:417–426
- Katsoufidou KS, Sioutopoulos DC, Yiantsios SG, Karabelas AJ (2010) UF membrane fouling by mixtures of humic acids and sodium alginate: fouling mechanisms and reversibility. *Desalination* 264:220–227
- Kose TE, Kivanc B (2011) Adsorption of phosphate from aqueous solutions using calcined waste eggshell. *Chem Eng J* 178:34–39
- Labidi NS, Djebaili A (2008) Studies of the mechanism of polyvinyl alcohol adsorption on the calcite/water interface in the presence of sodium oleate. *J Minerals Mater Charac Eng* 7(2):147–161
- Mohanty K, Das D, Biswas MN (2005) Adsorption of phenol from aqueous solutions using activated carbons prepared from *Tectona grandis* sawdust by ZnCl₂ activation. *Chem Eng J* 115:121–131
- Mousavi HZ, Seyedi SR (2011) Nettle ash as a low cost adsorbent for the removal of nickel and cadmium from wastewater. *Int J Environ Sci Tech* 8(1):195–202
- Muarakami FS, Rodrigues PO (2007) Physicochemical study of CaCO₃ from egg shells. *Cienc Technol Aliment Camp* 27(3):658–662
- Ngah WSW, Hanafiah MAKM, Yong SS (2008) Adsorption of humic acid from aqueous solutions on crosslinked chitosan-epichlorohydrin beads: kinetics and isotherm studies. *Colloids Surf B* 65:18–24
- Ngah WSW, Fatinathan S, Yosop NA (2011) Isotherm and kinetic studies on the adsorption of humic acid onto chitosan-H₂SO₄ beads. *Desalination* 272:293–300
- Oke IA, Olarinoye NO, Adewusi SRA (2008) Adsorption kinetics for arsenic removal from aqueous solutions by untreated powdered eggshell. *Adsorption* 14:73–83
- Okoye AI, Ejikeme PM, Onukwuli OD (2010) Lead removal from wastewater using fluted pumpkin seed shell activated carbon: adsorption modeling and kinetics. *Int J Environ Sci* 7(4):793–800
- Sonea D, Pode R, Manea F, Ratiu C, Lazau C, Grozescu I, Burtica G (2010) The comparative assessment of photolysis, sorption and photocatalysis processes to humic acids removal from water. *Chem Bull “Politehnica” Univ (Timisoara)* 55(69):148–151
- Tan IAW, Ahmad AL, Hameed BH (2009) Adsorption isotherms, kinetics, thermodynamics and desorption studies of 2,4,6-trichlorophenol on oil palm empty fruit bunch-based activated carbon. *J Hazard Mater* 164:473–482
- Tao Q, Xu Z, Wang J, Liu F, Wan H, Zheng S (2010) Adsorption of humic acid to aminopropyl functionalized SBA-15. *Micropor Mesopor Mater* 131:177–185
- Tsai WT, Yang JM, Lai CW, Cheng YH, Lin CC, Yeh CW (2006) Characterization and adsorption properties of eggshells and eggshells membrane. *Bioresource Technol* 97:488–493
- Ugurlu M, Gurses A, Yalcin M, Dogar C (2005) Removal of phenolic and lignin compounds from bleached kraft mill effluent by fly ash and sepiolite. *Adsorption* 11:87–97
- Uygunera CS, Suphandaga SA, Kercb A, Bekbolet M (2007) Evaluation of adsorption and coagulation characteristics of humic acids preceded by alternative advanced oxidation techniques. *Desalination* 210:183–193
- Wang S, Sun X, Liu X, Gong W, Gao B, Bao N (2008a) Chitosan hydrogel beads for fulvic acid adsorption: behaviours and mechanism. *Chem Eng J* 142:239–247
- Wang S, Terdkiatburana T, Tade MO (2008b) Single and co-adsorption of heavy metals and humic acid on fly ash. *Sep Purif Technol* 58:353–358
- Wang J, Han X, Ma H, Ji Y, Bi L (2011) Adsorptive removal of humic acid from aqueous solution on polyaniline/attapulgite composite. *Chem Eng J* 173:171–177
- Zhang X, Bai R (2003) Mechanism and kinetics of humic acid adsorption onto chitosan-coated granules. *J Colloid Interface Sci* 264:30–38
- Zulfikar MA, Mariske ED, Djajanti SD (2012) Adsorption of lignosulfonate compound using powdered eggshells. *Songklanakarin J Sci Technol* 34(3):309–316