



## THE POTENTIAL USE OF CLAY-FLY ASH GEOPOLYMER IN THE DESIGN OF ACTIVE-PASSIVE LINERS: A REVIEW

ELMIRA KHAKSAR NAJAFI<sup>1</sup>, REZA JAMSHIDI CHENARI\*<sup>1</sup>, AND MAHYAR ARABANI<sup>1</sup>

<sup>1</sup>Department of Civil Engineering, Faculty of Engineering, University of Guilan, P.O. 3756, Rasht, Guilan, Iran

**Abstract**—Because long-term leachate migration through a hydraulic barrier is inevitable, compacted clay and cementitious liners are commonly used as ‘active-passive’ liners to attenuate percolated leachate. The scarcity of suitable clay and because of the CO<sub>2</sub> emitted during the production of Portland cement as well as drying shrinkage, flow rate due to consolidation, limited attenuation capacity, and chemical instability may mean that these are not the best choices of materials to use for this purpose. An environmentally friendly method to improve the properties of local clay and provision for a long-term physical and chemical containment are essential. Geopolymers can be environmentally friendly substitutes for Portland cement to improve soil properties, not just because of the reduced carbon dioxide emission, but also because of its superior physical and chemical properties, as well as significant early strength, reduced shrinkage, freeze-thaw resistance, long-term durability, and attenuation capacity. According to previous studies, class-F fly ash-based geopolymers activated with NaOH exhibit superior attenuation capacity and long-term durability. The presence of silica, alumina, and iron oxides and the lack of calcium oxide play pivotal roles in the acceptable attenuation capacity and chemical stability of class-F fly ash. Accordingly, a clay-fly ash geopolymer may also work as a sustainable liner with appropriate physical and chemical performance. Clay can also participate in the geopolymerization process as an aluminosilicate precursor. All components of clay-fly ash geopolymers possess acceptable adsorption capacity. The type and percentage of the constituent raw materials control the attenuation capacity and physical properties of final products, however. The porosity and conductivity of typical geopolymers are related to the activator type and concentration, water content, and curing condition. Furthermore, the properties of liner materials can be adjusted with respect to the target contaminants. The present study aimed to present a comprehensive review of the relevant studies to highlight the properties required.

**Keywords**—Active-passive liner · Attenuation · Fly ash · Geopolymers · Heavy metals

### INTRODUCTION

Anthropogenic activities have caused various hazardous forms of pollution which range from the production of waste materials to construction materials. The pollution of soils by the migration of leachates containing heavy metals is a significant problem. Furthermore, carbon dioxide emitted by the materials industry, e.g. in the manufacture of cement, is also of significant environmental concern.

Geotechnical engineers have played a pivotal role in addressing these environmental concerns, i.e. through the treatment and disposal of wastes, since the late 1970s. Although landfilling as an engineered waste disposal system has been used widely since the 1970s, long-term control of leachate is still a major concern. Natural clay, compacted clay, and geosynthetic clay liners, which are current liner systems, are designed to reach a hydraulic conductivity of  $<9 \times 10^{-9}$  m/s. Nonetheless, the possibility of geosynthetic puncture, mechanical defects, and hydraulic defects reduces the physical containment by barriers because of the possibility of leachate migration. The long-term diffusion of pollutants through synthetic and mineral liners is of great concern (Daniel 1993). In general, mineral liners cannot perform as impermeable layers to leachate over the long term.

The natural attenuation technique, which simultaneously incorporates chemical attenuation and physical containment,

has attracted increased interest in terms of reducing the migration of potential contaminants. This approach, instead of providing a physical barrier only, exploits the attenuation capacity of a liner material to decrease major contaminants, contributing to increased landfill security with less environmental risk of leachate migration (Bagchi 1987; Thornton and Lerner 2001).

Even though mineral liners possess high attenuation capacity due to ion exchange, adsorption, and precipitation reactions (Bagchi 1987; Ganjian et al. 2004), shrinkage, desiccation cracking, chemical attack, expansion potential, and flow rate due to consolidation make their long-term performance unreliable (Daniel 1993; Ganjian et al. 2004). The scarcity of suitable local mineral materials that can satisfy the minimum requirements of active-passive barriers is also a pressing problem. Portland cement and lime have been used either to treat local soil or to modify the aforementioned imperfections (Rogers 1968; Firoozfar and Khosroshiri 2016). Composite soil-cement liners have also been utilized for the disposal of hazardous waste (Prashanth et al. 2001). However, due to the fact that one ton of CO<sub>2</sub> is emitted to produce one ton of Portland cement, means that the production of such cement is, itself, a threat to the environment. Moreover, Portland cement and lime threaten soil and water resources by changing the pH of these natural resources (Pacheco-Torgal et al. 2008). Alternative materials are required, therefore, to mitigate the environmental hazard. Geopolymers have received much attention in civil engineering projects as suitable alternatives to Portland cement. Despite their excellent properties, including good early strength, chemical durability, limited shrinkage, freeze-thaw resistance, corrosion resistance, and chemical

\* E-mail address of corresponding author: Jamshidi\_reza@guilan.ac.ir

containment capability (Davidovits 1994; Pacheco-Torgal et al. 2015), geopolymerization has not been applied widely in the design of active-passive liners in landfill sites.

Geopolymerization involves the activation of aluminosilicate resources with medium to highly alkaline solutions. Its reaction products are amorphous, alkaline, aluminosilicate hydrates considered to be a zeolite precursor (Pacheco-Torgal et al. 2015). Alkaline activation enhances the negatively charged sites that can adsorb cations in solution to reach a balance (Wang et al. 2007). In fact, a solution containing heavy metals may act as a charge-balancing agent. The high alkalinity of geopolymers favors the precipitation of heavy metals due to the formation of precipitates retained strongly by the matrix (Ganjian et al. 2004; Pacheco-Torgal et al. 2015). Moreover, the exchange of heavy metals and alkali is a reason for cation exchange reactions similar to those observed in clays and zeolites (Engelhardt and Michel 1987). Davidovits (1991) confirmed that geopolymers show a great capacity to adsorb toxic chemical wastes similar to zeolites due to their molecular sieving property. Some studies reported the applicability of geopolymeric materials to the stabilization and solidification of waste materials (Davidovits and Comrie 1988; Davidovits et al. 1990), which justify their attenuation capacity. Furthermore, a recent trend has begun to use geopolymer products in wastewater treatment and in the removal of heavy metals from solution (Al-Zboon et al. 2011; Javadian et al. 2015). Geopolymeric products can work as chemical containment systems.

In a geopolymerization process, reaction products and their properties depend heavily on the alkali type and concentration, aluminosilicate sources, reaction time, and curing condition (Pacheco-Torgal et al. 2015). Among available low-Ca precursors, fly ash has received much attention due to its availability and relatively low cost. Fly ash, as a by-product of coal-fired power-generating plants, is readily available in many countries, such as India, the USA, Thailand, and Brazil (Judith et al. 1992). In order to reduce the cost of fly-ash disposal, meaningful applications for its reuse are needed. In contrast to class C fly ash, which contains significant amounts of Ca, the main chemical components of class F fly ash are silica, alumina, and iron oxides. Class F fly ash shows pozzolanic behavior after mixing with alkaline materials (Pacheco-Torgal et al. 2015). The oxygen atoms of the silica, alumina, and iron oxides are free to react with water and control the charge of their surfaces based on the pH of the environment. The low- and high-pH environments create positively and negatively charged surfaces of silica, alumina, and iron oxides, respectively, contributing to geopolymer adsorption capacity in all pH conditions (Mohan and Gandhimathi 2009). Many researchers have confirmed the applicability of the raw fly ash, alkali-modified fly ash, and the by-products of fly ash to various applications, including soil stabilization, removal of heavy metals, geopolymerization, and zeolite production (Chakradhar and Kotach 2016; Pacheco-Torgal et al. 2015). As the dissolution of calcium is responsible for the degradation processes of cemented materials (Pacheco-Torgal et al. 2015), geopolymers containing low-Ca precursors, such as class F fly ash, exhibit

superior chemical stability compared to the cement products or high-Ca waste materials (Van Jaarsveld et al. 1998; Fernández Pereira et al. 2009). Regarding the type of alkaline solution, among alkalis used for alkaline activation, NaOH releases more alumina and silica and increases cation exchange capacity (CEC) (Van Jaarsveld et al. 1999). The performance of fly ash activated with NaOH solutions has been investigated extensively for the adsorption of organic dyes and the removal of heavy metals, such as Cu, Pb, and Cd (Li et al. 2006; Wang et al. 2007; Al-Zboon et al. 2011; Mužek et al. 2014; Javadian et al. 2015). For this reason, fly ash-based geopolymers may be viable alternatives to modified mineral materials as active-passive liners. The porosity and conductivity of the final products are controlled essentially by the type and concentration of activators, water content, and curing condition, which must be adjusted depending on the contaminants in the specific leachate. In the present study, the most relevant information about the efficiency of clay-fly ash-based geopolymers activated by NaOH solution will be reviewed as a sustainable active-passive liner material.

#### MINIMUM REQUIREMENTS FOR ACTIVE-PASSIVE LINER MATERIALS

##### *Hydraulic Conductivity*

The physical containment capability of a liner system depends heavily on hydraulic conductivity, which must remain at  $<9 \times 10^{-9}$  m/s for all sorts of waste. In order to meet this threshold, the compacted clay liner must possess intrinsic properties of minimum fines content of  $>20$ – $30\%$ , gravel content of  $<30\%$ , plasticity index of  $<7$ – $10\%$ , and maximum particle size of  $<25$ – $50$  mm (Daniel 1993). In many cases, clays that meet the parameters mentioned are in short supply. Furthermore, the low hydraulic conductivity of a compacted clay liner is associated with a high plasticity index of the clay, which decreases long-term serviceability because of increased consolidation flow rate and drying shrinkage. On the other hand, hydraulic conductivity, which is lower than this threshold limit, prevents leachate from percolation through a liner and consequently diminishes the natural attenuation performance of the liner (Bagchi 1987). This threshold can be taken into account as a boundary for both physical and chemical containments in an active-passive liner.

##### *Chemical Resistance*

Strong resistance to chemical attack plays an essential role in ensuring long-term durability and serviceability of liners because chemical attack and freeze-thaw cycles cause deterioration of the properties of liner materials and enhance their hydraulic conductivity (Chamberlain et al. 1990; Koch 2002).

##### *Attenuation Capacity*

The natural attenuation processes involved in a solid liner are sorption, ion exchange, biological action, precipitation, and filtration mechanisms (Bagchi 1987; Ganjian et al. 2004; Glasser 2013). The sorption process itself is divided into two individual processes referred to as adsorption and absorption

(filtration). As a physicochemical process, the former is controlled by the specific surface area and negatively charged sites. The latter, which is a physical mechanism, pertains to the diffusion of contaminants into the structure of a porous particle (Pignatello and Xing 1996). The extent of sorption depends heavily on the properties of sorbents and contaminants, including their size, shape, molecular structure, functional groups, solubility, polarity, charge distribution, and pH (Pignatello 1998). Filtration or absorption mechanisms physically entrap solid particles into pore structures of liner systems. The pore size of a liner and the hydraulic gradient of the leachate control the performance of this mechanism. Pore size and leachate gradients affect the filtration performance of liners (Fuller 1977). Precipitation is also influenced by ionic species, temperature, acid-base pH, redox potential, and solvent concentration (Minnesota 1978). Regardless of the initial pH of the soil, the pH of a leachate-saturated soil becomes near-neutral, adversely affecting the precipitation mechanism. Moreover, the ion exchange reactions are controlled by the atomic radius and the valence of the ions (Mitchell 1976). Microorganisms will also control the adsorption, breakdown, or containment of the contaminants due to biological actions (Fuller 1977).

#### *Shear Resistance*

Liners must also be strong enough to endure the pressure induced by dumping and compaction operations during field-operational phases. In order to provide a strong surface, an adequate compressive strength of 5 N/mm<sup>2</sup> was recommended by Ganjian et al. (2004). In addition, liners must be stable enough to satisfy the criteria for the stability of side slopes of above-ground landfills (Daniel 1993).

#### *Volumetric Shrinkage*

Desiccation cracks, occurring due to the loss of moisture, affect significantly the performance of liners. Desiccation cracks lead to reduced mechanical strength and greater compressibility and hydraulic conductivity (Chertkov 2000). The threshold limit of volume shrinkage must be limited to 4%, therefore (Kleppe and Olson 1985).

### COMMON ACTIVE-PASSIVE LINERS

Because geosynthetic layers are impermeable to water, geosynthetic clay liners possess insignificant leachate-attenuation capacities. At the other end of the spectrum, compacted clay liners have been used as natural attenuation systems because of their acceptable attenuation capacity. For hydraulic conductivity, however, the threshold limit of  $9 \times 10^{-9}$  m/s is practically impossible to reach. Furthermore, punctures and tears induced during waste placement, desiccation cracks, aging, and diffusion of chemical substances threaten physical containment in the synthetic membranes and compacted clay liners (Daniel 1993). Desiccation and cracking might also increase the hydraulic conductivity by as much as 1000 times compared with the value measured in the laboratory (Daniel 1984).

Compacted clay liners attenuate the concentration of heavy-metal ions by means of adsorption, precipitation, and cation-exchange mechanisms. The sorption capacity of kaolinite to remove lead, cadmium, nickel, and copper from landfill leachate was reported by Majone et al. (1998). Clay liners work well at adsorbing Pb, Zn, Cu, Ba, Cr, and Al, whereas they exhibit only moderate capacity to immobilize Ni, NH<sub>4</sub>, As, Cd, K, Na, Mg, and Fe and weak capacity to attenuate the concentration of B, sulfate, chloride, Mn, and Hg (Bagchi 1987). Macro-fabric fissures within a clay layer decrease proper contact between the leachate and the soil, however, thereby reducing the attenuation capacity of compacted clay liners (Bagchi 1987). The sealing properties of compacted clay liners may be affected adversely by chemical attack because strong acids and bases can dissolve soil structure, form channels, and enhance hydraulic conductivity (Daniel 1993). Furthermore, hydraulic conductivity and chemical properties change for several reasons, including particle flocculation, reduced double-layer thickness, desiccation, and variation in cation charge and the electrolyte concentration. These, consequently, threaten the chemical and physical containment in liners (Broderick and Daniel 1990). Cementitious materials are also applied either as physical or chemical containment barriers (Ganjian et al. 2004). Based on US guidelines, an impermeable flexible membrane, 30 mm thick, sandwiched between two 150-mm layers of soil-cement, showed promising results as a physical containment barrier for toxic waste (Schevon and Damas 1986; Dinchak 2009). Besides, the chemical containment mechanism in Portland cement has been investigated in detail for nuclear waste (UK Nirex 1993). A highly alkaline environment precipitates many metals in the form of relatively insoluble salts when they migrate through a cementitious liner. An increase in pH from 8 to 12.5 decreases the solubility of U, Pu, Pa, and Am by 1–3.5 orders of magnitude. Nonetheless, this process is a sacrificial action leading to the dissolution of cement hydrates and consequently diminishes the chemical and physical containment capacity of the liner. Moreover, electropositive metals may not be suitable or at least less appropriate for immobilization by Portland cement (Ganjian et al. 2004; Glasser 2013). The drawbacks of the current active-passive liners and/or the scarcity of suitable local soils which satisfy the above-mentioned requirements both mean that sustainable liner materials are required.

### CLAY-FLY ASH-BASED GEOPOLYMERS AS ACTIVE-PASSIVE LINER MATERIALS

Several studies have been carried out to evaluate the performance of waste materials, such as steel slag and fly ash, as liner materials (Nhan et al. 1996; Hettiaratchi et al. 1999; Sivapullaiah and Lakshmikantha 2004; Andreas et al. 2014). These residual materials can improve significantly the sorption capacity of volatile organic compounds in comparison to typical inorganic clays (Palmer et al. 2000). For multi-layer liners constructed with waste materials, suitable physical blocking, chemical buffering capacity, and relatively high resistance to organic acids were reported by Ganjian et al. (2004). Those

authors showed that the combination of cement kiln dust with Lagoon ash, shell sand and chrome alumina, granulated blast furnace slags and Run-of-Station ash, cement kiln dust, ferrosilicate slag or ground granulated blast furnace slag with the Portland cement, chrome alumina slag, and Greensand fulfills the requirements. Among all of the waste materials available, however, low-Ca precursors, including metakaolin and class-F fly ash, are favored for use in landfill liners because of their low Ca content – Ca adversely affects liner durability.

Among all available low-Ca precursors, class-F fly ash has been used most widely because of its interesting properties. Many studies have evaluated the utility of both classes of raw fly ash or a mixture of fly ash with other materials, e.g. bentonite, cement, lime, gypsum, or sand as a physical liner barrier (Vesperman et al. 1985; Shackelford and Glade 1994; Palmer et al. 2000; Prashanth et al. 2001; Yeheyis et al. 2009); Sivapullaiah and Moghal (2011) indicated that adding 10–20% bentonite, gypsum, or lime to fly ash could cause the hydraulic conductivity of the liner to decrease to  $<10^{-9}$  m/s. Mixtures of class-F and class-C fly ashes with coarse aggregates, compacted at water contents above optimal, could achieve hydraulic conductivity values near or  $<10^{-9}$  m/s, according to Palmer et al. (2000). The usability of the mixtures of cement and class-F fly ash for the construction of a landfill liner by evaluation of the hydraulic conductivity, shrinkage behavior, compressibility, and shear strength parameters was explored by Mishra and Ravindra (2015). The results showed that the mixture of 90% fly ash and 10% cement compacted at 5% optimum moisture content satisfied the value limits of hydraulic conductivity and volume shrinkage,  $9 \times 10^{-9}$  m/s and 4%, respectively. Regarding the attenuation potential, some research studies have shown that alkali-modified fly ash absorbs most toxic elements found in leachates (Chakradhar and Kotach 2016). Oruh and Nuri Ergun (2010) also suggested that fly ash and red mud were more effective than phosphor gypsum in mitigating Zn in leachate. Bowders et al. (1990) showed that the addition of cement or lime to fly ash reduced the leaching capacity of Cu, Cd, Cr, and Pb, while the addition of bentonite increased the metals content in leachate. The effectiveness of the addition of even 2.5% cement to fly ash in order to reduce the leaching rate of Mo and Cr was reported by Creek and Shackelford (1992).

Although raw or alkali-modified fly ashes exhibit acceptable adsorption capacity, their by-products including zeolites and geopolymers show superior sorption capacity because of the greater possibility of cation-exchange reactions, specific surface area, precipitation reactions, and molecular-sieving properties (Li et al. 2006; Al-Zboon et al. 2011; Mužek et al. 2014). Due to the adverse effects of Ca on the long-term durability and formation of zeolite, class-F fly ash is deemed to perform better than class-C fly ash as a landfill liner. Low-Ca geopolymers might be a suitable material for the immobilization of Zn because that reacts with the Ca in Portland cement and dissolves the cementitious matrix (Fernández Pereira et al. 2009). This is the so-called ‘sacrificial immobilization mechanism’ of Portland cement alluded to above (Ganjian et al. 2004; Glasser 2013). In spite of the Ca-rich


cement products, blends rich in class-F fly ash may form zeolite in the long term, which guarantees their long-term durability and attenuation capacity (Glasser 2013). The presence of a type of zeolite, i.e. hydroxy sodalite, was suggested as the by-product of a fly ash-based geopolymer with NaOH (Palomo et al. (2004). Hydroxysodalite, a superior sorptive zeolite, has often been used as a hydrophilic compound for the separation of water from various organic materials (Ruenngam et al. 2009). The presence of zeolites Na-P and herschelite as secondary reaction products are illustrated in Fig. 1 (Fernández-Jiménez et al. 2017).

The physical and chemical properties of geopolymers make them attractive candidates for both waste stabilization and heavy-metal immobilization (Davidovits and Comrie 1988; Davidovits et al. 1990). Geopolymerization, which may be promising in terms of chemical attenuation capacity, is a low-energy technique for creating an environmentally benign barrier from solid waste that can immobilize heavy metals. One study found that leaching of Pb with 6000 mg/L initial concentration from polluted samples decreased to a range varying from 25.3 mg/L to only 2.1 mg/L when polluted samples were treated by geopolymerization (Comire et al. 1989). The leaching behavior of Cu and Pb from a mixture of kaolinite and fly-ash activated with either NaOH or KOH was investigated by Van Jaarsveld et al. (1998). The Cu- and Pb-bearing samples showed similar leaching behaviors. In the immobilization process, heavy metals were incorporated into the matrix as cations through physical encapsulation and chemical bonding (Van Jaarsveld et al. 1998). The immobilization behaviors of Pb, Cu, and Zn showed that the mobilization of heavy metals decreased with an increase in pH. Other than for As, the other heavy metals, such as Cd, Pb, Zn, Sn, Ni, Mn, Cu, and Cr, were inert at high pH (Wajjarean et al. 2014). Leaching of Pb, Cu, and Zn was reduced by an increase in pH, according to Suzuki and Ono (2008). These results justify the use of alkaline activation to immobilize heavy metals. Geopolymeric powders are also used for the removal of heavy metals from wastewater by adsorption and ion-exchange mechanisms (Al-Zboon et al. 2011; Javadian et al. 2015). Not surprisingly, the physical and chemical properties of geopolymers control their attenuation capacity.

A comparison between the attenuation potential of conventional clay liners and geopolymers, drawn from the literature, is presented in Table 1. The majority of the investigations into geopolymers are about specific types of heavy metals.  $\text{NH}_4^+$  and  $\text{Cl}^-$  are adsorbed better by geopolymers than by clays, while  $\text{NH}_4^+$  is partly attenuated by the compacted clay liner due to cation-exchange reactions.

In order to define the steps of geopolymerization and the formation of aluminosilicate gels, a model was proposed (Fig. 2). The final stage of geopolymerization clearly produced a porous structure which controls the contaminant capacity and hydraulic conductivity of the final products. Water content and curing temperature are of paramount importance in determining the type of final reaction products (Table 2). Temperatures of  $\sim 40$ – $80^\circ\text{C}$  can be considered as the distinguishing line between “low” and “high” temperature (Provis et al. 2005). High



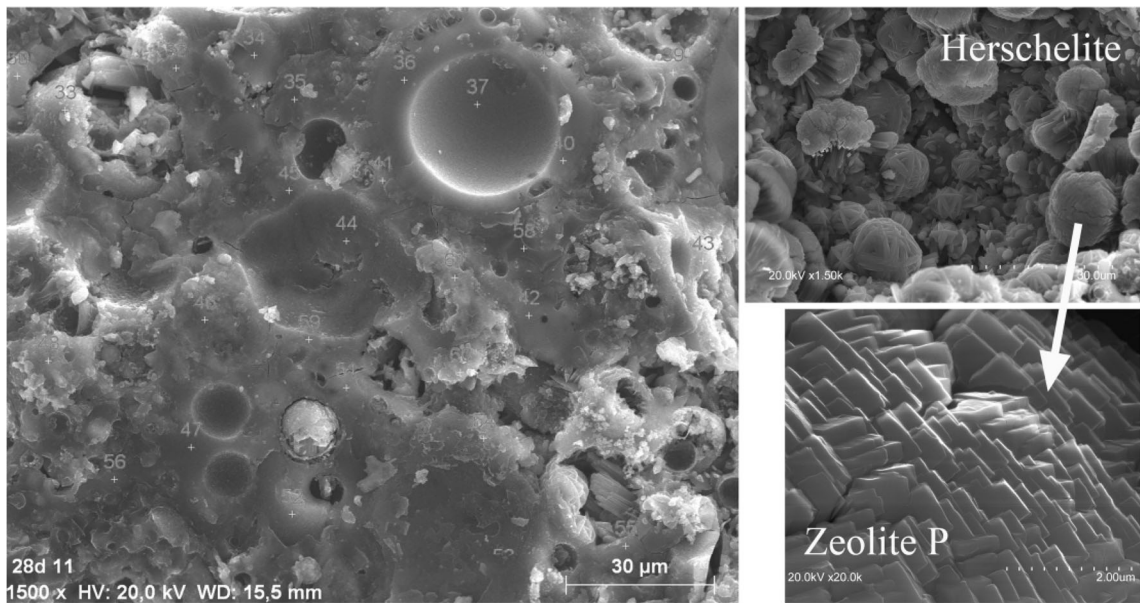

**Fig. 1.** The presence of zeolites Na-P and herschelite as secondary reaction products (reproduced from Fernández-Jiménez et al. 2017 with the permission of Elsevier)

temperatures, contributing to the formation of geopolymer or zeolite, cannot be practical in landfill sites. Nevertheless, the water content and alkali concentration can be adjusted appropriately to achieve suitable final products. At low temperatures, amorphous aluminosilicate gels and geopolymer can be produced with large and small water contents, respectively. Although the ratio of water to alkali is important, the range 10–20% is considered to mark the border between the large and small water contents (Provis et al. 2005). Geopolymer is the polymerization of aluminosilicate gels with the contributions of alkaline metals and smaller water contents and greater alkali concentrations leading to quicker reactions and more amorphous geopolymer.

A highly amorphous geopolymer was produced from waste coal fly ash as an adsorbent for removal of Pb from wastewater (Al-Zboon et al. 2011). Those authors combined certain portions of fly ash with 14 M NaOH solutions to obtain a mass ratio of 1.25 for the fly ash/NaOH; the adsorption capacity of the geopolymer was best when this ratio was >1.2. The paste was cured at 105°C for 24 h in an oven and then kept at ambient temperature for 3 days. The removal efficiency was enhanced when geopolymer dosage, contact time, and temperature increased and the initial concentration of Pb decreased (Al-Zboon et al. 2011). A similar preparation method was used by Mužek et al. (2014), who mixed portions of fly ash with 16 M NaOH and Na silicate solutions to reach 0.4 for the solution/ash ratio. The curing processes were selected as 24 h at 85°C followed by another 3 days at room temperature. Finally, the geopolymers were crushed to obtain particles with diameters of <0.045 mm. Fourier-transform infrared spectra for the geopolymer and raw fly ash are shown in Fig. 3. In all geopolymeric materials, new bonds in the regions of 1653  $\text{cm}^{-1}$  and 3456  $\text{cm}^{-1}$  are the signs of bending and

stretching vibrations of (H–O–H), referring to the presence of water necessary for the hydrolysis of aluminosilicate precursors. The peaks at 1087  $\text{cm}^{-1}$  and 1015  $\text{cm}^{-1}$  in the raw fly ash and geopolymer, respectively, refer to the asymmetric stretching vibrations of Si–O–Si and Al–O–Si bonds (Mollah 1994; Rao et al. 1994). The decrease observed in the intensity of the peaks could be attributed to the dissolution of primary phases and the formation of amorphous aluminosilicate gels.

The results of some major research studies of the attenuation capacity of raw fly ash and its by-products are listed in Table 3. As reported by Javadian et al. (2015), 0.08 g of fly ash-based geopolymer in a 25 mL solution could attenuate 84% of Cd, while Shahoo et al. (2013) showed that 120 g/L of alkali-modified fly ash could adsorb 71% of Cd. This proved the better performance of a fly ash-based geopolymer compared to an alkali-modified fly ash.

In previous research, the fusion method and hydrothermal processes were used to convert fly ash to amorphous geopolymers. In the fusion method, fly ash is mixed with solid alkali under fusion temperatures (Li et al. 2006; Wang et al. 2007). Due to the need for high temperature, this method is not applicable in the field to construct a liner. The hydrothermal process introduced by Davidovits (1991) can also produce amorphous aluminosilicate from fly ash. In this method, the aluminosilicate minerals react with an alkaline solution at temperatures of between 20 and 100°C, which are practical in the field.

The studies mentioned used geopolymer powders as adsorbent materials, while a liner system is expected to work as a finite layer. In such a case, the surface area available will be decreased and the micro- and macro-porosity of a liner play fundamental roles in its attenuation capacity. The first condition to attenuate chemical substances is attributed to the

**Table 1.** A comparison of attenuation capacity between compacted clay liners and geopolymers (data from Pacheco-Torgal et al. 2015; Bagchi 1987)

Chemical Constituents	Clay	Geopolymer	Chemical constituents	Clay	Geopolymer	Chemical constituents	Clay	Geopolymer	Chemical constituents	Clay	Geopolymer	Chemical constituents	Clay	Geopolymer
Al	H	-	Cd	M	H	CN <sup>-</sup>	L	-	Hg	L	-		L	-
NH <sup>4+</sup>	M	H	Ca	L	-	F <sup>-</sup>	L	-	Ni	M	M		M	M
As	M	L	COD <sup>1</sup>	M	-	Fe	M	-	NO <sub>3</sub>	L	-		L	-
Ba	H	-	Cl <sup>-</sup>	L	M	Pb	H	H	K	M	M		M	-
Be	H	H	Cr <sup>3+</sup> -Cr <sup>4+</sup>	H	M	Mg	M	-	Se	M	M		M	L
B	L	-	Cu	H	H	Mn	L	M	SiO <sub>2</sub>	M	M		M	-
Na	H-L	-	SO <sub>4</sub> <sup>2-</sup>	L	-	Zn	H	H	Cs	-	H		-	H
Sr	-	H	U	-	M		-	-		-	-		-	-


H: High, L: Low, M: Medium

percolation of leachate into liner systems. Further study is needed to obtain the correct fly ash/alkali ratio and alkaline solution concentration when a geopolymer is to be used as a finite layer.

Fly-ash properties, activator type and concentration, and curing condition are significant factors which control the pore structure of fly ash-based geopolymers. In contrast to the conditions that form an amorphous geopolymer, the porosity of the geopolymer will increase if the fly-ash particles are larger, the alkali concentration lower, the liquid/solid ratio higher, and the silica content lower (Zhang et al. 2012). Based on the target contaminants in a specific leachate, the alkali concentration, water content, and fly ash/alkali ratio must be adjusted in order to produce a simultaneously suitable porous structure. A small dosage of activator (18%) leads to a larger pore size with wide pore-size distribution (19.8–2342 Å) whereas a larger activator dosage (30%) results in a smaller pore size with narrower distribution (19.8–1155 Å). This is due to the fact that greater activator dosages increase the dissolution of particles and the formation of aluminosilicate gels (Ishwarya 2013). The porosity of geopolymers decreased with increases in the relative humidity of the environment (Criado et al. 2012). Samples cured for 30 days inside air-tight containers with relative humidity of 90% at 80°C were much more compacted than those cured at the same temperature but with 40–50% relative humidity.

Hydraulic conductivity tests reveal that the fly ash-based binders show lower hydraulic conductivity than in conventional cement binders (Fig. 4) due to the much smaller pore size, although their porosities may be comparable. If both moduli of activator and liquid/solid ratio are = 1.5, hydraulic conductivity shows the lowest value, while if the moduli of activator and liquid/solid ratio are 0.5 and 1.5, respectively, hydraulic conductivity is  $\sim 10^{-9}$  m/s (Ma et al. 2013). As noted above, this value has been presented as the threshold hydraulic conductivity for active-passive liners (Daniel 1993). A larger liquid/solid ratio produces more porosity with smaller pore size (Table 4). It also shows that the pore size of fly ash-based binders is mostly in the range 10–50 nm, while Portland cement binders have larger pores, ranging from 20 to 200 nm. The capillary absorption is very high for fly ash-based binders in comparison to Portland cement binders (Zhang et al. 2012). Greater capillary absorption may be appropriate for the attenuation capacity because absorption is a major mechanism involved in the attenuation process.

Some research studies have used geopolymerization appropriately to improve the mechanical properties of local soil (e.g. Rios et al. 2016). Because this process decreases the plasticity limits of clay, shrinkage cracking, long-term consolidation, and occasional chemical instability can, therefore, be controlled by geopolymerization. Montmorillonite showed a significant decrease in plastic limit after activation with NaOH, whereas small changes in plastic limit were observed for illite (Alastair et al. 2018). Clay minerals can also be used as a proper filler for fly ash-based geopolymers which might contribute to the attenuation process due to its aluminosilicate content.

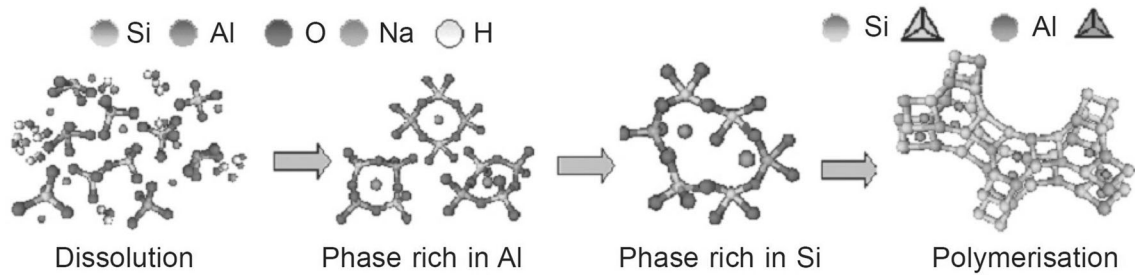

**Fig. 2.** Model proposed to form aluminosilicate gels (reproduced from Pacheco-Torgal et al. 2015, with the permission of Elsevier)

Finally, geopolymers can satisfy all the minimum requirements introduced earlier for an active-passive barrier. A compressive strength of 35 MPa for fly ash activated with 8–12 M NaOH solution was reported by Palomo et al. (1999). Both fly ash-based geopolymers and clay-fly ash-based geopolymers may be sustainable active-passive liners that can reduce the intrinsic problems of the common liners. Evaluation of the attenuation capacity of clay-treated fly ash-based geopolymers is often ignored, however. For this reason, as the properties of final products are related directly to the primary composition, the following sections clarify the characteristics of the components involved in the use of clay-fly ash-based geopolymers as liner materials.

#### COMPONENTS OF THE PROPOSED LINER (CLAY-FLY ASH GEOPOLYMER)

##### *Fly Ash and its Sorption and Durability*

As a source of amorphous aluminosilicates, class-F fly ash consists of hollow spheres of various sizes, including major vitreous phases with some minor crystalline phases, such as quartz, mullite, hematite, magnetite, and some calcium oxides. An advantage of fly ash is its Si to Al ratio in the range of 1–2, which is appropriate for geopolymerization (Pacheco-Torgal et al. 2008).

Class-F fly ash possesses a high affinity for metal ions because of the existence of alumina, silica, Fe oxides, and unburned carbon in its chemical composition. Furthermore, it has a porous structure, fine particles, and a large specific surface area in any environment. The low- and high-pH values lead to positively and negatively charged silica surfaces, respectively, which adsorb variously charged particles. Alumina and iron oxides also follow the same pattern of developing positive or negative charges depending on the pH value of the environment (Mohan and Gandhimathi 2009). Accordingly, raw fly ashes are appropriate adsorbent materials, especially in

alkaline environments (Chakradhar and Kotach 2016). However, they show less adsorption capacity than their by-products, which include zeolites and geopolymers (Li et al. 2006; Wang et al. 2007; Al-Zboon et al. 2011; Mužek et al. 2014). Studies which prove the adsorption capacities of raw fly ash and amorphous geopolymers are listed in Table 3. The research confirmed that class F fly ash-based geopolymer has superior adsorption capacity, which suggests fly ash as an alternative material containing reactive aluminosilicates. All of this makes the class-F fly ash-based geopolymer a viable alternative for heavy-metal removal from aqueous solutions. The ambient temperature, NaOH content, initial concentration of contaminants, and adsorbent dosage all influence the removal efficiency of heavy metals. The sorption of Cu ions was reported by Mužek et al. (2014) to increase with increase in temperature, which is a positive feature because waste degradation usually produces heat, enhancing the sorption capacity. Commonly only 50% of fly ash participates in the geopolymerization process (Palomo et al. 2004). Thus, the sorption capacity of non-reacted fly ash is also regarded as a worthwhile benefit to attenuate contaminants by geopolymeric liners.


Long-term chemical resistance is also a significant advantage of low-Ca fly ash-based geopolymers over cementation and clay liners. In general, alkaline aluminosilicates are more durable than Ca aluminosilicate because most degradation processes of cemented materials, such as sulfate, alkali, and acid attacks, are attributed to the dissolution of Ca (Pacheco-Torgal et al. 2008). Fly ash-based geopolymer shows high resistance in acid media, elevated temperatures, and against freeze-thaw cycles and are also less prone to expansion (Bakharev 2005; Fu et al. 2011). A decrease of only 30% was observed in the resistance of alkaline activated fly ash binders after 150 freeze-thaw cycles (Dolezal et al. 2007). Drying shrinkage was also very high for a fly ash-based geopolymer, as confirmed by Ma and Ye (2015) but did not cause early age cracking in the fly ash-based geopolymer because it had a very small early-age elastic modulus and also showed large creep strains with relaxation. Although fly-ash geopolymers exhibited greater drying shrinkage compared to Portland cement (Temuujin et al. 2009), their drying shrinkage was considerably less than in compacted clays.

##### *NaOH and its Sorption and Durability*

The type of the alkaline solution exerts considerable control over the dissolution of aluminosilicate components. NaOH

**Table 2.** Products of solid aluminosilicates at various temperatures and water contents (reproduced from Provis et al. 2005; copyright 2005 the American Chemical Society)

Water content	Temperature	
	Low	High
Small	Geopolymer	Geopolymer or zeolite
Large	Aluminosilicate gel	Zeolite

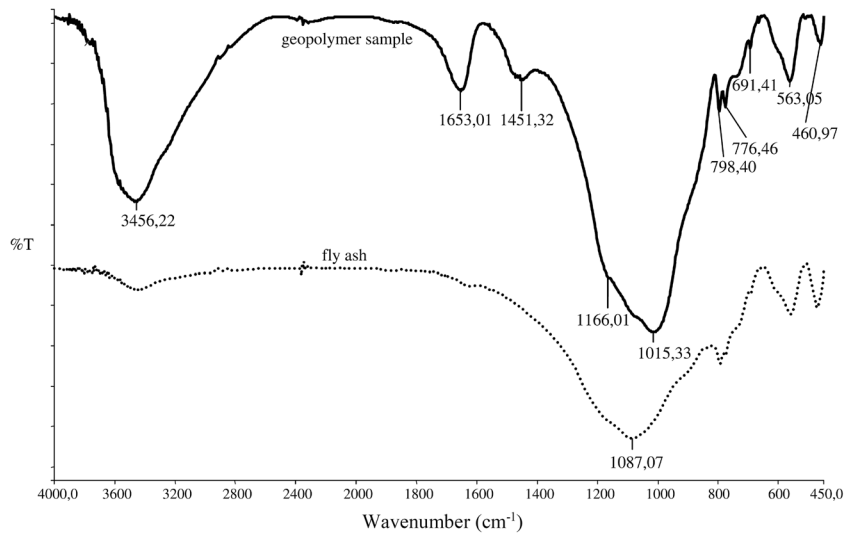


**Fig. 3.** FTIR spectra of raw fly ash and geopolymer sample (reproduced with permission from Mužek et al. 2014; copyright 2014, the European Desalination Society).

**Table 3.** A summary of selected studies elaborating on the adsorption ability of raw fly ash and by-products

Researchers	Type of fly ash used	The quality of modification	Optimum condition	Removal of
Komnitsas et al. (2004)	Lignite fly ash barriers			Fe, Zn, Mn, Ni, Cd, Co, Al, and Cu from acidic leachates
Majone et al. (1998)	Raw fly ash		2 g/L	39%, 28%, 74%, 42%, and 71% for Cu, Mn, Pb, Zn, and Cd, respectively
Sahoo et al. (2013)	Alkali modified fly ash with 1 M NaOH solution after keeping at 90 °C for 24 h	Less Si and Al, greater surface area and higher pH	120 g/L	99, 89, 92, 94, 96, and 60% of Al, Ni, Zn, Pb, Fe, and Mn
Li et al. (2006)	Amorphous aluminosilicate with 1.2/1 NaOH/fly-ash ratio and 250–350°C, fusion method			Basic dyes, methylene blue and crystal violet
Al-Zboon et al. (2011)	Amorphous geopolymer with 14 M NaOH and constant mass ratio of 1.25	Greater Na content, less silica and Al oxide	pH = 5	Pb
Wang et al. (2007)	Amorphous aluminosilicate with NaOH fusion method		0.1, 3, 5 and 92 mg/g, for raw fly ash, natural zeolite, fly ash-based geopolymer	Cu
Mužek et al. (2014)	Amorphous aluminosilicate with water glass solution and 16 M NaOH	Solution/ash ratio = 0.40		Cu
Javadian et al. (2015)	Amorphous aluminosilicate with 1 M NaOH fusion solid-state conversion at 600°C	Porous aluminosilicate, increasing the surface area, pore volume, and adsorption capacity	0.08 g sorbent dose in 25 mL of Cd at pH = 5	84% Cd



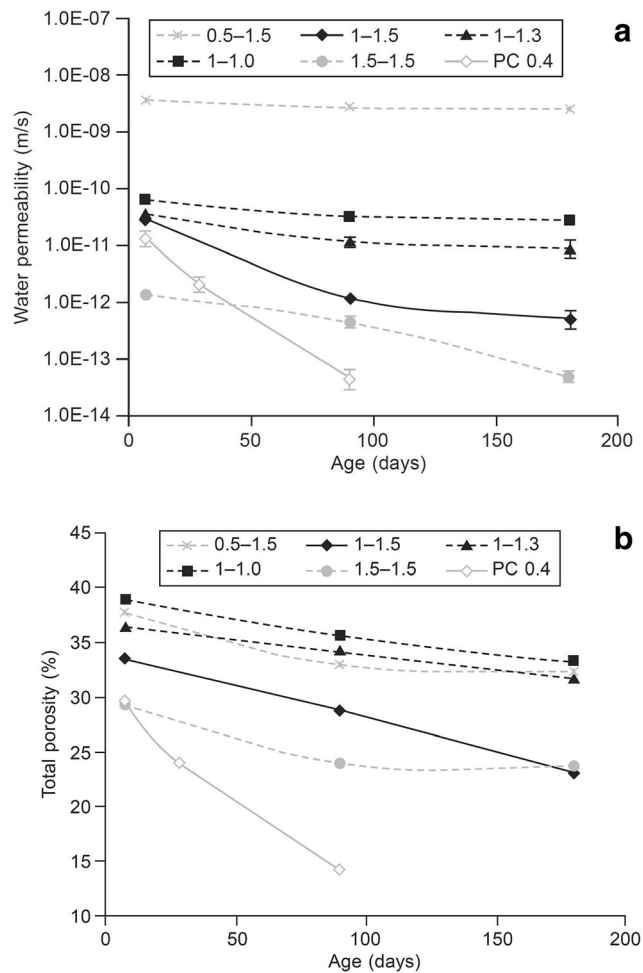

**Fig. 4.** Variation in **a** hydraulic conductivity and **b** porosity of geopolymers with activator modulus and liquid:solid ratio (reproduced from Ma et al. 2013 with the permission of Elsevier)

solution increases the leaching of silica and Al ions compared to KOH solution (Van Jaarsveld et al. 1999), contributing to the production of more aluminosilicate gels.

A solution produced using KOH and Na silicate forms amorphous products, while NaOH solution may produce compositions similar to that of natural zeolite (Palomo et al. 1999). The possibility of zeolite-like products, higher pH, and more dissolution of aluminosilicate contents make NaOH solution a rewarding option for the geopolymerization of fly ash.

The most efficient immobilization of Pb, Cu, and Cd was recorded for NaOH solution rather than for a Na silicate-containing solution (Phair et al. 2004). Because Na ions lead to weaker bonds compared to K, it is more exchangeable and, thus, increases the CEC, which contributes to greater adsorption capacity. All of the above-mentioned studies (Table 3), which investigated the adsorption capacity of fly ash-based geopolymers, used NaOH as the alkaline activator (Skvara et al. 2012).

Furthermore, the type of alkali activator affects considerably the pore size and porosity of fly ash-based geopolymer. Fly ash activated by NaOH possessed much greater porosity

than the binder activated by a solution of NaOH mixed with Na silicate (Fig. 5) (Paloma et al. 1999). Because a larger silica content forms a more compacted structure due to the formation of more aluminosilicate gel, a fly ash-based geopolymer activated by NaOH has greater porosity than binders activated by  $\text{Na}_2\text{O} \cdot 0.5\text{SiO}_2$  (Kohljenović et al. 2010). Bakharev (2005) also confirmed that specimens activated with non-silicate alkaline activators resisted sulfate attack better.

## CONCLUSION AND FUTURE PROSPECTS



In presenting a scope of work for the future, this review provides general information about the usability of clay-fly ash-based geopolymers as active-passive liners in order to reduce environmental concerns. Although raw fly ash performs well as an active-passive barrier, its by-products, including geopolymers, show superior attenuation capacity which justifies their utilization as active-passive liners. In general, in addition to showing superior long-term durability and sorption capacity, fly ash activated with NaOH can produce various porous structures depending on

**Table 4.** The fraction (%) of total porosity represented by various pore sizes from <10 to >100 nm and total porosity for fly ash-based binders prepared with various liquid/solid and water/solid ratios. Values for Portland cement are given for comparison (Zhang et al. 2012).

Binder	Liquid/solid ratio	Water/solid ratio	Pore size (nm)				Porosity (%)
			<10	<20	<50	>100	
FA-based	0.6	0.32	19.3	71.5	93.3	3.7	27.2
FA-based	0.7	0.36	24.6	76.4	93.2	4.4	31.2
FA-based	0.8	0.41	22.3	74.8	93.5	3.2	33.8
Portland cement	0.35	0.35	5.0	24.4	45.0	34.1	8.0

the alkaline concentration, Si content, and curing condition. It can offer admixtures with flexible components that can be adjusted to tweak the properties of the final geopolymers, thereby making them most suitable for the contaminant species in a leachate. In general, the following are the proposed grounds for prospective research on the potential performance of clay-fly ash-based geopolymers as active-passive liners.

- (1) NaOH solution offers promise as a competent activator owing to the fact that it improves CEC, immobilization, the dissolution of aluminosilicate precursors, the possibility of forming zeolites, and porous structure. Further elaboration is needed.
- (2) Fly ash provides an appropriate Si:Al ratio, which is in the range of 1–2. Furthermore, in contrast to clays, all

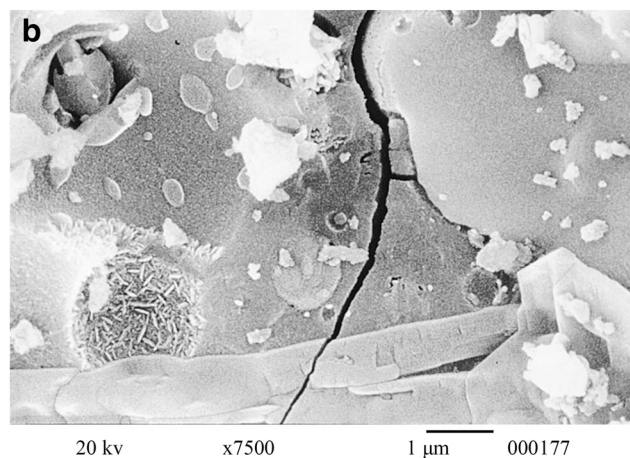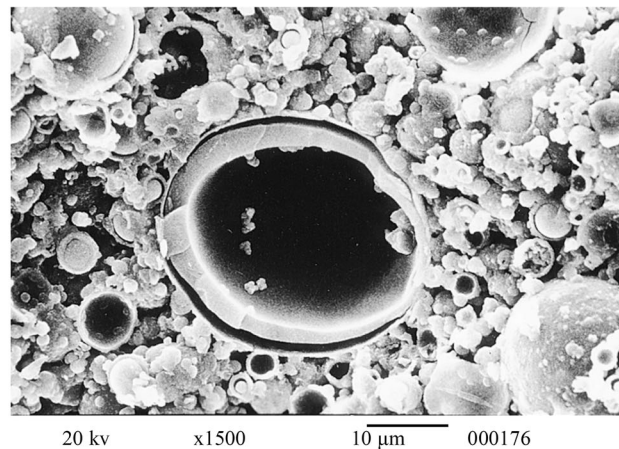

**Fig. 5.** SEM images of fly ash-based binders using various activator solutions: **a** activated by 12 M NaOH for 24 h at 85°C, Si/Al = 1.5; **b** activated by Na<sub>2</sub>O·SiO<sub>2</sub> for 24 h at 85°C, Si/Al = 2.8 (reproduced from Palomo et al. 1999 with the permission of Elsevier)

- states of fly ash included in the final geopolymers, such as raw fly ash, alkali-modified fly ash, aluminosilicate gels, and zeolites, exhibit excellent sorption capacity. Fly ash is, therefore, suggested as a good precursor for active-passive liners. Again, further elaboration is required.
- (3) Because the physical properties of fly ash-based geopolymers, including porosity and hydraulic conductivity, are very dependent on the activator concentration, water content, and curing conditions, the components of fly ash-based geopolymers can be adjusted according to the requirements of specific projects. So, they offer flexible admixtures for liner materials to reach the requirements. Further investigations are suggested to shed more light on this issue.
  - (4) The agglomeration of nano-crystalline zeolites bonded by aluminosilicate gels guarantees the long-term durability of liners. Unlike current liner materials, the passage of time is expected to enhance the long-term performance of geopolymers because of the possibility of forming zeolites. Further scrutiny is required here also.
  - (5) Smaller alkali concentration, larger liquid:solid ratios, and smaller silica contents will cause greater porosity in geopolymers, while these conditions reduce the possibility of the formation of amorphous geopolymers. Further investigations are necessary to determine appropriate alkali concentration, water content, and the ratio of fly ash to alkali to reach appropriate pore structure and produce enough amorphous geopolymer.
  - (6) When geopolymerization is used to modify the properties of local clay minerals, the clays, as filler by default, also form a good aluminosilicate precursor, providing more Si. Clay minerals can participate in the attenuation process while their desiccation shrinkages, long-term consolidation, and chemical instability can be improved. This, however, is subject to further clarification.

## Compliance with Ethical Standards

### Conflict of Interest

No funding was received to carry out this research. There are no conflicts of research to be reported. No human/animal rights issue is relevant here.

## REFERENCES

- Alastair, M., Andrewa, H., Pascaline, P., Mark, E., & Pete, W. (2018). Alkali activation behavior of un-calcined montmorillonite and illite clay minerals. *Applied Clay Science*, *166*, 250–261.
- Al-Zboon, K., Al-Harashsheh, M. S., & Bani Hani, F. (2011). Fly ash-based geopolymer for Pb removal from aqueous solution. *Hazardous Materials*, *188*, 414–421.
- Andreas, L., Diener, S., & Lagerkvist, A. (2014). Steel slags in a landfill top cover—Experiences from a full-scale experiment. *Waste Management*, *34*, 692–701.
- Bagchi, A. (1987). Natural attenuation mechanisms of landfill leachate and effects of various factors on the mechanisms. *Waste Management & Research*, *453*–463.
- Bakharev, T. (2005). Durability of geopolymer materials in sodium and magnesium sulphate solutions. *Cement Concrete Research*, *35*, 1233–1246.
- Bowders, J., Gidley, J., & Usmen, M. (1990). Permeability and leachate characteristics of stabilized class F fly ash. Pp. 70–77 in: *Transportation Research Record 1288 TRB*, National Research Council, Washington D.C., April 1991.
- Broderick, G. P., & Daniel, D. E. (1990). Stabilizing compacted clay against chemical attack. *Geotechnical Engineering*, *116*, 1549–1567.
- Chakradhar, V. & Katoch, S.S. (2016). Study of fly ash in hydraulic barriers in landfills – A review. *International Journal of Advanced Science, Engineering & Technology*, *5*, 32–38.
- Chamberlain, E.J., Iskander, I., & Hunsicker, S.E. (1990). Effect of freeze-thaw cycles on the permeability and macrostructure of soils. Pp. 145–155 in: *Proceeding of International Symposium on Frozen Soil Impacts on Agricultural, Range, and Forest Lands*.
- Chertkov, V. Y. (2000). Using surface cracks spacing to predict crack network geometry in swelling soils. *Soil Science Society of America*, *64*, 1918–1921.
- Comire, D.C., Paterson, J.H., & Ritcey, D.J. (1989). Applications of geopolymer technology to waste stabilization. Pp. 161–165 in: *Third International Conference On New frontiers for Hazardous Waste Management - Proceedings*. US Government Printing Office, Cincinnati, Ohio, USA.
- Creek, D. & Shackelford, C. (1992). Permeability and leaching characteristics of fly ash liner materials. *Transportation Research Record 1345 TRB*, National Research Council, Washington, D.C., 74–83.
- Criado, M., Fernández Jiménez, A., Sobrados, I., Palomo, A., & Sanz, J. (2012). Effect of relative humidity on the reaction products of alkali activated fly ash. *Journal of European Ceramic Society*, *32*, 2799–2807.
- Daniel, D. E. (1984). Predicting hydraulic conductivity of clay liners. *Geotechnical Engineering*, *110*, 285–300.
- Daniel, D. E. (1993). *Geotechnical Practice for Waste Disposal*. Dordrecht, The Netherlands: Springer Science, Business, Media.
- Davidovits, J. (1991). Geopolymers: Inorganic polymeric new materials. *Journal of Thermal Analysis*, *37*, 1633–1656.
- Davidovits, J. (1994). Alkaline cement and concretes, properties of geopolymer cements. In: *Proceedings of the First International Conference on Alkaline Cements and Concretes*, Kiev, Ukraine, 131–149.
- Davidovits, J., & Comrie, D. (1988). Archaeological long-term durability of hazardous waste disposal: preliminary results with geopolymer technologies, Division of Environmental Chemistry. *American Chemical Society*, Extended Abstracts, 237–240. See also: Long term durability of hazardous toxic and nuclear waste disposals. *Geopolymer '88: First European Conference on Soft Mineralurgy*, 125–134.
- Davidovits, J., Comrie, D., Paterson, J., & Ritcey, D. (1990). Geopolymeric concretes for environmental protection. *ACI Concrete International*, *12*, 30–40.
- Dinchak, W.G. (2009). A soil cement/synthetic liner for hazardous waste impoundments. *Water International*, 79–83.
- Dolezal, J., Skvara, F., Svoboda, P., Sulc, R., Kopecky, L., Pavlasova, S., Myskova, L., Lucuk, M. & Dvoracek, K. (2007). Concrete based on fly ash geopolymers. Pp. 185–197 in: *Alkali activated materials – research, production and utilization 3rd conference*, Prague, Czech Republic.
- Engelhardt, G., & Michel, D. (1987). *High Resolution Solid State RMN of Silicates and Zeolites*. New Delhi: John Wiley & Sons.
- Fernandez-Jiménez, A., Cristelo, N., Miranda, T., & Palomo, A. (2017). Sustainable alkali activated materials: precursor and activator derived from industrial wastes. *Journal of Cleaner Production*, *114*, 40–48.
- Fernández Pereira, C., Galiano, Y., Querol, X., Antenucci, P., & Vale, J. F. (2009). Waste stabilization/solidification of an electric arc furnace dust using fly ash-based geopolymers. *Fuel*, *88*, 1185–1193.

- Firoozfar, A., & Khosroshiri, N. (2016). Kerman clay improvement by lime and bentonite to be used as materials of landfill liner. *Geotechnical & Geology Engineering*, 35, 559–571.
- Fu, Y., Cai, L., & Wu, Y. (2011). Freeze–thaw cycle test and damage mechanics models of alkali-activated slag concrete. *Construction Building & Materials*, 25, 3144–3148.
- Fuller, W.H. (1977). Movement of Selected Metals, Asbestos and Cyanide in Soil, Applications to Waste Disposal Problems. EPA-600/2-77-020, U.S. EPA.
- Ganjan, E., Classie, P., Tyrer, M., & Atkinson, A. (2004). Preliminary investigations into the use of secondary waste minerals as a novel cementitious landfill liner. *Construction Building & Materials*, 18, 689–699.
- Glasser, F. P. (2013). *Cement in radioactive waste disposal*. Waste Technology Section, Vienna: International Atomic Energy Agency.
- Hettiaratchi, J. P. A., Achari, G., Joshi, R. C., & Okoli, R. E. (1999). Feasibility of using fly ash admixtures in landfill bottom liners or vertical barriers at contaminated site. *Environmental Science and Health – A*, 34, 1897–1917.
- Ishwarya, G. (2013). *Development of geopolymer concrete cured at ambient temperature*. M. Technical thesis, Roorkee, India: CSIR-Central Building Research Institute (AcSIR).
- Javadian, H., Ghorbani, F., Tayebi, H. A., & Hosseini, S. M. (2015). Study of the adsorption of Cd (II) from aqueous solution using zeolite-based geopolymer, synthesized from coal fly ash; kinetic, isotherm and thermodynamic studies. *Arabian Journal of Chemistry*, 8, 837–849.
- Judith, L. L., Stephen, K., & Michael, W. G. (1992). Zeolite formation in class F fly ash blended cement pastes. *Journal of the American Ceramic Society*, 75, 1574–1580.
- Kleppe, J. H., & Olson, R. E. (1985). Desiccation cracking of soil barriers hydraulic barriers in soil and rock. *Hydraulic Barriers Soil Rock*, 874, 263–275.
- Koch, D. (2002). Bentonites as a basic material for technical base liners and site encapsulation cut-off walls. *Applied Clay Science*, 21, 1–11.
- Komljenović, M., Baščarević, Z., & Bradić, V. (2010). Mechanical and microstructural properties of alkali-activated fly ash geopolymers. *Journal of Hazardous Materials*, 181, 35–42.
- Komnitsas, K., Bartzas, G., & Paspaliaris, I. (2004). Clean-up of acidic leachates using fly ash barriers: laboratory column studies. *Global Nest Journal*, 6, 81–89.
- Li, L., Wang, S., & Zhu, Z. (2006). Geopolymeric adsorbents from fly ash for dye removal from aqueous solution. *Advances in Colloid & Interface Science*, 300, 52–59.
- Ma, Y., Hua, J., & Ye, G. (2013). The pore structure and permeability of alkali activated fly ash. *Fuel*, 104, 771–780.
- Ma, Y., & Ye, G. (2015). The shrinkage of alkali activated fly ash. *Cement Concrete Research*, 68, 75–82.
- Majone, M., Papini, M. P., & Rolfe, E. (1998). Influence of metal speciation in landfill leachates on kaolinite sorption. *Water Research*, 32, 882–890.
- Minnesota, P. C. A. (1978). *Disposal of Residuals by Landfilling*. Minneapolis, Minnesota, U.S.A.: Minnesota PCA.
- Mishra, A., & Ravindra, V. (2015). On the utilization of fly ash and cement mixture as a landfill liner material. *International Journal of Geosynthetics and Ground Engineering*, 1, 16–22.
- Mitchell, J. K. (1976). *Fundamentals of Soil Behavior*. New York: John Wiley & Sons.
- Mohan, S., & Gandhimathi, R. (2009). Removal of heavy metal ions from municipal solid waste leachate using coal fly ash as an adsorbent. *Hazardous Materials*, 169, 351–359.
- Mollah, M. Y. A., Hess, T. R., & Cocke, D. L. (1994). Surface and bulk studies of leached and un-leached fly ash using XPS, EDS, SEM and FT-IR techniques. *Cement and Concrete Research*, 24, 109–118.
- Mužek, M. N., Svilović, S., & Zelić, J. (2014). Fly ash-based geopolymeric adsorbent for copper ion removal from wastewater. *Desalination & Water Treatment*, 52, 2519–2526.
- Nhan, C. T., Graydon, J. W., & Kirk, D. W. (1996). Utilizing coal fly ash as a landfill barrier material. *Waste Management*, 16, 587–595.
- Oruh, S., & Nuri Ergun, O. (2010). Use of fly ash, phosphogypsum and red mud as a liner material for the disposal of hazardous zinc leach residue waste. *Hazardous Materials*, 173, 468–473.
- Pacheco-Torgal, F., Castro-Gomes, J., & Jalali, S. (2008). Alkali-activated binders: A review: Part 1. Historical background, terminology, reaction mechanisms and hydration products. *Construction and Building Materials*, 22, 1305–1314.
- Pacheco-Torgal, F., Labrincha, J., Leonelli, C., Palomo, A., & Chindaprasirt, P. (2015). *Handbook of Alkali activated Cements, Mortars and Concretes*, Woodhead Publishing in Civil and Structural Engineering, Elsevier, Amsterdam.
- Palmer, B. G., Edil, T. B., & Benson, C. H. (2000). Liners for waste containment constructed with class F and C fly ashes. *Hazardous Materials*, 76, 193–216.
- Palomo, A., Grutzeck, M. W., & Blanco, M. T. (1999). Alkali-activated fly ashes – a cement for the future. *Cement Concrete Research*, 29, 1323–1329.
- Palomo, A., Alonso, S., & Fernandez-Jiménez, A. (2004). Alkaline activation of fly ashes: NMR study of the reaction products. *American Ceramic Society*, 87, 1141–1145.
- Phair, J. W., Van Deventer, J. S. J., & Smith, J. D. (2004). Effect of Al source and alkali activation on Pb and Cu immobilisation in fly-ash based “geopolymers”. *Applied Geochemistry*, 19, 423–434.
- Pignatello, J. J. (1998). Soil organic matter as a nonporous sorbent of organic pollutants. *Advances in Colloid Interface Science*, 76, 445–467.
- Pignatello, J. J., & Xing, B. (1996). Mechanisms of slow sorption of organic chemicals to natural particles. *Environmental Science & Technology*, 30, 1–11.
- Prashanth, J. P., Sivapullaiah, P. V., & Sridharan, A. (2001). Pozzolanic fly ash as a hydraulic barrier in land fill. *Engineering Geology*, 60, 245–252.
- Provis, J. L., Lukey, G. C., & Van Deventer, J. S. J. (2005). Do geopolymers actually contain nanocrystalline zeolites? A re-examination of existing results. *Materials Chemistry*, 17, 3075–3085.
- Rao, R. K. A., Hess, T. R., Cocke, D. L., & Lauer, H. V. (1994). Fraction and characterisation of Texas lignite class F fly ash by XRD, TGA, FTIR and SFM. *Cement and Concrete Research*, 24, 1153–1164.
- Rios, S., Cristelo, C., Viana Da Fonseca, A., & Ferreira, C. (2016). Structural performance of alkali activated soil-ash versus soil-cement. *Material in Civil Engineering*, 28(2).
- Rogers, E.H. (1968). Soil-cement linings for water-containing structures. Pp. 95–105 in: *Proceedings of Second Seepage Symposium*, Phoenix, Arizona, USA, 95–105.
- Ruen-ngam, D., Rungsuk, D., Apiratikul, R., & Pavasant, P. (2009). Zeolite formation from coal fly ash and its adsorption potential. *Air & Waste Management Association*, 59, 1140–1147.
- Sahoo, P. K., Tripathy, S., Panigrahi, M. K. P., & Equeenuddin, S. K. M. D. (2013). Evaluation of the use of an alkali modified fly ash as a potential adsorbent for the removal of metals from acid mine drainage. *Applied Water Science*, 3, 567–576.
- Schevon, G. R., & Damas, G. (1986). Using double liners in landfill design and operation. *Waste Management & Research*, 4, 161–176.
- Shackelford, C. D., & Glade, M. J. (1994). Constant flow and constant gradient permeability tests on sand-bentonite fly ash mixtures. *Hydraulic Conduct Waste Contaminant Transport Soil ASTM STP*, 1142, 521–545.
- Sivapullaiah, P. V., & Lakshmikantha, H. (2004). Properties of fly ash as hydraulic barrier. *Soil and Sediment Contamination*, 13, 391–406.
- Sivapullaiah, P., & Moghal, A. (2011). Role of gypsum in the strength development of fly ashes with lime. *Materials in Civil Engineering*, 23, 197–206.
- Skvara, F., Šmilauer, V., Hlaváček, P., Kopecký, L., & Čilová, Z. (2012). A weak alkali bond in (N, K)-A-S-H gels: evidence from leaching and modeling. *Ceramic Silikaty*, 56, 374–382.



- Suzuki, K., & Ono, Y. (2008). Leaching characteristics of stabilized/solidified fly ash generated from ash melting plant. *Chemosphere*, 71, 922–932.
- Temuijin, J., Van Riessen, A., & Williams, R. (2009). Influence of calcium compounds on the mechanical properties of fly ash geopolymer pastes. *Hazardous Material*, 167, 82–88.
- Thornton, S. F., & Lerner, D. N. (2001). Attenuation of landfill leachate by clay liner materials in laboratory columns: 2. Behavior of inorganic contaminants. *Waste Management & Research*, 19, 70–88.
- UK Nirex (1993). Report No. 525, Scientific Update. (Harwell, Didcot, OXON UK): United Kingdom Nirex Ltd, p. 25.
- Van Jaarsveld, J. G. S., Van Deventer, J. S. J., & Lorenzen, L. (1998). Factors affecting the immobilisation of metals in geopolymerised fly ash. *Metallurgy and Materials Transaction-B*, 29, 283–291.
- Van Jaarsveld, J. G. S., Van Deventer, J. S. J., & Schwartzman, A. (1999). The potential use of geopolymeric materials to immobilise toxic metals: Part II. Material and leaching characteristics. *Minerals Engineering*, 12, 75–91.
- Vesperman, K. D., Edil, T. B., & Berthouex, P. M. (1985). Conductivity of fly ash and fly ash sand mixtures. *Hydraulic Barriers Soil Rock*, 874, 289–298.
- Waijarean, N., Asavapisit, S., & Sombatsompop, K. (2014). Strength and microstructure of water treatment residue-based geopolymers containing heavy metals. *Construction and Building Materials*, 50, 486–491.
- Wang, S. H., Li, L., & Zhua, Z. H. (2007). Solid-state conversion of fly ash to effective adsorbents for Cu removal from wastewater. *Hazardous Materials*, 139, 254–259.
- Yeheyis, M. B., Shang, J. Q., & Yanful, K. Y. (2009). Feasibility of using coal fly ash for mine waste containment. *Environmental Engineering*, 136, 682–690.
- Zhang, Z., Wang, H., & Provis, J. L. (2012). Quantitative study of the reactivity of fly ash in geopolymerization by FTIR. *Sustainable Cement-Based Materials*, 1, 154–166.

(Received 14 August 2019; revised 8 April 2020; AE: Luyi Sun)