

ORIGINAL ARTICLE

Egg white-based strong hydrogel via ordered protein condensation

Tatsuya Nojima^{1,2} and Tomokazu Iyoda³

Despite the well-known thermal gelation property of egg white and its wide use in the food industry, the applications of gelled egg white in materials science are limited owing to the brittleness caused by the network structure of randomly associated denatured proteins. In this study, a gel material with high mechanical strength was fabricated from crude egg white proteins. Fluid materials containing orderly condensed proteins at regular intervals were prepared by addition of ionic surfactants to an egg white protein solution. The initiation of the heat denaturation of proteins from this ordered state with spatial confinement resulted in the formation of hydrogel materials with high mechanical strength. The maximum compressive fracture strength of the fabricated egg white-based hydrogel was 34.5 MPa, which is 150-fold higher than that of gelled egg white prepared by boiling and comparable to that of strong chemically synthesized hydrogels. Chemical modification of sulfhydryl groups of proteins and treatment with a denaturant revealed that denatured polypeptide chains were covalently linked by disulfide bonds and non-covalently associated; these findings showed that the high mechanical strength of our material is due to the synergic effects of both covalent and non-covalent networks.

NPG Asia Materials (2018) 10, e460; doi:10.1038/am.2017.219; published online 5 January 2018

INTRODUCTION

The development of protein-based materials with excellent mechanical strength and functional properties is a major goal in materials science. Fibrous proteins, such as elastins, keratins, collagens, cotton silks and spider dragline silks, are widely used to create materials,^{1–3} whereas soluble globular proteins are less commonly used.

Hen egg is one of the most ubiquitous foodstuffs, and hen egg white (HEW) is a widely available protein resource. HEW contains more than 100 types of soluble proteins at high concentrations (100–110 mg ml⁻¹). Thermal gelation of HEW is a well-known property with extensive applications in the food industry. However, HEW gels are not used to create advanced materials because of their weak mechanical strength. Gelled HEW is a type of hydrogel with a network structure constructed by aggregations of heat-denatured proteins.⁴ The protein aggregation is mediated by non-covalent interactions (hydrophobic interactions, electrostatic interactions and hydrogen bonds) and intermolecular disulfide cross-linking.^{5,6} Since the thermal denaturation and aggregation are random processes, the network structure of gelled HEW is not homogeneous. We assumed this inhomogeneity could explain the mechanical fragility of the HEW gel.

In the past decade, various types of chemically synthesized hydrogels with high mechanical strength have been reported. The homogeneity and order of the network structure of polymer chains are important factors determining the strength of gel materials. Tetra-PEG gel is a representative high-strength hydrogel with a homogeneous network structure. Sakai and coworkers reported that the combination

of two types of four-arm macromonomers with end-linking groups that react with each other results in a homogeneous network.^{7,8} The structural monodispersity of proteins is advantageous for use as a macromonomer for the construction of the ordered network structure and for the creation of protein-based hydrogels with high mechanical strength. However, in contrast to the macromonomers of tetra-PEG gel, denatured proteins exhibit multimodal interactions at various regions. Therefore, protein denaturation and network formation need to start from a spatially confined situation with an ordered arrangement of proteins to prevent random aggregation.

Recently, we reported the surfactant-mediated ordered condensation of proteins and the formation of a high-protein-content fluid material referred to as a protein condensate (PC).⁹ The PC is a liquid phase separated from water that is prepared by the simple mixing of a protein solution and a combination of anionic and cationic surfactants (C_xE_y). Both surfactants have a hydrophobic alkyl chain and a hydrophilic PEG chain. Ionic groups are positioned at the terminus of PEG. PC is generated by the assembly of the proteins surfactant complex, in which PEG chains are electrostatically bound to the protein surface while alkyl chains are located outside. Hydrophobic interactions between outer alkyl chains organize the complex to form the PC. Despite the clear phase separation from water, PC contains water retained by PEG chains. Proteins inside PC are in a water-rich environment, maintaining their native structure and function. Surfactants surrounding the protein prevent the direct contact of proteins, resulting in the packing of proteins at regular intervals in the PC.

¹Institute of Innovative Research, Tokyo Institute of Technology, Kanagawa, Japan; ²State Key Laboratory of Bioelectronics, School of Biological Science and Medical Engineering, Southeast University, Nanjing, China and ³Harris Science Research Institute, Doshisha University, Kyoto, Japan
Correspondence: Dr T Nojima, State Key Laboratory of Bioelectronics, School of Biological Science and Medical Engineering, Southeast University, Nanjing 210096, China.
E-mail: tatsuya.nojima@gmail.com

Received 2 September 2017; revised 13 October 2017; accepted 29 October 2017

Various proteins can be used to form the PC by optimizing the ratio of anionic and cationic surfactants based on the electrostatic characteristics of the target protein.

Here we demonstrated the ionic surfactant-mediated ordered condensation of water-soluble HEW proteins and showed that heating of the condensed HEW protein resulted in the formation of a hydrogel with high mechanical strength.

MATERIALS AND METHODS

Materials

Homogenized and clear hen egg white protein solution was prepared by a previously reported procedure, with modifications.¹⁰ HEW was collected from fresh eggs, filtered two times through a mesh net, diluted with an equal weight of water, stirred for 1 h at 4 °C, and centrifuged (10 000 g for 20 min). The supernatant was dialyzed using a 3500 MW cutoff tube against water at 4 °C and centrifuged (15 000 g for 40 min). The supernatant was collected and stored at 4 °C. Protein concentration was determined by the BCA method (Pierce, Rockford, IL, USA) with bovine serum albumin as the standard.

Aqueous solutions (100 mM) of anionic and cationic C_xE_y ($x=12$, $y=4.5$ and 9) were prepared as previously reported.⁹

Preparation of protein condensates

PC of HEW: To 1 ml of 10 mg ml⁻¹ HEW solution, 20 and 80 μl of 100 mM anionic and cationic surfactants ($C_{12}E_9$ or $C_{12}E_{4.5}$) were added. The cloudy solution was centrifuged (10 000 g for 1 min) and PC(HEW- $C_{12}E_9$) and PC(HEW- $C_{12}E_{4.5}$) were observed at the bottom of the tube as a pale-yellow transparent liquid. The procedure could be scaled up to prepare large quantities.

Preparation of PC-Gel

PCs were heated at 70 °C for 20 min on heat blocks or in a water bath. The PC-gels were stored in water at 4 °C.

Water content measurement

A thermogravimetric analysis was performed on a TG/DTA 6300 (Seiko Instruments Inc., Chiba, Japan) using ~10 mg of sample in air by increasing

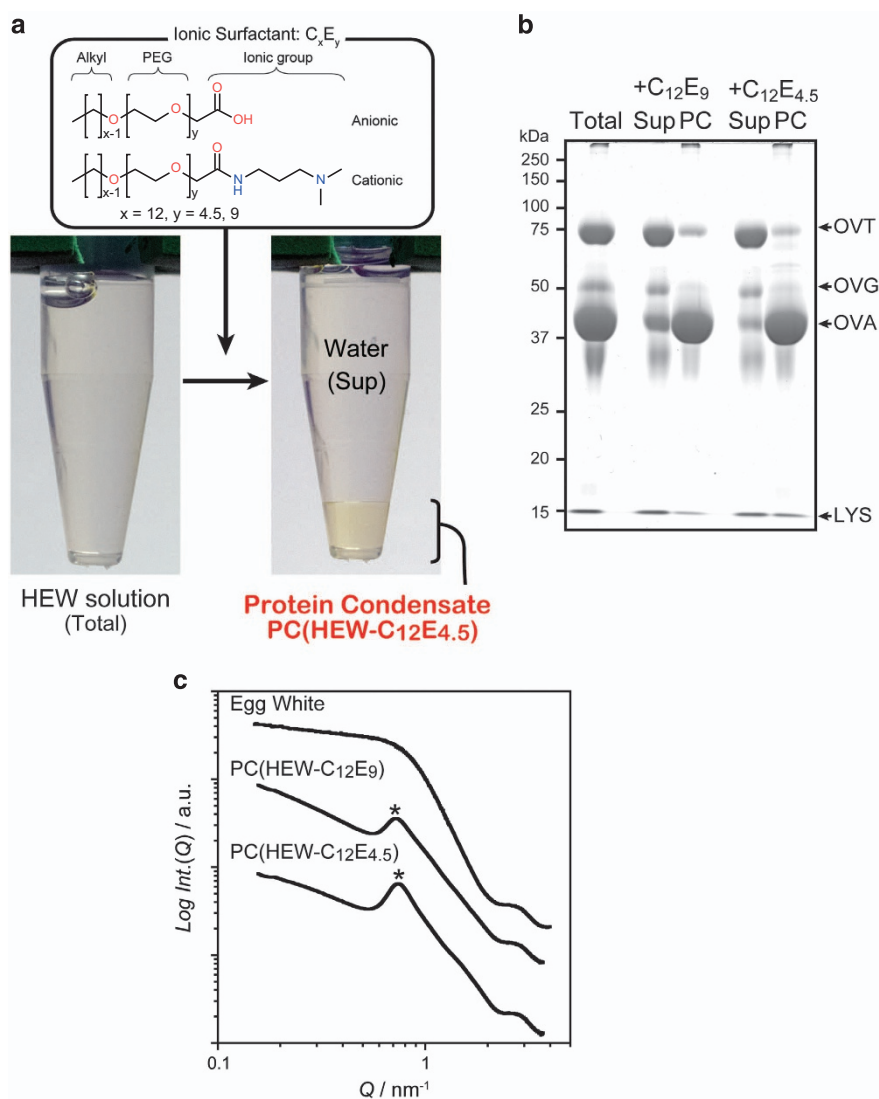


Figure 1 Formation of a PC from HEW protein. (a) The addition of an anionic and cationic surfactant to the HEW protein solution resulted in PC formation after centrifugation, observed as a pale-yellow fluid. (b) SDS-PAGE analysis of proteins in the PC and the supernatant (Sup). Total indicates total HEW proteins. Major proteins are indicated (OVT, ovotransferrin; OVG, ovoglobulin; OVA, ovalbumin; LYS, lysozyme). (c) SAXS profiles of egg white, PC(HEW- $C_{12}E_9$), and PC(HEW- $C_{12}E_{4.5}$). PCs showed scattering peaks (asterisks).

the temperature from 20 to 600 °C at a rate of 5 °C min⁻¹. The water content was determined based on the weight loss up to 150 °C.

Protein content measurement

An aliquot of 100 µl of PC(HEW) was mixed with 900 µl of 20 mM Tris-HCl buffer (pH 8.0) containing 200 mM NaCl. Under these salt conditions, PC (HEW) was converted back to aqueous solution; protein concentration was then determined by the BCA method (Pierce, Rockford, IL, USA) with bovine serum albumin as the standard.

Small angle X-ray scattering (SAXS) measurement

SAXS was performed using a NANOPIX with a two-dimensional detector and a CuK α X-ray with a wavelength of $\lambda = 1.54$ Å (Rigaku Corp., Tokyo, Japan). Samples for SAXS experiments were mounted in a Kapton film cell (path length 1.1 mm). An empty cell was used to determine background scattering. The scattering from the sample and background were measured for the same time period and normalized to the intensity of the transmitted beam.

Mechanical strength measurements

The compressive stress–strain measurements were performed using an INSTRON 5565 (Instron Corp., Norwood, MA, USA). The cylindrical gel sample with a diameter of 8.7 mm and thickness of 3.5 mm was compressed at a strain rate of 0.4 mm min⁻¹. The compressive elastic modulus was independently measured using a SMT1-10N (Shimadzu Corp., Kyoto, Japan). The tensile stress–strain measurements were performed using an INSTRON 5943 (Instron Corp.). The dumbbell-shaped specimens with a length of 50 mm, narrowest breadth of 5 mm, and height of 1 mm were stretched at a strain rate of 5 mm min⁻¹.

RESULTS AND DISCUSSION

In general, protein purification from biological samples is a costly process involving multiple steps and is disadvantageous for large-scale material production. Here we used unpurified crude HEW proteins for PC formation. The protein density of PC can be regulated by the

chain length of the surfactant. In this study, we used two surfactant types with different PEG chain lengths, that is, C₁₂E₉ and C₁₂E_{4.5}. We added various ratios of anionic:cationic surfactants to the homogenized HEW solution and observed PC formation at a ratio of 20:80 in both C₁₂E₉ and C₁₂E_{4.5} (Figure 1a). As in the case of purified proteins, after the addition of surfactants at the optimal ratio, the clear HEW solution became cloudy within a second. After centrifugation, the cloudy solution was clearly separated to an upper aqueous phase and lower PC. The obtained PCs were referred to as PC(HEW–C₁₂E₉) and PC(HEW–C₁₂E_{4.5}), individually, and PC(HEW), collectively. PC (HEW) was a transparent fluid that could be handled using a laboratory pipette. The protein contents of PC(HEW–C₁₂E₉) and PC(HEW–C₁₂E_{4.5}) were 124 mg ml⁻¹ and 154 mg ml⁻¹, respectively, similar to that of intact egg white (100–110 mg ml⁻¹). PC(HEW–C₁₂E₉) and PC(HEW–C₁₂E_{4.5}) contained 80% and 76% (w/w) water, respectively, based on a thermogravimetric analysis (Supplementary Figure S1).

The protein-based yields were 50% for PC(HEW–C₁₂E₉) and 66% for PC(HEW–C₁₂E_{4.5}), and approximately half of the proteins remained in the upper aqueous supernatant. Proteins contained in the PC and those remaining in the aqueous supernatant (Sup) were analyzed by SDS-PAGE (Figure 1b). An obvious difference in the protein components between the PC and Sup fraction was observed. PC(HEW–C₁₂E₉) and PC(HEW–C₁₂E_{4.5}) showed nearly identical components. PC(HEW) was mainly composed of OVA (ovalbumin). Small amounts of OVT (ovotransferrin) and LYS (lysozyme) were detected in the PC.

SAXS was used for the structural analysis of PC(HEW) (Figure 1c). PCs of purified proteins showed scattering peaks arising from the interference between constituent proteins, indicating the ordered arrangement of proteins at regular intervals.⁹ As in the case of purified proteins, PC(HEW) showed scattering peaks that were not observed in

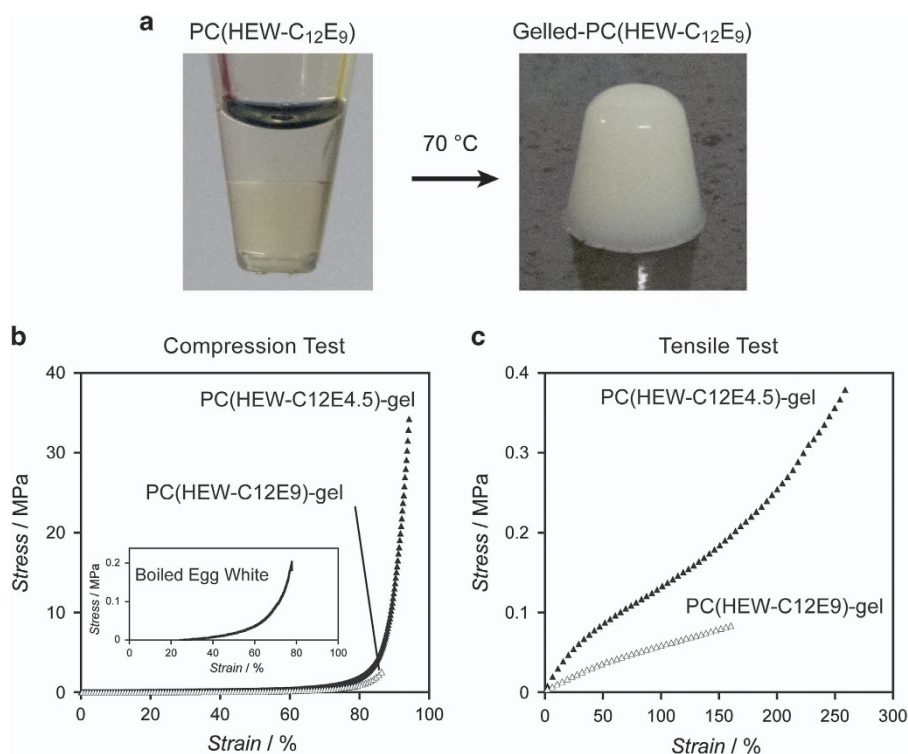


Figure 2 Thermal gelation of PC(HEW) and its mechanical strength. (a) Fluidic PC(HEW) was gelled by heating at 70 °C. (b) Compressive stress–strain curve of PC(HEW)-gels. Inset: stress–strain curve of boiled egg white. (c) Tensile stress–strain curve of PC(HEW)-gels.

Table 1 Compressive and tensile strength properties

No.	Name	Treatment	Compressive fracture stress (MPa)	Compressive fracture strain (%)	Compressive elastic modulus (kPa)	Tensile fracture stress (MPa)	Tensile fracture strain (%)	Tensile elastic modulus (kPa)
1	PC(HEW - C ₁₂ E ₉)-gel		2.9	87.0	50.1	0.09	165	73.0
2	PC(HEW - C ₁₂ E _{4.5})-gel		34.5	94.3	117.8	0.38	260	249.9
3	PC(HEW - C ₁₂ E _{4.5})-gel	IAA-treated ^a	0.4	73.7				
4	PC(HEW - C ₁₂ E _{4.5})-gel	GdmCl-treated ^b	0.6	87.0				
5	PC(HEW - C ₁₂ E _{4.5})-gel	GdmCl-removed ^c	0.4	80.0				
6	PC(OVA - C ₁₂ E ₉)-gel		5.4	87.0	125.0	0.21	191	266.0
7	PC(OVA - C ₁₂ E _{4.5})-gel		33.8	94.5	194.9	0.32	193	448.6
8	Boiled egg white ^d		0.2	77.8				

^aPC formation and gelation were performed in the presence of 80 mM IAA.^bSample 2 was incubated in 4 M GdmCl for over 1 week.^cSample 4 was incubated in water for over 3 days.^dHen egg was boiled for 20 min.

the SAXS profile of egg white, indicating that various proteins, such as OVA, OVT and LYS, were packed inside the PC with an ordered structure. Consistent with the higher protein content of PC(HEW - C₁₂E_{4.5}), the protein-protein correlation distance calculated from the scattering peak position ($d = 2\pi/Q$) of PC(HEW - C₁₂E_{4.5}) ($Q = 0.743 \text{ nm}^{-1}$, $d = 8.45 \text{ nm}$) was shorter than that of PC(HEW - C₁₂E₉) ($Q = 0.718 \text{ nm}^{-1}$, $d = 8.75 \text{ nm}$), revealing the closer packing of proteins.

Similar to the HEW protein solution,¹⁰ PC(HEW) became a white opaque gel by heating at 70 °C for 20 min (Figure 2a). The PC(HEW - C₁₂E₉)-gel and PC(HEW - C₁₂E_{4.5})-gel retained 82% and 76% (w/w) water, respectively (Supplementary Figure S1). PCs were dissolved in an NaCl solution, which disrupts the electrostatic interactions between proteins and surfactants.⁹ The PC(HEW)-gel was stable in the NaCl solution and was degraded by protease (Supplementary Figure S2). NaCl stability and protease degradability indicated that the network structure of PC(HEW)-gel was constructed by polypeptide chains.

The mechanical strengths of PC(HEW)-gels are summarized in Figures 2b and c and Table 1. To prepare samples for measurement, PC(HEW) was poured into a mold and heated (Supplementary Figure S3). Figure 2b shows the compressive stress-strain curves of the PC(HEW - C₁₂E₉)-gel and PC(HEW - C₁₂E_{4.5})-gel, with a stress of 2.9 MPa and 34.5 MPa, respectively. The fracture strength for PC(HEW - C₁₂E_{4.5})-gel was 150-fold higher than that for boiled egg white (-0.2 MPa; Figure 2b, inset)¹¹ and was comparable to that of synthesized high-strength hydrogels.^{7,12} The 11-fold higher strength of the PC(HEW - C₁₂E_{4.5})-gel compared to the PC(HEW - C₁₂E₉)-gel would be due to the higher protein content with appropriate ordered arrangement of proteins in PC(HEW - C₁₂E_{4.5}). As shown in tensile testing (Figure 2c), PC(HEW - C₁₂E_{4.5})-gel showed a fracture strain of 260%. This result revealed the elastic property of the PC(HEW - C₁₂E_{4.5})-gel, which contrasts with the typical nature of boiled egg white. The PC(HEW - C₁₂E_{4.5})-gel showed a higher compressive and tensile elastic modulus than the PC(HEW - C₁₂E₉)-gel, indicating a higher network density of the PC(HEW - C₁₂E_{4.5})-gel.

OVA is the most abundant protein in HEW making up over half of the total protein content of egg white and is the dominant factor for the gelation property of egg white.¹³ We investigated whether OVA, the main protein in PC(HEW), also promotes the heat-induced gelation of PC(HEW). In our previous study, we demonstrated PC formation from purified OVA and LYS⁹ (Supplementary Materials and Supplementary Table S1). Here, we tested the thermal gelation property of both PCs (Supplementary Materials and Supplementary Figure S4). Although the PC of LYS did not form a gel on heating at 70 °C, the PC of OVA became an opaque gel with high mechanical strength, comparable to that of the PC(HEW)-gel. We concluded that the thermal gelation property of PC(HEW) and the high mechanical strength of the gel resulted from the network structure constructed by OVA.

OVA contains four free SH groups that are buried in the native structure.¹⁴ When OVA is heat denatured, the SH groups are exposed and disulfide bonds form between denatured proteins.¹⁵ The contributions of covalent disulfide bonds and non-covalent interactions for the construction of the PC(HEW)-gel network were separately revealed (Figure 3).

Iodoacetamide (IAA) covalently modifies the SH group of cysteine residues and prevents the formation of disulfide bonds (Figure 3a).¹⁶ PC(HEW - C₁₂E_{4.5}) was prepared in the presence of IAA. Although disulfide bond formation was prevented, IAA-treated PC(HEW - C₁₂E_{4.5}) formed an opaque gel by heating on 70 °C. This result shows

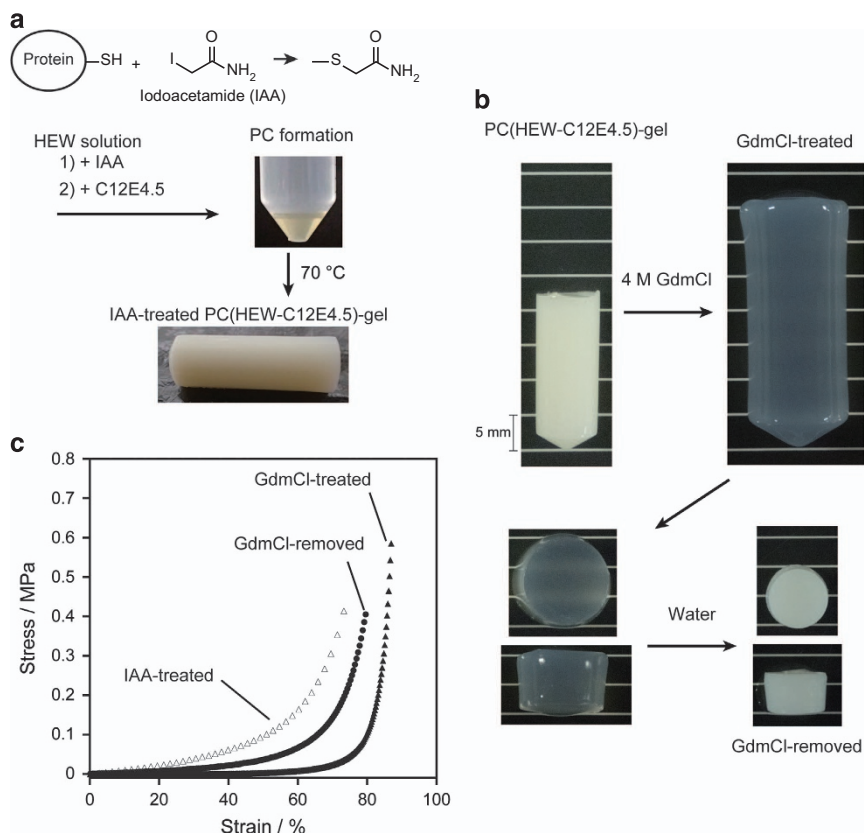


Figure 3 Non-covalent network and covalent disulfide bond network coexist in PC(HEW)-gel. (a) IAA prevents disulfide bond formation. HEW proteins formed PC by the addition of the C₁₂E_{4.5} surfactant in the presence of 80 mM IAA. IAA-treated PC was gelled by heating at 70 °C. (b) The PC(HEW-C₁₂E_{4.5})-gel swelled and became semitransparent when kept in 4 M GdmCl for 144 h. The GdmCl-treated PC(HEW-C₁₂E_{4.5})-gel was sliced and incubated in water to remove GdmCl for 24 h. The gel regained a white opaque appearance (GdmCl removed). (c) Compressive stress-strain curve of IAA-treated, GdmCl-treated, and GdmCl-removed PC(HEW-C₁₂E_{4.5})-gel.

that heat-denatured proteins inside PC formed a network structure via non-covalent interactions during the gelation process.

The protein denaturant reagent guanidinium chloride (GdmCl) solubilizes non-covalent protein associations and improves the water solubility of denatured proteins. The PC(HEW-C₁₂E_{4.5})-gel was immersed in 4 M GdmCl (Figure 3b). The gel swelled, maintaining its overall structure, and became semitransparent due to the solubilization of the large structures of non-covalently associated polypeptide chains and the extension of polypeptide chains in the GdmCl solution.¹⁷ Treatment of the PC(HEW-C₁₂E_{4.5})-gel with 6 M urea and 2% (w/v) sodium dodecyl sulfate (SDS) showed similar results (Supplementary Figure S5a). The swollen gel was dissolved by addition of dithiothreitol, which is a reducing reagent used for the cleavage of disulfide bonds (Supplementary Figure S5a). These results showed that the covalent network structure was constructed by disulfide bonds between denatured proteins.

Interestingly, both IAA and GdmCl-treated PC(HEW-C₁₂E_{4.5})-gels showed drastically weakened compressive strengths of 0.43 and 0.59 MPa, respectively (Figure 3c). This result indicates that the high mechanical strength of the PC(HEW)-gel can be attributed to the synergistic non-linear effects of non-covalent and covalent networks with different properties. The synergistic effects of the combination of two independent polymer networks with different properties for improved mechanical strength has been described as a DN (double network) gel.¹⁰ In our PC(HEW)-gel, the two networks were not independent because different regions within single denatured proteins mediated

the formation of non-covalent and covalent networks. We investigated the effect of the arrangement of both networks. After immersion of the GdmCl-treated PC(HEW-C₁₂E_{4.5})-gel in water, the gel shrank and regained a white opaque appearance, indicating regeneration of the non-covalent network (Figure 3c). However, synergic effects were not observed and the gel showed a weak compressive strength of 0.42 MPa. We concluded that the non-covalent and covalent networks should be formed from the spatially confined PC state to construct ordered and orchestrated network structures with high mechanical strength.

The heat-induced gelation of egg white and its fragility are common knowledge. Our results open up new possibilities for egg white proteins as a resource for the development of materials. The method is simple and effective, and could be applied to other proteins together with protein engineering technology (for example, introduction of cysteine residues for covalent network formation) for the development of a new class of functional soluble globular protein-based materials.

CONFLICT OF INTEREST

The authors declare no conflict of interest.

ACKNOWLEDGEMENTS

This work was supported by JST ERATO Iyoda Supra-Integrated Material Project, Grant Number JPMJER1001 and Keikai Research Foundation. The authors acknowledge Dr M. Sugiyama (Kyoto University) and Dr R. Inoue (Kyoto University) for support with SAXS measurement; Dr A. Shishido (Tokyo Institute of Technology) for support with tensile strength measurement;

Dr T. Miyata (Kansai University) and C. Norioka (Kansai University) for support with compressive strength measurement; and Dr H. Taguchi (Tokyo Institute of Technology) for support with lab equipment.

PUBLISHER'S NOTE

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

- 1 Hu, X., Cebe, P., Weiss, A. S., Omenetto, F. & Kaplan, D. L. Protein-based composite materials. *Mater. Today* **15**, 208–215 (2012).
- 2 Nojima, T., Suzuki, S. & Iyoda, T. Atelocollagen-templated fabrication of tangled fibrous silica. *J. Mater. Chem. B* **4**, 6640–6643 (2016).
- 3 Numata, K., Ifuku, N., Masunaga, H., Hikima, T. & Sakai, T. Silk resin with hydrated dual chemical-physical cross-links achieves high strength and toughness. *Biomacromolecules* **18**, 1937–1946 (2017).
- 4 Campbell, L., Raikos, V. & Euston, S. R. Modification of functional properties of egg-white proteins. *Nahrung* **47**, 369–376 (2003).
- 5 Sun, Y. X. & Hayakawa, S. Heat-induced gels of egg white/ovalbumins from five avian species: thermal aggregation, molecular forces involved, and rheological properties. *J. Agr. Food Chem.* **50**, 1636–1642 (2002).
- 6 Van der Plancken, I., Van Loey, A. & Hendrickx, M. E. G. Changes in sulfhydryl content of egg white proteins due to heat and pressure treatment. *J. Agr. Food Chem.* **53**, 5726–5733 (2005).
- 7 Sakai, T., Matsunaga, T., Yamamoto, Y., Ito, C., Yoshida, R., Suzuki, S., Sasaki, N., Shibayama, M. & Chung, U. Design and fabrication of a high-strength hydrogel with ideally homogeneous network structure from tetrahedron-like macromonomers. *Macromolecules* **41**, 5379–5384 (2008).
- 8 Matsunaga, T., Sakai, T., Akagi, Y., Chung, U. & Shibayama, M. Structure characterization of tetra-PEG gel by small-angle neutron scattering. *Macromolecules* **42**, 1344–1351 (2009).
- 9 Nojima, T. & Iyoda, T. Water-rich fluid material containing orderly condensed proteins. *Angew. Chem. Int. Edit* **56**, 1308–1312 (2017).

- 10 Iwashita, K., Inoue, N., Handa, A. & Shiraki, K. Thermal aggregation of hen egg white proteins in the presence of salts. *Protein J.* **34**, 212–219 (2015).
- 11 Hsieh, Y. L. & Regenstein, J. M. Failure deformation and stress-relaxation of heated egg-white gels. *J. Food Sci.* **58**, 113–115 (1993).
- 12 Gong, J. P., Katsuyama, Y., Kurokawa, T. & Osada, Y. Double-network hydrogels with extremely high mechanical strength. *Adv. Mater.* **15**, 1155–1158 (2003).
- 13 Iwashita, K., Handa, A. & Shiraki, K. Co-aggregation of ovalbumin and lysozyme. *Food Hydrocolloid* **67**, 206–215 (2017).
- 14 Huntington, J. A. & Stein, P. E. Structure and properties of ovalbumin. *J. Chromatogr. B* **756**, 189–198 (2001).
- 15 Rumbo, M., Chirido, F. G., Fossati, C. A. & Anon, M. C. Analysis of structural properties and immunochemical reactivity of heat-treated ovalbumin. *J. Agr. Food Chem.* **44**, 3793–3798 (1996).
- 16 Anson, M. L. The reactions of iodine and iodoacetamide with native egg albumin. *J. Gen. Physiol.* **23**, 321–331 (1940).
- 17 Kohn, J. E., Millet, I. S., Jacob, J., Zagrovic, B., Dillon, T. M., Cingel, N., Dothager, R. S., Seifert, S., Thiagarajan, P., Sosnick, T. R., Hasan, M. Z., Pande, V. S., Ruczinski, I., Doniach, S. & Plaxco, K. W. Random-coil behavior and the dimensions of chemically unfolded proteins. *Proc. Natl Acad. Sci. USA* **101**, 12491–12496 (2004).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>

© The Author(s) 2018

Supplementary Information accompanies the paper on the NPG Asia Materials website (<http://www.nature.com/am>)